



Trigon Metals Inc.

**NI 43-101 Technical Report on the
Kombat Copper Project, Namibia**

Mineral Resource Report

Qualified Person:

Mr. Uwe Engelmann

*BSc (Zoo. & Bot.), BSc Hons (Geol.), Pr.Sci.Nat.,
MGSSA*

Minxcon Reference: M2017_015a

Effective Date: 01 April 2017

Version: Final

Issue Date: 02 June 2017

Prepared by Minxcon (Pty) Ltd

Suite 5 Coldstream Office Park,
Little Falls, Roodepoort, South Africa
Tel: +2711 958 2899



DATE AND SIGNATURE PAGE

This Report titled “NI 43-101 Technical Report on the Kombat Copper Project, Namibia - Mineral Resource Report” was prepared on behalf of Trigon Metals Inc.. The Report is compliant with National Instrument 43-101 and Form 43-101 F1. The effective date of this Report is 01 April 2017.

The Qualified Person responsible for this Report is Mr. Uwe Engelmann and signed:-



U Engelmann


BSc (Zoo. & Bot.), BSc Hons (Geol.)


Pr.Sci.Nat., MGSSA


DIRECTOR, MINXCON (PTY) LTD

Signed at Little Falls, Gauteng, South Africa, on 02 June 2017.


CONTRIBUTING AUTHORS



PG Obermeyer (Mineral Resource Manager)
 BSc Hons (Geol.), Pr.Sci.Nat.



L Hope (Senior Resource Geologist)
 NHD (Econ. Geol.), Pr.Sci.Nat.


M Antoniadou (Geologist)
 BSc Hons (Geol.), Cand.Sci.Nat., MGSSA


DS Rathogwa (Exploration Geologist)
 BSc (Geol. & Math.), BSc Hons (Geol.), MGSSA

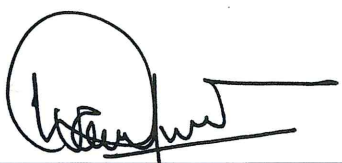

J Burger (Mining Engineer)
 B Eng (Min.), PG Dip. (Fin. Man.), MMC,
 Pr.Eng., MSAIMM



JW Knight (Senior Process Engineer)
 B Eng (Chem.), B Eng Hons (MOT), Pr.Eng.,
 MSAIMM



FJ Visser (Mechanical Engineer)
 B Eng (Min.), GCC


OW Warschkuhl (Mining Engineer)
 B Eng (Min.), B Eng Hons (Min.), MSAIMM

REVIEWED BY DIRECTORS


D van Heerden (Director)
 B Eng (Min.), MCom (Bus. Admin.), MMC,
 Pr.Eng., FSAIMM, AMMSA

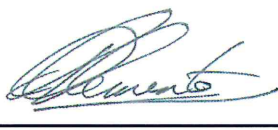
NJ Odendaal (Director)
 BSc (Geol.), BSc (Min. Econ.), MSc (Min. Eng.),
 Pr.Sci.Nat., FSAIMM, MGSSA


D Clemente (Director)
 NHD (Ext. Met.), GCC, BLDP (WBS), MMA,
 FSAIMM

INFORMATION RISK

This Report was prepared by Minxcon (Pty) Ltd (“Minxcon”). In the preparation of the Report, Minxcon utilised information relating to operational methods and expectations provided to them by various sources. Where possible, Minxcon has verified this information from independent sources after making due enquiry of all material issues that are required in order to comply with the requirements of the NI 43-101 and Form 43-101 F1. Minxcon and its directors accept no liability for any losses arising from reliance upon the information presented in this Report. The authors of this report are not qualified to provide extensive commentary on legal issues associated with rights to the mineral properties and relied on the information provided to them by the issuer. No warranty or guarantee, be it express or implied, is made by the authors with respect to the completeness or accuracy of the legal aspects of this document.

OPERATIONAL RISKS

The business of mining and mineral exploration, development and production by their nature contain significant operational risks. The business depends upon, amongst other things, successful prospecting programmes and competent management. Profitability and asset values can be affected by unforeseen changes in operating circumstances and technical issues.

POLITICAL AND ECONOMIC RISK

Factors such as political and industrial disruption, currency fluctuation and interest rates could have an impact on future operations, and potential revenue streams can also be affected by these factors. The majority of these factors are, and will be, beyond the control of any operating entity.

FORWARD LOOKING STATEMENTS

Certain statements contained in this document other than statements of historical fact, contain forward-looking statements regarding the operations, economic performance or financial condition, including, without limitation, those concerning the economic outlook for the mining industry, expectations regarding commodity prices, exchange rates, production, cash costs and other operating results, growth prospects and the outlook of operations, including the completion and commencement of commercial operations of specific production projects, its liquidity and capital resources and expenditure, and the outcome and consequences of any pending litigation or enforcement proceedings.

Although Minxcon believes that the expectations reflected in such forward-looking statements are reasonable, no assurance can be given that such expectations will prove to be correct. Accordingly, results may differ materially from those set out in the forward-looking statements as a result of, among other factors, changes in economic and market conditions, changes in the regulatory environment and other State actions, success of business and operating initiatives, fluctuations in commodity prices and exchange rates, and business and potential risk management.

TABLE OF CONTENTS

Item 1	- Executive Summary	1
Item 1 (a)	- Property Description	1
Item 1 (b)	- Ownership of the Property	2
Item 1 (c)	- Geology and Mineral Deposit	3
Item 1 (d)	- Overview of the Project Geology	7
Item 1 (e)	- Local Property Geology	8
Item 1 (f)	- Status of Exploration	10
Item 1 (g)	- Mineral Resource Estimates	10
Item 1 (h)	- Qualified Person's Conclusions and Recommendations	12
Item 2	- Introduction	13
Item 2 (a)	- Issuer Receiving the Report	13
Item 2 (b)	- Terms of Reference and Purpose of the Report	13
Item 2 (c)	- Sources of Information and Data Contained in the Report	13
Item 2 (d)	- Qualified Persons' Personal Inspection of the Property	14
Item 3	- Reliance on Other Experts	15
Item 4	- Property Description and Location	16
Item 4 (a)	- Area of the Property	16
Item 4 (b)	- Location of the Property	18
Item 4 (c)	- Mineral Deposit Tenure	19
Item 4 (d)	- Issuer's Title to/Interest in the Property	20
Item 4 (e)	- Royalties and Payments	21
Item 4 (f)	- Environmental Liabilities	22
Item 4 (g)	- Permits to Conduct Work	22
Item 4 (h)	- Other Significant Factors and Risks	22
Item 5	- Accessibility, Climate, Local Resources, Infrastructure and Physiography	23
Item 5 (a)	- Topography, Elevation and Vegetation	23
Item 5 (b)	- Access to the Property	23
Item 5 (c)	- Proximity to Population Centres and Nature of Transport	23
Item 5 (d)	- Climate and Length of Operating Season	23
Item 5 (e)	- Infrastructure	25
Item 6	- History	27
Item 6 (a)	- Prior Ownership and Ownership Changes	27
Item 6 (b)	- Historical Exploration and Development	27
Item 6 (c)	- Historical Mineral Resource Estimates	29
Item 6 (d)	- Historical Mineral Reserve Estimates	30
Item 6 (e)	- Historical Production	30
Item 7	- Geological Setting and Mineralisation	32
Item 7 (a)	- Regional Geology	32
Item 7 (b)	- Local Geology	35
Item 7 (c)	- Property Geology	37
Item 7 (d)	- Mineralisation	40
Item 8	- Deposit Types	43
Item 8 (a)	- Mineral Deposits being Investigated	43
Item 8 (b)	- Geological Model	43
Item 9	- Exploration	55
Item 9 (a)	- Survey Procedures and Parameters	55
Item 9 (b)	- Sampling Methods and Sample Quality	55

Item 9 (c) - Sample Data	56
Item 9 (d) - Results and Interpretation of Exploration Information	57
Item 10 - Drilling	59
Item 10 (a) - Type and Extent of Drilling	59
Item 10 (b) - Factors Influencing the Accuracy of Results	63
Item 10 (c) - Exploration Properties - Drillhole Details	63
Item 11 - Sample Preparation, Analyses and Security	65
Item 11 (a) - Sample Handling Prior to Dispatch	65
Item 11 (b) - Sample Preparation and Analysis Procedures	65
Item 11 (c) - Quality Assurance and Quality Control	67
Item 11 (d) - Adequacy of Sample Preparation	76
Item 12 - Data Verification	77
Item 12 (a) - Data Verification Procedures	77
Item 12 (b) - Limitations on/Failure to Conduct Data Verification	79
Item 12 (c) - Adequacy of Data	80
Item 13 - Mineral Processing and Metallurgical Testing	81
Item 14 - Mineral Resource Estimates	82
Item 14 (a) - Assumptions, Parameters and Methods Used for Resource Estimates	82
Item 14 (b) - Disclosure Requirements for Resources	119
Item 14 (c) - Individual Grade of Metals	120
Item 14 (d) - Factors Affecting Mineral Resource Estimates	120
Item 15 - Mineral Reserve Estimates	129
Item 16 - Mining Methods	129
Item 17 - Recovery Methods	129
Item 18 - Project Infrastructure	129
Item 19 - Market Studies and Contracts	129
Item 20 - Environmental Studies, Permitting and Social or Community Impact	130
Item 20 (a) - Relevant Environmental Issues and Results of Studies Done	130
Item 20 (b) - Waste Disposal, Site Monitoring and Water Management	130
Item 20 (c) - Permit Requirements	131
Item 20 (d) - Social and Community-Related Requirements	131
Item 20 (e) - Mine Closure Costs and Requirements	131
Item 21 - Capital and Operating Costs	132
Item 22 - Economic Analysis	132
Item 23 - Adjacent Properties	133
Item 23 (a) - Public Domain Information	133
Item 23 (b) - Sources of Information	134
Item 23 (c) - Verification of Information	134
Item 23 (d) - Applicability of Adjacent Property's Mineral Deposit to Project	134
Item 23 (e) - Historical Estimates of Mineral Resources or Mineral Reserves	135
Item 24 - Other Relevant Data and Information	136
Item 24 (a) - Upside Potential	136
Item 25 - Interpretation and Conclusions	156
Item 26 - Recommendations	159
Item 27 - References	161
Appendix	162

FIGURES

Figure 1: Location of the Project Areas	17
Figure 2: Location of the Deposits.....	18
Figure 3: Regional Location of the Project	19
Figure 4: Corporate Structure	21
Figure 5: Kombat Area Average Annual Temperature Graph	24
Figure 6: Kombat Area Average Annual Precipitation Graph	25
Figure 7: Asis Far West Historical Inferred Mineral Resource Area, as per P&E as at April 2014	30
Figure 8: Historic Feed Tonnes and Grade between 1961 and 2007	31
Figure 9: Historic Copper Concentrate Production between 1961 and 2007	31
Figure 10: Location of the Damara Orogenic Belt during the Amalgamation of the Gondwana Supercontinent	32
Figure 11: Location of the Cratons and Orogenic Belts, with Tectonics in Play during the Formation of the Damara Orogen.....	33
Figure 12: Stratigraphy of the Damara Supergroup and the Relative Stratigraphic Locations of Known Mineral Deposits	34
Figure 13: Geology of the Otavi Mountainland and the Locations of Known Mineral Deposits.....	35
Figure 14: A Historical Map Depicting the Geology of the Otavi Valley Syncline.....	36
Figure 15: A Schematic Section through the Otavi Valley Syncline.....	37
Figure 16: Geology of Kombat Mine depicting the En 'Echelon Geometry of the Orebodies and the Kombat West Fault	38
Figure 17: Schematic Diagram Depicting the Relation of the Hanging Orebodies relative to the Roll Structures and Phyllite/Dolomite Contact.....	39
Figure 18: Wireframe Section View of the Recoded Drillhole Traces for the Interpretation of the Phyllite / Dolomite Contact	44
Figure 19 : Oblique View of the Rough Dolomite/Phyllite Contact Wireframe Showing the Interpreted Final Flagging in the Drillholes	45
Figure 20: Geological Plan Used to Identify Major Structures for Segmenting the Rough Dolomite/Phyllite Contact Wireframe	46
Figure 21: Final Dolomite/ Phyllite Interface with the Major Faulting Taken into Account	46
Figure 22: Oblique View (Looking Northwest) of the Kombat West Fault and Its Impact on the Dolomite/Phyllite Wireframe Model	47
Figure 23: Plan View of the Faults in Datamine as used in the Geological Modelling	48
Figure 24: The Impact of the Modelled Faults on Orebody Grade Shells	48
Figure 25: Log Probability Plot of the Combined Cu+Pb Showing the Inflection Point of 0.3%	49
Figure 26: Plan View of a 0.3% Cu/Pb Grade Shell with the Historic Development	50
Figure 27: Oblique View of a 0.3% Cu/Pb Grade Shell that was Expanded to Encompass the Historical Stopping	51
Figure 28: Section Showing the Mineralised Halos at 0.3% CuPb and the Limiting of the Dolomite/Phyllite Interface	52
Figure 29: Oblique Section of the Otavi Mineralised Halos at 0.3% CuPb.....	53
Figure 30: Oblique View Looking East Showing the New Topographical Surface with the Current Open Cast and Underground Mine Development.....	54
Figure 31: Oblique View of the Kombat and Asis Mineralised Halos at 0.3% CuPb	54
Figure 32: Aeromagnetic Contour Plan with Superimposed Geology	55
Figure 33: Kombat Regional Soil Geochemistry	56
Figure 34: Soil Geochemistry Results.	57

Figure 35: Historical Sample Preparation and Analysis Flow Chart at Kombat Mine Laboratory	66
Figure 36: Blank QAQC Results for Silver	68
Figure 37: Blank QAQC Results for Lead	69
Figure 38: Blank QAQC results for Copper.....	70
Figure 39: AMIS0309 QAQC Graph for Copper.....	71
Figure 40: AMIS0309 QAQC Graph for Silver	71
Figure 41: AMIS0424 QAQC Graph for Copper.....	72
Figure 42: Core Duplicates QAQC Graph for Copper Analysis	73
Figure 43: Core Duplicates QAQC Graph for Lead analysis.	73
Figure 44: Core Duplicates QAQC Graph for Silver Analysis	74
Figure 45: Pulp Duplicates QAQC Graph for Copper Analysis	75
Figure 46: Pulp Duplicates QAQC Graph for Lead Analysis	75
Figure 47: Pulp Duplicates QAQC Graph for Silver Analysis	76
Figure 48: Stretch Values of a Single Sample over 5 m	77
Figure 49: Historical Wireframes for the Asis Far West and Asis West	78
Figure 50: Historical Voids for the Kombat and Asis Sections	79
Figure 51: Kombat Section Raw Copper Histogram	84
Figure 52: Asis Section Raw Copper Histogram.....	85
Figure 53: Otavi Section Raw Copper Histogram	85
Figure 54: Oblique Plan View looking South Showing the Domains and Faults in the Kombat Section and Asis Section.....	86
Figure 55: Log Probability Plot of the Cu Values with the Capping Indicated for the Kombat Section	87
Figure 56: Log Probability Plot of the Cu Values with the Capping Indicated for the Asis Section	88
Figure 57: Log Probability Plot of the Cu Values with the Capping Indicated for the Otavi Section	89
Figure 58: Log Probability Plot of the Pb Values with the Capping Indicated for the Kombat Section.....	90
Figure 59: Log Probability Plot of the Pb Values with the Capping Indicated for the Asis Section	91
Figure 60: Log Probability Plot of the Pb Values with the Capping Indicated for the Otavi Section	92
Figure 61: Histogram of the Raw Sample Lengths	93
Figure 62: Log Variogram for Copper for the Kombat Section	94
Figure 63: Log Variogram for Copper for the Asis Section.....	94
Figure 64: Log Variogram for Copper for the Otavi Section.....	95
Figure 65: Asis West Block Model in Section looking North and West. Showing the Reduction of the Estimate by Restricting the Z Search in the Estimation	97
Figure 66: Kombat Mine Mineral Resource with no Cut-off Applied and no Historical Voids Removed.....	98
Figure 67: Kombat Mine Mineral Resource with a CuEq Cut-off of 1.4% Applied and the Historical Voids Removed	98
Figure 68: Asis Mine Mineral Resource with No Cut-off Applied and no Historical Voids Removed	99
Figure 69: Asis Mine Mineral Resource with a CuEq Cut-off of 1.4% Cu Applied and the Historical Voids Removed	100
Figure 70: Otavi Mine Mineral Resource Looking East with no Cut-off Applied and a CuEq Cut-off of 0.77% Applied	100
Figure 71: Kombat Central Section model Looking East with a CuEq cut-off of 0.77% Applied.....	101
Figure 72: Asis West Section Model Looking East with a CuEq Cut-off of 1.4% Applied	102
Figure 73: Asis Far West Section Model Looking East with a CuEq Cut-off of 1.4% Applied	102
Figure 74: Kombat East Estimation Model at a CuEq Cut-Off of 0.77 % with Historical Mining Voids.....	103
Figure 75: Kombat Central Estimation Model at a CuEq cut-off of 0.77 % with Historical Mining Voids	104
Figure 76: Kombat West Estimation Model at a CuEq cut-off of 0.77 % with Historical Mining Voids	105
Figure 77: Asis West Estimation Model at a CuEq cut-off of 1.40 % with Historical Mining Voids	106
Figure 78: Asis Far West Estimation Model at a CuEq cut-off of 1.40 % with Historical Mining Voids	107

Figure 79: Historical Longitudinal Sections Showing the Mined-out Areas	108
Figure 80: Historical Longitudinal Section Showing Void Digitised into Datamine	109
Figure 81: Visual Check of the Otavi Model versus the Estimated Grade Model.....	110
Figure 82 Kombat Section Scatter Plot of the Copper and Lead Estimation versus the Average Drillhole Values	111
Figure 83: Asis Section Scatter Plot of the Copper and Lead Estimation versus the Average Drillhole Values	112
Figure 84: Otavi Section Scatter Plot of the Copper and Lead Estimation versus the Average Drillhole Values	113
Figure 85: Kombat and Asis Section Swath Plan and Section	114
Figure 86: Kombat/Asis Section Copper Swath Analysis East to West and Vertically.....	115
Figure 87: Kombat/Asis Section Lead Swath Analysis East to West and Vertically	116
Figure 88: Otavi Section Swath Plan and Section	117
Figure 89: Otavi Section Copper Swath Analysis East to West and Vertically.....	118
Figure 90: Otavi Section Lead Swath Analysis East to West and Vertically.....	119
Figure 91: Optimised Open Pit Simulation for the Kombat Section.....	121
Figure 92 Historical Copper and Lead Prices used for the Cut-off Parameters	122
Figure 93: Kombat Section Copper Grade Tonnage Curve.....	125
Figure 94: Asis Mine Copper Grade Tonnage Curve	126
Figure 95: Gross Otavi Section Copper Grade Tonnage Curve	127
Figure 96: Adjacent Properties (Sabre Resources).....	133
Figure 97: Regional Location with Nearby Mines.....	134
Figure 98: TSF Wireframe with the Drillholes	136
Figure 99: Inverse Distance Squared Estimation of the TSF shows Potential at 0.3% Cu Cut-off	137
Figure 100: The Interpreted Asis West Upside Potential “Gap” Area Requiring Exploration Drilling	138
Figure 101: Pit Designs: Kombat East and Kombat Central	141
Figure 102: Underground Designs: Asis Far West and Asis West	141
Figure 103: Diluted Plant Feed Tonnes	142
Figure 104: Block Flow Schematic of the Kombat Plant	143
Figure 105: Kombat - East and Central Open Pit Infrastructure Layout	144
Figure 106: Capital Schedule Based on PEA Study	146
Figure 107: Saleable Products	149
Figure 108: Monte Carlo Simulation Summary Report.....	151
Figure 109: Open Pit Stand-alone Annual and Cumulative Cash Flow.....	152
Figure 110: Peak Project Funding Requirement per Annum	153
Figure 111: Combined Annual and Cumulative Cash Flow.....	153
Figure 112: Project Sensitivity (NPV _{11.02%}).....	154

TABLES

Table 1: Kombat Licence Areas and Associated Deposits.....	16
Table 2: Mineral Licences	19
Table 3: History of Exploration and Development	27
Table 4: Asis Far West Historical Inferred Mineral Resources at Various Copper Cut-off Grades, as per P&E as at April 2014	29
Table 5: Average Production 1961-2007	30
Table 6: Significant Trench Intercepts (>0.5% Cu) for 2015.....	58
Table 7: Significant Mineralised Intercepts (>2.0% Cu) for the 2015 Kombat Section Drilling Programme ..	61

Table 8: Significant Mineralised Intercepts (>2.0% Cu) for the 2012 Gross Otavi Drilling Programme.	63
Table 9: Recent Diamond Drillhole Summary	64
Table 10: Details of AMIS0309	70
Table 11: Details of AMIS0424 CRM.	72
Table 12: Kombat Drillhole Statistics	83
Table 13: Asis Drillhole Statistics	83
Table 14: Otavi Drillhole Statistics	84
Table 15: Capping of the Metal Content for Each Section	86
Table 16: Variogram Summary for the Different Areas for Cu, Pb, Ag and Zn.....	93
Table 17: Block Model Origin and Cell Size	96
Table 18: Search Parameters for the Kombat, Asis and Otavi Sections	96
Table 19: Cut-off Values Relative to Cu and Pb Recovery Values as Calculated for Each Mining Area.....	123
Table 20: Open Pittable Mineral Resources for the Kombat Operations at a Copper Equivalent Cut-off of CuEq 0.77% as at April 2017	123
Table 21 Underground Mineral Resources for the Kombat Operations at a Copper equivalent Cut-off of CuEq 0.77% as at April 2017.....	124
Table 22: Combined Mineral Resources for the Kombat Operations as at April 2017	124
Table 23: Open Pit Mineral Resource Split into 10 m Benches	128
Table 24: Potential Mineral Resources for the TSF at a 0.3 % Cu and 0.4 % Cu Cut off	137
Table 25: Mining and Processing Operating Cost Summary.....	147
Table 26: Financial Cost Indicators.....	147
Table 27: Combined Production Breakdown in Life of Mine	148
Table 28: Macro-Economic Forecasts and Commodity Prices over the LoM (Real Terms)	149
Table 29: Valuation Summary	150
Table 30: Monte Carlo Input Ranges.....	150
Table 31: NPV _{11.02%} Sensitivity to Net Turnover and Average Copper Grade (USD million)	155
Table 32: NPV _{11.02%} Sensitivity to Cash Cost and Average Copper Grade (USD million)	155

EQUATIONS

Equation 1: Revised Tsumeb Formula	95
--	----

APPENDICES

Appendix 1: Qualified Persons' Certificates	162
Appendix 2: Historical QAQC Results	166

LIST OF UNITS AND ABBREVIATIONS

The following units were used in this Report, and are in metric terms:-

Unit	Description
%	Per cent
/	Per
°	Degrees
°C	Degrees Celsius
cm	Centimetres
g/t	Grams per tonne
ha	Hectares
kg	Kilogram
km	Kilometres
kt	Kilo tonnes
ktpm	Kilo tonnes per month
kV	Kilo volt
m	Metres
mm	Millimetres
m ³	Cubic metres
m ³ /h	Cubic metres per hour
Ma	Million years
Mt	Million tonnes
MVA	Mega volt ampere
ppm	Parts per million
ppb	Parts per billion
t	Tonnes
tpd	Tonnes per day

The following abbreviations were used in this Report:-

Abbreviation	Description
Ag	Silver
AMIS	African Mineral Standards
amsl	Above Mean Sea Level
Bureau Veritas	Bureau Veritas Namibia (Pty) Ltd Mineral Laboratory
Capex	Capital Expenditure
CIM	Canadian Institute of Mining, Metallurgy and Petroleum
Cu	Copper
CuEq	Copper Equivalent
DCF	Discounted Cash Flow
DDH	Diamond Drillholes
ECC	Environmental Clearance Certificate
EIA	Environmental Impact Assessment
EMA	Environmental Management Act, No. 7 of 2007
EMP	Environmental Management Plan
FCFF	Free Cash Flow to Firm
Grove	Grove Mining (Pty) Ltd
Kombat Copper	Kombat Copper Inc.
Kombat or Project	Kombat Copper Project
Manila	Manila Investments (Pty) Ltd
MET	Ministry of Environment and Tourism
Minerals Act	Minerals (Prospecting and Mining) Act, No. 33 of 1992
Minxcon	Minxcon (Pty) Ltd
MME	Ministry of Mines and Energy
NI 43-101	National Instrument 43-101 (Standards of Disclosure for Mineral Projects), Form 43-101F1 and the Companion Policy Document 43-101CP
NPV	Net Present Value
OMEG	Otavi Minen und Eisenbahn Gesellschaft
OML	Otavi Mountainland
Ongopolo	Ongopolo Mining and Processing Limited
Ongopolo Mining	Ongopolo Mining Limited
Opex	Operating Expenditure
P&E	P&E Mining Consultants Inc.
PEA	Preliminary Economic Assessment
Pb	Lead
RC	Reverse Circulation
Sabre	Sabre Resources Limited
SLR Namibia	SLR Consulting Namibia (Pty) Ltd
TCL	Tsumeb Corporation Limited
The Report	NI 43-101 Technical Report on the Kombat Copper Project, Namibia - Mineral Resource Report" prepared for Trigon Metals Inc. with an effective date of 01 April 2017
TLB	Tractor-Loader-Backhoe
Trigon or the Client	Trigon Metals Inc.
TSF	Tailings Storage Facility
Weatherly	Weatherly International PLC
Zn	Zinc

ITEM 1 - EXECUTIVE SUMMARY

Minxcon (Pty) Ltd (“Minxcon”) was commissioned by Trigon Metals Inc. (“Trigon” or “the Client”) to complete a Mineral Resource estimation on their Kombat Copper Project (“Kombat” or “Project”), situated in Grootfontein District, Otjozondjupa Region, Namibia.

This Report was compiled in compliance with the specifications embodied in the Standards of Disclosure for Mineral Projects as set out by the Canadian Code for reporting of Mineral Resources and Mineral Reserves - National Instrument 43-101 (Standards of Disclosure for Mineral Projects), Form 43-101F1 and the Companion Policy Document 43-101CP (“NI 43-101”). Only terms as defined by The Canadian Institute of Mining, Metallurgy and Petroleum (“CIM”) have been utilised in this Report.

Item 1 (a) - PROPERTY DESCRIPTION

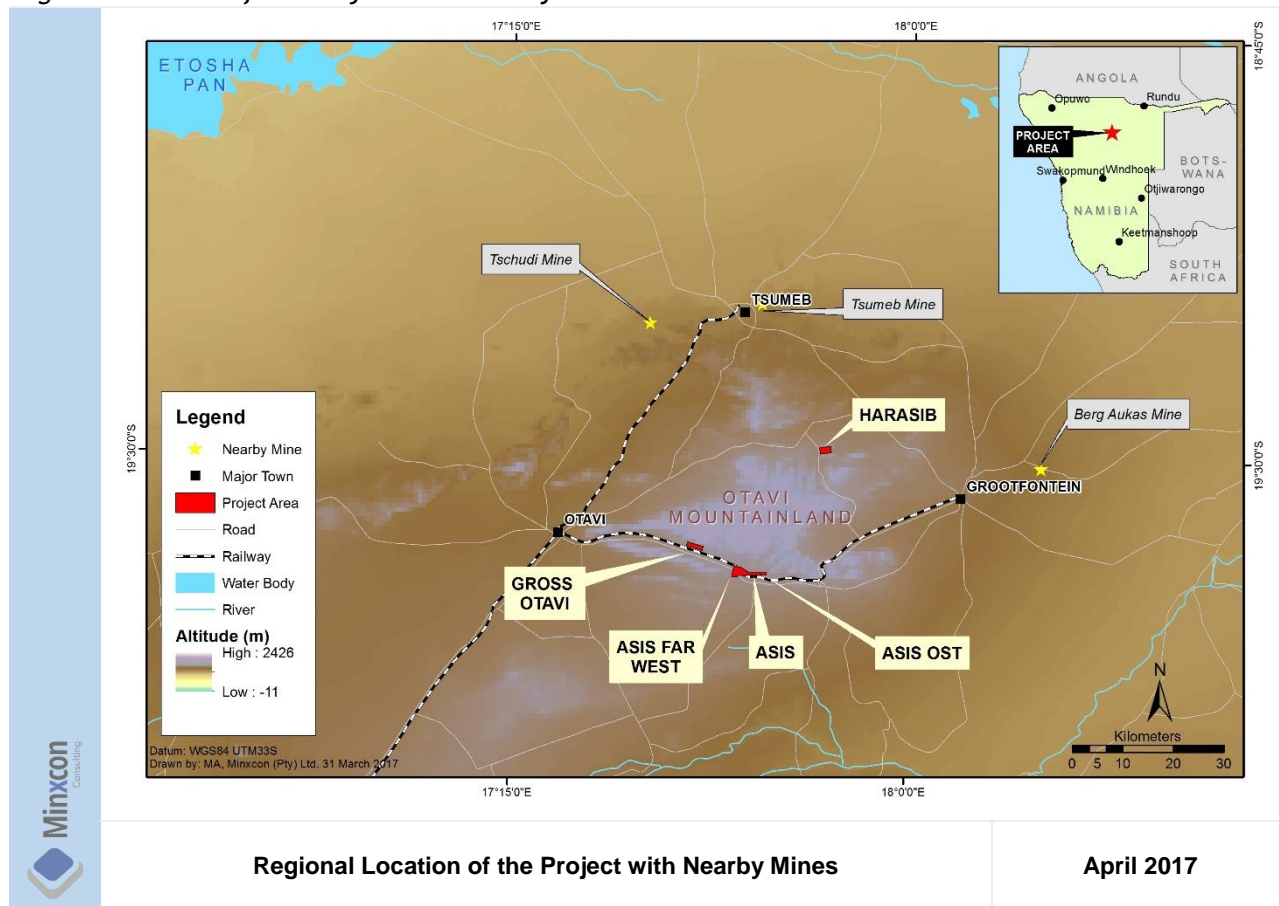
The Kombat Copper Project occurs within the Otavi Mountain Range in a region which is associated historically and currently with high grade copper mineralisation and as such, is littered with old workings. The copper mineralisation is also associated with substantial lead and silver content. Kombat is situated on the B8 road to Grootfontein, some 37 km east of Otavi and 45 km due west of Grootfontein. The small ex-mining town of Kombat lies adjacent to the south of the Project. The Project is easily accessible via paved roads with direct access to the individual properties via unpaved district and farm roads. A rail network traverses the Project Areas, linking the Kombat concentrator to the Tsumeb smelter in Tsumeb as well as Walvis Bay port some 500 km southwest.

The Project is a collective term for the licence areas and deposits that include Gross Otavi, Asis (including the Kombat Central, Kombat West and Kombat East deposits), Asis Far West (including the Asis West and Asis Far West deposits) and Asis Ost. A ~39 ha tailings storage facility (“TSF”) for the processed ore is located off the licence areas some 1.5 km south of the Asis licence boundary. The Harasib lead-zinc exploration project lies to the northeast, but is excluded from this Mineral Resource estimation.

The contiguous Asis Far West, Asis and Asis Ost licence areas are centred on the co-ordinates 19°42’37”S 17°42’13”E (WGS84 UTM 33S), with Gross Otavi situated some 8 km due northwest of the Asis licence areas and the TSF 1 km south.

The regional location of the Project is illustrated in the following figure.

Regional Location of the Project with Nearby Mines



Item 1 (b) - OWNERSHIP OF THE PROPERTY

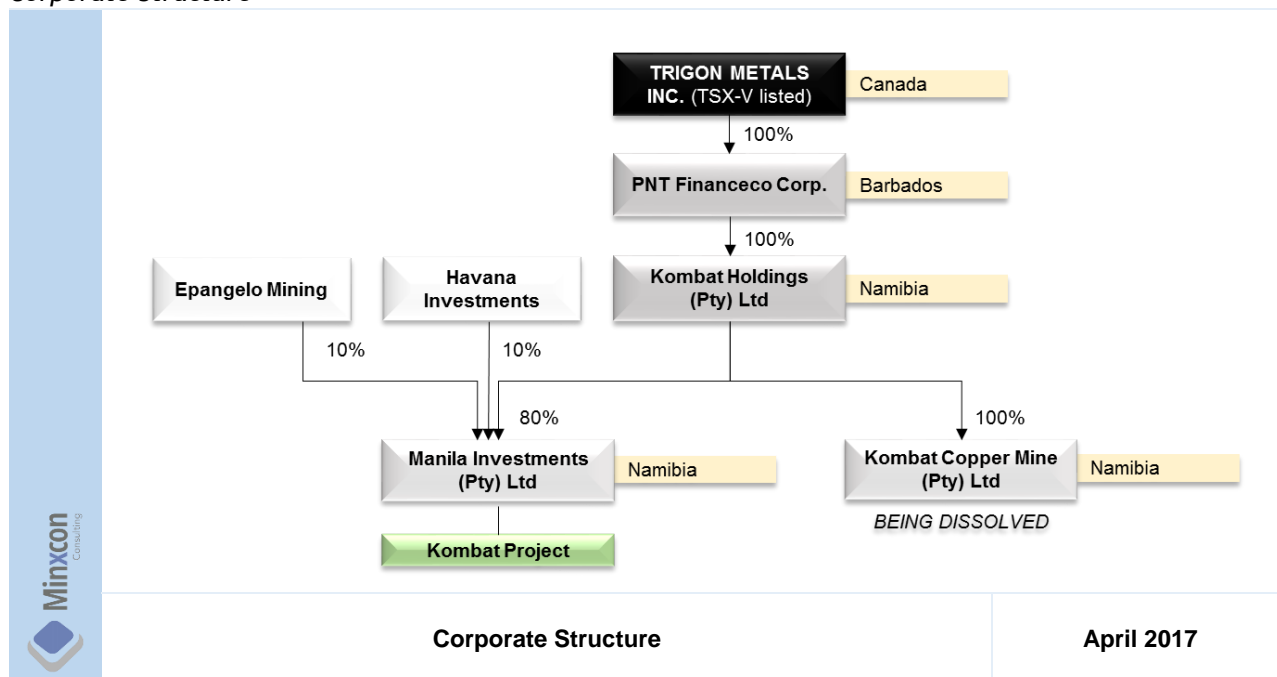
The Project is comprised of five valid mining licences, namely the contiguous ML9 (Asis Ost), ML16 (Asis Far West) and ML73B (Asis), as well as ML21 (Harasib) and ML73C (Gross Otavi). The total combined area covered by the licences is 1,216.7 ha. All the licences are held in the name of Manila Investments (Pty) Ltd (“Manila”) - an indirect subsidiary of Trigon - and all are valid and expire on 31 March 2019.

The TSF is located within the Kombat Town limits and does not fall within any mineral rights area. Trigon does, however, own the land over which the TSF is situated. As the current Minerals Act does not deal with the utilisation of tailings and specifically includes tailings under the definition of waste, an Environmental Clearance Certificate (“ECC”) will be required in order to extract resources from the TSF.

In April 2012, Kombat Copper Inc. (“Kombat Copper”) acquired 80% of the outstanding shares of Manila whose primary asset was a 100% interest in the formerly producing Kombat Copper Mine, as well as all related mining licences and assets, including all mining surface infrastructure and equipment. In June 2016, Kombat Copper initiated a corporate restructuring plan. In addition to various other corporate initiatives, Kombat Copper also undertook a rebranding in December 2016, in terms of which the company was renamed Trigon Metals Inc.

The corporate structure of Trigon is shown in the following figure.

Corporate Structure




Item 1 (c) - GEOLOGY AND MINERAL DEPOSIT

Regional Tectonics

The Damara Orogenic Belt (or Damara Orogen) was formed late during the supercontinent formation of Gondwana at the collisional triple junction of the Congo, Kalahari and Rio de la Plata Cratons as presented in the figure below.

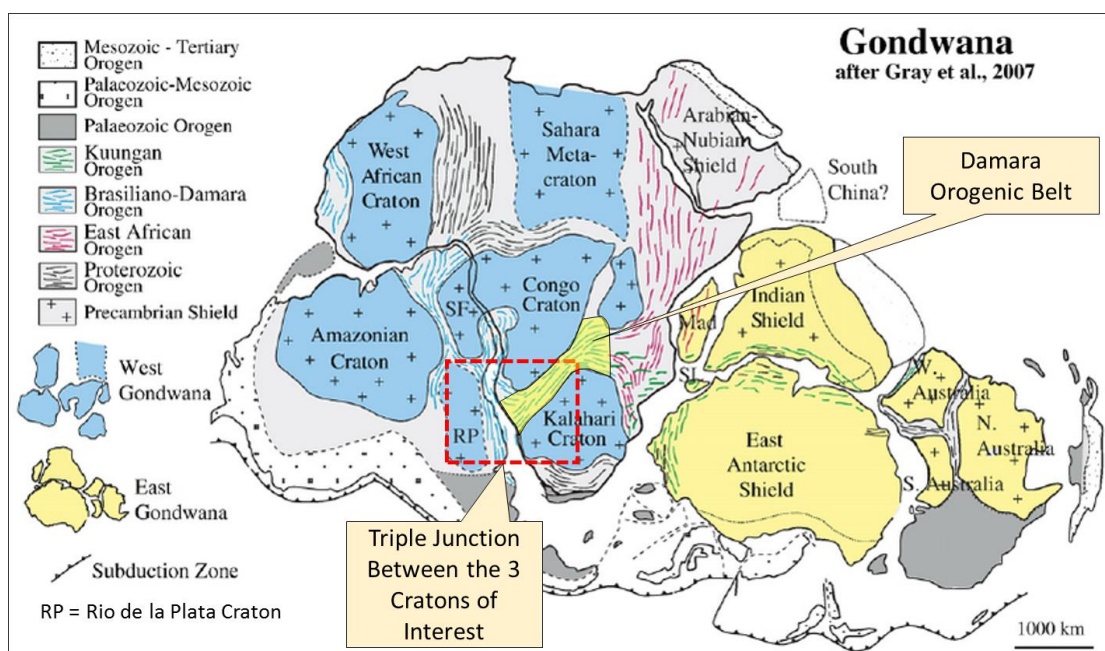Location of the Damara Orogenic Belt during the Amalgamation of the Gondwana Supercontinent



Source: Adapted from Meert and Lieberman (2007)


Location of the Damara Orogenic Belt during the Amalgamation of the Gondwana Supercontinent

April 2017

The northeast trending Damara Orogenic Belt was formed when the passive continental margins of the Congo and Kalahari Cratons collided with thrusting of basin sediments onto the Kalahari Craton from 495 Ma through to 480 Ma.

The Damara Orogenic Belt may be divided into three major zones separated by northeast trending lineaments, namely the 1) Northern 2) Central and 3) Southern Zones (refer to the figure below). The Damara Belt is bordered to the north by the Northern Platform on the Congo Craton and to the south by the Southern Foreland of the Kalahari Craton. The contact between the Northern Platform and the Northern Zone is marked by an arcuate chain of major basement ridges and domes extending over 1,000 km and which affected later carbonate sedimentation called the Otavi Mountainland ("OML").

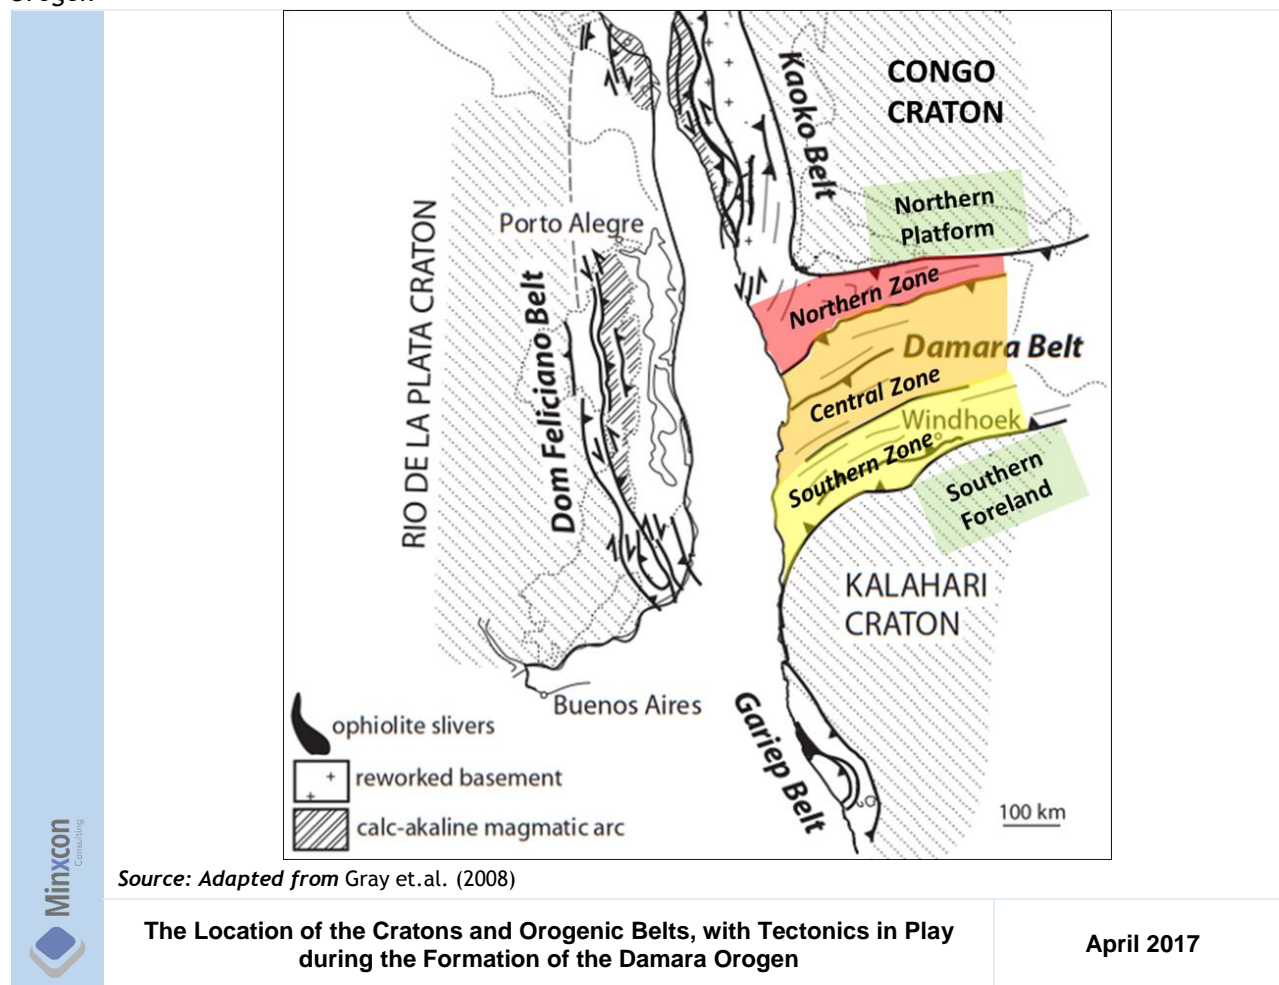Location of the Cratons and Orogenic Belts, with Tectonics in Play during the Formation of the Damara Orogen



Stratigraphy of the Damara Orogenic Belt

The Paleoproterozoic basement to the Damara Supergroup is known as the Grootfontein Inlier. The Damara Supergroup is divided into the Nosib, Otavi and Mulden Groups as presented in the stratigraphic column in the following figure.

Stratigraphy of the Damara Supergroup and the Relative Stratigraphic Locations of Known Mineral Deposits

GROUP		FORMATION	LITHOLOGY	DEPOSIT
MULDEN		Kombat	slate phyllite sandstone	
		Tschudi	arenite subgreywacke conglomerate	Tschudi Cu-(Ag)
OTAVI	Tsumeb Subgroup	Huttenberg	dolostone, oolite chert dolostone shale stromatolite chert, breccia	Kombat Cu-Pb-(Zn) Tsumeb Pb-Cu-Zn-(Ge)
		Elandschoek	dolostone chert breccia dolostone	
		Maieberg	dolostone limestone	Abenab V Khusib Springs Cu-Pb-Zn
		Ghaub	dolostone diamictite	
	Abenab Subgroup	Auros	stromatolite chert, limestone	Abenab West Pb-Zn-V
		Gauss	breccia oolite dolostone chert	Berg Aukas Zn-Pb-V
		Berg Aukas	dolostone, chert	
		Varianto	diamictite	
		Askevold	tuff, quartzite quartzite sandstone conglomerate	Nosib Cu; Askevold Cu
	NOSIB	Nabis		
GROOTFONTEIN BASEMENT COMPLEX				

Source: Kamona, A.F. & Günzel, A. (2007)

Minxcon Consulting

The Stratigraphy of the Damara Supergroup and the Relative Stratigraphic Locations of Known Mineral Deposits

April 2017

The Otavi Group was deposited as a carbonate platform on the Northern Platform of the Congo Craton and consists of the Abenab Subgroup and the overlying Tsumeb Subgroup.

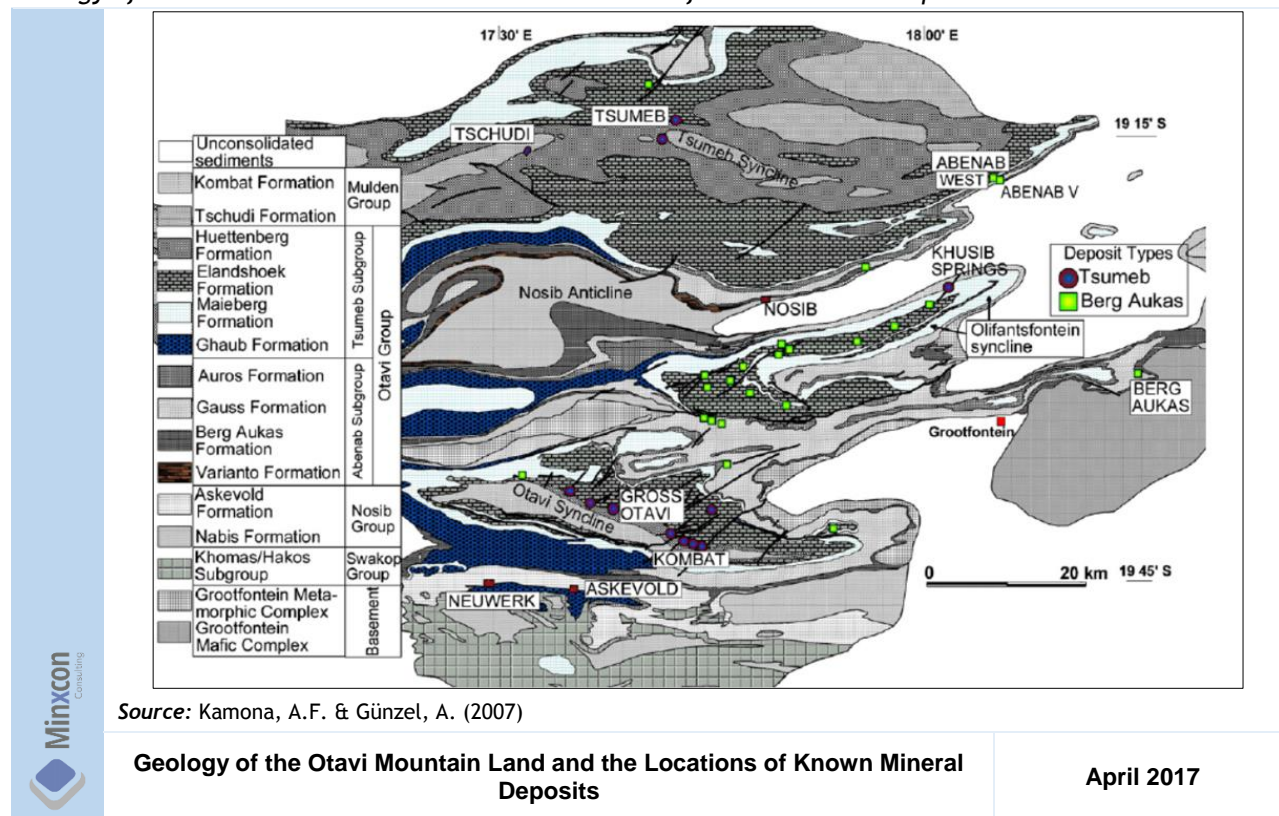
The Kombat ore deposits are located towards the top of the Hüttenberg Formation, where erosion of the formation resulted in the development of karst topography and a major unconformity prior to deposition of the overlying Mulden Group. The Mulden Group consists of the Tschudi and Kombat Formations as depicted in the figure above.

The Tschudi Formation consists of a basal conglomerate, a fining-upward feldspathic arenite with minor greywacke and intraformational breccias. The Kombat Formation overlies the Tschudi Formation and consists of a sequence of siltstone, sandstone and shale separated by a prominent middle member of black shale with siltstone. In some areas the Kombat Formation has been metamorphosed to form slate which at Kombat limits the vertical extent of the orebodies.

Item 1 (d) - OVERVIEW OF THE PROJECT GEOLOGY


The Kombat Mine is located in the OML on the Northern Platform Margin of the Damara Orogenic Belt. The Damara Supergroup rocks of the OML have been folded into generally east to west trending synclines and anticlines, as presented in the figure below.

Geology of the Otavi Mountain Land and the Locations of Known Mineral Deposits



The formation of a complex foreland thrust belt to the west may have influenced sedimentary patterns of the Mulden Group within the OML, while closure of the Damara Orogenic Belt resulted in recumbent shearing with an overthrust sense to the southwest on a low-angle shear zone. High temperature rocks containing metamorphic brines were thrust over the cooler Mulden Formation rocks, resulting in the formation of the Otavi Valley syncline as depicted in the figure below. Further instability of the cratonic plates resulted in northwest-trending open, upright warps.

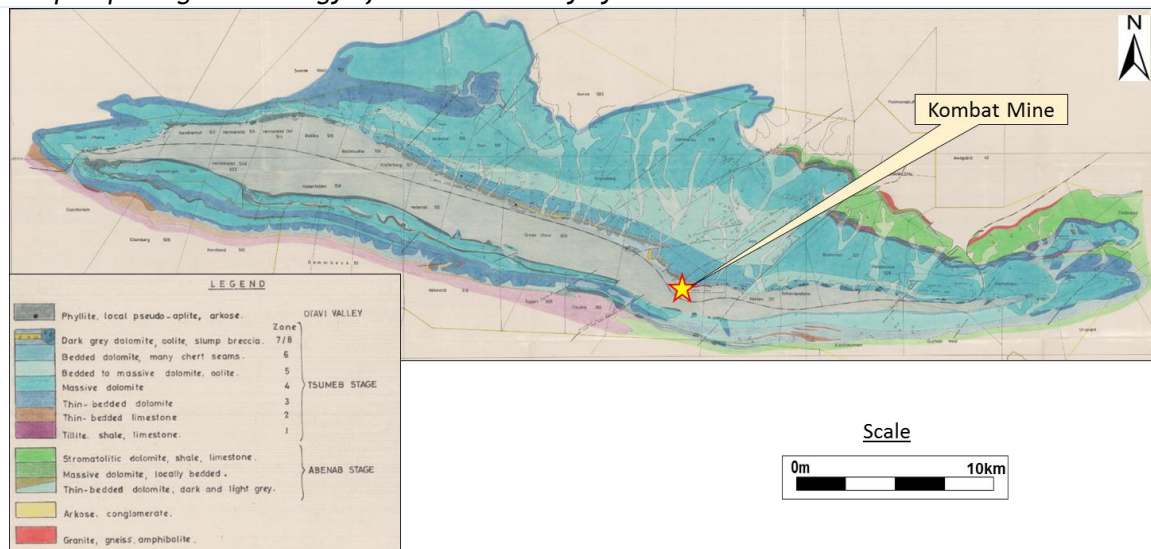Historical Map Depicting the Geology of the Otavi Valley Syncline



Source: Map Supplied by Kombat Mine

Historical Map Depicting the Geology of the Otavi Valley Syncline


April 2017

Item 1 (e) - LOCAL PROPERTY GEOLOGY

The orebodies on Kombat and Otavi are situated on the northern limb of the canoe-shaped Otavi Valley Syncline. The northern limb dips to the south at between 20° and 75°. Several northeast and east trending normal and strike-slip faults cross-cut the syncline and post-date mineralisation.

Seven distinct zones of mineralisation separated by barren dolostone are strung out over a distance of 6km along the Kombat monoclinial lineament. All mineralised zones have surface expression except for Asis West where the orebody is down-faulted along the Kombat West Fault, as depicted in the figure below.

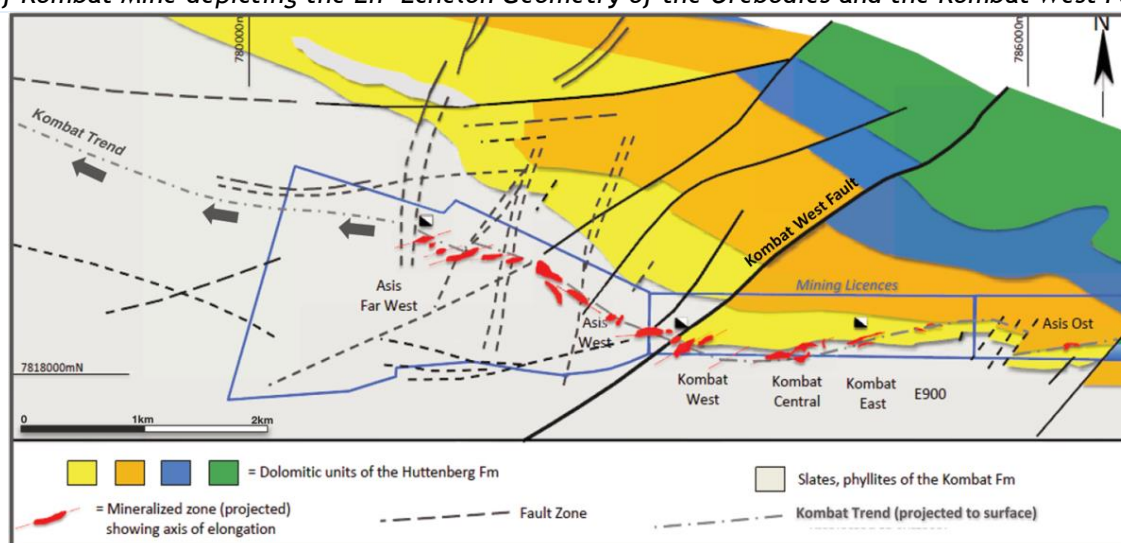Geology of Kombat Mine depicting the En 'Echelon Geometry of the Orebodies and the Kombat West Fault



Source: Trigon Metals Presentation, March 2017


Geology of Kombat Mine depicting the En 'Echelon Geometry of the Orebodies and the Kombat West Fault

April 2017

The orebodies occur in the dolostone of the Hüttenberg Formation below monoclinial flexures on the contact between the Kombat and Hüttenberg Formations. In general the ore loci are defined by breccia bodies in dolostone and a variety of structural controls resulting in an en échelon pattern and a crosscutting relationship with the contact.

The country rock above the orebodies is sheared and fractured into “roll structures”. A relation between the orebodies and the feldspathic sandstone of the Kombat Formation is also indicated. The ore lenses abut against the contact and hang like pendants beneath the flexures as depicted in the figure below.

Schematic Diagram Depicting the Relation of the Hanging Orebodies relative to the Roll Structures and Phyllite/Dolomite Contact

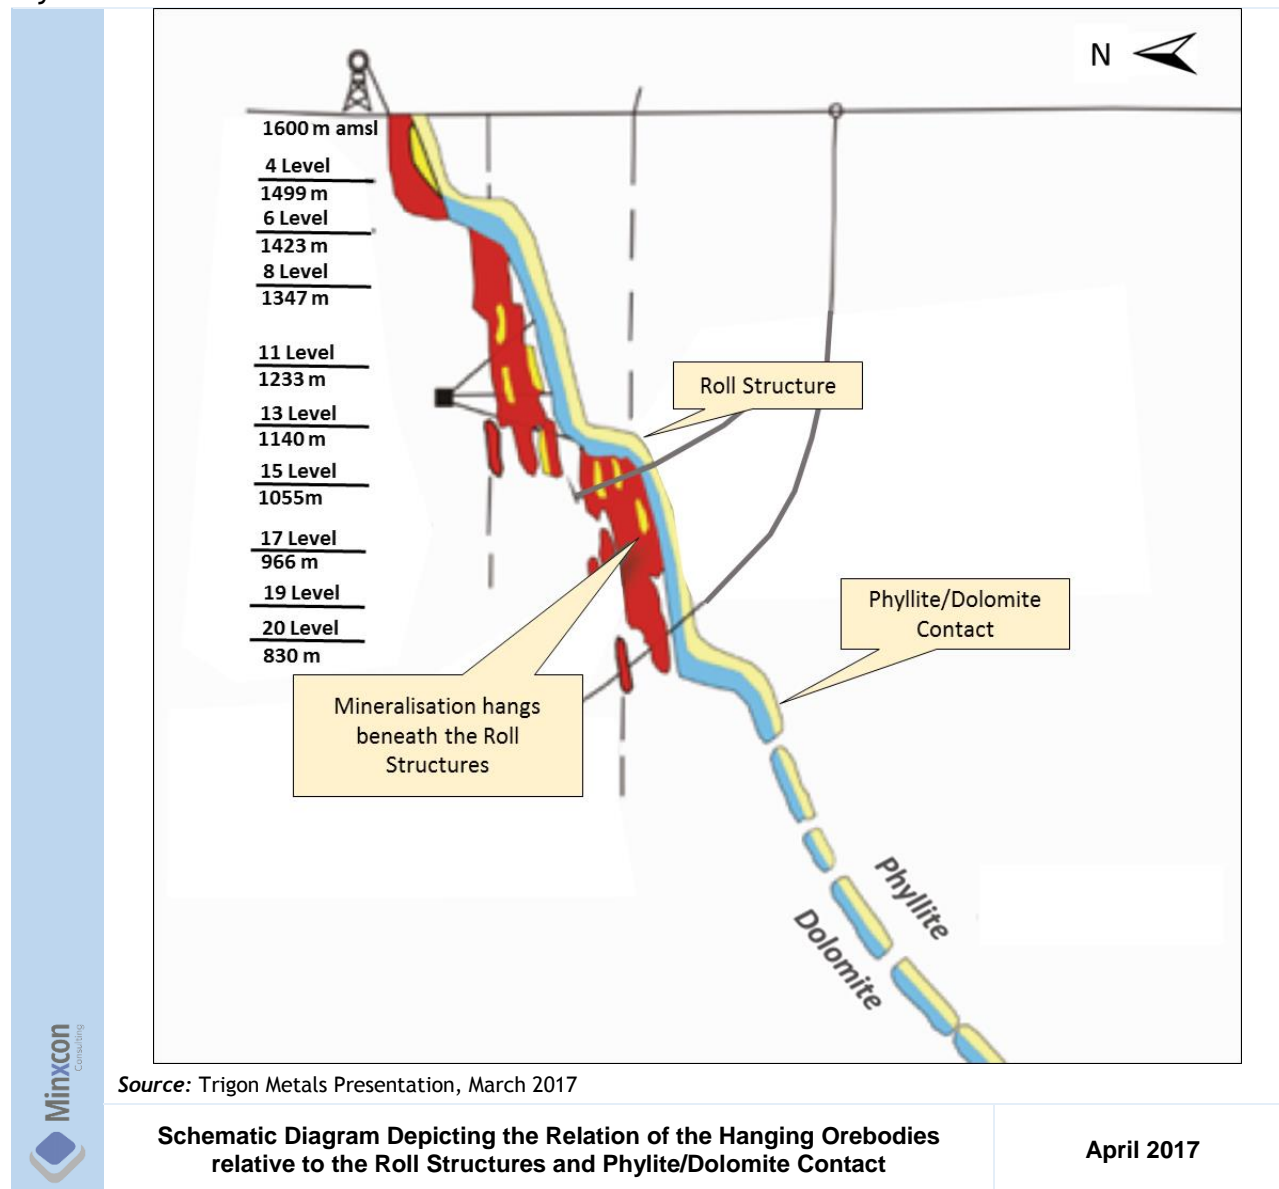

They are steep in orientation and transgressive to stratigraphy. With depth the massive sulphides horsetail and merge into thready, stringers until they become disseminated in calcitised zones of net-vein fractures.

The Kombat orebodies are interpreted to have formed as a result of the release of both CO_2 and CH_4 from the Mulden shales. This converted the anhydrite (in the dolostones) to calcite releasing SO_4 into the brines. The brines also migrated along the basin margin faults and thrusts, picking up base metals along the way.

The CO₂ and S reacted with downward migrating oxidizing groundwater producing sulphuric acid that ate its way up through the last four hundred metres of the rotated fold-thrust fracture systems in the carbonates, forming a hypogene karst system. Unconsolidated sand was subsequently forced through the fracture system forming sandstones. The overlying Mulden phyllite acted as a barrier preventing the upward migration of base metal bearing brines, subsequently precipitating sulphides by reduction in structurally controlled roll structures.

Item 1 (f) - STATUS OF EXPLORATION

The Kombat operations are classed as an advanced property, which historically has undergone long-lived production and plenty of historical exploration from geophysical geochemical surveys conducted during the 1960s to 1990s to surface and underground drilling, where some 2,183 drillholes have been recorded and validated.

Recent surface drilling programmes commenced in 2012 through to 2015 under the auspices of Kombat mine personnel, which utilised modern QAQC methodologies. Drilling prior to 2012 is classed as historical as very little QAQC was conducted on this core (which is mostly still available on site) with the exception of some confirmatory sampling conducted by P&E Mining Consultants in 2014.

Further exploration in the form of drilling has been recommended in order to upgrade the existing Mineral Resources.

Item 1 (g) - MINERAL RESOURCE ESTIMATES

The Mineral Resource statement for the Kombat operations is presented relative to the 150 m depth cut-off with respect to the possible employable mining strategy. The open pittable Mineral Resources are stated at a calculated copper equivalent ("CuEq") value of CuEq 0.77% cut-off, and the underground mineable Mineral Resources are stated at the calculated cut-off value of CuEq 1.4% (Refer to Item 14).

The Gross Otavi section in the Mineral Resources has been discounted by 1% in order to account for minimal historical mining with an additional 7.5% as a porosity factor due to the presence of karst voids. An additional 15% geological loss has been applied to the Mineral Resources for all sections. Density for the hard rock has been estimated. Only Inferred Mineral Resources have been stated for all the Kombat operations. The table below presents the estimated Mineral Resources for the potential open pit areas.

Open Pittable Mineral Resources for the Kombat Operations at a Copper Equivalent Cut-off of CuEq 0.77% as at April 2017

Section	Mineral Resource Classification	Tonnes	Density	Cu	Pb	Ag	Cu Content	Pb Content	Ag Content
		Mt	t/m ³	%	%	ppm	t	t	kg
Kombat East	Inferred	1,208	2.82	1.36	1.01	1.72	16,465	12,187	2,074
Kombat Central	Inferred	0,848	2.82	1.79	0.33	6.90	15,135	2,767	5,848
Kombat West	Inferred	0,354	2.88	2.76	2.63	2.20	9,785	9,303	780
Kombat Total	Inferred	2,410	2.83	1.72	1.01	3.61	41,385	24,257	8,702
Gross Otavi	Inferred	0,643	2.84	0.93	2.50	0.85	6,006	16,053	546
Gross Otavi Total	Inferred	0,643	2.84	0.93	2.50	0.85	6,006	16,053	546
Total Open Pit	Inferred	3,053	2.83	1.54	1.35	2.98	47,391	40,310	9,248

Notes:

1. Historical mine voids have been depleted from the Mineral Resource.
2. Historical mine voids were not available for Gross Otavi so the tonnage has been reduced by 1% for historical mining.
3. Additional 7.5 % porosity factor has been applied to Gross Otavi for the karst voids.
4. The open pit Mineral Resource is declared to a depth of 150 m with a CuEq cut off of 0.77 %.
5. No tailings have been declared at a 0.4 % Cu cut off (upside potential at 0.3 % Cu cut-off).
6. Densities for the hard rock material have been modelled.
7. A geological loss of 15 % has been applied to the Mineral Resource.
8. All reported Mineral Resources are limited to fall within the property boundaries of the project area.

9. Columns may not add up due to rounding.
10. The Inferred Mineral Resources have a large degree of uncertainty as to their existence and whether they can be mined economically. It cannot be assumed that all or any part of the Inferred Mineral Resource will be upgraded to a higher confidence category.

The table to follow presents the estimated Mineral Resources for the potential underground areas.

Underground Mineral Resources for the Kombat Operations at a Copper Equivalent Cut-off of CuEq 1.40% as at April 2017

Section	Mineral Resource Classification	Tonnes	Density	Cu	Pb	Ag	Cu Content	Pb Content	Ag Content
		Mt	t/m ³	%	%	ppm	t	t	kg
Kombat East	Inferred	0.024	2.87	1.90	2.94	0.61	459	708	15
Kombat Central	Inferred	-	-	-	-	-	-	-	-
Kombat West	Inferred	0.104	2.91	2.79	4.15	3.27	2,899	4,307	339
Kombat Total	Inferred	0.128	2.90	2.63	3.92	2.77	3,358	5,015	354
Asis West	Inferred	2.475	2.88	4.05	1.28	32.36	100,214	31,735	80,078
Asis Gap	Inferred	0.166	2.83	2.35	0.35	21.15	3,909	590	3,514
Asis Far West	Inferred	1.082	2.85	3.42	0.10	35.81	37,000	1,036	38,763
Asis Total	Inferred	3.723	2.87	3.79	0.90	32.86	141,122	33,361	122,355
Total Underground	Inferred	3.851	2.87	3.75	1.00	31.86	144,480	38,376	122,709

Notes:

1. Historical mine voids have been depleted from the Mineral Resource.
2. The underground Mineral Resource (below 150m) is declared at a CuEq cut off of 1.4 %.
3. No tailings have been declared at a 0.4 % Cu cut off (upside potential at 0.3 % Cu cut-off).
4. Densities for the hard rock material have been modelled.
5. A geological loss of 15 % has been applied to the Mineral Resource.
6. All reported Mineral Resources are limited to fall within the property boundaries of the project area.
7. Columns may not add up due to rounding.
8. The Inferred Mineral Resources have a large degree of uncertainty as to their existence and whether they can be mined economically. It cannot be assumed that all or any part of the Inferred Mineral Resource will be upgraded to a higher confidence category.

The table below presents the total combined Mineral Resources for the Kombat operations.

Combined Mineral Resources for the Kombat Operations as at April 2017

Section	Mineral Resource Classification	Tonnes	Density	Cu	Pb	Ag	Cu Content	Pb Content	Ag Content
		Mt	t/m ³	%	%	ppm	t	t	kg
Kombat East	Inferred	1.232	2.83	1.37	1.05	1.70	16,924	12,895	2,089
Kombat Central	Inferred	0.848	2.82	1.79	0.33	6.90	15,135	2,767	5,848
Kombat West	Inferred	0.458	2.89	2.77	2.97	2.44	12,684	13,610	1,119
Kombat Total	Inferred	2.538	2.83	1.76	1.15	3.57	44,743	29,272	9,056
Gross Otavi	Inferred	0.643	2.84	0.93	2.50	0.85	6,006	16,053	546
Gross Otavi Total	Inferred	0.643	2.84	0.93	2.50	0.85	6,006	16,053	546
Asis West	Inferred	2.475	2.88	4.05	1.28	32.36	100,214	31,735	80,078
Asis Gap	Inferred	0.166	2.83	2.35	0.35	21.15	3,909	590	3,514
Asis Far West	Inferred	1.082	2.85	3.42	0.10	35.81	37,000	1,036	38,763
Asis Total	Inferred	3.723	2.87	3.79	0.90	32.86	141,122	33,361	122,355
Total Mineral Resources	Inferred	6.905	2.85	2.78	1.14	19.11	191,871	78,685	131,957

Notes:

1. Historical mine voids have been depleted from the Mineral Resource.
2. Historical mine voids were not available for Gross Otavi so the tonnage has been reduced by 1% for historical mining.
3. Additional 7.5 % porosity factor has been applied to Gross Otavi for the karst voids.
4. The open pit Mineral Resource is declared to a depth of 150 m with a CuEq cut off of 0.77 %.
5. The underground Mineral Resource (below 150m) is declared at a CuEq cut off of 1.4 %.
6. No tailings have been declared at a 0.4 % Cu cut off (upside potential at 0.3 % Cu cut-off).
7. Densities for the hard rock material have been modelled.
8. A geological loss of 15 % has been applied to the Mineral Resource.
9. All reported Mineral Resources are limited to fall within the property boundaries of the project area.
10. Columns may not add up due to rounding.
11. The Inferred Mineral Resources have a large degree of uncertainty as to their existence and whether they can be mined economically. It cannot be assumed that all or any part of the Inferred Mineral Resource will be upgraded to a higher confidence category.

Item 1 (h) - QUALIFIED PERSON'S CONCLUSIONS AND RECOMMENDATIONS

Conclusions

Minxcon reviewed all the information and has made the following observations regarding the Project:-

The Inferred confidence in the Mineral Resource classification for the Kombat operations is based on a combination of factors such as low local drillhole data density, lack of QAQC on the historical drillhole datasets, inaccurate depletion voids and the fact that underground stope sampling data was not available to assist in constraining the mineralised halos.

A considerable volume of historical geological mapping and interpretation and drillhole core exists in the mine that has not been included in the current modelling which may serve to significantly increase the confidence in the Mineral Resource estimate in future.

Minimal measured bulk density values are available to support the current estimate contributing to the Inferred Mineral Resource classification, regardless of the use of the Tsumeb Formula used in density calculations, which relates sulphide make-up and sulphide content to bulk density.

Recommendations

Minxcon recommends that all sections and plans with historical stope void profiles be digitised and incorporated into the mine void model in order to accurately deplete the Mineral Resource estimate.

Largescale re-assay and bulk density assessments should be undertaken from the existing wealth of drillhole core on the mine in order to increase assay confidence in the historical drilling dataset. All samples should be sent to an accredited laboratory, while the mine may consider purchasing a scale to conduct its own bulk density measurements in order to save costs.

Historical geological mapping (underground and surface) should be digitally captured and elevated in order to lend further integrity to the digital Mineral Resource estimation process.

Additional drilling is recommended to improve confidence in the orebody and Mineral Resources.

Preliminary Economic Assessment

Minxcon was commissioned by Trigon in April 2017 to complete a scoping level study on the Kombat Project. This Report details a scoping-level study in the form of a Preliminary Economic Assessment ("PEA") conforming to NI 43-101 standards and requirements. The PEA includes Inferred Mineral Resources that are considered too speculative geologically to have the economic considerations applied to them that would enable them to be categorised as Mineral Reserves (the "PEA Study"), and there is no certainty that the PEA will be realised.

The purpose of the PEA is to investigate the economic viability of the open pit and underground mining potential targeting the copper and lead resources at Kombat East, Kombat Central, Asis Far West, Asis West and Gross Otavi areas. The PEA investigated mining methods, treatment methods and development of additional infrastructure. The study focussed on the total Inferred Mineral Resource to determine the economic viability, upside potential as well as future exploration requirements. A discounted cash flow ("DCF") valuation was carried out on the PEA Study areas and includes only Inferred Resources. The value derived from the PEA is considered representative of the upside potential value of the current copper and lead resources.

The results of the PEA study are detailed in Item 24 (a) of this Report.

ITEM 2 - INTRODUCTION

Item 2 (a) - ISSUER RECEIVING THE REPORT

Minxcon (Pty) Ltd (“Minxcon”) was commissioned by Trigon Metals Incorporated (“Trigon” or “the Client”) to complete a Mineral Resource estimation on their Kombat Copper Project (“Kombat” or “Project”), situated in Namibia.

Trigon is an incorporated company listed on the Toronto Venture Exchange, trading under the symbol *TM*.

Item 2 (b) - TERMS OF REFERENCE AND PURPOSE OF THE REPORT

Minxcon was commissioned by the Client to compile a Mineral Resource Report for the Project located in Otjozondjupa Region, Namibia (this “Report”).

This Report, entitled NI 43-101 Technical Report on the Kombat Copper Project, Namibia - Mineral Resource Report was compiled in compliance with the specifications embodied in the Standards of Disclosure for Mineral Projects as set out by the Canadian Code for reporting of Mineral Resources and Mineral Reserves - National Instrument 43-101 (Standards of Disclosure for Mineral Projects), Form 43-101F1 and the Companion Policy Document 43-101CP (“NI 43-101”). Only terms as defined by The Canadian Institute of Mining, Metallurgy and Petroleum (“CIM”) have been utilised in this Report.

The effective date of this Report is 01 April 2017.

Minxcon carried out the following scope of work for this Report:-

- Review History of the Project;
- Produce Key Plans and Maps for Report;
- Describe Topography and Climate;
- Review Legal Aspects and Security of Tenure;
- Review Project Data which includes:-
 - Sampling Governance;
 - Sample Method, Collection, Validation, Preparation & Storage;
- Complete the Geological Modelling, Interpretation And Estimation;
- Complete a Resource Estimation;
- Mineral Resource Classification; and
- Prepare NI 43-101 Technical Report.

Item 2 (c) - SOURCES OF INFORMATION AND DATA CONTAINED IN THE REPORT

In the compilation of this Report, Minxcon utilised information as provided by the Client. This includes internal company reports, technical correspondence and maps, as received from the following persons:-

- Mr Fanie Müller: VP Operations and Country Manager for Trigon.
- Mr Willem Kotze: Kombat Mine previous Technical Manager; currently an independent consultant to Trigon.

Minxcon has also relied on information from the following reports:-

- Awmack, H.J. (2012). Technical (NI43-101) Report on the Kombat Project, Prepared for Pan Terra Industries Inc., January 31, 2012.
- P&E Mining Consultants Inc. (2014). Technical Report and Resource Estimate on the Kombat Copper Project, Grootfontein District, Otjozondjupa Region, Namibia. Latitude 19° 42' 35"S Longitude 17°

42° 09'E UTM Zone 33K 783301 m E 7818395 m S for Kombat Copper Inc. Effective Date 20 May 2014.
Authored by Puritch, E., Routledge, R., Sutcliffe, R., Burga, D. and Hayden, A. 114pp.

Additional information was sourced from those references listed in Item 27 and duly referenced in the text where appropriate.

Item 2 (d) - QUALIFIED PERSONS' PERSONAL INSPECTION OF THE PROPERTY

The Qualified Person of the Report is Mr. U Engelmann (BSc (Zoo. & Bot.), BSc Hons (Geol.), Pr.Sci.Nat., MGSSA).

A site inspection was conducted on 6 March to 7 March 2017 and attended by the following Minxcon personnel:-

- Mr Daan van Heerden in the capacity of Minxcon Director.
- Mr Julian Knight in the capacity of Metallurgist.
- Mr Paul Obermeyer in the capacity of Mineral Resource Manager.

The site visit was led by Trigon Resource team consisting of:-

- Mr Fanie Müller in the capacity of VP Operations and Country Manager.
- Mr Willem Kotze: Kombat Mine previous Technical Manager; currently an independent consultant to Trigon.

Mr Obermeyer reviewed all available data as provided on site, as well as reviewed the core storage and geological archives on the mine during the site visit to the mine. He also viewed some of the underground workings and existing open pits. In addition, he took receipt of all data and reports pertinent to Mineral Resource estimation for the purposes of generating the Mineral Resource estimate covered in this Report.

An additional site visit was also conducted on 9 April to 10 April 2017 by the following Minxcon personnel:-

- Mr Uwe Engelmann in the capacity of Minxcon Director and Qualified Person for this Report.
- Mr Laurence Hope in the capacity of Mineral Resource Geologist.

The site visit was led by Trigon team:-

- Mr Fanie Müller in the capacity of VP Operations and Country Manager.
- Mr Willem Kotze: Kombat Mine previous Technical Manager; currently an independent consultant to Trigon.

During the second site visit, Mr Engelmann and Mr Hope presented the geological model to the Kombat team for validation, review and scrutiny. In addition, Mr Engelmann visited the core storage facilities and other areas of interest on the mine site.

ITEM 3 - RELIANCE ON OTHER EXPERTS

Minxcon utilised the services of Mr André Deiss as an Associate Consultant to Minxcon, who assisted with the determination of the natural grade cut-off utilised in the generation of the grade shells. Mr Deiss was also responsible for conducting the Mineral Resource estimate for Trigon.

ITEM 4 - PROPERTY DESCRIPTION AND LOCATION

Item 4 (a) - AREA OF THE PROPERTY

The Kombat Copper Project occurs within the Otavi Mountain Range in a region associated historically and currently for its high grade copper mineralisation and as such, is littered with old workings. The copper mineralisation is also associated with substantial lead and silver content.

The Project is a collective term for the licence areas and deposits as presented in Table 1. The five licence areas encompass a total of approximately 1,217 ha.


Table 1: Kombat Licence Areas and Associated Deposits

Licence Area	Deposit
Gross Otavi	Gross Otavi
Asis	Kombat Central
	Kombat West
	Kombat East
Asis Far West	Asis West
	Asis Far West
	Asis Gap
Asis Ost	Asis Ost


The Asis Ost deposit has been mined out and therefore is not included in this report nor the Mineral Resource estimation. A ~39 ha tailings storage facility ("TSF") for the processed ore is located off the licence areas some 1.5 km south of the Asis licence boundary. The TSF has been included in the Mineral Resource estimation. In addition to these, Trigon also holds rights to the ~264 ha Harasib exploration project that targets a lead-zinc anomaly, but has been excluded from this Mineral Resource estimation.

The location of the project areas relative to each other is depicted in Figure 1.

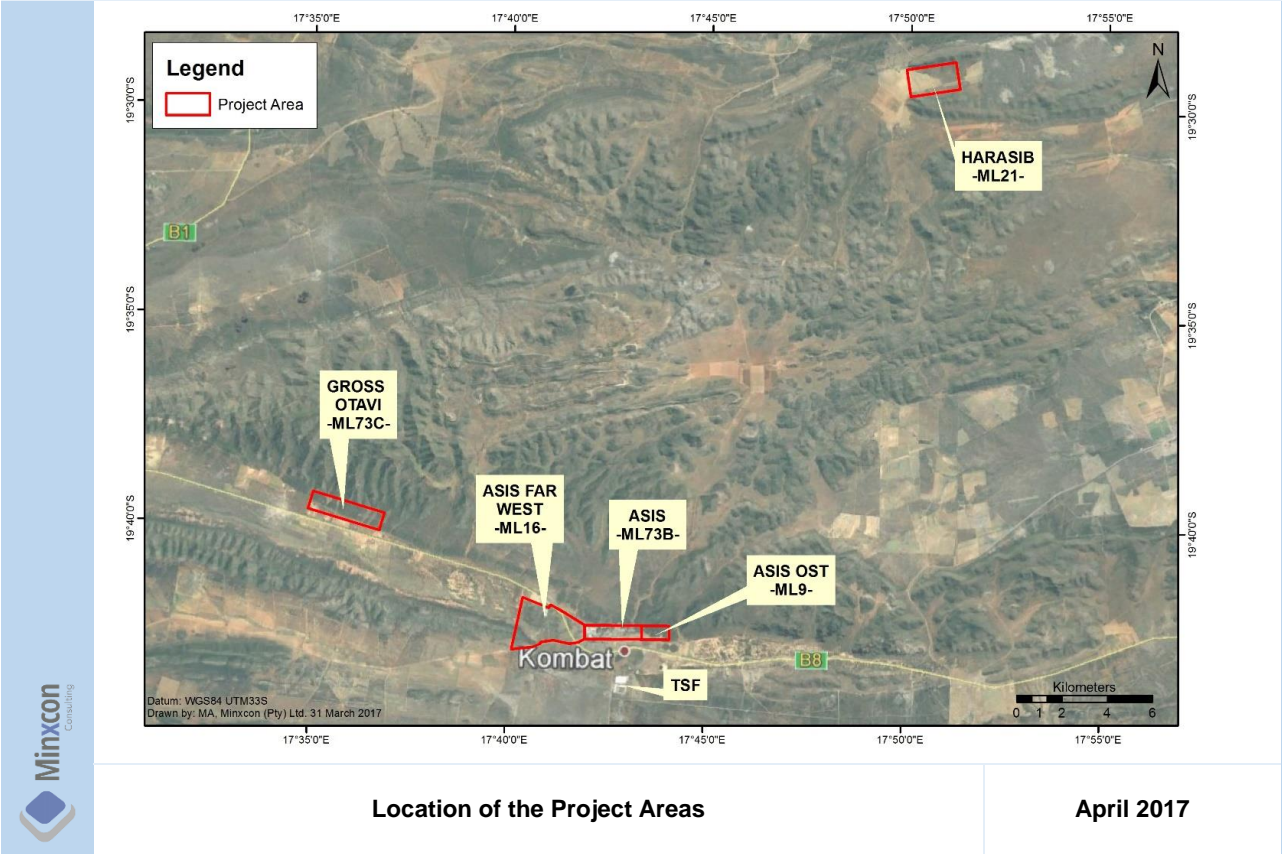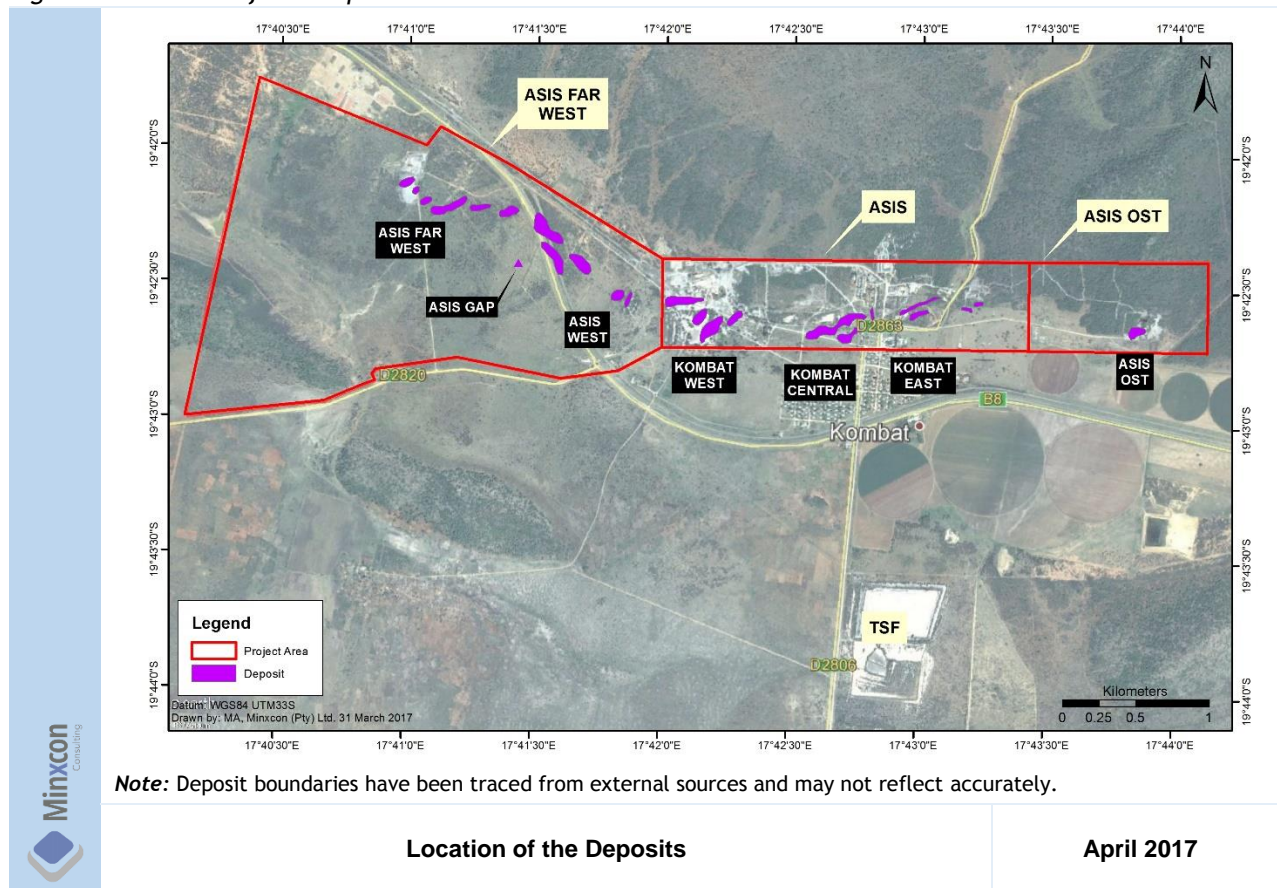Figure 1: Location of the Project Areas



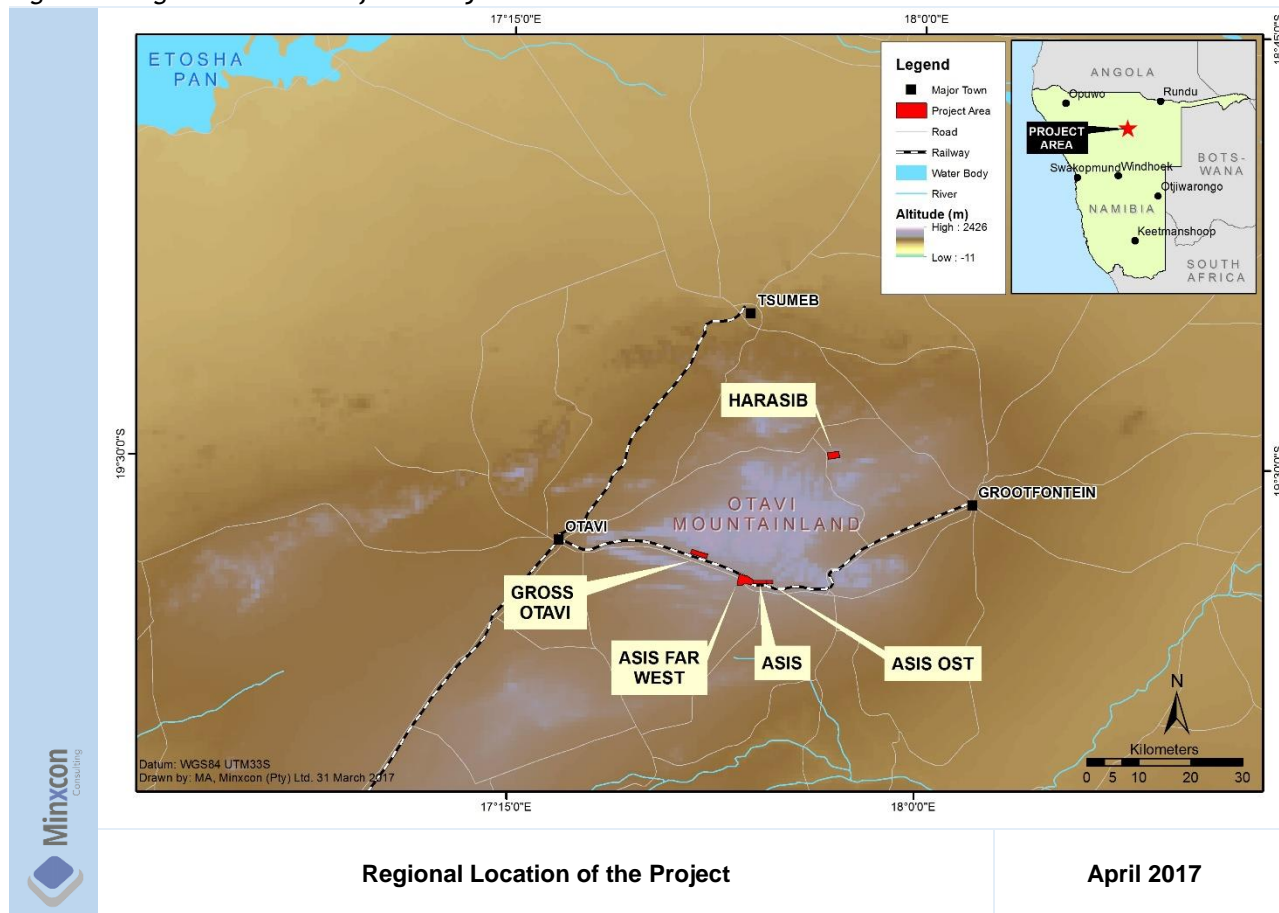
The location of the deposits on the Asis and Kombat sections is presented in Figure 2.

Figure 2: Location of the Deposits**Item 4 (b) - LOCATION OF THE PROPERTY**

The Kombat Copper Project occurs within the Grootfontein District, Otjozondupa region, Namibia. Kombat is situated on the B8 road to Grootfontein, some 37 km east of Otavi and 45 km due west of Grootfontein. Tsumeb lies 50 km due north of Asis. The country capital of Windhoek is situated 326 km due south-southwest, while the regional capital Otjiwarongo is approximately 139 km southwest of Kombat (as the crow flies). In addition, the small ex-mining town of Kombat lies adjacent to the south of the Project. This is clearly shown in Figure 2. The Etosha Pan lies 145 km northwest.

The contiguous Asis Far West, Asis and Asis Ost licence areas are centred on the co-ordinates 19°42'37"S 17°42'13"E (WGS84 UTM 33S). Gross Otavi lies some 8 km due northwest of the Asis licence areas, while the TSF lies 1 km to the south. Harasib lies 27 km due northeast on the co-ordinates 19°29'07"S 17°50'25"E (WGS84 UTM 33S).

Figure 3 shows the regional location of the Project Areas.

Figure 3: Regional Location of the Project**Item 4 (c) - MINERAL DEPOSIT TENURE**

The issuing and control of mineral rights in Namibia is regulated by the Minerals (Prospecting and Mining) Act, No. 33 of 1992 (“Minerals Act”); the Diamond Act, No. 13 of 1999; and the Minerals Development Fund of Namibia Act, No. 19 of 1996. Mineral rights are administered by the Ministry of Mines and Energy (“MME”).

The Project is comprised of five valid mining licences in the Grootfontein District, namely the contiguous ML9, ML16 and ML73B, as well as ML21 and ML73C. The licences comprise a total area of 1,216.7 ha are held in the name of Manila Investments (Pty) Ltd (“Manila”). The following Table 2 details the licences.

Table 2: Mineral Licences

ML Number	Area	Minerals	Issue Date	Expiry Date	Area ha
14/2/3/2/9	Asis Ost	All minerals, except natural oil, salt, gypsum, limestone and marble	20 July 1971	31 March 2019	74.0
14/2/3/2/16	Asis Far West	Base and rare metals	3 August 1977	31 March 2019	467.1
14/2/3/2/21	Harasib	Base and rare metals	24 April 1980	31 March 2019	263.6
14/2/3/2/73B	Asis	Base and rare metals and precious metals	1 April 1994	31 March 2019	150.0
14/2/3/2/73C	Gross Otavi	Base and rare metals and precious metals	1 April 1994	31 March 2019	262.0
Total Area					1,216.7

Source: P&E (2014)

Minxcon is not qualified to give legal opinion and has relied on the licence details as provided in the filed P&E report of 2014, as well as the P&E Competent Person's reliance on legal counsel Lorentz Angula Inc. their legal due diligence opinion. Minxcon has had site of the above licences and is satisfied with their validity. ML renewal applications are due for submission in early 2018.

TSF

The TSF currently does not fall within a mining right area.

The Minerals Act does not deal with the utilisation of tailings and specifically includes tailings under the definition of waste and not under the definition of mineral. Thus, it is interpreted that the Minerals Act does not apply to tailings. The scope of Environmental Management Act, No. 7 of 2007 ("EMA"), however, is wider than the Minerals Act and applies to the extraction of all resources, not only resources that fall under the definition of minerals in the Minerals Act. Any extraction of resources from tailings dams will therefore be a listed activity. An Environmental Clearance Certificate ("ECC") is therefore required in order to extract resources from tailings dams.

Currently, there is no valid ECC over the area of the TSF. Such will be required should the TSF be mined.

Item 4 (d) - ISSUER'S TITLE TO/INTEREST IN THE PROPERTY


Corporate Structure

In April 2012, Kombat Copper Incorporated ("Kombat Copper", formerly Pan Terra Industries Incorporated) acquired 80% of the outstanding shares of Manila whose primary asset was a 100% interest in the formerly producing Kombat Copper Mine, as well as all related mining licences and assets, including all mining surface infrastructure and equipment (P&E, 2014).

In June 2016, Kombat Copper initiated a corporate restructuring plan. In December of that year, Kombat Copper closed a financing to raise CAD1 million, which is the first tranche of a larger ongoing fund raising process, intended to raise sufficient funds to bring the Kombat mine back into production on a phased basis over the next few years. In addition to various other corporate initiatives, Kombat Copper also undertook a rebranding in December 2016, in terms of which the company was renamed Trigon Metals Incorporated.

The following Figure 4 shows the current corporate structure and shareholding of Trigon, as provided by the Client.

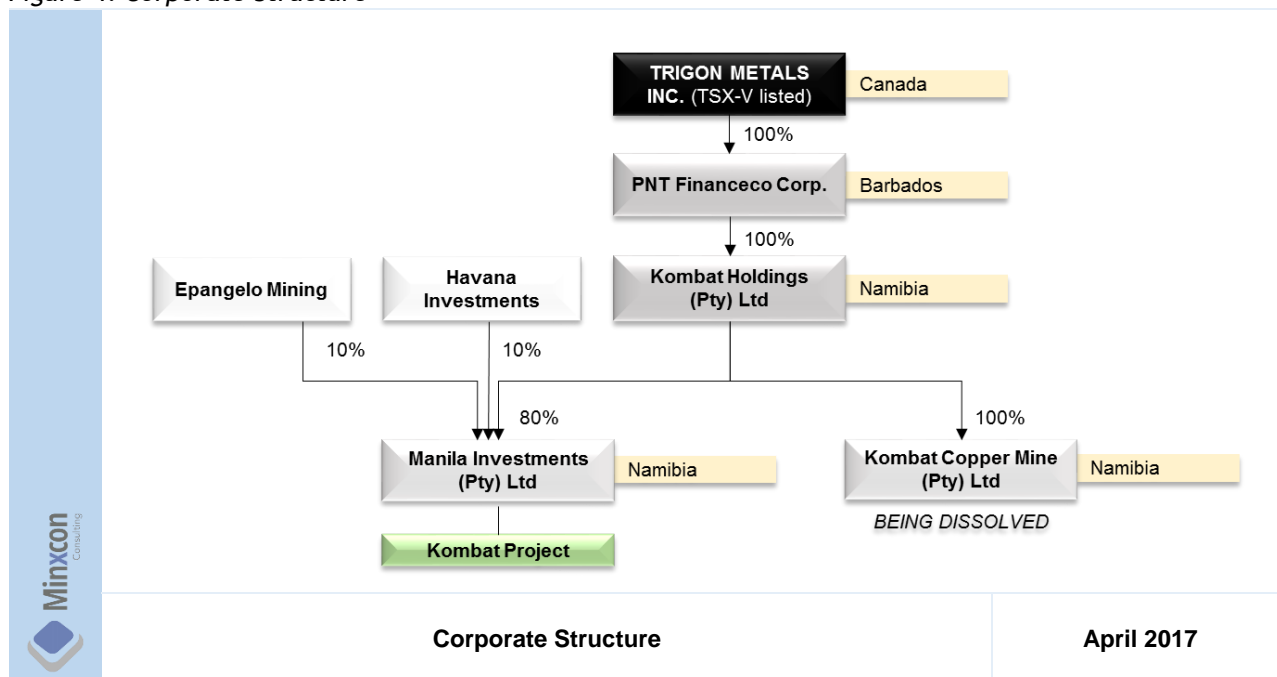Figure 4: Corporate Structure



TSF

The TSF is located within the Kombat Town limits and does not fall within any mineral rights area held by Trigon or its subsidiaries. Trigon does, however, own the land under the TSF.

Surface Rights

In terms of the Namibian Minerals Act, the holder of a mineral licence may carry out such operations authorised by the licence on, or under, the land in respect of which the licence was granted. If the holder is for any reason prevented by the owner of private land from entering the land in order to exercise his rights in terms of his licence, he may apply to the Minerals Ancillary Rights Commission to be granted those rights.

Manila acquired the surface area for the mine infrastructure area including the office, the Kombat Central Pit area (Erf 8) and the #3 shaft infrastructure area (Erf 78) that lies within the Asis ML area. The transfer tax has been paid; confirmation of transfer having been registered is pending.

The Gross Otavi and Harasib surface areas are farmland. Asis Far West is classified as government settlement land, although previous management indicated that as the shaft has been sunk there, it will be made available for mining.

Trigon or its subsidiaries do not own the surface rights on the other ML areas and there are currently no agreements in place with any of the landowners. This will have to be established in order to carry out exploration and mining activities.

Item 4 (e) - ROYALTIES AND PAYMENTS

The Namibian government confirmed a royalty schedule in 2006, originally introduced in 2004, for the following:-

- 3% Royalty levied on the market value of base, precious, and rare metals and nonnuclear mineral fuels; and

- 2% Royalty levied on semi-precious stones, industrial minerals and nuclear mineral fuels.

For the Project, a 3% government royalty is applicable.

Normal tax is levied on taxable income of companies, trusts and individuals from sources within or deemed to be within Namibia. Mining companies other than diamond mining companies are subject to a company tax rate of 37.5%.

Apart from the government taxes and royalties, there are no further back-in-rights, payments or other agreements and encumbrances to which the properties are subject.

Item 4 (f) - ENVIRONMENTAL LIABILITIES

In terms of the Minerals Act, the holder of a mineral licence must take all steps to the satisfaction of the minister to remedy any damage caused by any mining activities. Currently, Trigon does not have an environmental trust fund or financial provision for closure and rehabilitation. This will have to be established with the submission of ML renewals in early 2018.

Item 4 (g) - PERMITS TO CONDUCT WORK

In terms of the EMA a mineral licence may only be issued once the applicant has been furnished with an ECC (valid for three years), which in turn may require an Environmental Impact Assessment ("EIA") to be completed as determined by the Environmental Commissioner. In September 2016, SLR Consulting Namibia (Pty) Ltd ("SLR Namibia") completed an environmental gap analysis for the Project Areas and found that no valid ECC exists for mining activities at the ML areas. An ECC for the exploration activities on MLs 73B, 73C, 16, 9 and 21 was issued on 24 July 2014 and will expire on 24 July 2017. SLR Namibia has been engaged to renew the ECC.

The following findings regarding environmental permitting were also presented by SLR Namibia:-

- No Environmental Contract could be found (*i.e.* Environmental Contract between the Mine Owner, the Ministry of Environment and Tourism ("MET") and the MME.
- Water supply to the Kombat Copper office, etc. is supplied from a tie-in off the NamWater pipeline (abstracting water from the mine's underground water). It cannot be confirmed whether NamWater has a water abstraction permit in place.
- A "domestic wastewater & effluent discharge exemption" permit was issued to Manila Investments in 2016 for the wastewater treatment system/facility. This facility was sold with the Kombat Town and the permit is therefore issued under the wrong company/entity.

Once Trigon is in a position to recommence mining, a water abstraction permit will have to be obtained in terms of the Water Act, No. 54 of 1956.

Item 4 (h) - OTHER SIGNIFICANT FACTORS AND RISKS

High pressure groundwater at the mine areas has historically been a challenge for mining. Going forward, emphasis should be placed on geohydrological assessments and continued groundwater monitoring. All work should be conducted taking cognisance of groundwater levels and impacts.

Minxcon is not aware of any significant factors or risks prevalent to the Project that may affect access or operations.

ITEM 5 - ACCESSIBILITY, CLIMATE, LOCAL RESOURCES, INFRASTRUCTURE AND PHYSIOGRAPHY

Item 5 (a) - TOPOGRAPHY, ELEVATION AND VEGETATION

The Project is located in the southern part of the Otavi Mountains within a large synclinal feature that creates a roughly east-west trending valley sloping westwards, namely the Otavi Valley. The Project Areas occur on the northern inner limb of this syncline, thus the land gently dips to the south. The topography is characterised by gently rolling hills with rugged karst topographical outcrops caused by the dolomitic nature of the majority of underlying rocks.

Elevations range from 1,600 m above mean sea level ("amsl") within the valley up to over 1,900 m amsl towards the valley edges. The Kombat Mine lies at some 1,610 m amsl.

Vegetation in the region is dominantly low grasslands with rocky outcrops generally covered by low shrubs to thorny, bushveld-type trees.

Item 5 (b) - ACCESS TO THE PROPERTY

The Kombat Copper Project is easily accessible as it is located along the B8 highway, midway between the towns of Grootfontein and Otavi. Grootfontein lies 1 km north and Harasib 25 km north-northeast of this highway. Access to the individual properties is via unpaved district and farm roads (P&E, 2014).

The Transnamib railway line traverses the copper Project Areas, as shown in Figure 3, and a rail siding occurs at Asis. In addition to connecting the Project with major Namibian cities, the railroad also connects the Project to port facilities at Walvis Bay some 500 km southwest and to the Tsumeb smelter in Tsumeb.

Item 5 (c) - PROXIMITY TO POPULATION CENTRES AND NATURE OF TRANSPORT

The populations of the nearby towns of Tsumeb, Otavi and Grootfontein are respectively about 19,000, 5,000 and 24,000 (2011 statistics). Basic services such as food, lodging and fuel can be found at these towns, as well as labour. Both skilled and unskilled labour are available at these towns, with many of them having previous mining experience. Tsumeb hosts an operational copper smelter and a full range of mining-related services and suppliers can be sourced from here (P&E, 2014).


The Project lies immediately adjacent to the small ex-mining town of Kombat. Apart from housing, the town hosts a school, clinic, police station and derelict recreational facility.

Tsumeb, Otavi and Grootfontein are linked via established road and railway networks. Grootfontein town hosts an airport with two asphalt runways some 4 km south of the town's centre (P&E, 2014). Tsumeb also hosts a small airport, located just east of the town. A small landing strip provides private services to Kombat town.

Item 5 (d) - CLIMATE AND LENGTH OF OPERATING SEASON


The prevailing climate at Kombat is known as a local steppe, or semi-arid, climate (climate-data.org).

The region experiences high average temperatures throughout the year. Summer months are from September to February, with temperatures averaging 30°C, and winters from March to August, with temperatures averaging 20°C. October is generally the warmest month and July the coolest. Figure 5 shows the average annual temperatures as recorded at Kombat.

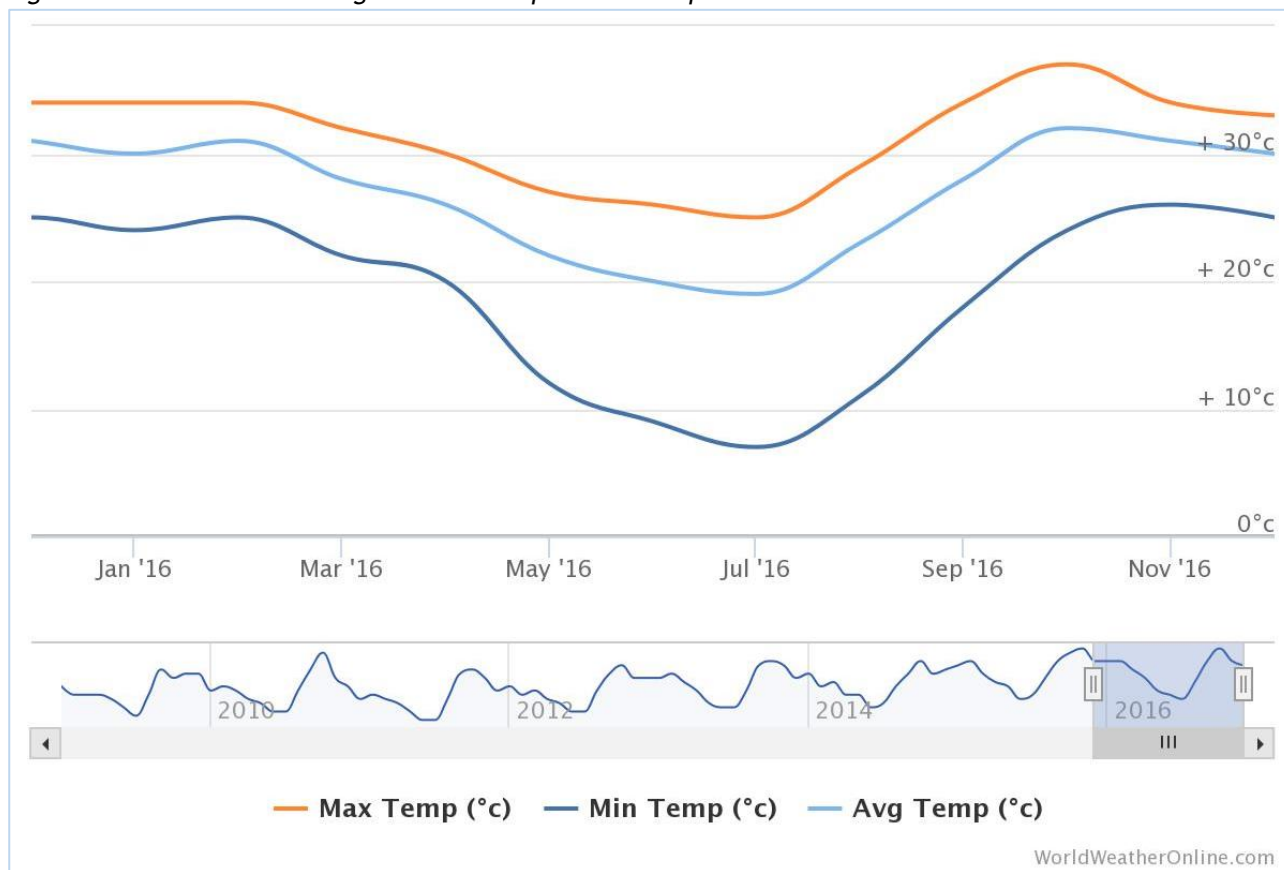Figure 5: Kombat Area Average Annual Temperature Graph

Source: www.worldweatheronline.com

During the year, there is little rainfall in Kombat. The average annual rainfall is 546 mm (climate-data.org). The region experiences a rainy season from November to March, with measured precipitation averaging 110 mm. A dry season is experienced from June to September, where generally no precipitation is experienced. The average annual precipitation is graphically illustrated in Figure 6.

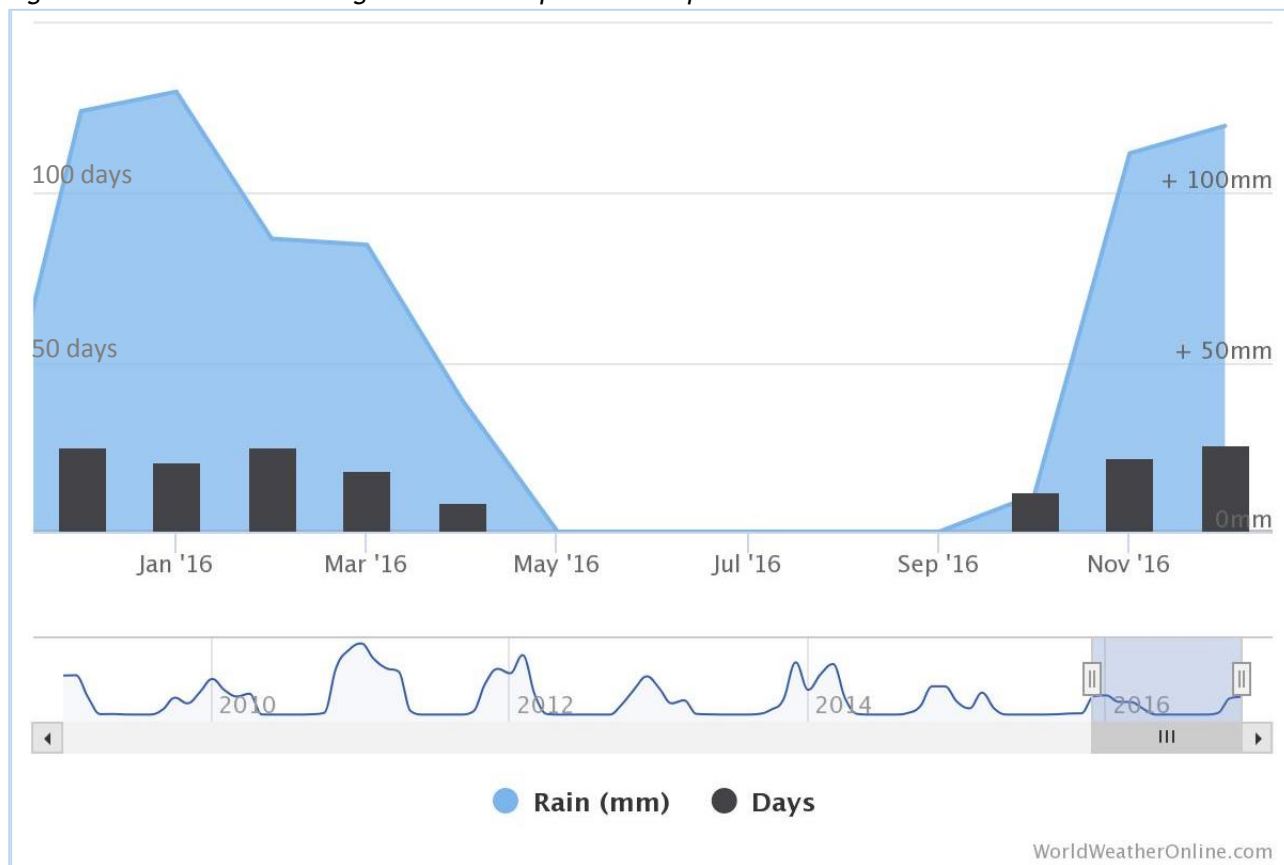Figure 6: Kombat Area Average Annual Precipitation Graph

Source: www.worldweatheronline.com

There are no major climatic influences that may hinder operations. Mining and mining-related activities can continue throughout the year.

Item 5 (e) - INFRASTRUCTURE

Per P&E (2014), Kombat Mine was operational during the periods 1911-1925 and 1962-2008. In 2008, a major power outage lead to unmanageable flooding of the underground workings. Owing to the mining history of the Project, all the expected mining infrastructure exists, which requires minimal rehabilitation (Awmack, 2012):-

- Three recently operational shafts, from east to west: No. 3 (± 330 m deep), No. 1 (± 460 m deep) and Asis Far West (± 800 m deep) as well as an up cast vent raise located at No. 1 Shaft;
- Ramps and extensive underground workings primarily developed around the No. 3 and No. 1 shafts, from surface to the bottom of the mine and flooded to about 60 m below surface;
- An 1,100 tpd concentrator, operational until early 2008;
- Rail spur and load-out connected to the Namibian rail system;
- Mine offices, warehouses, maintenance facilities, etc.;
- A tailings facility measuring approximately 600 m x 400 m x 25 m high;
- A town site with approximately 110 houses, single worker's quarters, golf course, tennis courts, airfield, etc.;
- Two main NamPower power lines servicing the area. One designed for 132 kV and both energized at 66 kV feeding the NamPower substation located adjacent to the mine;
- Power is supplied to the mine via two existing 11 kV lines feeding into the mines intake substation which in turn supplies power to surface and underground infrastructure;

- Diesel generator with a capacity of 50 kVA is available on site;
- A pumping system connected to the NamWater distribution network for eventual use in Windhoek, currently pumping 800 m³/h - 1,200 m³/h; and
- Ongoing dewatering of the mine provides abundant water for operation of the concentrator and town site.

The existing infrastructure also includes an explosive magazine, tailings storage facilities and backfilling capability. A copper smelter, owned by Dundee Precious Metals, is located at Tsumeb and toll-treats ore from regional mines.

Water supply is from a tie-in off the NamWater pipeline (abstracting water from the mine's underground water).

ITEM 6 - HISTORY

Item 6 (a) - PRIOR OWNERSHIP AND OWNERSHIP CHANGES

Mineralisation in the region was first reported by Sir Frances Galton in 1851. The company Otavi Minen und Eisenbahn Gesellschaft ("OMEG") took ownership of the Kombat Project areas commencing with Gross Otavi operations in 1909 and Kombat (Asis area) in 1911, ceasing all operations in 1925. Tsumeb Corporation Limited ("TCL") took over the Project in the early 1950s. TCL was later liquidated and ownership passed on to Ongopolo Mining and Processing Limited ("Ongopolo") in 1999.

In 2006, ATM-listed Weatherly International PLC ("Weatherly") purchased Ongopolo in 2006 and ownership of Kombat, Gross Otavi and Harasib were transferred to their subsidiary, Ongopolo Mining Limited ("Ongopolo Mining").

After placing the mine on care and maintenance due to flooding in 2008, the Grove Mining (Pty) Ltd ("Grove") took over ownership, later selling the assets to Manila Investments. Ownership was again transferred in 2012 to Kombat Copper.

Item 6 (b) - HISTORICAL EXPLORATION AND DEVELOPMENT

The following Table 3 provides an overview of the exploration and development historically conducted at the Kombat Copper Project.

Table 3: History of Exploration and Development

Year	Company	Summary
1851	Francis Galton	Mineralisation in the Otavi Mountainland first reported.
1909 -1941	OMEG	Gross Otavi was historically mined by OMEG from 1909 until 1941.
1911	OMEG	Mining operations commenced in the Kombat Project area, including limited surface production at Kombat and underground mining at both Kombat and Gross Otavi.
1925	OMEG	Production suspended due to problems with excessive water in the Kombat underground workings.
Post WWII - 1950s	TCL	TCL purchased assets from OMEG and explored the Kombat Property through the 1950s.
1962	TCL	Commenced milling in April 1962 (Innes and Chaplin, 1986).
1960s - 1990s	TCL	Numerous geochemical and geophysical surveys undertaken in the vicinity of the Kombat Mine from the 1960s to 1990s. These included soil geochemical, ground magnetic, induced polarization and seismic surveys, however, documentation and results are not available for all surveys.
1962 -1981	TCL	Production records for the Kombat Mine are limited. During the period 1962-1991, production was reported at 8.8 million tonnes of ore grading 2.74% Cu, 1.67% Pb and 22 g/t Ag; There are limited other production records available from the TCL operations at Kombat.
1986	TCL	Surface diamond drilling carried out at Kombat to test the hypothesised westward contamination of the Cu-Pb mineralisation associated with the roll in the dolostone/phyllite contact. A series of mother holes were drilled steeply to the north, with up to eight holes wedged off each mother hole. These pierce-points covered 1,600 m of strike length, from mine Section 600W (roughly the westernmost extent of current mining at Asis West) to 2200W.
1988	TCL	The mine suffered from heavy water inflows throughout its history, particularly along NE-trending cross-faults. Catastrophic inflows led to loss of life in 1988 and to periodic flooding of portions of the mine.
1988 - 1989	TCL	TCL and Gold Fields Namibia evaluated the Gross Otavi area by diamond drilling and a decline was begun in 1988 with the intention of commencing production as a satellite deposit to feed the Kombat mill. All work was halted in early 1989 when work was re-focused on the Kombat Mine. Core is not available
1999	Ongopolo	TCL was liquidated and ownership passed to Ongopolo who operated the Kombat Mine and other assets of TCL including the copper smelter at Tsumeb, for the next several years.
2005	Ongopolo	An 800 m shaft sunk at Asis Far West with loan guarantees from the Namibian Government, in order to access the Asis Far West orebodies. Only limited amounts of

Year	Company	Summary
		development, drilling and mining were carried out from it, before mine closure in January 2008.
2006	Weatherly	Weatherly, purchased Ongopolo in 2006; with the sale of the Tsumeb smelter and corporate reorganization, ownership of Kombat, Gross Otavi and Harasib were transferred to Ongopolo Mining Limited, a subsidiary of Weatherly.
2007	Weatherly	More work carried out at Gross Otavi, including reverse circulation drilling with positive results as disclosed in a news release dated 23 October 2007. Chip samples are still available.
2006 -2007	Ongopolo Mining	The potential for near-surface copper mineralisation over the three km west from the Asis Ost orebody to the No. 1 shaft at the Kombat mine was tested. A database was generated with over 1,200 drillholes: core (10 holes), reverse circulation (258 holes: 27,750 m) and percussion (16,500 m). Holes were relatively short, averaging 107 m for the reverse circulation holes and generally <40 m for the percussion holes. The RC' holes were mainly drilled at an inclination of -60° to the north along 24 irregularly-spaced section lines, 125 m apart on average. The drilled area was divided into Blocks A-E from west to east and section lines within each block were also numbered from west to east; the westernmost section line (A1) passed immediately west of the No. 1 shaft. Many of the percussion holes were vertical, drilled on 10 m centres in areas of interest (Ongopolo. 2007).
2005 -2007	Ongopolo Mining	Production figures are not available for most of Ongopolo Mining's tenure as operator of the Kombat Mine, however, monthly records are available for 13 months between May 2005 and December 2007. The mill processed underground ore for nine of those months, with an average monthly throughput of 10,289 tonnes grading 2.54% Cu, 0.45% Pb and 28 g/t Ag. Flooding of the underground workings led to milling of open pit ore starting in April 2007; production in the four months for which records are available averaged 16,492 tonnes grading 0.64% Cu, 0.29% Pb and 4 g/t Ag. The size of the Kombat tailings pile has been estimated at 10.6 Mt (Kotze, 2011. Assuming that the tailings represent about 90% of mill feed, this would imply that about 12 Mt of ore were mined and processed at Kombat between 1962 and 2008.
2008	Ongopolo Mining	Poor copper prices and difficulty in de-watering the mine after another episode of flooding led to closure of the mine in 2008.

Source: P&E (2014)

German explorers prospected the region until 1911 when OMEG commenced mining operations, ultimately ceasing operations in 1925 due to major influx of groundwater. TCL conducted exploratory drilling below the old mine. Although this was unsuccessful in defining additional resources, additional ore was discovered to the east and west of the original prospect.

The old shaft was re-equipped and while development proceeded, a new 335 m shaft was sunk northwest of the orebody and a concentrating plant commissioned in 1962. In 1964, a third shaft was completed to cover the eastern ore lenses. Production continued uninterrupted until mid-1976, where steady state production was curtailed to 1978 due to low metal prices, but during this period underground exploration and development resulted in the discovery of the rich Asis West area; production was then returned to steady state levels. Asis West production continued until November 1988 when the mine was flooded and production ceased for nearly one year, but was continued thereafter. Mining again stopped between January and June 1997 due to flooding (SMS, 2014).

TCL liquidated in March 1999 and was taken over by Ongopolo in March 2000 until November 2006. Ongopolo intermittently explored, developed and mined from an exploration shaft sunk at Asis Far West on the basis of surface drillhole intersections. In the process, expenditure on mining from the original areas was severely curtailed and as a consequence, the mine started flooding in March 2005 (SMS, 2014). Weatherly then took over and seized all operations in February 2008, declaring all mines on care and maintenance. The 2008 closure was triggered by two power outages in quick succession each lasting one hour. Weatherly sold the smelter to Dundee Precious Metals to raise funds. The smelter is now a standalone tolling business.

Item 6 (c) - HISTORICAL MINERAL RESOURCE ESTIMATES

In 2014, qualified persons Mr R. Routledge (M.Sc. (Applied), P.Geo.) and Mr E. Puritch (P.Eng.) of P&E Mining Consultants Inc. ("P&E") estimated an Inferred Mineral Resource only for the Asis Far West block in accordance with NI 43-101, as presented in Table 4. The total Inferred Mineral Resource for a 1% Cu block cut-off grade was calculated at 1.7 Mt averaging 1.93% Cu, 0.13% Pb and 15.9 g/t Au, or 2.15% CuEq. It is not clear, or evident why Mineral Resources were not declared for the other areas which have been declared in this Report.

Table 4: Asis Far West Historical Inferred Mineral Resources at Various Copper Cut-off Grades, as per P&E as at April 2014


Cut-Off Grade	Tonnes	Bulk Density	Cu	Pb	Ag	CuEq ⁴
Cu%	kt	t/m ³	%	%	g/t	%
Wireframe	2.967	2.82	1.39	0.17	12.6	1.58
0.25	2.938	2.82	1.4	0.16	12.7	1.59
0.50	2.729	2.82	1.48	0.15	13.2	1.67
1.00	1.679	2.83	1.93	0.13	15.9	2.15
1.50	787	2.85	2.71	0.13	20.3	2.98
2.00	439	2.86	3.51	0.1	26.2	3.83
2.50	286	2.88	4.19	0.09	30.7	4.56
3.00	206	2.89	4.76	0.09	34.7	5.18
3.50	155	2.9	5.27	0.09	38.8	5.73
4.00	114	2.91	5.82	0.09	42.8	6.33
4.50	78	2.92	6.53	0.09	48.1	7.10
5.00	54	2.94	7.32	0.09	55.7	7.97

Notes:

1. CIM definitions were followed for Mineral Resources.
2. The Qualified Persons for this Mineral Resource estimate are: Richard Routledge, M.Sc. (Applied), P.Geo. and Eugene Puritch, P.Eng. of P&E Mining Consultants Inc.
3. Mineral Resources are estimated by conventional 3D block modelling based on wireframing at a 0.5% CuEq cut-off grade and inverse distance cubed grade interpolation.
4. CuEq is based on metal price only using the formula: $\text{CuEq} = \text{Cu}\% + (0.28 * \text{Pb}\%) + (0.0113 * \text{Ag g/t})$.
5. Metal prices for the estimate are: US\$3.43/lb Cu, US\$0.95/lb Pb, US\$26.47/oz Ag based on a two-year trailing average as of February 28, 2014.
6. A variable bulk density of 2.79 t/m³ or higher based on density weighting has been applied for volume to tonnes conversion. The "revised Tsumeb" formula was used for bulk density calculation where $\text{bulk density} = 363 / (130 - (0.874 * (\text{Cu}\% + \text{Pb}\%)))$.
7. Mineral Resources are estimated from 1,307 m elevation to 677 m elevation, approximately 300 m depth to 947 m depth below surface.
8. Mineral Resources are classified as Inferred based on drill hole spacing, geologic continuity and quality of data.
9. A small amount of the resource may have been mined at the east end of the Asis Far West zone but stope location and amount of material removed is uncertain.
10. Mineral resources which are not mineral reserves do not have demonstrated economic viability. The estimate of mineral resources may be materially affected by environmental, permitting, legal, title, taxation, socio-political, marketing, or other relevant issues. There is no certainty that all or any part of the Inferred Mineral Resource will be upgraded to an Indicated or Measured Mineral Resource as a result of continued exploration.
11. P&E recommends reporting resources at the 1%Cu block model cut-off grade.

The Mineral Resource area is illustrated in the Figure 7.

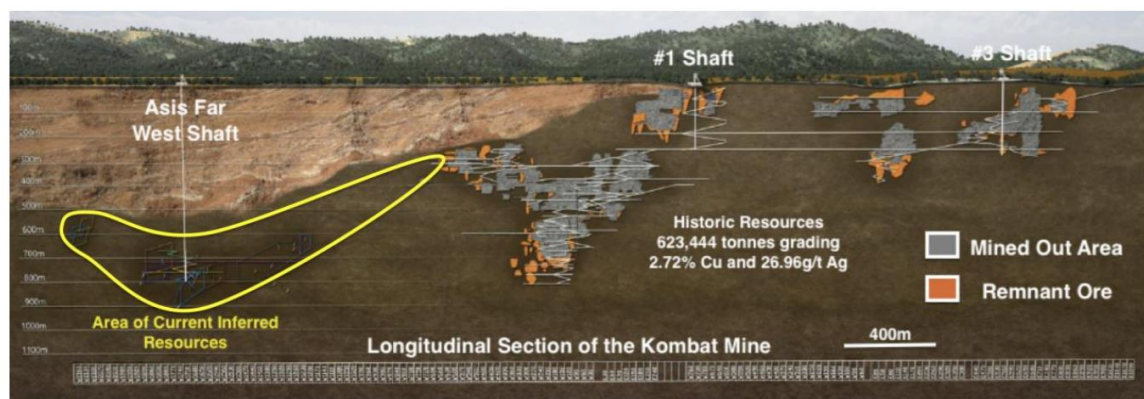Figure 7: Asis Far West Historical Inferred Mineral Resource Area, as per P&E as at April 2014



Source: <http://media3.marketwire.com/docs/kbt0520fig1.pdf>

Asis Far West Historical Inferred Mineral Resource Area, as per P&E as at April 2014

April 2017

Item 6 (d) - HISTORICAL MINERAL RESERVE ESTIMATES

No historical Mineral Reserves have been reported.

Item 6 (e) - HISTORICAL PRODUCTION

Table 5, Figure 8 and Figure 9 below provides a summary of historical production from 1961 to 2007. No ore was treated in 1999. A total of some 12.6 Mt was treated at an average rate of 749 tpd. The mine was officially closed on 15 January 2008.

Table 5: Average Production 1961-2007

Item	Total
Tonnes (total, kt)	12,573.2
Average tpd	748.9
Head	
% Cu	2.6
% Pb	1.5
Cu Concentrate	
Tonnes (total, kt)	951.5
% Cu in concentrate	29.7
% Pb in concentrate	7.2
Cu % Recovery	85.7
Pb % Recovery	35.3
Pb Concentrate	
Tonnes (total, kt)	205.6
% Cu in concentrate	10.4
% Pb in concentrate	48.2
Cu % Recovery	6.5
Pb % Recovery	51.1

Historical production records for the period of 2000 to 2007 revealed that approximately 44,208 kg of silver concentrate was produced.

Figure 8: Historic Feed Tonnes and Grade between 1961 and 2007


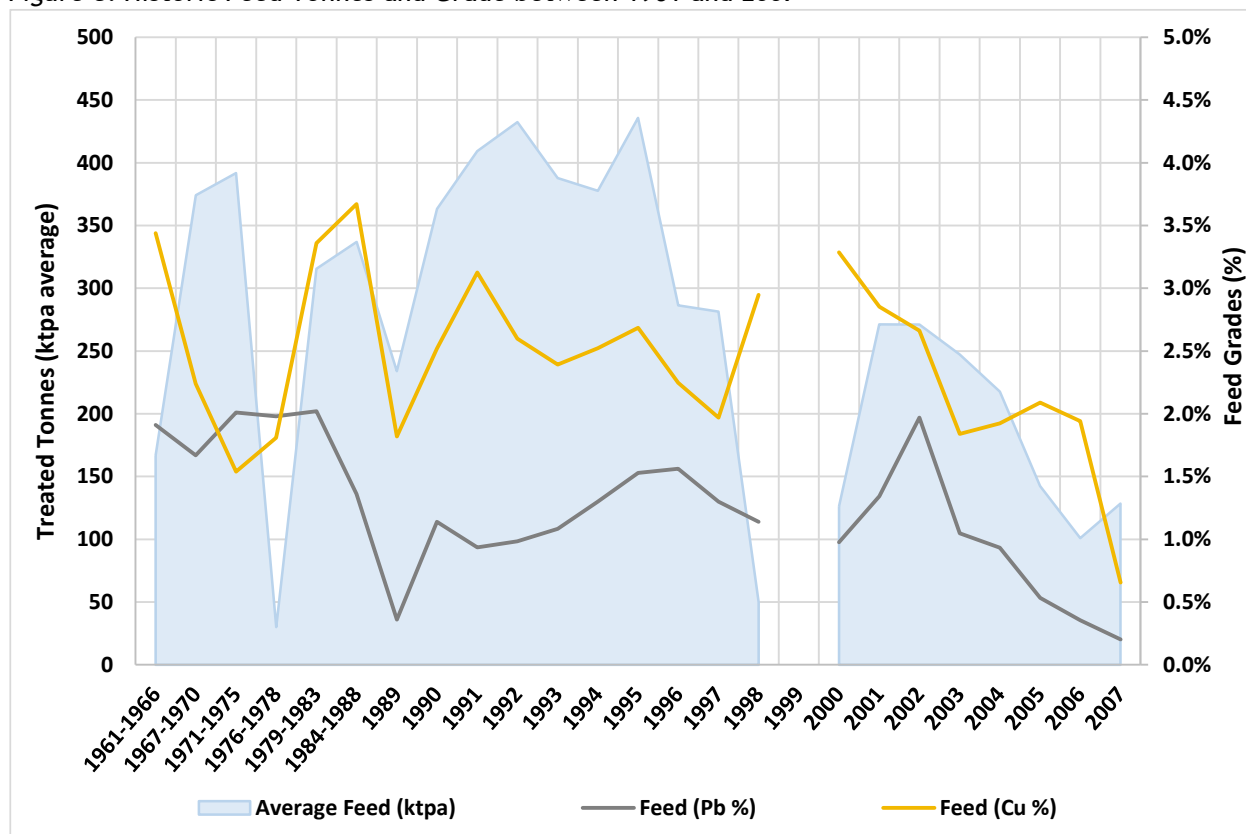


Figure 9: Historic Copper Concentrate Production between 1961 and 2007

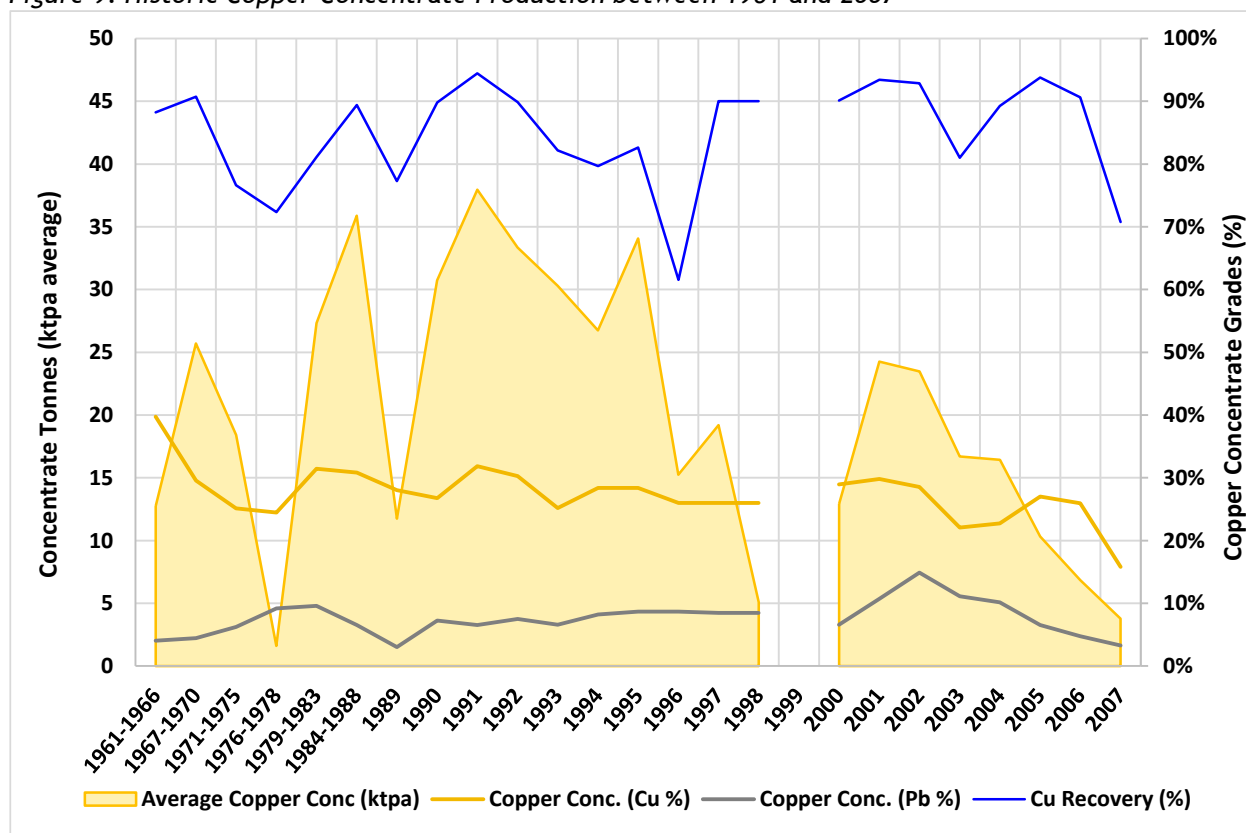


ITEM 7 - GEOLOGICAL SETTING AND MINERALISATION

Item 7 (a) - REGIONAL GEOLOGY

Regional Tectonics

The divergent Damara Orogenic Belt was formed late (ca. 550 Ma and 495 Ma) during the supercontinent formation of Gondwana (Figure 10) at the collisional triple junction of the Congo, Kalahari and Rio de la Plata Cratons (Meert and Lieberman, 2007; Gray *et.al.*, 2008), referred to as the Damara Orogen.

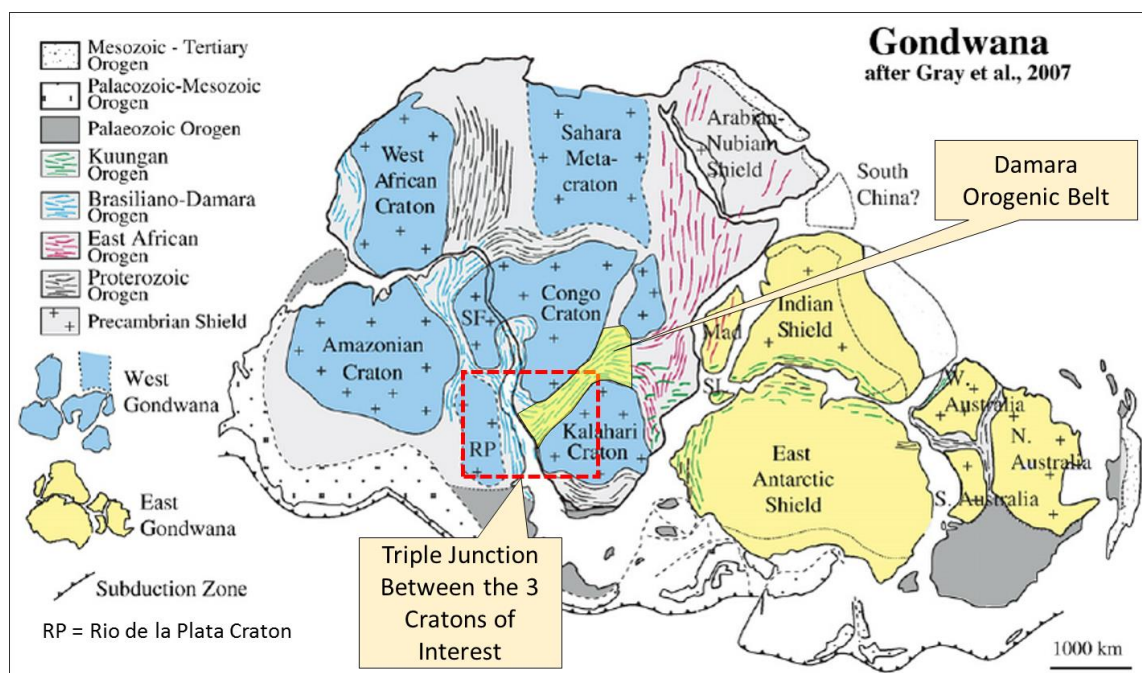Figure 10: Location of the Damara Orogenic Belt during the Amalgamation of the Gondwana Supercontinent




Source: Adapted from Meert and Lieberman (2007)

Location of the Damara Orogenic Belt during the Amalgamation of the Gondwana Supercontinent

April 2017

The Gariep and Kaoko orogenic belts generated strike-slip compressional deformation followed by later large scale rifting, while the northeast trending Damara Orogenic Belt was formed when the passive continental margins of the Congo and Kalahari Cratons collided with thrusting of basin sediments onto the Kalahari Craton from 495 Ma through to 480 Ma (Figure 11).

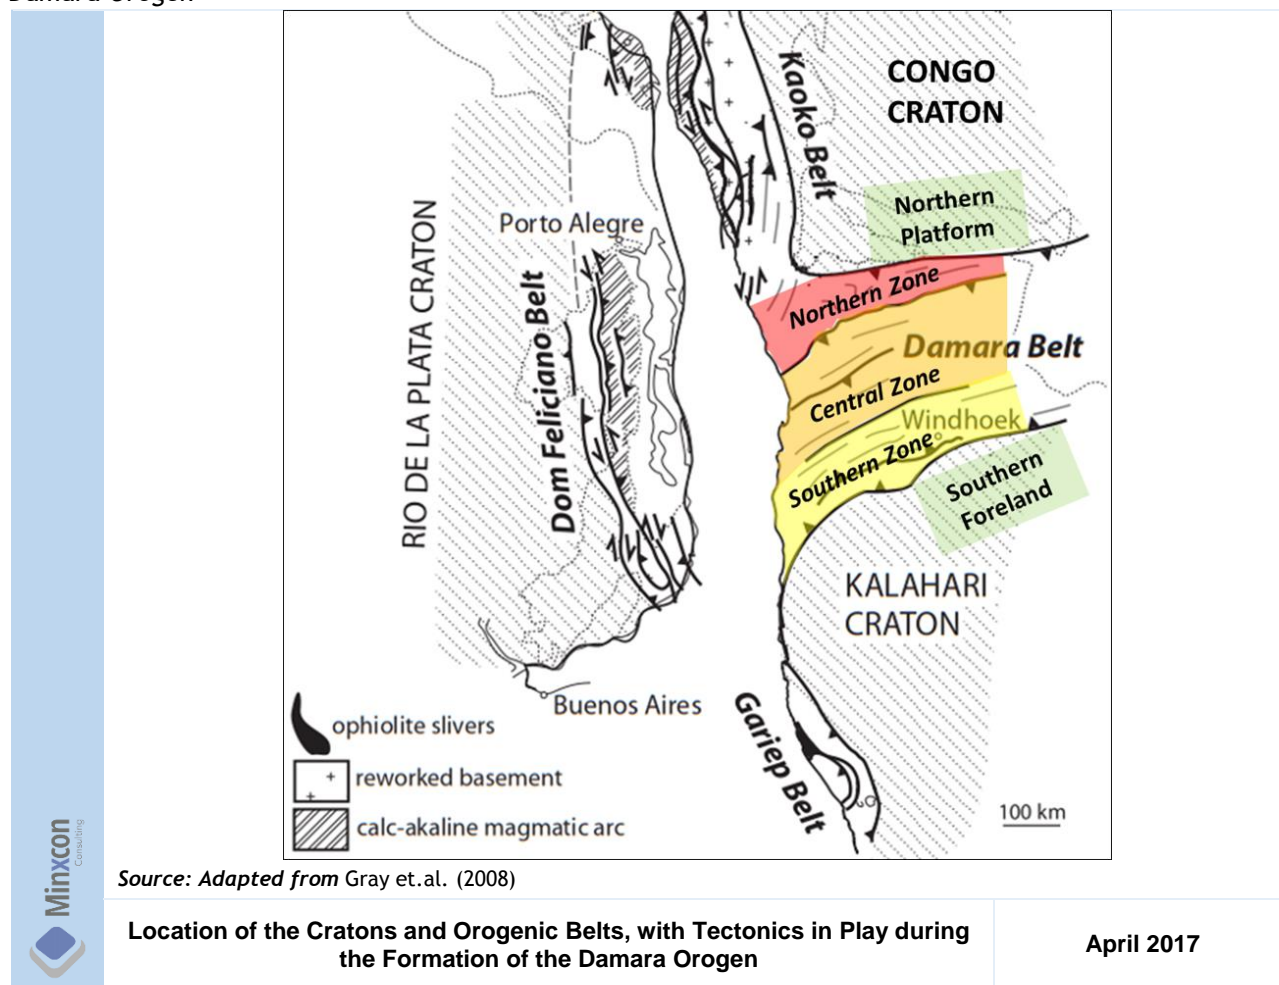Figure 11: Location of the Cratons and Orogenic Belts, with Tectonics in Play during the Formation of the Damara Orogen



The Damara Orogenic Belt may be divided into three major zones separated by northeast trending lineaments, namely 1) the Northern 2) Central and 3) Southern Zones (Figure 11). The Northern Zone is separated from the Central Zone by the Omaruru Lineament Zone, while it in turn is separated from the Southern Zone by the Okavango Lineament Zone. The Damara Belt is bordered to the north by the Northern Platform on the Congo Craton and to the south by the Southern Foreland of the Kalahari Craton (Kruger, T. and Kisters, A., 2016). The contact between the Northern Platform and the Northern Zone is marked by an arcuate chain of major basement ridges and domes which extend over 1,000 km (Deane, 1995) which affected later carbonate sedimentation which is called the Otavi Mountainland (“OML”).

Stratigraphy of the Damara Orogenic Belt


The Paleoproterozoic basement to the Damara Supergroup is known as the Grootfontein Inlier and may be subdivided into the Grootfontein Metamorphic Complex (consisting of alkline/calc-alkaline granites and granodiorites) and the Grootfontein Mafic Body (anorthosites, gabbros, biotite gneisses, granites and amphibolites) (Laukamp, 2006).

The Damara Supergroup may be divided into the Nosib, Otavi and Mulden Groups (Figure 12). The Nosib Group (780-740 Ma) is divided into the Nabis Formation (mainly siliclastics) and the Askeveld Formation (consisting of intercalated metavolcanics). It was deposited in a pre-Pan-African, NE-trending horst-graben-system that developed due to the break-up of the Supercontinent (Laukamp, 2007; Kamona and Günzel, 2007).

Figure 12: Stratigraphy of the Damara Supergroup and the Relative Stratigraphic Locations of Known Mineral Deposits

GROUP		FORMATION	LITHOLOGY	DEPOSIT
MULDEN		Kombat	slate phyllite sandstone	
		Tschudi	arenite subgreywacke conglomerate	Tschudi Cu-(Ag)
OTAVI	Tsumeb Subgroup	Huttenberg	dolostone, oolite chert dolostone shale stromatolite chert, breccia	Kombat Cu-Pb-(Zn) Tsumeb Pb-Cu-Zn-(Ge)
		Elandshoek	dolostone chert breccia dolostone	
		Maieberg	dolostone limestone	Abenab V Khusib Springs Cu-Pb-Zn
		Ghaub	dolostone diamictite	
	Abenab Subgroup	Auros	stromatolite chert, limestone	Abenab West Pb-Zn-V
		Gauss	breccia oolite dolostone chert	Berg Aukas Zn-Pb-V
		Berg Aukas	dolostone, chert	
		Varianto	diamictite	
		Askevold	tuff, quartzite quartzite sandstone conglomerate	Nosib Cu; Askevold Cu
		Nabis		
NOSIB				
		GROOTFONTEIN BASEMENT COMPLEX		

Source: Kamona, A.F. & Günzel, A. (2007)



Stratigraphy of the Damara Supergroup and the Relative Stratigraphic Locations of Known Mineral Deposits

April 2017

The Otavi Group was deposited as a carbonate platform on the Northern Platform of the Congo Craton (Gray, 2008; Kruger and Kisters, 2016; and Laukamp, 2007), consists of the Abenab Subgroup and the overlying Tsumeb Subgroup (Laukamp, 2007; Kamona and Günzel, 2007).

The Abenab Subgroup is comprised of the basal Varianto Formation which consists of a glaciogenic diamictite. Laminated, stromatolitic and massive dolostone beds make up the Berg Aukas Formation which unconformably overlies the older rocks of the Varianto Formation and Nosib Group. The Berg Aukas Formation represents a transition from clastic deposition to predominantly chemical precipitation. The Gauss Formation conformably overlies the Berg Aukas Formation and consists of a varied massive dolostone sequence of grainstone, mudstone and boundstone with megadomal stromatolites at the top of the package. The Auros Formation consists of interbedded dolostone, limestone and calcareous shale (Kamona and Günzel, 2007).

The onset of the Tsumeb Subgroup is also represented by a diamictite belonging to the Ghaub Formation with clasts of dolostone, limestone and quartzite, minor chert, gneiss and granite in a matrix of fine-grained dolomite, calcite, quartz and pyrite. The overlying Maieberg Formation is characteristically thinly bedded,


with platy limestone overlain by dolostone beds and is used as a datum in stratigraphic logs due to its wide distribution. The Elandshoek Formation overlies the Maieberg Formation and consists of three dolostone units, namely a lower massive grainstone, a middle dolostone unit with oolitic and stromatolitic chert interbeds, and an upper unit with repetitive minor cycles of dolomitic mudstone capped by boundstone. The Elandshoek Formation is in turn overlain by the Hüttenberg Formation. The Hüttenberg Formation was deposited in a low-energy, tidal flat environment on an inner shelf with local hypersaline conditions where algal mats thrived is indicated by the occurrence of evaporite beds and dessication cracks in algal chert bands (Kamona and Günzel, 2007).

Erosion of the Hüttenberg Formation resulted in the development of karst topography and a major unconformity, prior to deposition of the overlying Mulden Group, consisting of the Tschudi and Kombat Formations. The Kombat ore deposits are located towards the top of the Hüttenberg Formation (Figure 12). The Tschudi Formation generally consists of a basal conglomerate and a fining-upward feldspathic arenite with minor greywacke and intraformational breccias. The Kombat Formation overlies the Tschudi Formation and consists of a sequence of siltstone, sandstone and shale separated by a prominent middle member of black shale with siltstone. The Kombat Formation in some areas has been metamorphosed to form slate (Kamona and Günzel, 2007).

Item 7 (b) - LOCAL GEOLOGY

The Kombat Mine is located in the OML, just north of the boundary between the Northern or Outjo Tectonic Zone and the Northern Platform Margin of the Damara Orogenic Belt. The OML is characterised by various formations belonging to the Damara Supergroup which have been folded into generally east to west trending synclines and anticlines (Kamona and Günzel, 2007), as depicted in Figure 13.

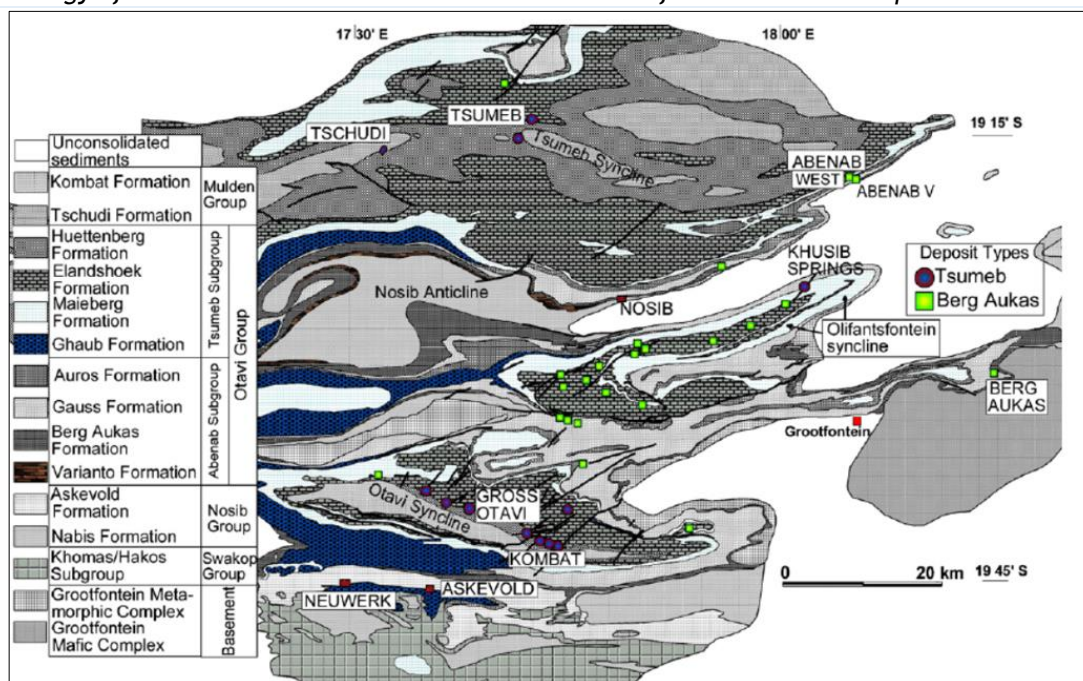Figure 13: Geology of the Otavi Mountainland and the Locations of Known Mineral Deposits



Source: Kamona, A.F. & Günzel, A. (2007)


The Geology of the Otavi Mountainland and the Locations of Known Mineral Deposits

April 2017

Three Damaran deformational events have affected the OML. D1 (ca. 650 Ma) marked the closure of the Proto-Atlantic with the formation of large recumbent south-easterly vergent. This vergence resulted in thrusts moving intensely deformed high grade metamorphic rocks over the platform carbonates on the southwestern margin of the Congo Craton. In the OML the effects of this deformation are minimal, and gentle north-south trending, open warps are evident on a large scale. However, the formation of a complex foreland thrust belt to the west may have influenced sedimentary patterns of the Mulden Group within the OML. D2 involved closure of the intracontinental arm (or Damara Orogenic Belt) resulting in recumbent shearing with an overthrust sense to the southwest on a low-angle shear zone (Coward, 1983) with relatively high temperature rocks containing metamorphic brines being thrust over the cooler Mulden Formation rocks. These structures vary in orientation and intensity and resulted in the formation of the Otavi Valley syncline. In the OML, D3 (ca. 450-457 Ma) involved a change in relative plate movement, resulting in northwest-trending open, upright warps.


Kombat Mine is located within the Otavi Valley Syncline as depicted below in Figure 14.

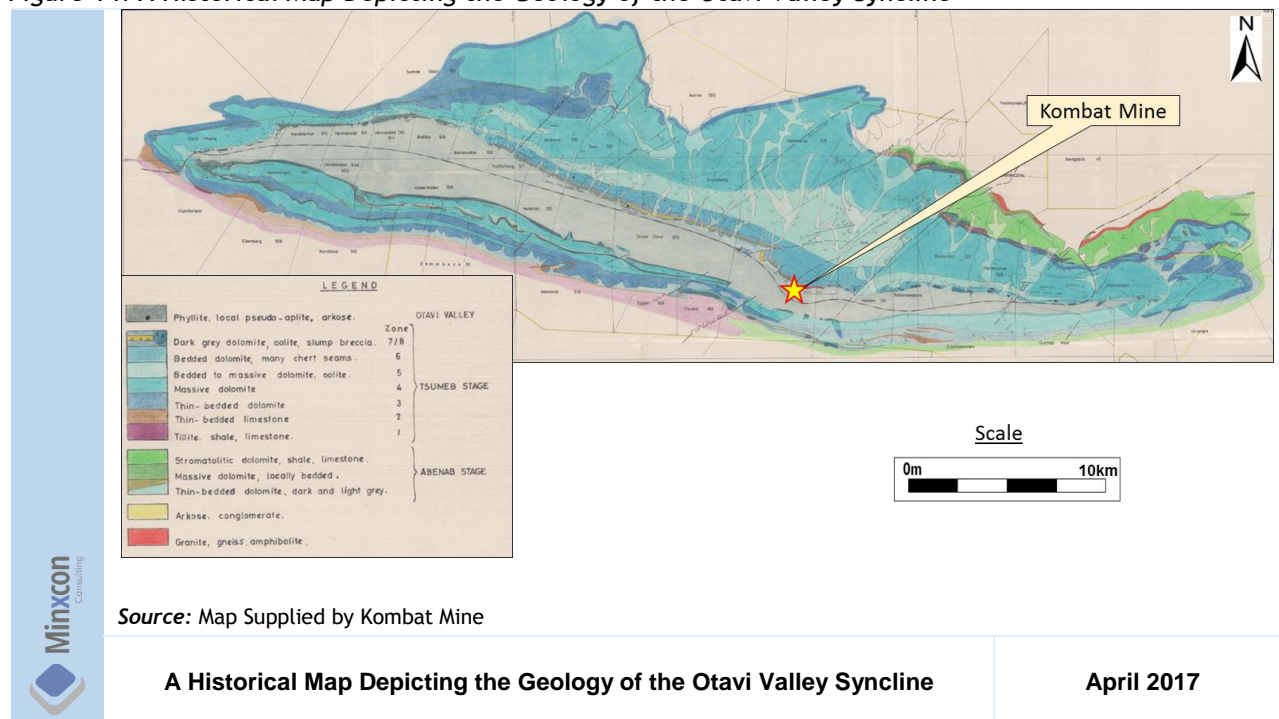Figure 14: A Historical Map Depicting the Geology of the Otavi Valley Syncline



A schematic cross-section through the Otavi Valley Syncline (Deane, 1995) is presented in Figure 15 and depicts the inferred movement of the metamorphic brines that would later lead to the formation of the Kombat orebodies.

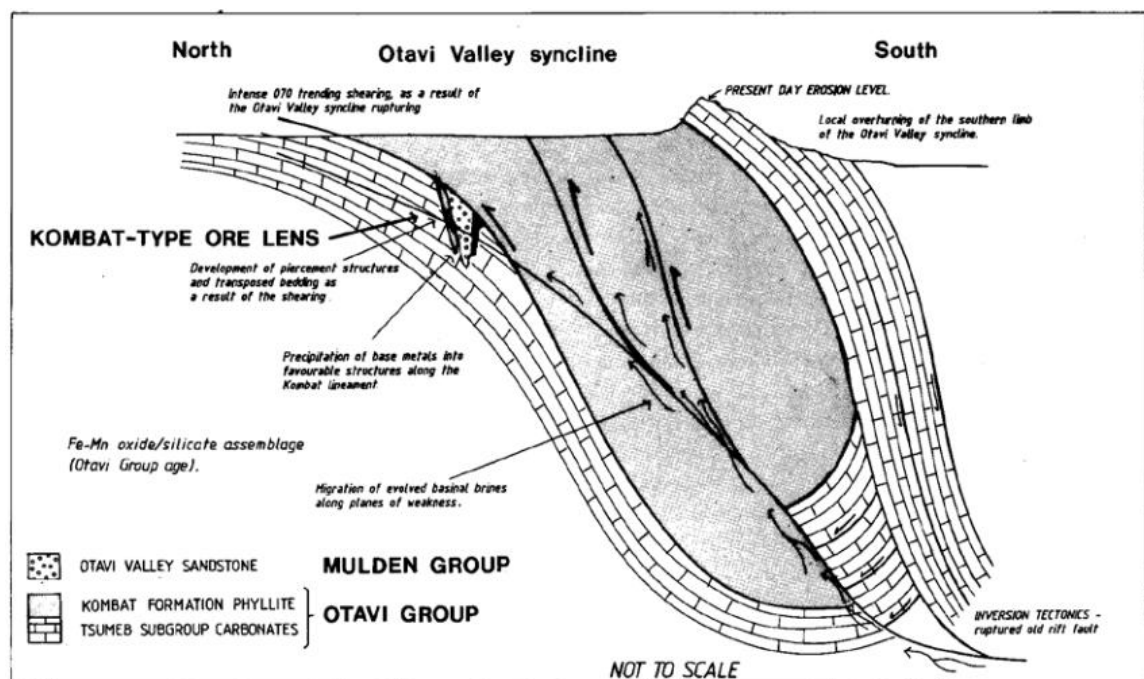Figure 15: A Schematic Section through the Otavi Valley Syncline



Source: Deane, 1995

A Schematic Section through the Otavi Valley Syncline


April 2017

Item 7 (c) - PROPERTY GEOLOGY

Very limited information is available on the geology or mineralisation of the Gross Otavi project area and discussion is therefore limited to the Kombat Mine. However, it may be assumed that the general geology applicable to Kombat Mine will apply to Gross Otavi. The orebodies on Kombat are situated on the northern limb of the double plunging, canoe-shaped Otavi Valley Syncline with its northern limb dipping south at 20° to 75° to the south. Several northeast and east trending normal and strike-slip faults cross-cut the syncline. The northeast trending normal faults post-date mineralisation.

Seven distinct zones of mineralisation separated by barren dolostone are strung out over a distance of 6 km along the so-called Kombat monoclinical lineament. All zones have surface expression except for Asis West where the orebody is down-faulted along the Kombat West Fault (Figure 16).

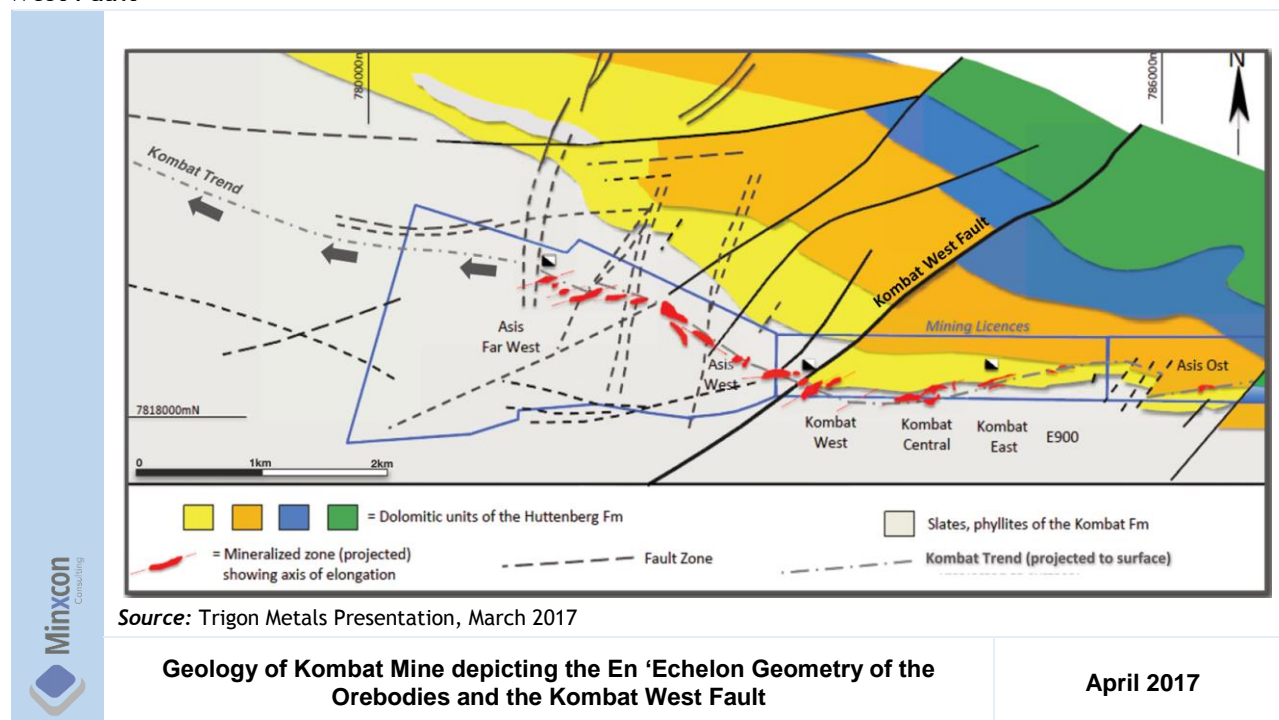
Figure 16: Geology of Kombat Mine depicting the En 'Echelon Geometry of the Orebodies and the Kombat West Fault



Hosted by the dolostone of the Hüttenberg Formation, the ore occurs below monoclinial flexures on the contact between the Kombat and Hüttenberg Formations. This affinity for the contact is not obvious at the Asis Ost and E900 as the orebodies are truncated here by erosion. The amplitude of the flexures varies from 75 m to 100 m and the wavelength ranges from 150 m to 250 m. In general the ore loci are defined by breccia bodies in dolostone and a variety of structural controls (e.g. steeply-dipping zones of shearing, net-vein fractures, joints, and fracture cleavages). These planar structures are sub-parallel within the orebodies (Figure 16) and diverge from the contact, hence imparting an échelon pattern to the orebodies and a crosscutting relationship with the contact (Innes and Chaplin, 1986; Dean, 1995). They are interpreted as D2 structures into which the Pb- and Cu-sulphides were remobilised.

The country rock above the orebodies is sheared and fractured into what is described by the term “roll structures”. A relation between the orebodies and the feldspathic sandstone of the Kombat Formation is also indicated. The ore lenses abut against the contact and hang like pendants beneath the flexures (Figure 17).

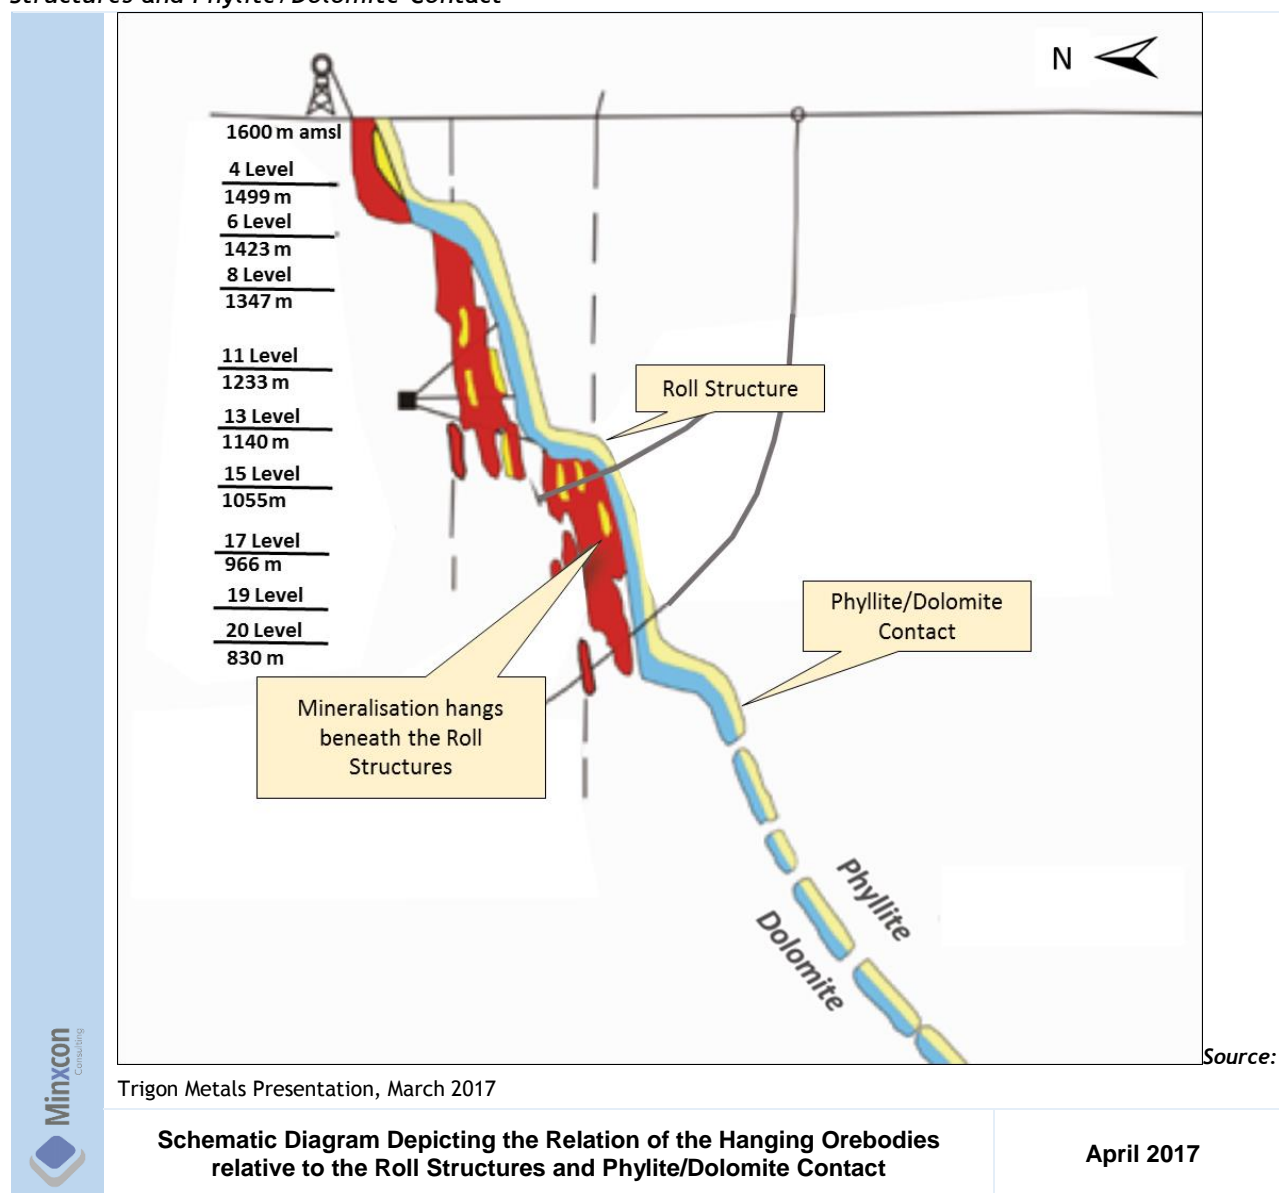Figure 17: Schematic Diagram Depicting the Relation of the Hanging Orebodies relative to the Roll Structures and Phyllite/Dolomite Contact



They are steep in orientation and transgressive to stratigraphy. With depth the massive sulphides horsetail and merge into thready, stringer type until they become disseminated in calcitized zones of net-vein fractures.

The Kombat orebodies are interpreted to have formed as a result of the release of both CO_2 and CH_4 from the Mulden shales. This converted the anhydrite (in the dolostones) to calcite releasing SO_4 into the brines. The brines also migrated along the basin margin faults and thrusts, picking up base metals along the way.

The CO_2 and S reacted with downward-migrating, oxidising groundwater producing sulphuric acid that ate its way up through the last 400 m of the rotated fold-thrust fracture systems in the carbonates, forming a hypogene karst system. Unconsolidated sand was subsequently forced through the fracture system forming sandstones. The overlying Mulden phyllite acted as a barrier preventing the upward migration of base metal bearing brines, subsequently precipitating sulphides by reduction in structurally controlled roll structures.

Item 7 (d) - MINERALISATION

The following section contains copied and adapted work from Minz (2008) and P&E (2014).

The orebodies are epigenetic, hydrothermal, and metasomatic replacement and fracture-fill Cu-Pb-(Ag) type deposits. Common to all types of mineralisation is the small quantity of associated hydrothermal gangue minerals such as calcite, quartz, dolomite, and seldom barite. The degree of oxidation of massive sulphides is independent of the depth, it is controlled by the proximity of the ores to the water-bearing faults and steeply foliated sandstone aquifers.

Massive and Semi-massive Sulphides

These are elongated, foliated zones of mineralised dolostone related to centres of tectonic and sedimentary brecciation in dolostone stratigraphy. The replacement ore is best developed in breccia matrices, lenses of feldspathic sandstone, in pervasively calcitised dolostone and particularly in oölitic, pelletal/detrital units closest to the slate contact.

At least four breccia types can be distinguished. These are firstly the syn-depositional sedimentary breccia with angular dolostone clasts in a micritic and often calcitic matrix and secondly the stylo-breccia with an anastomosing or quadrangular meshwork of net-vein fractures. The fault breccia (associated with post-ore fractures) and the solution collapse breccia (associated with karsting and localised by a north-east trending fault) have little volumetric extent and no control on hypogene mineralisation (Innes and Chaplin, 1986). A foliation is frequently superimposed where breccia grades into transposition breccia in which clasts are attenuated and boudinaged. High grade mineralisation extends away from the centres of brecciation along zone of recrystallised dolostone. All gradations of mineralisation from finely disseminated sulphides to completely replaced rock exist in the sandstone and in the dolostone. Five types of massive and semi-massive sulphides are recognised: 1) bornite and chalcopryrite (+/-galena, sphalerite and tennantite); 2) galena; 3) pyrite and galena; 4) chalcopryrite +/- pyrite in a carbonaceous host; and 5) a supergene assemblage consisting of chalcocite, digenite and malachite (+/- covellite, cuprite, native copper and native silver) (Innes and Chaplin, 1986). This assemblage is localised at the water-bearing Kombat West Fault. At Asis West (E140-11) cerussite, anglesite, leadhillite, pyromorphite and wulfenite crystals were described.

Net-vein Fracture System

A reticulate or anastomosing mesh of mineralised calcitic micro-fractures is developed adjacent to shears, faults and broad zones of pervasive calcitization below massive sulphides. It is therefore regarded as the “root zones” of the massive ore (Dean, 1995). With increasing deformation it grades into sutured stylolites.

The stylo-cumulates contain magnetite, bornite, galena and chalcopryrite. In oxidised zones chalcocite, malachite, copper and hematite are found. It is common for mineralisation of this type to merge into alteration breccias and massive replacement Cu-Pb ores (Innes and Chaplin, 1986).

Galena-rich Alteration Breccias

This type of mineralisation is confined to Kombat East orebodies where steep breccia bodies of pipe-like configuration exist. An unaltered core of close-packed angular dolostone blocks is surrounded by a bleached, calcitised fringe induced by hydraulic fracturing which permitted increased fluid flow along the fracture system. The mineral assemblage comprises galena, pyrite and subordinate chalcopryrite.

Pyrite-Sericite Association

It is an alteration facies of the feldspathic sandstone affected by penetrative deformation and therefore formed early in the mineralizing process. Fine-grained, euhedral pyrite is disseminated in a generally strongly foliated sericite-quartz matrix. Ore minerals are seldom present.

Iron-manganese Oxide/silicate Association

This compositionally and texturally layered Fe- and Mn-assemblage is always associated with feldspathic sandstone and discrete steeply orientated zones of tectonic deformation. It forms an integral part of the orebodies of Asis West, Kombat Central and Kombat East. Larger bodies, with an estimated undeformed size of 50 m in length by 10 m thick comprise hematite and magnetite in juxtaposition to layered Mn-oxides and -silicates within a zone of transposition. There is no intralayer admixture of magnetite and Mn ores. All Mn-Fe orebodies contain interfoliated sandstone sliver and lenticles. The main banded ore minerals are magnetite, hausmannite, hematite, barite, calcite, tephroite, alleghanyite, pyrochroite, and small amounts of pinkish jasperoid rock. Sulphides such as pyrite, chalcopryite, and galena are present in small amounts.

Mn-ores are fine grained and polymineralic aggregates with a well-defined internal mineral banding (band width: 1 to 6 mm) of magnetite alternate with the assemblage leucophoenicite-tephroite-Cu and kutnahorite-barite-barysilite. They occur only in zones of tectonic transposition. In Fe-rich ores, granular magnetite is interlayered with schistose specular hematite and sandstone (Dean, 1995).

The layered Fe-Mn bodies are confined to the Kombat Mine and predate the sulphide formation. Fe-rich metasomatism of the dolostone could be expected to produce large amounts of Ca- and Mg amphiboles, epidote, diopside-hedenbergite, and andradite but only an amphibole(-mica) association with small amounts of epidote has been formed in the dolostone. Shortly before the deposition of the Kombat Formation, the emplacement of Fe- and Mn-carbonates/-hydrous oxides on the carbonate platform margin together with the feldspathic sandstone could have taken place during a rifting phase (Dean, 1995). The analogy between the layered Fe-Mn bodies of Kombat and volcanic exhalative class of Fe-Mn ore is described by Innes and Chaplin (1986).

Mineralised Fracture Fillings

Dilation features are developed in predictable geometric relationship to S3 shears and a joint pattern is superimposed on altered net-vein fractures and mineralised dolostone. Early shear type fractures adjacent to steeply dipping, foliated zones of massive replacement sulphides contain blebby, disseminated bornite, chalcopryite, pyrite, chalcocite and rare galena. Post-ore shears, characterized by peripheral, en echelon, sigmoidal gash veins are infilled by sparry calcite, quartz and dolomite.

Epithermal Association

This association commonly comprises transgressive vuggy veins containing euhedral calcite, quartz, and chalcopryite. It postdates the main period of mineralisation. In addition, a number of narrow veins containing galena, sparry rhodochrosite, helvite, and barite cross-cut the lenses of Fe-Mn oxides/silicates and adjacent bodies of massive galena-chalcopryite (Innes and Chaplin, 1986).

Orebody Dimensions and Mineralisation Zonation

Sulphide and carbonate minerals occur in zones around and running parallel to the major northeast striking cross-cutting faults. The malachite-azurite zone averages 50 m in width and is closest to the faults. The covellite-chalcocite zone is approximately 50 m wide and further away from the fault and the covellite-chalcocite zone is up to 100 m wide and surrounded by the chalcopryite zone. The zonation marks the alteration of the basic chalcopryite mineralisation by oxidizing groundwater.

Broad zones of calcitisation flank sulphide lenses; at depth, these can form 200-300 m widths of sugary limestone. Calcitisation is the dominant alteration associated with mineralisation.

Steeply-dipping lenses of compositionally and texturally layered Fe-Mn oxide-silicate mineralisation are generally found near feldspathic sandstone lenses and are commonly associated with the peripheries of the Cu-Pb mineralised zones. These Fe-Mn bodies are layered, lenticular and typically 100 m long by 50 m wide and may reach sizes up to 300 m long by 100 m wide.

ITEM 8 - DEPOSIT TYPES

Item 8 (a) - MINERAL DEPOSITS BEING INVESTIGATED

The Kombat mineralised zones are carbonate-hosted base metal sulphide deposits associated with hypogene filled karst cavities and only occur along parallel “roll structures”, which are thrust-related folds. One “roll” parallel to the main Kombat Mine “roll” is present at surface at Kombat Station approximately 1,500 m to the north. The mineralised karst is thought to be caused by the upward migration of corrosive, evaporite-derived brines through the Huttenberg carbonates. These brines were expelled from the basin during compression, migrated up the thrusts into folds and encountered oxidized meteoric groundwater and formed corrosive sulphuric and carbonic acids. These acids were blocked by the impermeable and reducing Mulden shales resulting in the precipitation of base metal sulphides.

Item 8 (b) - GEOLOGICAL MODEL

A 3D grade shell “mineralisation halo” wireframe model was constructed in Leapfrog Geo™ software for the Mineral Resource evaluation and refined using Datamine Studio™. The following paragraphs in this section describe the process conducted to generate the geological model in detail.


Primary Lithological and Structural Boundary Construction

The genetic model for the formation of the deposit was used as the foundation on which all geological modelling was done. This required the construction of lithological contact between the dolostones and sandstones of the Otavi Group and the overlying slates and phyllites of the Kombat Formation.

The full drillhole database of 2,183 drillholes was considered during the construction of the dolomite/phyllite contact. This is seen as a hard boundary between the mineralisation occurring within the underlying karst, dolostones and sandstone fill and the barren phyllite/shale overburden. Leapfrog Geo™ was used to create this interface.


An additional field in the drillhole database was created which defined the correctly grouped lithologies to generate drillhole intercepts of the dolomite/phyllite contact for this purpose. The original lithological coding was used to flag the interface between dolomite and phyllite as presented below in Figure 18

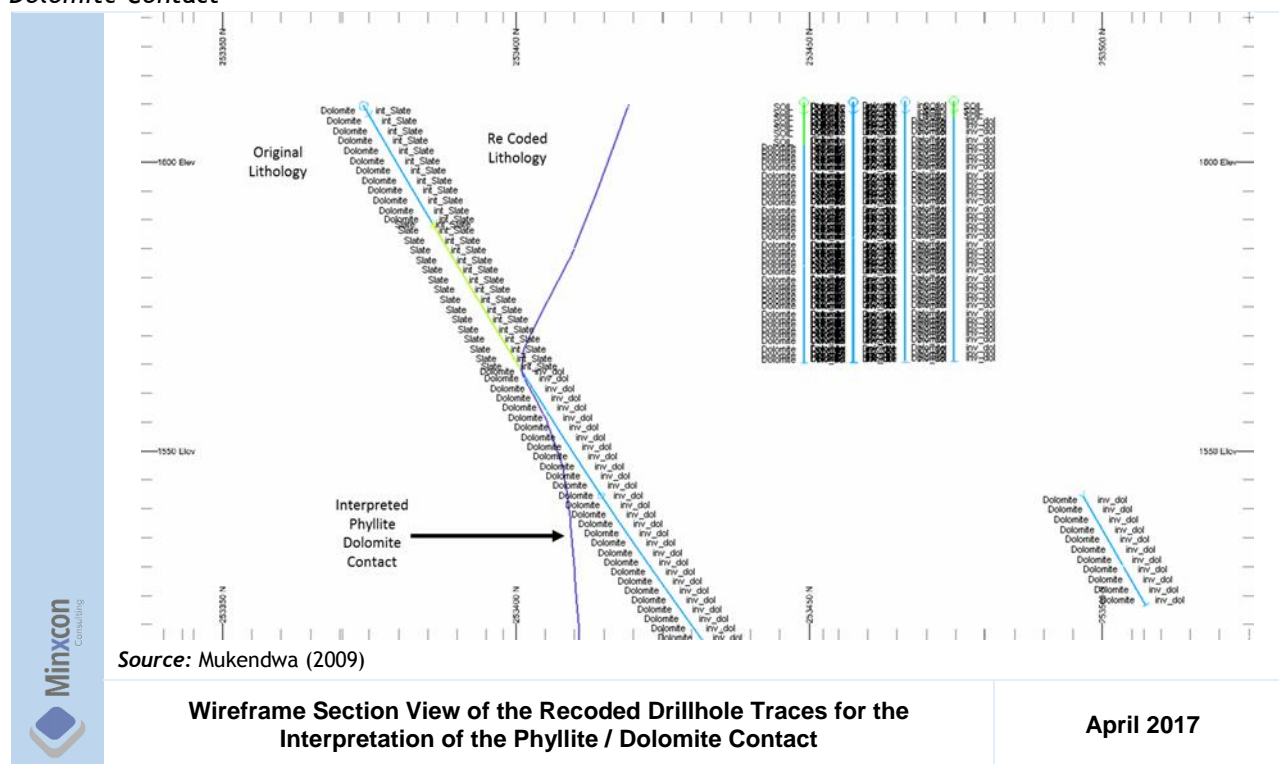Figure 18: Wireframe Section View of the Recoded Drillhole Traces for the Interpretation of the Phyllite / Dolomite Contact




Where the hard boundary was poorly defined due to lack of logging detail, the surrounding holes were then used to guide the flagging of that hole. This resulted in an unbroken, rough dolomite/phyllite wireframe as presented in Figure 19.

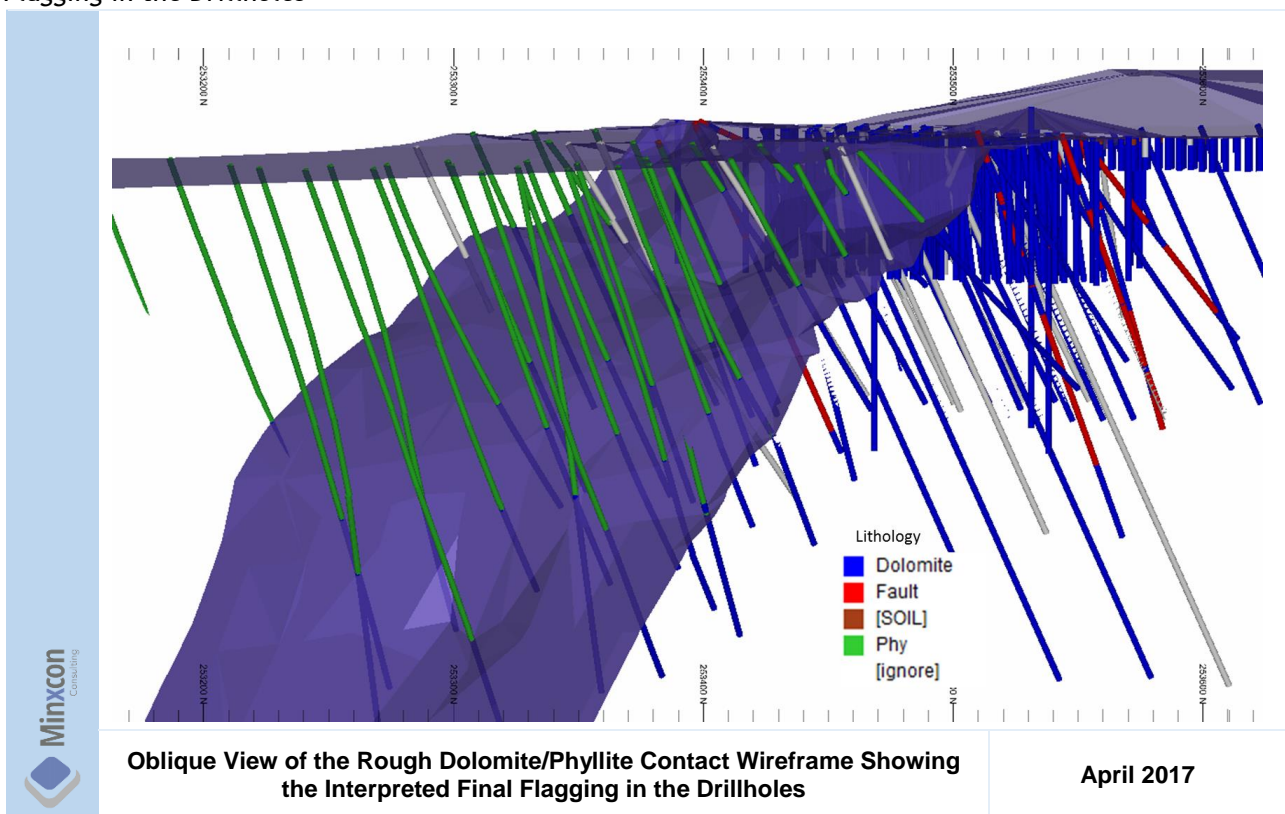Figure 19 : Oblique View of the Rough Dolomite/Phyllite Contact Wireframe Showing the Interpreted Final Flagging in the Drillholes



Minxcon reviewed the rough dolomite/phyllite wireframe in conjunction with historically mapped and interpreted geological structures which Minxcon digitised from Mukendwa (2009) (refer to Figure 20) and various other historical plans for consideration and incorporation into the geological model.

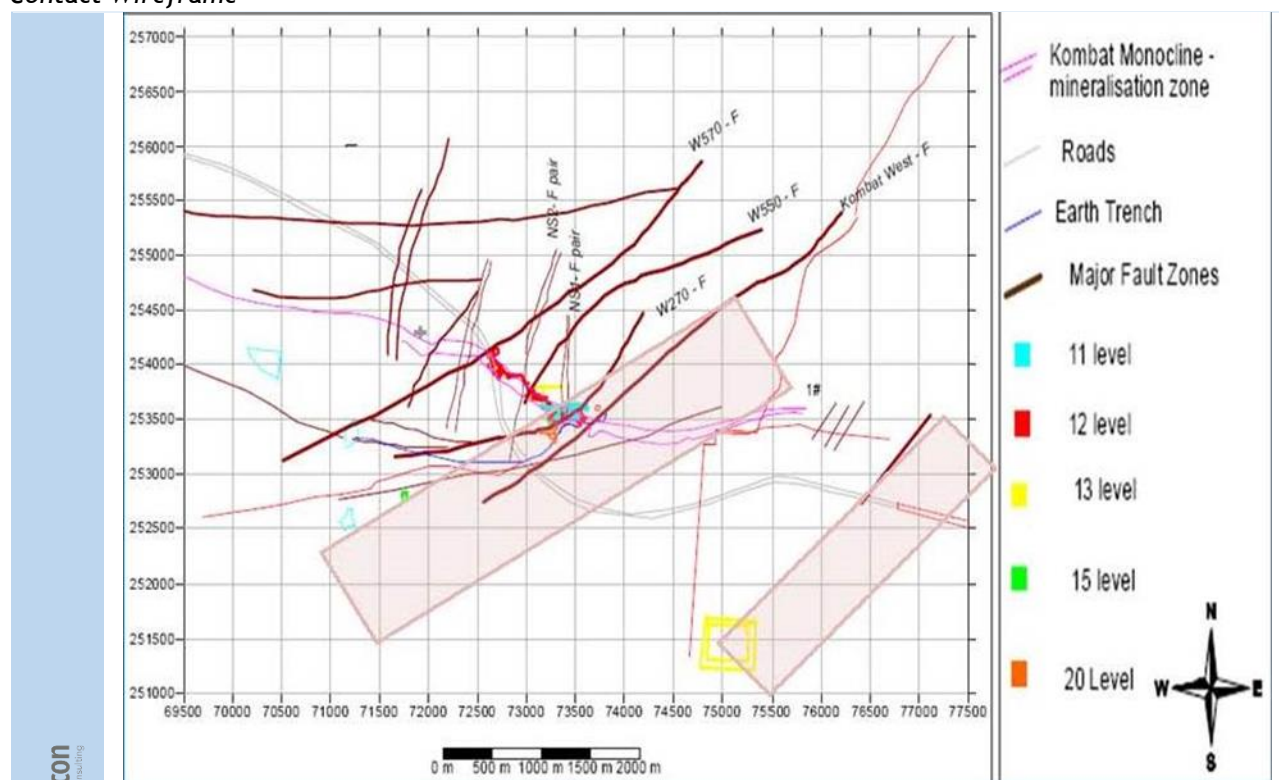Figure 20: Geological Plan Used to Identify Major Structures for Segmenting the Rough Dolomite/Phyllite Contact Wireframe




Source: Mukendwa (2009)

Geological Plan Used to Identify Major Structures for Segmenting the Rough Dolomite/Phyllite Contact Wireframe

April 2017

Where dislocations between sets of drillholes corresponded to mapped or interpreted faults, these faults were constructed in Leapfrog Geo™ and used to cut off and refine the dolomite/phyllite contact wireframe resulting in the final product as presented below in Figure 21.

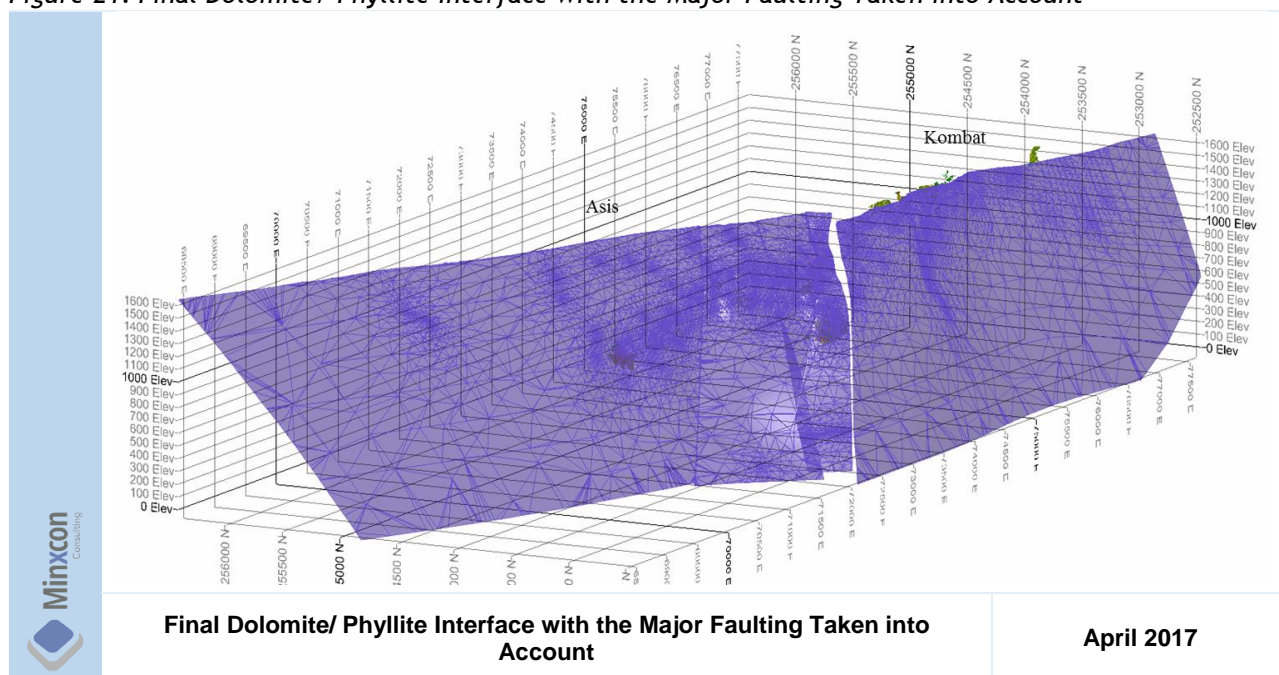Figure 21: Final Dolomite/ Phyllite Interface with the Major Faulting Taken into Account




Final Dolomite/ Phyllite Interface with the Major Faulting Taken into Account


April 2017

The Kombat West Fault was found to have the most impact on the geological model, as well as the Mineral Resource as it has a significant downthrow of between 100 m and 150 m to the west and splits the model between mining sections into Asis and Kombat property areas, with dextral strike-slip component of 160 m. The impact of the Kombat West Fault is depicted below in Figure 22. The fault was adjusted to the drilling in Leapfrog Geo™ and used as a boundary for the creation of the grade shell.

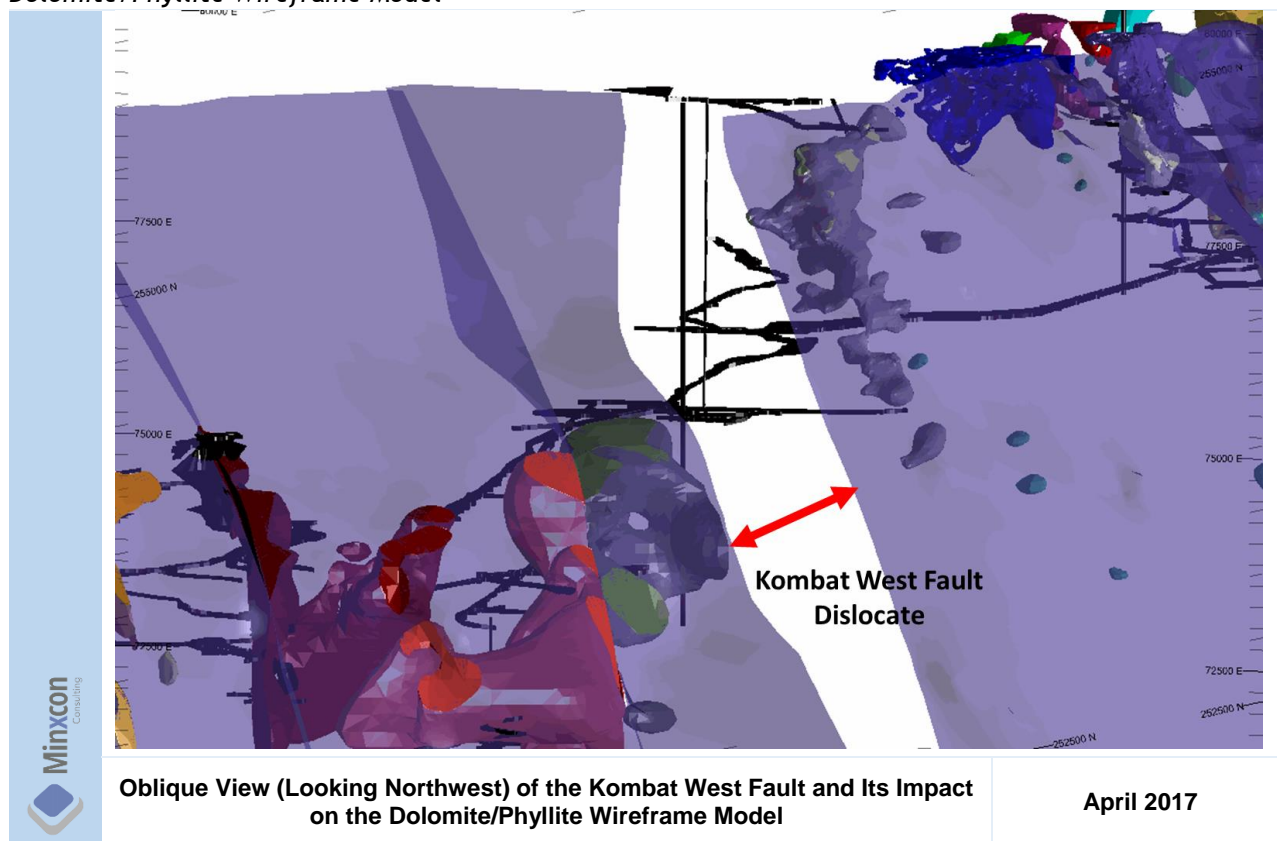
Figure 22: Oblique View (Looking Northwest) of the Kombat West Fault and Its Impact on the Dolomite/Phyllite Wireframe Model



The faults W270, W550 and W570 as presented in Figure 20 were also modelled and projected down at 90°. Figure 23 below depicts a plan view of these faults in Datamine Studio™ after modelling.

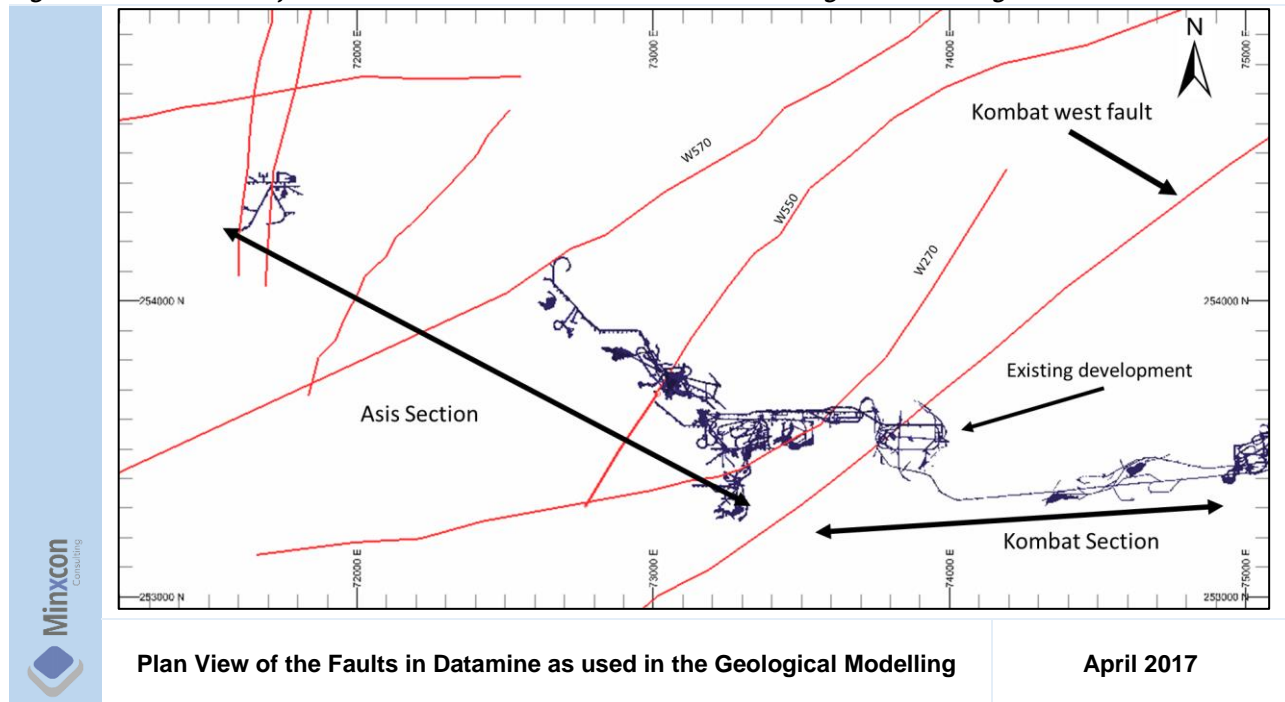Figure 23: Plan View of the Faults in Datamine as used in the Geological Modelling


The interpreted faults that were also treated as hard boundaries and were later used to cut the grade shells as shown in the Figure 24 below. This depicts the faulting to have a significant impact on the strike length of an orebody when the historic development is shown in conjunction with the faulting.

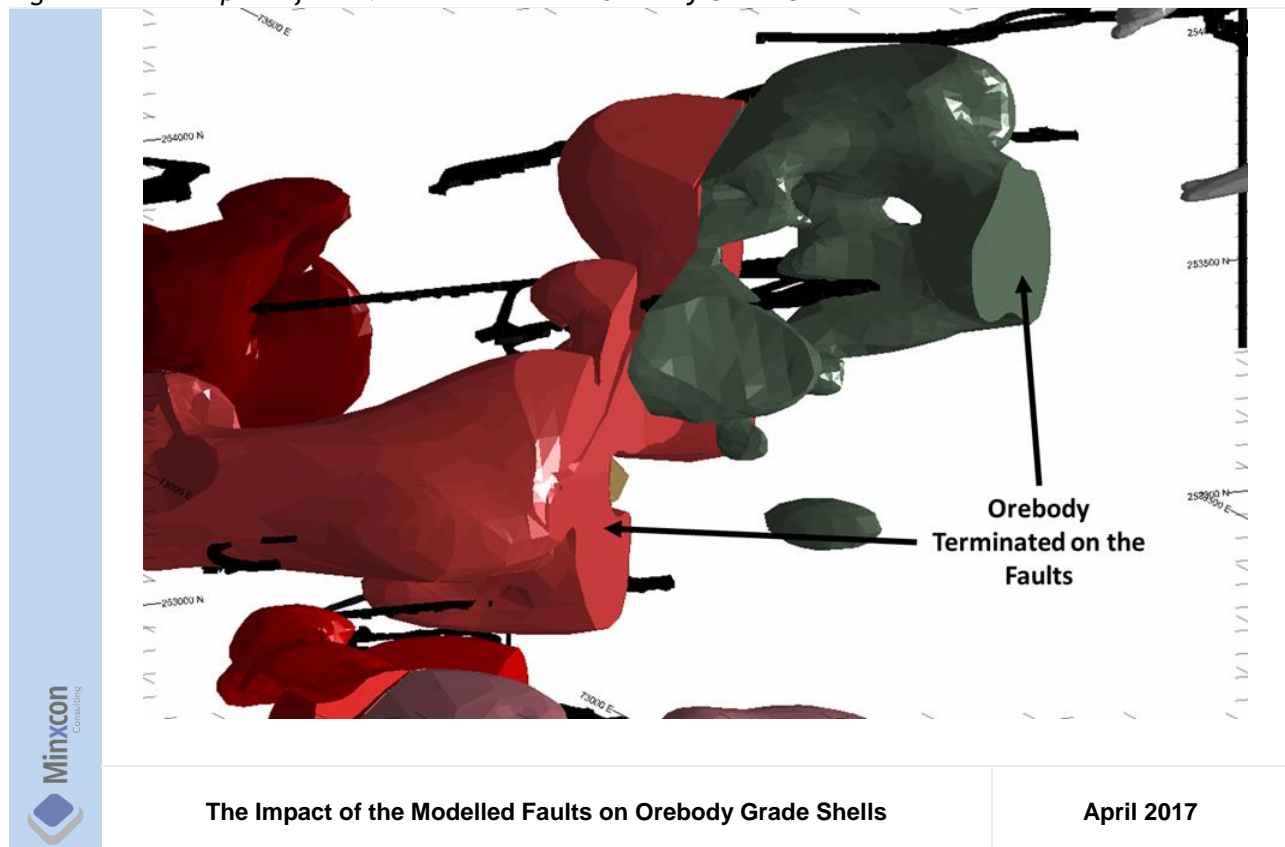Figure 24: The Impact of the Modelled Faults on Orebody Grade Shells


Grade Shell Construction

Grade shells or “mineralisation halos” were defined and created in Leapfrog Geo™ using the combined Cu-Pb cut-off of 0.3% for mineralised material. It is assumed that all material below 0.3% Cu+Pb% is waste material and it is the intention that the grade shells or mineralisation halos do not represent orebodies, but much larger estimation volumes where higher grade zones or orebodies can be identified above different grade cut-offs within the encompassing grade shells (Refer to Item 14). The cut-off was determined as the natural mineralised cut-off based on an analysis of the sampling. Minxcon looked for an inflection point investigated in conjunction with the various laboratory’s detection levels in order to indicate the true natural minimum value for mineralised material. Thus the natural cut-off for the combined Copper Lead was set at 0.3% as determined and depicted in Figure 25 below.

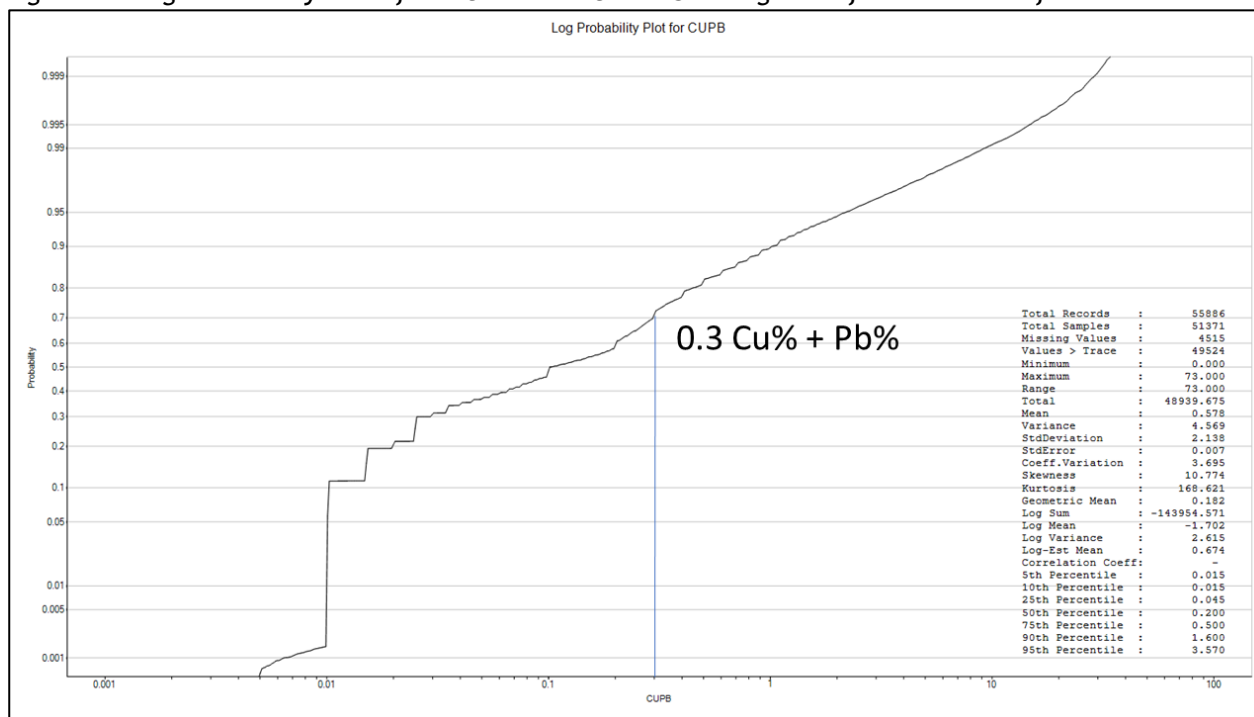Figure 25: Log Probability Plot of the Combined Cu+Pb Showing the Inflection Point of 0.3%




The grade shells were generated taking cognisance of the strike of the dolomite/phyllite interface and by allowing the drillhole grades to dictate the final dip orientation of the grade shells. Based on data spacing, the wireframe extrapolation range was set to 200 m to determine and validate the interpreted continuity of the mineralisation in any direction. The rough grade shells prior to refining are presented below in Figure 26.

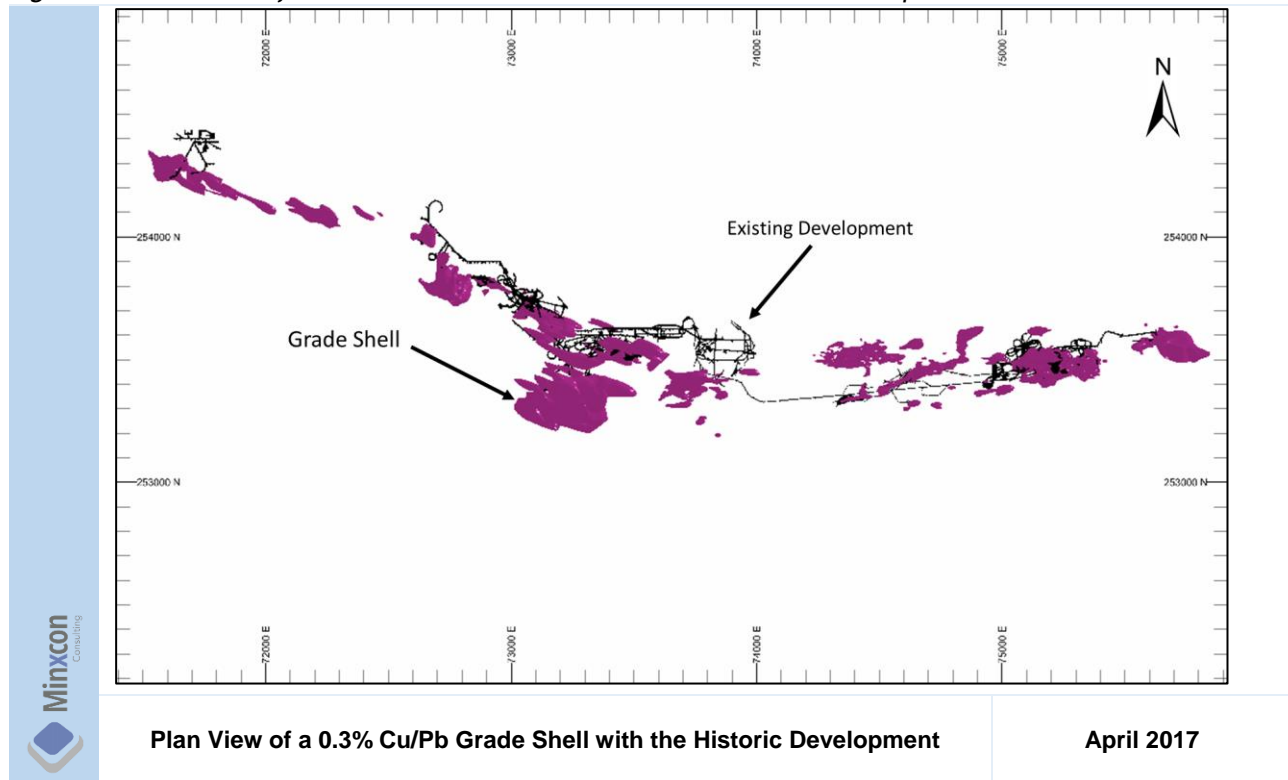Figure 26: Plan View of a 0.3% Cu/Pb Grade Shell with the Historic Development


Where historic stopping had occurred, but drilling density was found to be insufficient for the purposes of creating the grade shells which covered the mining, additional points were inserted to cover the mined-out areas. This was done due to the lack of the instope sampling which would have assisted with grade shell delineation. The intention with this exercise was to be able to see if any potential pillars might exist in the region of these mined out orebodies. An example where this exercise was conducted is presented below in Figure 27.

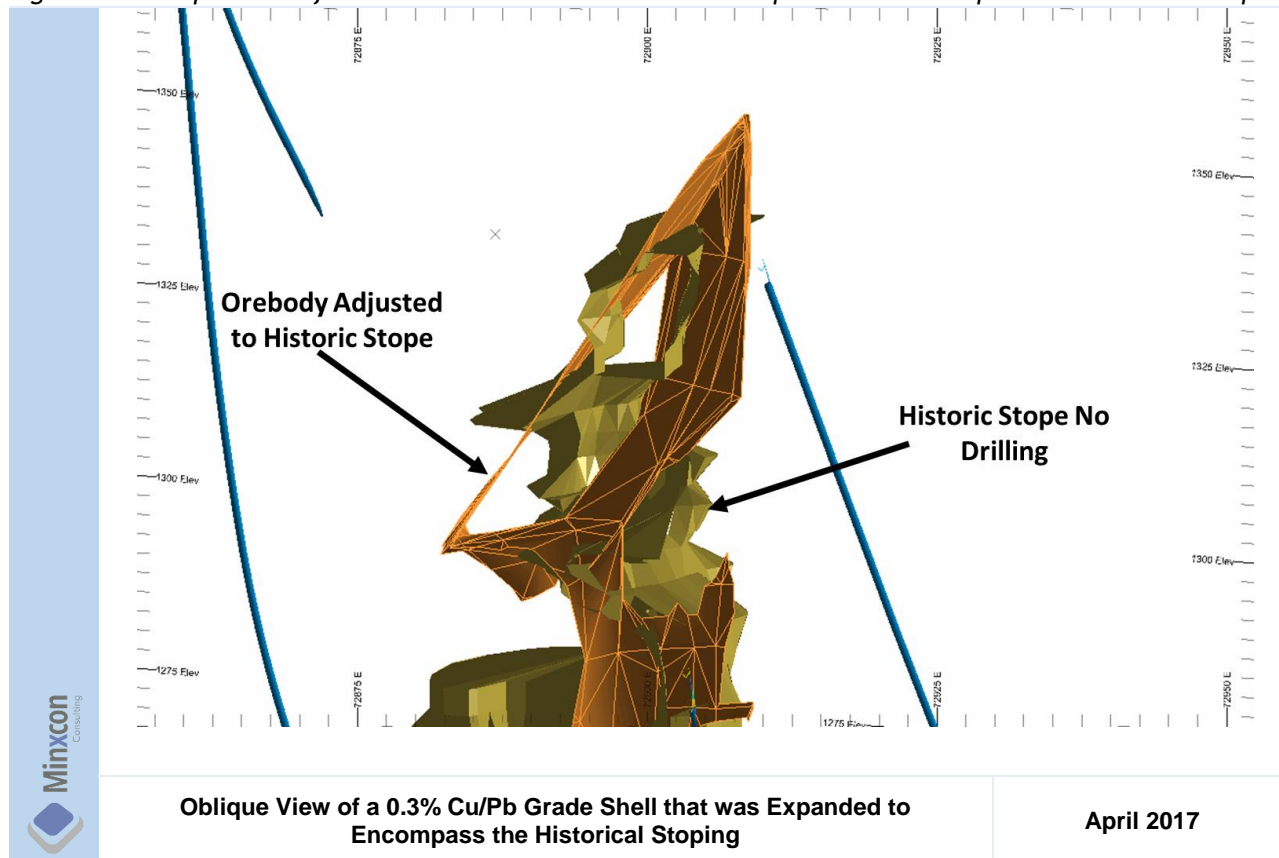Figure 27: Oblique View of a 0.3% Cu/Pb Grade Shell that was Expanded to Encompass the Historical Stopping




Once all the grade shells had been adjusted relative to the sampling, they were further refined by means of cutting them off against the final dolomite/phyllite wireframe model as presented in Figure 28.

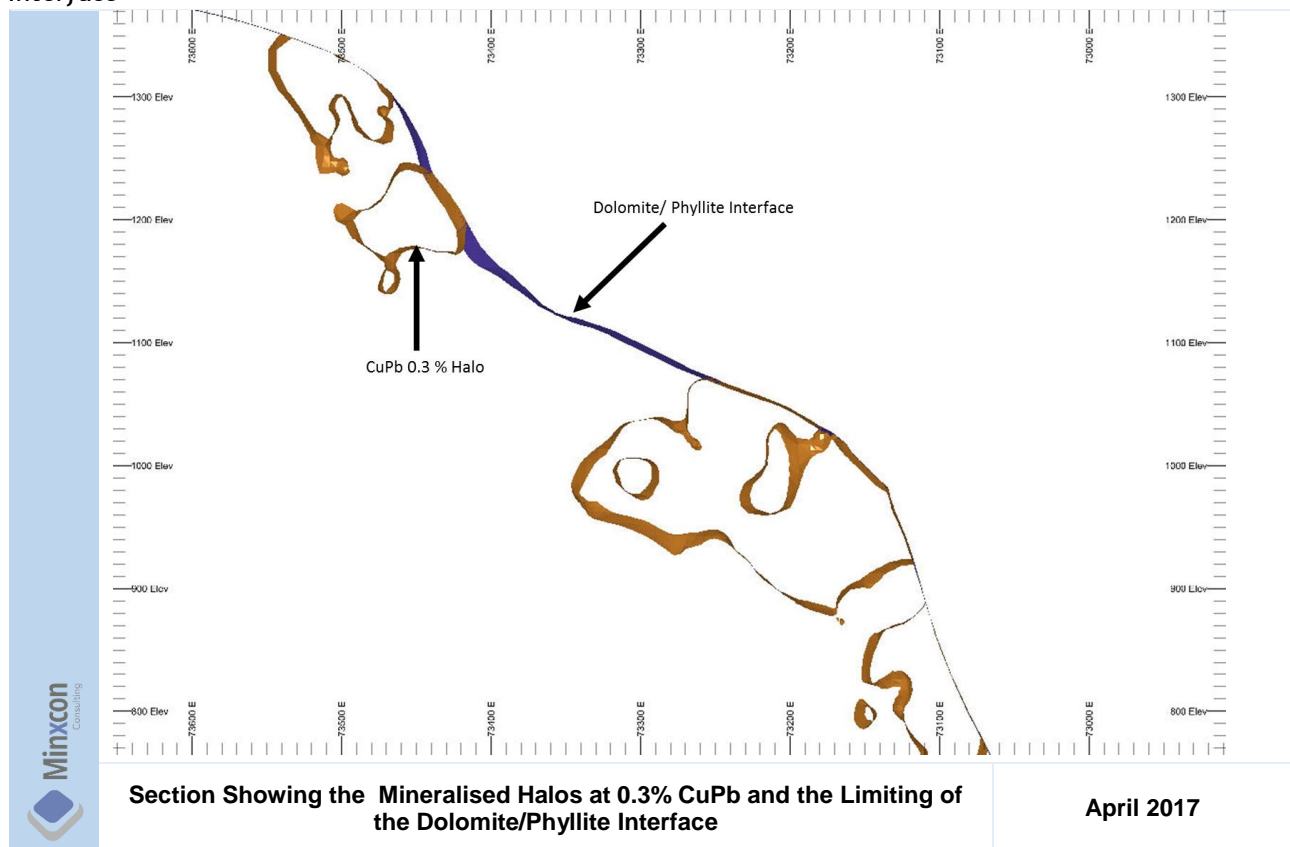Figure 28: Section Showing the Mineralised Halos at 0.3% CuPb and the Limiting of the Dolomite/Phyllite Interface




The Otavi grade shell was manually created in Datamine Studio™ using the Leapfrog Geo™ shell to inform the wireframing to include drillholes that were just beyond the ranges of the criteria in Leapfrog Geo™. The final Otavi shell is presented in Figure 29.

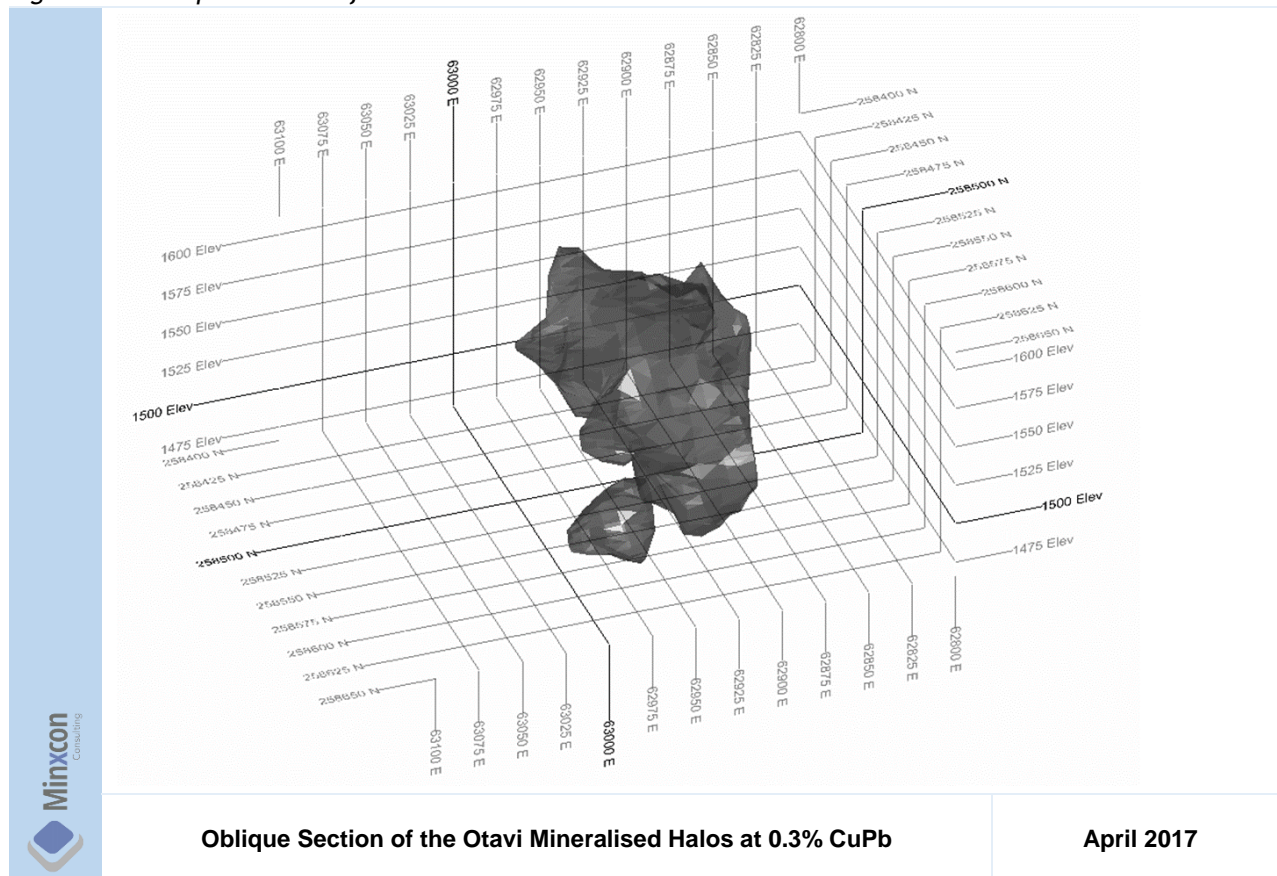Figure 29: Oblique Section of the Otavi Mineralised Halos at 0.3% CuPb


Once all the geological wireframes had been refined and dislocated as appropriate, they were finally cut off against the overlying surface topography. A bare earth Lidar survey was flown over the property. This information was translated into a wireframe and was then used for the cutting. Figure 30 below depicts a portion of the Lidar topographic surface with final grade shells and development added for perspective.

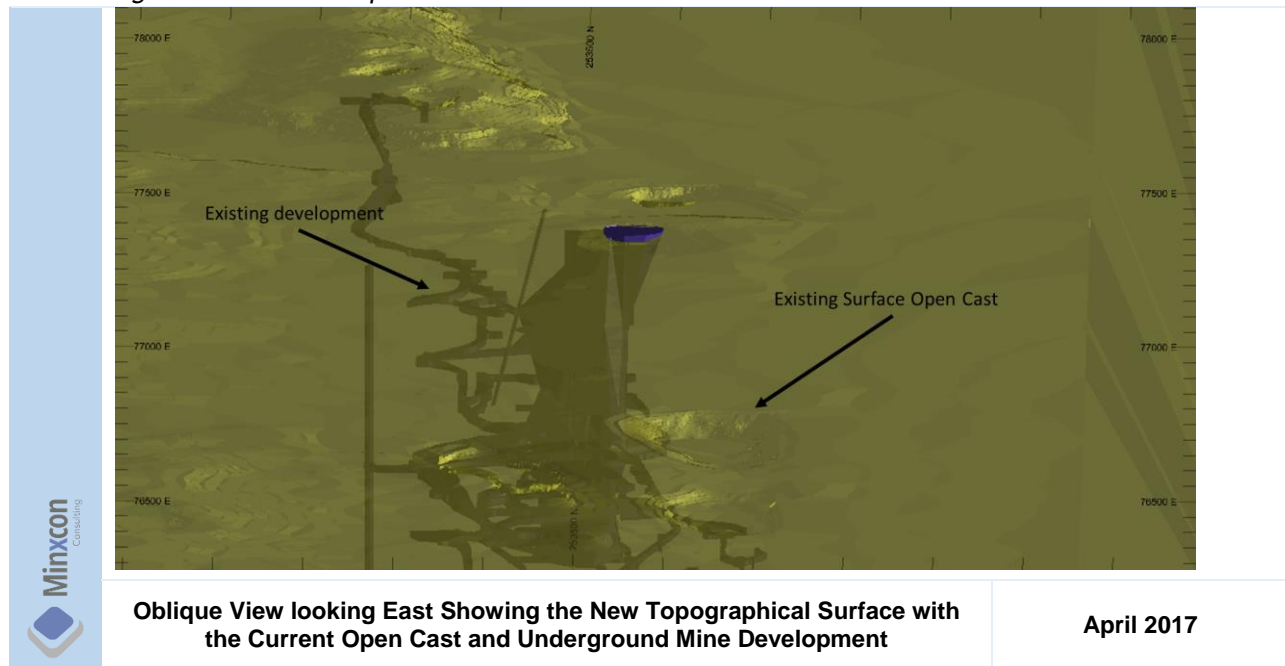Figure 30: Oblique View Looking East Showing the New Topographical Surface with the Current Open Cast and Underground Mine Development



The final grade shells covering the Asis and Kombat properties are presented in Figure 31 below. These grade shells were then used for restricting the mineralised volume during the grade interpolation phase.

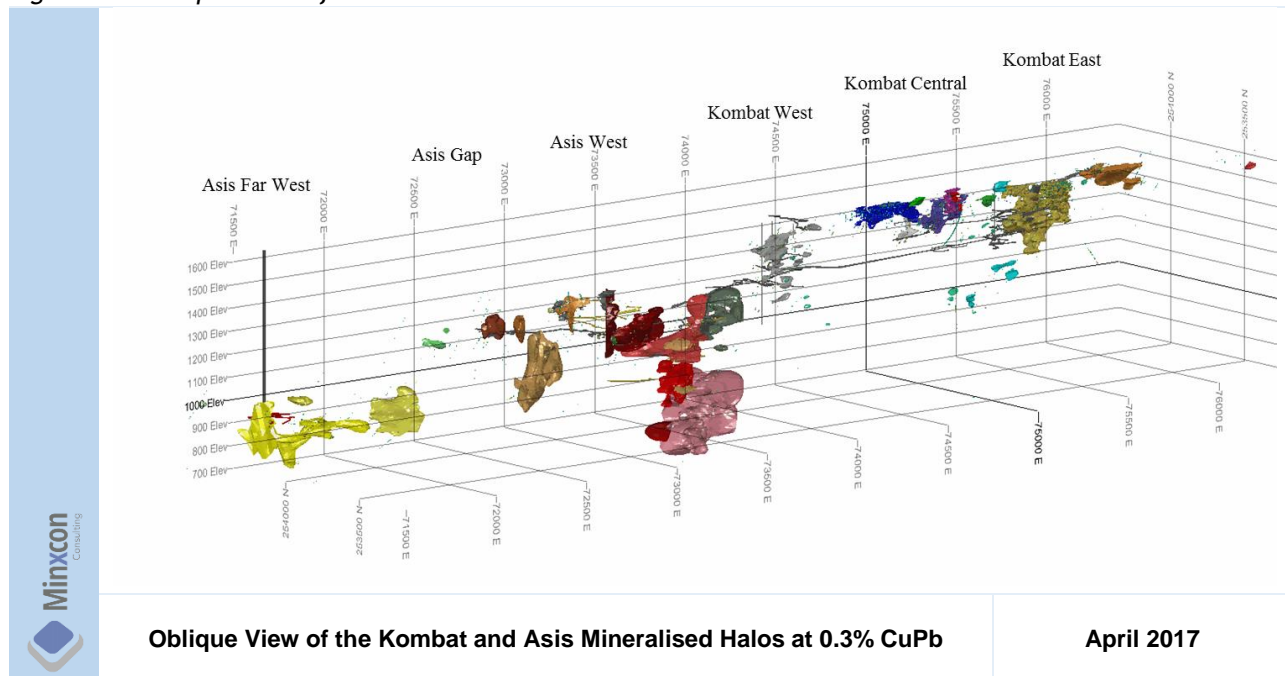Figure 31: Oblique View of the Kombat and Asis Mineralised Halos at 0.3% CuPb



ITEM 9 - EXPLORATION

It should be noted the Kombat Project is a Brownfields Project and not an exploration project as defined in accordance with NI 43-101. Kombat is a mining operation which is currently on care and maintenance.


Minxcon is of the opinion that this section is not relevant, but is included for completeness sake. In addition, extensive diamond, RC, percussion and RAB drilling has taken place.

Item 9 (a) - SURVEY PROCEDURES AND PARAMETERS

Numerous geochemical and geophysical surveys have been undertaken on, as well as in the vicinity of the Kombat Mine from the 1960s to 1990s by Tsumeb Consolidated Limited. These included soil geochemical, ground magnetic, aeromagnetic, induced polarisation and seismic surveys. However, documentation and results are not available for all the surveys in question.

Figure 32 below presents aeromagnetic contour plan with superimposed geology from the 1980s.

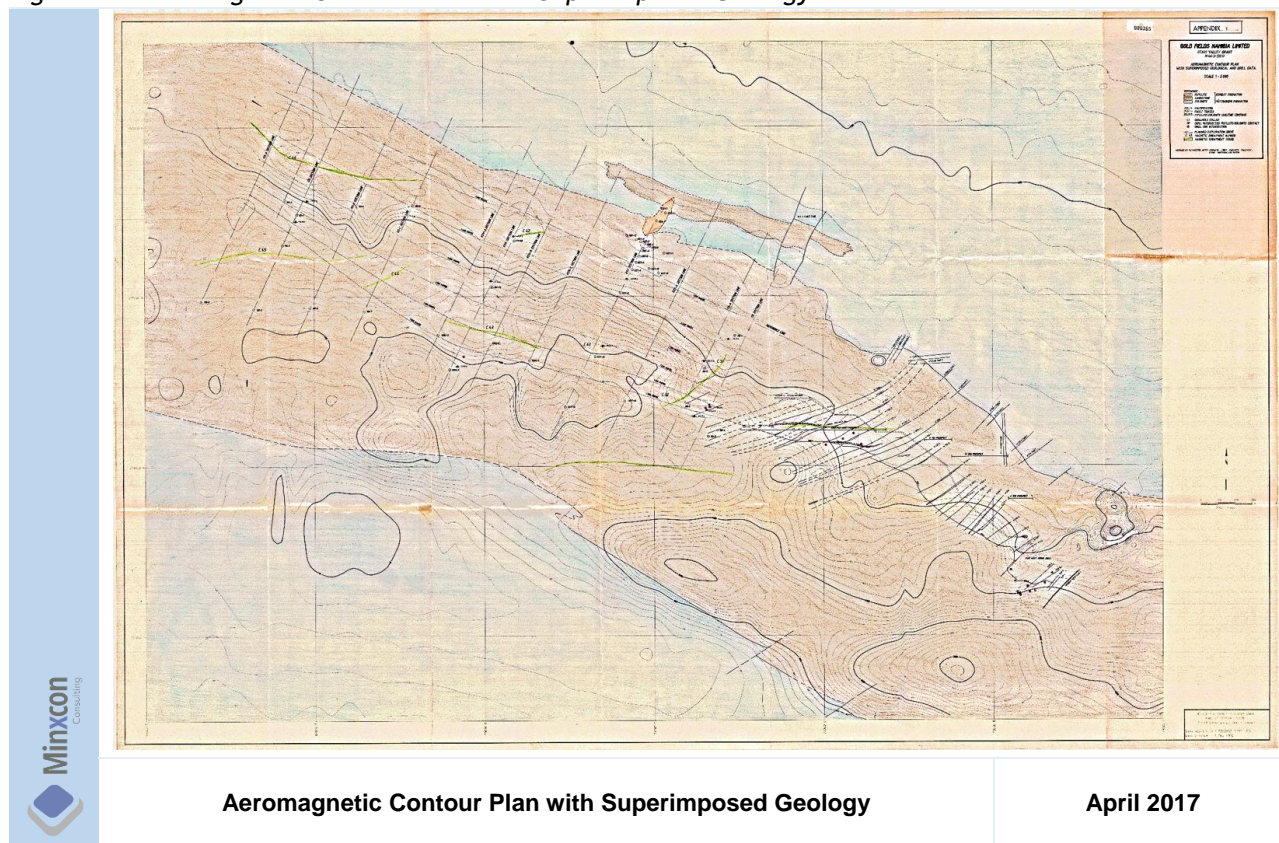Figure 32: Aeromagnetic Contour Plan with Superimposed Geology



Item 9 (b) - SAMPLING METHODS AND SAMPLE QUALITY

Soil Geochemistry

Limited information is available pertaining sampling methods and sampling quality, however from the available data, it is evident that soil geochemistry investigations were undertaken at Asis West. Numerous geochemical surveys were undertaken at Asis Far West from the 1960s to 1990s, though this is not related to the underlying orebodies which do not outcrop at surface. Samples were collected at a line spacing of between 50 m and 200 m and samples were collected every 20 m at a depth of 25 cm.

Trenching


Hand written sampling results for two trenches conducted on Asis West during the 1980s are available, however no records available pertaining the historical sampling methods and sample quality are available nor the coordinates for the trenching in question. In 2015, a trench was excavated by a Tractor-Loader-Backhoe (“TLB”) and sampling was conducted at 2 m intervals. A total of 10 samples were collected, including a chip sample which was collected on the bedrock outcrop. This single trench is not viewed as being representative of the geology, nor the targeted underlying orebodies

Item 9 (c) - SAMPLE DATA

Soil Geochemistry

Limited information is available pertaining sampling methods and sampling quality, however from the available data, it is evident that soil geochemistry investigations were undertaken at Asis West. Numerous geochemical surveys were undertaken at Asis Far West from the 1960s to 1990s. Sampling was conducted at a line spacing of between 50 and 200 m and samples were collected every 20 m at a depth of 25 cm. Figure 33 below presents an early regional soil geochemistry survey over Asis West and Asis Far West conducted by Tsumeb Consolidated Limited.

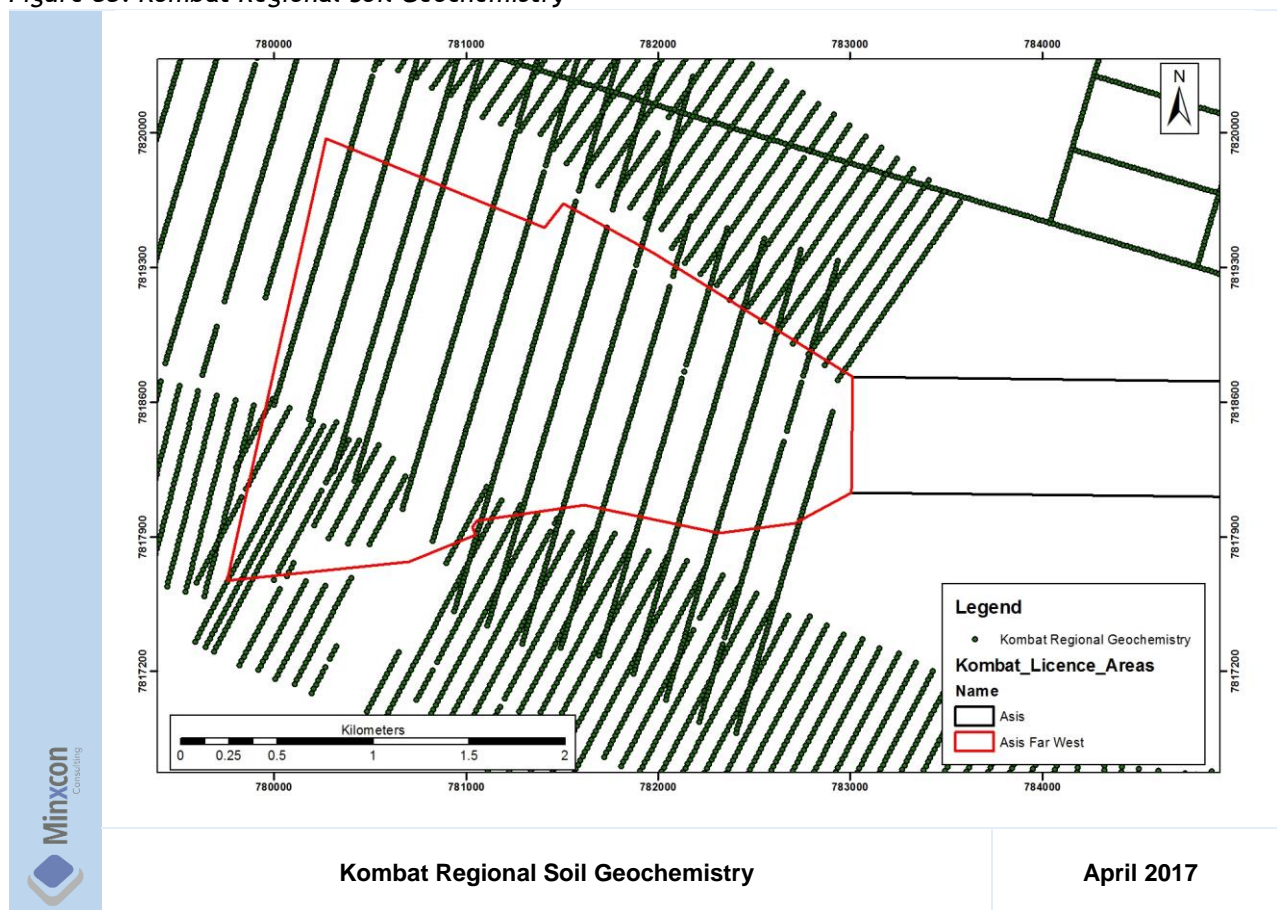Figure 33: Kombat Regional Soil Geochemistry



Trenching

In October 1980, two trenches were excavated to expose the bedrock. Trench 1 was 27 m long and trench 2 was 30 m long. These two trenches were dug at Asis 656 farm and the spatial location of these trenches is unknown.


An additional trench was excavated in 2015, and the trench is approximately 16 m long, 2 m wide and 2.5 to 3 m deep orientated in a northwest-southeast direction. The spatial location of this trench is unknown. A total of 10 samples were collected, including a chip sample which was collected on the bedrock outcrop. This single trench is not viewed as being representative of the geology, nor the targeted underlying orebodies.

Item 9 (d) - RESULTS AND INTERPRETATION OF EXPLORATION INFORMATION

Soil Geochemistry

Figure 34 below presents regional soil geochemistry results conducted by Tsumeb Consolidated Limited.

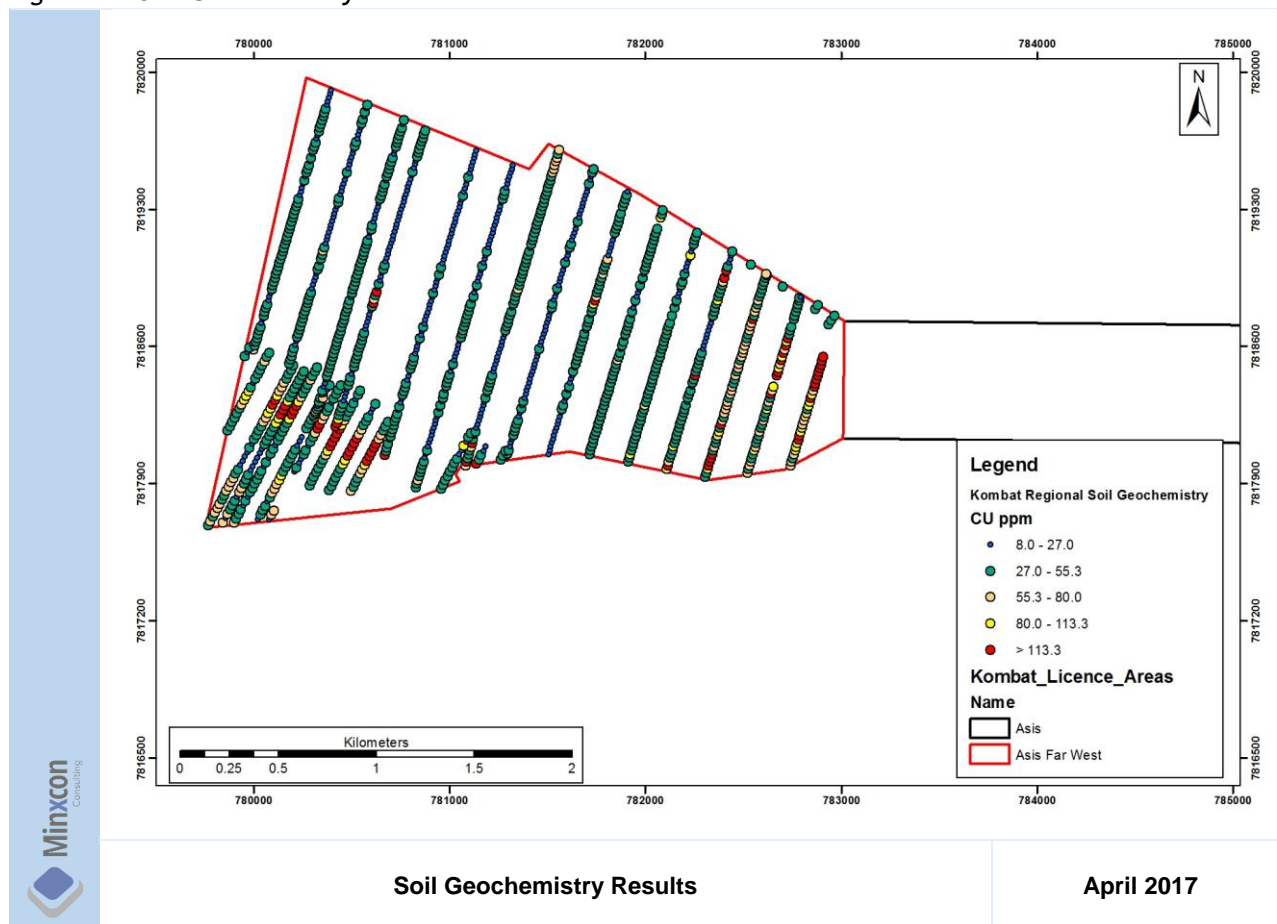Figure 34: Soil Geochemistry Results.



Trenching

The 1980 trenching results on Asis West are not presented as Minxcon is of the opinion the data is now irrelevant due to the extent of exploration drilling as well as historical mining on the Asis West property. In addition, the actual location where these trenches were dug is not recorded.

Table 6 below presents the 2015 significant trench intercepts (>0.5% Cu).

Table 6: Significant Trench Intercepts (>0.5% Cu) for 2015.

SampleID	From m	To m	Width m	Cu %	Pb %	Ag ppm
KT01	Chip Sample continuous Across the Face			0.53	0.01	11.80
KT02	0.00	2.00	2.00	2.05	0.41	26.10
KT03	2.00	4.00	2.00	0.90	0.81	9.90
KT04	4.00	6.00	2.00	1.42	1.27	16.90
KT05	6.00	8.00	2.00	0.90	0.61	9.10
KT06	8.00	10.00	2.00	1.13	0.27	16.60
KT07	10.00	12.00	2.00	6.28	0.25	53.80
KT08	12.00	14.00	2.00	7.55	0.50	81.10
KT09	14.00	16.00	2.00	1.15	2.31	2.60
KT10	Bedrock Outcrop			1.29	0.99	1.60

ITEM 10 - DRILLING

It should be noted that the Kombat Project is a Brownfields Project and not an exploration project as defined in accordance with NI 43-101. Kombat is a mining operation that is currently on care and maintenance.

A database totalling some 2,183 drillholes was provided to Minxcon in the form of a MS Excel™ Spreadsheet. The database contains summaries of all historical and recent drillholes (diamond, RC and RAB drillholes). Data provided to Minxcon includes drillhole collar, elevation, dip, azimuth, end of drillhole, survey, assay sheet and lithological logs. Historical drillhole collar and significant intercepts are not listed in this section due the number of drillholes that have been drilled, the fact that no QAQC was conducted on the drilling conducted prior to 2012.

This section will only cover recent drilling (2012 to 2015) conducted by the issuer and historical drilling conducted by the previous operator has been summarised in Item 6 (b).

Item 10 (a) - TYPE AND EXTENT OF DRILLING

2015 Drilling Campaign

Kombat Section

A total of 35 diamond drillholes totalling 2,014.9 m were drilled at Kombat Section during 2015.

K15-001 was collared to intersect the area above the OMEG underground workings. It intersected primarily dolomites with minor sandstone and was variably mineralised over a significant length. It appears to have clipped some underground workings. There is no lead mineralisation. There is a strong positive correlation with phosphorous (P) in the form of collophane apatite, which is often >10,000 ppm.

K15-002 was collared to test an area south of the No. 1 shaft in a location where old raises come to surface. There is a pit to the southwest where old stopes broke through to surface. This drillhole had an azimuth of 294°.

K15-003 was collared just north of the security gate along the north-south fence boundary. It was thought that it would intersect a mineralised zone but in hindsight it appears to have intersected a gap between the northern and southern mineralised zones.

K15-004 was collared east of the No. 2 fill pit. It intersected phyllite to approximately 29 m and then sandstone to 40.73 m followed by dolomite. The mineralised zone extended from 32.0 m to 51 m.

K15-005 was collared to the west of K15-004 and slightly to the north. It intersected phyllite to 11.6 m the sandstone to 16.2 m, followed by phyllite to 17.1 m, then by sandstone to 34.4 m and dolomite to the end of hole. Significant lead values with very little copper were intersected.

K15-006 was collared to the east of Kombat Central Pit in order to try and extend mineralisation to the east. This drillhole encountered dolomite throughout its length. Mineralisation was encountered from 1.5 m to 10.2 m.

K15-007 was collared to the west of K15-006. It encountered dolomite throughout its length, some of which were oolitic. These oolitic sections were usually mineralised. Mineralisation was encountered from 15.1 m to 23.57 m.

K15-008 was collared immediately north of the Kombat Central Pit at the east end looking for extensions in this direction.

K15-009 was collared in the eastern part of Kombat Central Pit. It encountered dolomite throughout but very little mineralisation. A weak zone of chalcocite and malachite was intersected at 17.15 m.

K15-010 was collared in the centre of Kombat Central Pit, possibly close to a mapped fold structure. This drillhole encountered dolomite throughout. Scattered but at times strong mineralisation was encountered from 0.0 m to 19.25 m. Mineralisation consisted of chalcocite, malachite, bornite and chalcopyrite.

K15-011 was collared south of K15-010 at the south edge of Kombat Central Pit. Dolomite was seen throughout the hole with one narrow bed of sandstone.

K15-012 was drilled at the west end of Kombat Central Pit on its southern edge.

K15-013 was drilled south of the west end of central Pit looking for an extension in that direction. It encountered dolomite throughout its length and several styles of brecciation. Oolites and algal mats are mentioned and are coincident with mineralisation. Mineralisation in the form of malachite and chalcocite were intersected from 5.4 m to 24.52 m.

K15-014 was collared east of No. 2 Fill Pit. It investigated an area of possible mineralisation east of 2 Level workings. Mineralisation was in the form of chalcopyrite and bornite.

K15-015 was drilled on a northern mineralised zone that has received very little attention in the past. The hole intersected dolomite throughout its length.

K15-016 was collared north of the No. 2 Fill Pit and north of 2 Level underground workings. It encountered dolomite throughout its length but no copper mineralisation of any kind was noted.

K17-017 was collared along an interpreted zone of mineralisation that was tested by K15-014. Mineralisation was mostly in the form of chalcopyrite and very minor cuprite.

K15-018 was drilled to the east of the glory hole, which is an historically mined out void situated in the central east of Asis and that is currently filled with water.

K15-019 was drilled south east of the glory hole and southwest of the Fe-Mn Pit.

K15-20 was drilled south of the Fe-Mn pit. It intersected primarily dolomite with numerous thin units of sandstone. The copper was mostly in the form of chalcopyrite and bornite.

K15-021 was drilled under the west end of the Fe-Mn pit. It intersected significant mineralisation. Alternating dolomite and sandstone were encountered from 0.0 m to 19.69 m.

K15-022 was drilled west of K15-017. This drillhole intersected dolomite to 16.5 m with abundant karst breccia, phyllite to 20.6 m and dolomite for the remainder of the drillhole.

K15-023 was drilled in the No. 2 Fill Pit testing the north wall contact area. Weak mineralisation was seen in one of the sandstone units from 6.82 m to 11.26 m.

K15-24 was drilled to the northeast of No. 1 Fill Pit. It intersected dolomite to 7.85 m, a mix of dolomite and sandstone to 11.04 m and then no core recovery to 14.04 m. This drillhole encountered either a karst hole or non-recorded underground working and was subsequently abandoned.

K15-025 was collared southwest of No. 1 Fill Pit. No copper or lead values of interest were noted.

K15-026 was collared to the west of the core shack area.

K15-027 was drilled to test the magazine area just off the No. 1 ramp where malachite mineralisation had been seen underground. This drillhole encountered dolomite, some of it oolitic, throughout its length but no copper mineralisation was noted. It was subsequently determined that the azimuth of the drillhole was 5° off and missed its target. No samples were taken.

K15-028 was drilled south of the 1A shaft. Mineralisation consisted of malachite, chalcocite, chalcopyrite with minor pyrite and galena.

K15-29 was collared west of No. 1A shaft drilling toward OMEG underground workings. It intersected dolomite throughout its length some of which was oolitic and stromatolitic.

K15-30 was collared to the east of the “open pit” south of No. 1 shaft. It investigated the ramp area and the southern zone of mineralisation.

K15-031 was collared west of Kombat Central Pit just north of the water pipeline. An outcrop containing some malachite was found just north of the collar of the drillhole. This drillhole intersected dolomite, some of which was oolitic and some contained algal mats. A cavity was intersected from 5.8 m to 6.4 m, possible karst. Only minor copper mineralisation was intersected, usually in the form of malachite and chalcocite with minor chalcopyrite and bornite.

K15-032 is located just west of the glory Hole.

K15-033 was collared south of K15-018 and southeast of the glory hole.

K15-034 was a shallow hole (20 m) collared to the east of K15-015 (cuprite hole). It intersected dolomite throughout its length, some of which was brecciated. A cavity (potentially karst) was note from 8.8 m to 9.58 m. No significant copper mineralisation was noted.

K15-035 was collared to the east of drillhole K15-017. This drillhole intersected deep overburden to 10.91 m, karst to 11.58 m. No significant copper mineralisation was noted.

The drilling company who conducted the drilling is not known and the core barrel width was unavailable. Core photos were taken for all drillholes including the intersections.

Downhole surveying was carried out systematically with a Reflex EZ-Trac multi-shot tool. Core recoveries as well as RQD were calculated for each drill run and expressed as percentage.

Table 7 presents significant mineralised intercepts (>2.0% Cu) for the 2015 Kombat section drilling programme.

Table 7: Significant Mineralised Intercepts (>2.0% Cu) for the 2015 Kombat Section Drilling Programme

BHID	From m	To m	Width m	Cu %	Pb %	Ag ppm
K15-001	15.97	20.68	4.71	2.93	0.01	49.74
K15-001	21.45	22.69	1.24	2.08	0.00	35.10
K15-001	25.24	26.43	1.19	5.03	0.01	75.60
K15-001	30.50	31.39	0.89	4.28	0.00	61.00
K15-002	23.55	24.58	1.03	2.05	0.13	22.50
K15-004	38.64	39.93	1.29	4.96	18.25	36.42
K15-004	40.73	41.93	1.20	2.86	3.68	39.30
K15-004	50.00	51.00	1.00	2.15	0.03	37.10
K15-005	33.68	34.37	0.69	2.71	4.03	6.30
K15-005	45.65	46.65	1.00	7.22	0.01	64.40

BHID	From m	To m	Width m	Cu %	Pb %	Ag ppm
K15-006	9.44	10.20	0.76	5.32	0.00	37.90
K15-007	21.30	21.90	0.60	4.94	0.00	44.70
K15-008	32.21	33.43	1.22	4.01	0.00	28.40
K15-010	2.00	3.00	1.00	3.50	0.00	48.00
K15-010	9.10	10.68	1.58	2.20	0.00	27.40
K15-010	15.80	17.00	1.20	2.62	0.01	20.80
K15-010	18.10	19.25	1.15	7.50	0.01	43.70
K15-012	10.32	11.88	1.56	6.53	0.00	70.17
K15-013	7.00	8.00	1.00	2.87	0.00	30.30
K15-013	20.30	20.82	0.52	2.26	0.00	22.20
K15-013	22.52	23.52	1.00	2.97	0.00	32.80
K15-014	46.25	47.40	1.15	3.77	0.00	3.10
K15-015	9.66	10.60	0.94	>40	0.16	183.00
K15-020	41.90	43.10	1.20	8.63	0.01	1.30
K15-021	34.00	35.00	1.00	2.89	14.95	19.20
K15-021	36.00	37.03	1.03	2.47	3.86	6.30
K15-021	42.72	46.33	3.61	2.71	0.01	56.88
K15-022	35.45	37.06	1.61	3.89	1.11	11.30
K15-022	39.05	41.60	2.55	2.70	0.02	10.05
K15-028	29.20	30.40	1.20	10.95	0.16	142.00
K15-029	46.00	46.95	0.95	8.43	0.02	77.30
K15-030	29.47	30.89	1.42	6.00	4.10	82.60
K15-030	31.10	32.00	0.90	6.43	6.88	61.70
K15-030	44.27	45.00	0.73	4.18	0.01	40.40
K15-033	11.50	12.24	0.74	3.80	0.08	19.00

Note: Width is reported as downhole length. True width has not been calculated or measured.

2013 Drilling Campaign

No drilling was undertaken on the properties except on the Asis Far West Property.

Asis Far West

SRK was approached by Kombat Copper Inc. to provide drillholes targeting the Asis Far West deposit to further delineate and increase the level of confidence of copper mineralisation near the 800 m deep Asis Far West shaft. Drilling commenced on the 11th January 2013 and was completed on the 10th May 2013. One mother hole (SRK1) and three wedges (SRK1A, SRK1C and SRK1D, all wedged from the mother hole) were completed totalling 1,390.14 m (including the mother hole). SRK1 was collared at 781,196.6 m E, 7,818,928.9 m N and at an elevation of 1,610 m. The hole was drilled at an inclination of -80° and an azimuth of 14.5°.

Drilling was undertaken with a D/C 2 drill rig and the downhole survey was carried using Reflex EZ-Trac multi shot instrument. It was reported by P&E Mining that a Gyro survey was used for confirmation surveying. Core recoveries were not measured or calculated for the SRK1 drillhole.

During the 2013 drilling campaign, no significant copper intersections (>2.0% Cu) were realised.

2012 Drilling Campaign

During the 2012 drilling programme, drilling was only conducted at the Gross Otavi property.

Kombat Copper Inc. conducted a preliminary drilling programme to confirm the presence of mineralisation. The drilling program consisted of three diamond drillholes, namely; GC5A-12, GC5B-12 and GC15B-12.

GC5A-12 drillhole was first to be drilled with the purpose to twin historical drillhole GC5. This drillhole was drilled at an inclination of -50° and at an azimuth of 019° . However, this drillhole was abandoned at a depth of 50.2 m due to an obstruction of steel from an old drillhole. GC5B-12 was then drilled approximately 4.0 m to the west of GC5A-12 at an inclination of -50° and at an azimuth of 019° .

GC15B-12 was drilled to twin historical drillhole GC15 and was also drilled at an inclination of -50° and an azimuth of 019° .

Downhole surveys were carried out systematically with a Reflex EZ-Trac multi-shot tool and drillhole collar coordinates were determined by use of a differential GPS. It is not known if core recoveries were measured or calculated.

Table 8 below presents significant mineralised intercepts ($>2.0\%$ Cu) for the 2012 Gross Otavi Drilling Programme.

Table 8: Significant Mineralised Intercepts ($>2.0\%$ Cu) for the 2012 Gross Otavi Drilling Programme.

BHID	From m	To m	Width m	Cu %	Pb %	Zn %	Ag g/t	V %
GC5B-12	89.00	90.02	1.02	4.33	1.26	0.48	32.00	*
GC15A-12	53.35	57.47	4.12	2.06	9.52	5.37	23.50	*
GC15A-12	64.93	67.84	2.91	2.65	4.91	*	9.50	*
GC15A-12	132.00	134.62	2.62	2.60	4.06	0.13	73.80	0.20
including	133.00	133.62	0.62	9.36	11.20	1.14	312.00	0.56

Note:

1. Width is reported as downhole length and true width has not been calculated or measured.
2. * Values not significant.

It was noted that the historical drillhole intervals do not directly correlate with the recent twinned holes, however there were numerous high grade intersections in both the historical and recent core that might potentially be associated.

Item 10 (b) - FACTORS INFLUENCING THE ACCURACY OF RESULTS

Minxcon is not aware of any drilling, sampling or recovery factors that could materially impact the accuracy and reliability of the exploration results with respect to the diamond and reverse circulation ("RC") drilling.

Item 10 (c) - EXPLORATION PROPERTIES - DRILLHOLE DETAILS

This paragraph has been included for completeness. This section will only cover recent drilling (2012 to 2015) conducted by the issuer.

Table 9 summarises the number of recent diamond drillholes ("DDH") that were drilled within the limits of the Goss Otavi and Kombat sections. These drillholes were drilled between 2012 and 2015. The table presents summaries of drillhole easting, northing and elevation of the drillhole collars, as well as the dip, azimuth and the final depth.

Table 9: Recent Diamond Drillhole Summary

BHID	Easting	Northing	Elevation	Azimuth	Dip	EOH	Type	Year	Project
	Schwarzeck		m	°	°	m			
SRK1	71,631.01	253,983.28	1,610.00	14.5	-80	950.65	DDH	2013	Asis Far West
GC5A-12	62,884.00	258,466.00	1,623.20	19	-50	50.20	DDH	2012	Gross Otavi
GC5B-12	62,884.00	258,466.00	1,623.05	19	-50	206.10	DDH	2012	Gross Otavi
GC15A-12	62,941.00	258,446.00	1,622.07	19	-50	321.98	DDH	2012	Gross Otavi
K15-001	73,940.16	253,433.23	1,607.53	341	-48	70.55	DDH	2015	Kombat Section
K15-002	73,803.65	253,465.48	1,607.74	294	-56	62.12	DDH	2015	Kombat Section
K15-003	74,162.73	253,425.75	1,608.39	360	-61	56.27	DDH	2015	Kombat Section
K15-004	74,683.63	253,422.11	1,606.98	350	-59	71.25	DDH	2015	Kombat Section
K15-005	74,656.92	253,427.95	1,607.53	351	-62	60.10	DDH	2015	Kombat Section
K15-006	74,575.02	253,527.74	1,609.65	335	-60	60.10	DDH	2015	Kombat Section
K15-007	74,548.18	253,530.56	1,609.45	339	-61	60.23	DDH	2015	Kombat Section
K15-008	74,518.01	253,553.61	1,610.14	337	-61	59.10	DDH	2015	Kombat Section
K15-009	74,485.23	253,536.14	1,605.59	337	-61	62.15	DDH	2015	Kombat Section
K15-010	74,449.94	253,527.81	1,604.83	337	-60	60.10	DDH	2015	Kombat Section
K15-011	74,454.04	253,508.21	1,604.15	336	-60	62.33	DDH	2015	Kombat Section
K15-012	74,399.18	253,507.82	1,605.59	323	-60	60.50	DDH	2015	Kombat Section
K15-013	74,369.36	253,490.63	1,611.33	338	-60	62.26	DDH	2015	Kombat Section
K15-014	74,800.37	253,462.94	1,606.70	358	-59	65.08	DDH	2015	Kombat Section
K15-015	74,835.86	253,574.86	1,609.49	3	-59	26.33	DDH	2015	Kombat Section
K15-016	74,629.18	253,481.90	1,607.92	359	-63	60.15	DDH	2015	Kombat Section
K15-017	74,981.45	253,470.27	1,607.38	357	-60	83.16	DDH	2015	Kombat Section
K15-018	75,276.08	253,461.61	1,607.34	328	-60	71.20	DDH	2015	Kombat Section
K15-019	75,301.32	253,387.43	1,606.68	340	-60	53.08	DDH	2015	Kombat Section
K15-020	75,345.11	253,410.62	1,605.98	352	-59	70.80	DDH	2015	Kombat Section
K15-021	75,342.21	253,462.02	1,600.77	22	-55	65.10	DDH	2015	Kombat Section
K15-022	74,951.34	253,469.97	1,607.51	5	-60	65.16	DDH	2015	Kombat Section
K15-023	74,582.23	253,416.94	1,596.05	331	-60	50.12	DDH	2015	Kombat Section
K15-024	74,410.95	253,442.33	1,608.33	178	-58	14.04	DDH	2015	Kombat Section
K15-025	74,240.28	253,362.84	1,606.25	2	-61	60.07	DDH	2015	Kombat Section
K15-026	74,009.19	253,422.12	1,607.52	356	-61	59.34	DDH	2015	Kombat Section
K15-027	73,987.81	253,488.77	1,609.13	341	-59	40.20	DDH	2015	Kombat Section
K15-028	73,903.46	253,404.30	1,606.28	315	-60	38.20	DDH	2015	Kombat Section
K15-029	73,884.11	253,457.64	1,607.78	163	-60	56.05	DDH	2015	Kombat Section
K15-030	73,829.70	253,389.22	1,606.06	358	-61	60.00	DDH	2015	Kombat Section
K15-031	74,307.36	253,475.42	1,610.75	3	-62	60.40	DDH	2015	Kombat Section
K15-032	75,155.61	253,479.99	1,608.14	0	-60	65.05	DDH	2015	Kombat Section
K15-033	75,284.81	253,426.40	1,606.25	1	-55	68.05	DDH	2015	Kombat Section
K15-034	74,911.51	253,575.63	1,609.30	7	-59	20.16	DDH	2015	Kombat Section
K15-035	75,018.37	253,470.39	1,607.22	351	-60	56.13	DDH	2015	Kombat Section

ITEM 11 - SAMPLE PREPARATION, ANALYSES AND SECURITY

Due to unavailability of original data, as well as the fact that the operation is currently on care and maintenance, Minxcon was not able to review sample preparation, analyses and security. The information relevant to this section was extracted and edited from P&E Mining Consultants Inc. Report dated 20 May 2014.

Item 11 (a) - SAMPLE HANDLING PRIOR TO DISPATCH

The procedure for sample handling prior to dispatch was as follows:-

- All samples were transported from the core yard to the laboratory sample receiving bay;
- The drillhole number and the sample ticket number were captured in the laboratory sample book and laboratory assay sheet as received;
- Samples were placed in plastic bags and a laboratory code number and paper bag for pulp were assigned;
- The pulp bag contained the sample number, laboratory number, department and laboratory receiving date.

Item 11 (b) - SAMPLE PREPARATION AND ANALYSIS PROCEDURES

Historical Drilling

Sample preparation and analysis for the historical drilling programmes were carried out at the non-accredited Kombat Mine Laboratory, while some additional work in terms of check sampling on pulps was also conducted at the non-accredited Tsumeb Mine laboratory. According to P&E, assaying for the KST and KDF series of drillholes may have been completed at the Tsumeb facility.

The core samples were subjected to two-stage comminution by a jaw crusher and a rolls crusher after being dried. An air spray pipe was utilised to clean the crushing equipment before and after every sample. According to P&E, samples were apparently not necessarily processed in numeric order which could imply that no QAQC was implemented. QAQC data only appears to have been captured from 2012 onwards.

The crushing equipment was located in the sample-receiving bay. Mughungora (2007) noted that the sample receiving bay was very dusty - a potential source of contamination. The following process was followed for sample preparation (Figure 35):-


- All samples were pulverised in one sample preparation room;
- The crushed material was riffle split and the rejects discarded;
- The riffle splitter was cleaned after every sample;
- The crushed material was pulverized for four minutes in a vibrating swing mill (puck and ring) and the pulp placed in the numbered paper bag;
- The pulp was then split to 0.5 g for analysis. Mughungora (2007) reports that the pulveriser mill was cleaned after every sample batch; and
- Grind time was reduced to one minute in the case of sample overload or mill equipment problems. This may have affected particle sizing and the digestion of the pulps. As of 2007, the laboratory had two swing mills, one of which was unserviceable, other partially serviceable with no timer.

The 0.5 g pulp was placed in a 250 ml beaker and digested by 10 ml HNO-HClO (or Aqua Regia HCl:HNO₃) mixed acid and 1 ml hydrofluoric acid. After heating and fuming, 50 ml tap water and 10 ml of HNO₃ acid

was added and the solution re-heated and cooled. The solution was topped up to 200 ml with tap water and shaken.

The analyte was analysed by means of an atomic absorption spectrometer (AAS) for copper and lead. No data is available pertaining to how silver and zinc were analyzed, however, these analyses were likely to have been conducted on pulp splits at the Tsumeb complex by AAS, similar to the Kombat Mine laboratory.

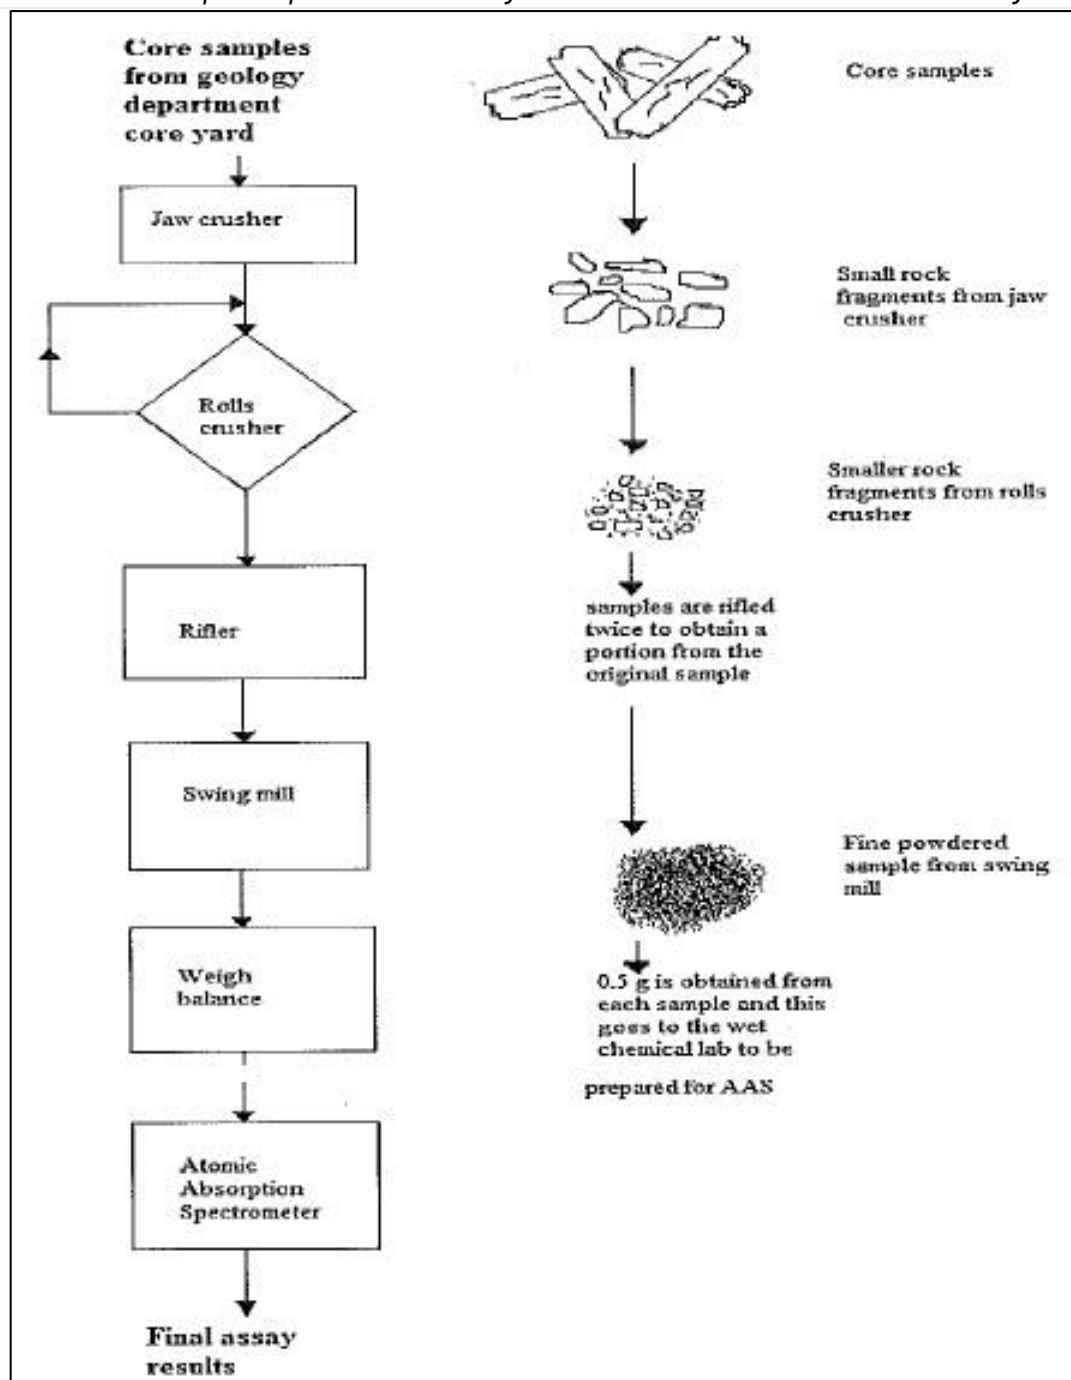Figure 35: Historical Sample Preparation and Analysis Flow Chart at Kombat Mine Laboratory



Source: P&E after Mughungora (2007)

Historical Sample Preparation and Analysis Flow Chart at Kombat Mine Laboratory

April 2017

2013 Drilling Campaign

A total of 188 samples including quality control samples were sent to the Bureau Veritas Namibia (Pty) Ltd Mineral Laboratory ("Bureau Veritas") for sample preparation (SANAS accreditation, Facility Accreditation Number: TEST -5 0003). Bureau Veritas is located in Swakopmund, Namibia. The laboratory is ISO 17025 certified.

Bureau Veritas carried out sample preparation and shipped the pulp samples to Acme Analytical Laboratories (Vancouver) Ltd. for wet chemical analysis.

Sample preparation carried out at Bureau Veritas involved sorting and drying, crushing the entire core sample to -2 mm, riffle splinting to 250 g and a grinding/vibrating pulveriser stage that ensured a 90% pulp at 75 µm (90% passing a 75 micron sieve).

At Acme Analytical Laboratories (Vancouver) Ltd, 30 g pulps were digested in 1:1:1 Aqua Regia and analysed for 37 elements by ICPMS (Acme 1F03, now 1F04-AQ252 geochemical package). The lower detection limit for Cu and Pb was 0.01 ppm; Zn was 0.1 ppm and silver was 2 ppb.

2015 Drilling Campaign

ALS Minerals Laboratory carried out sample preparation and the procedures as follows:-

- Received sample weight;
- Pulp login - RCD w/o barcode;
- Sample login -RCD w/o barcode;
- Fine crushing - 70% < 2 mm;
- Splitting samples - riffle splitter;
- Pulverise split to 85 % <75 µm;
- Crushing QC test; and
- Pulverising QC test.

Item 11 (c) - QUALITY ASSURANCE AND QUALITY CONTROL

No data was available pertaining to historical QAQC protocols. Due to unavailability of 2012/2013 QAQC data, the QAQC section for 2012 and 2013 was extracted from P&E (2014). These QAQC results are attached as Appendix 2. Minxcon has presented, after review the QAQC, graphs and opinions for the 2015 drilling programme as follows:-

2015 Drilling Programme

A total of 1,085 samples including certified reference material, blanks and duplicates were collected and dispatched to ALS Mineral Laboratory in Swakopmund, Namibia. ALS Mineral Laboratory is located at No: 6 & 7 Einstein Street, Swakopmund, Namibia. The laboratory is not SANAS accredited. The analytical procedure utilised at the laboratory is ME-ICP61 4 Acid ICP-AES; OG62 Four Acid for Overlimit Cu, Pb, Ag.


The QAQC material were inserted as follows; eight regular samples (10001 to 10008), followed by a low-grade standard (10009), followed by eight regular samples (10010 to 10017), followed by a core duplicate (10018 is the second half of sample 10017 which has been quartered), followed by eight regular samples (10019 to 10026), followed by our high-grade standard (10027), followed by eight regular samples (10028 to 10035), followed by a preparation duplicate (10036, where the preparation facility is requested to make a second pulp from 10035 - an empty numbered bag containing a note to this effect was used for pulp duplicates), followed by eight regular samples (10037 to 10044), followed by a blank (10045). The rotation started again with eight regular samples.

A total of 119 out of 1,085 samples consisted of QAQC samples, equating to approximately 11 % of the total sample stream. Minxcon is of the opinion that this represents an adequate number of QAQC samples (certified reference materials or “CRMs”, blanks, core duplicates and pulp duplicate) used during sampling programme.


Unknown Blank.

A total of 25 blank samples were dispatched to ALS Mineral Laboratory as part of the QAQC programme. Minxcon is not aware of the source of this blank material, or whether it was certified or not. The results indicate that there was no contamination for silver analysis (Figure 36). All samples plotted below the upper limit for silver (the upper limit was defined by three times the detection limit which is 0.5 ppm).

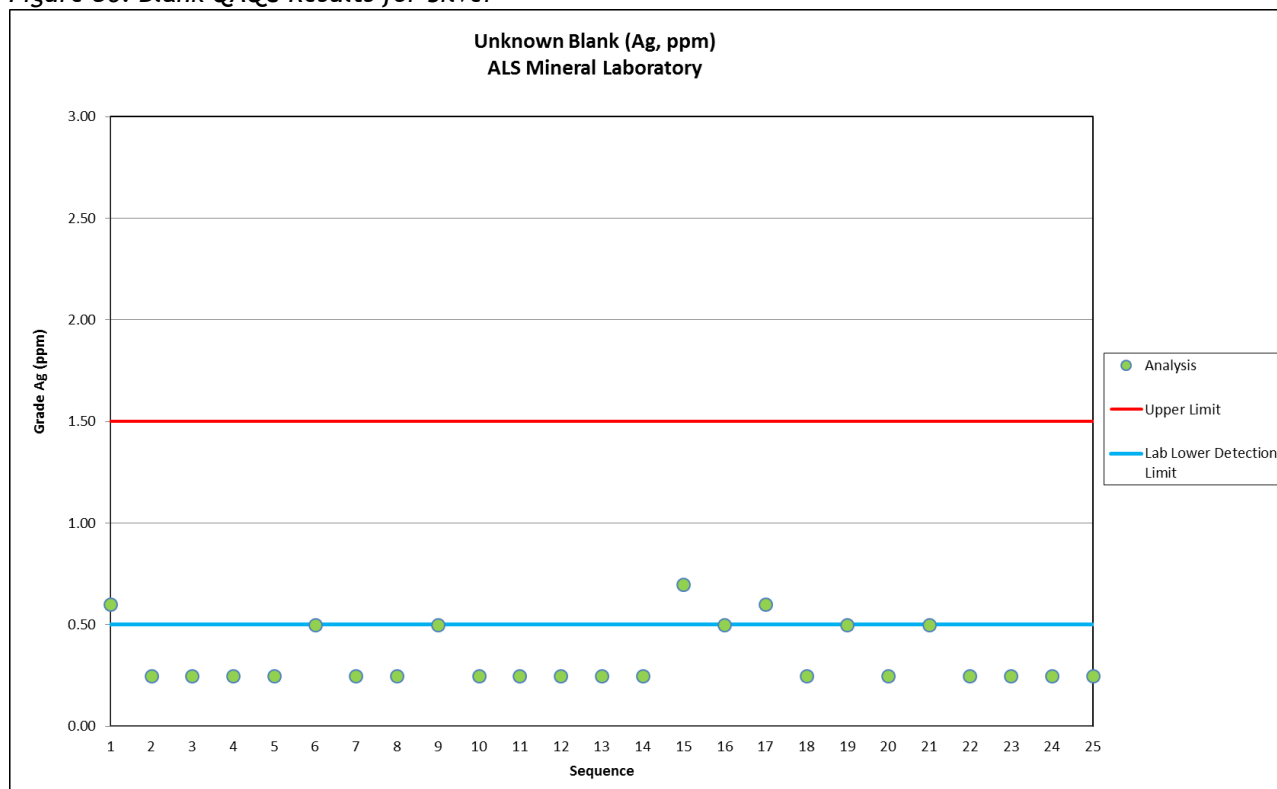
Figure 36: Blank QAQC Results for Silver



One sample (2,479) failed the blank QAQC for lead (Figure 37). The cause may be due to contamination at the laboratory. Note that the upper limit was defined by three times the detection limit of 0.001%.

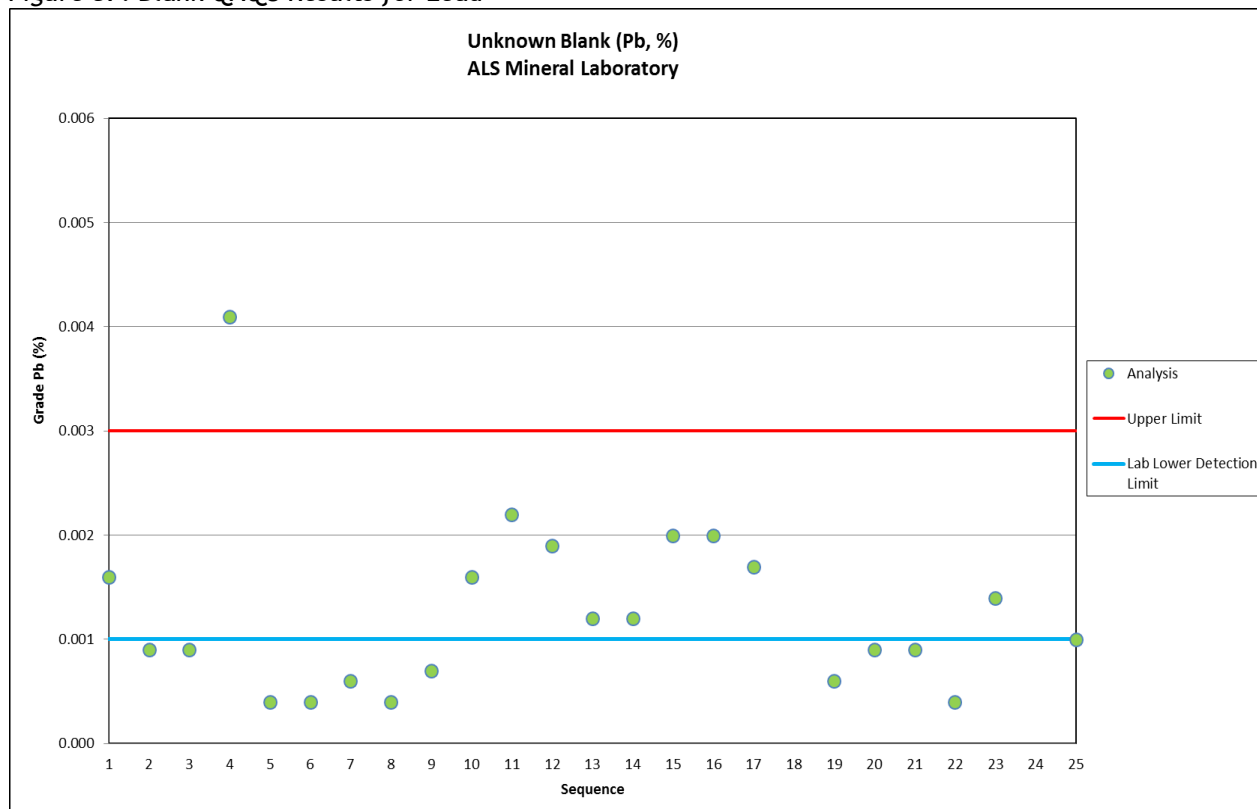Figure 37: Blank QAQC Results for Lead

Two samples (2990 and 3336) also failed the blank QAQC for copper (Figure 38), also attributed to possible contamination at the laboratory. The batch which contained the failed samples should have been re-assayed. It is not known whether this was done, as no formal QAQC reports for the drilling programme were available for Minxcon's scrutiny. Note that that the upper limit was defined by three times the detection limit of 0.001 %.

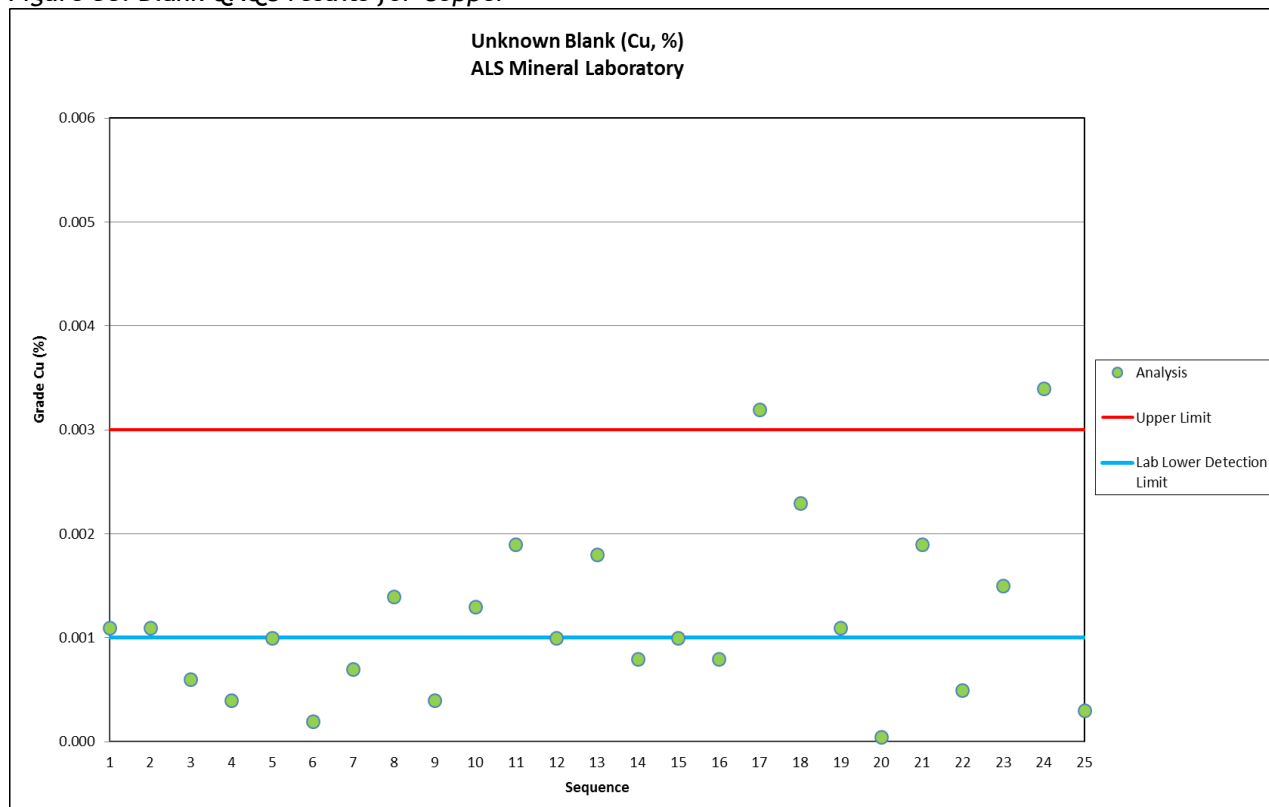Figure 38: Blank QAQC results for Copper

Certified Reference Materials

CRMs used during the 2015 drilling campaign were purchased from African Mineral Standards (“AMIS”). One high grade CRM (AMIS0424) and one low grade (AMIS0309) CRM were utilised. The source areas of these CRMs are as follows:-

- AMIS0309, Gold and Copper ore, greenstone, Buzwagi Mine (SAG Mill discharge), Tanzania.
- AMIS0424, Copper ore, carbonatite, Palabora Mine, South Africa

AMIS0309 CRM

A total of 23 AMIS0309 CRMs were used during sampling. It must be noted that AMIS0309 is certified for copper and silver and not for lead. A conversion factor of 10,000 was used to convert Cu ppm to Cu %. Table 10 below presents the certified concentration of AMI0359.

Table 10: Details of AMIS0309

ID	Cu F	Cu M/ICP	Au Pb Collection	Specific Gravity	Ag M/ICP
	ppm	ppm	g/t		ppm
AMIS0309	1,361 ± 92	1406 ± 68	0.96 ± 0.06	2.80 ± 0.08	2.1 ± 0.4

Although two standard deviations is recommended by the manufacturer, Minxcon recommends that those samples falling outside two standard deviations but within three standard deviations should be passed. Three samples (2668, 3255 and 3300) failed the QAQC graph for copper (Figure 39). Minxcon is of the opinion that the batches containing those samples which failed the QAQC should have been re-assayed. It is not known whether this was done or not.

Figure 39: AMIS0309 QAQC Graph for Copper


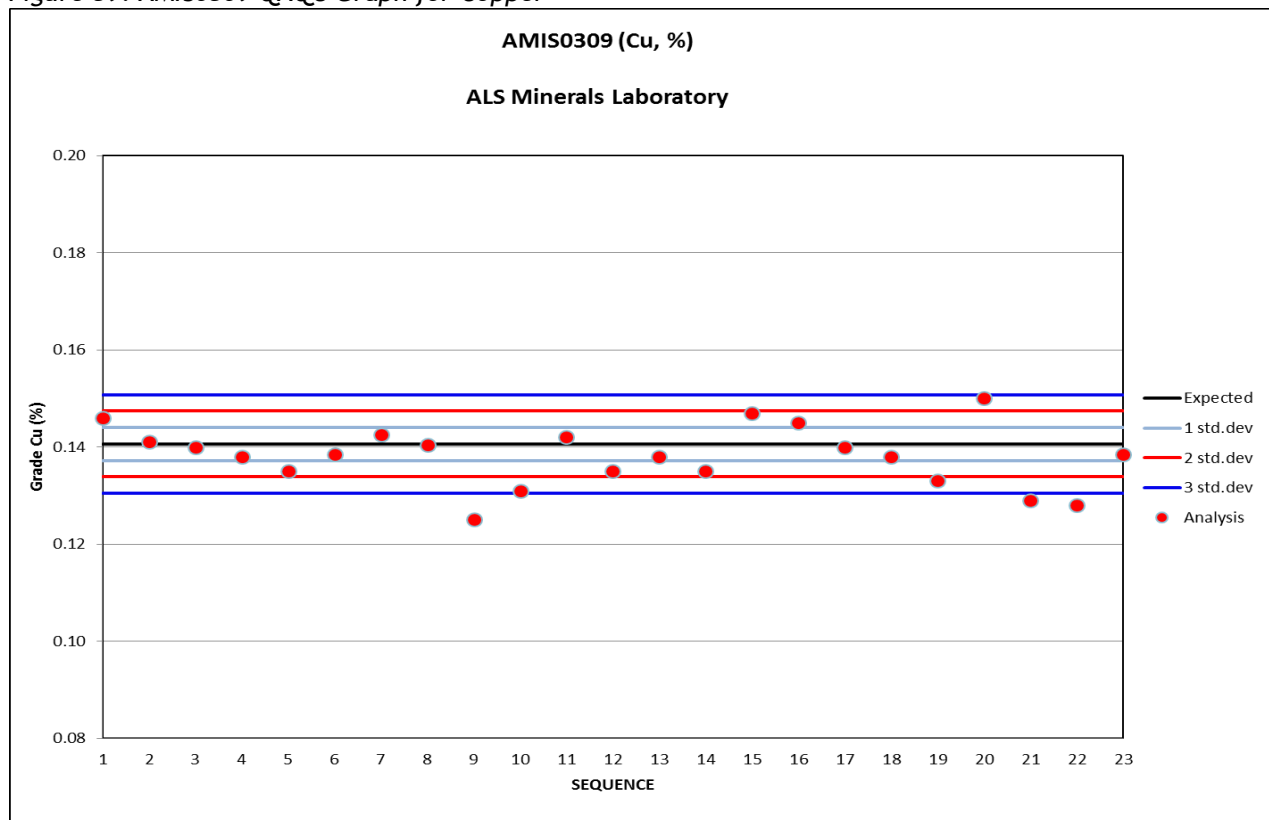


Figure 40 presents the QAQC graph for silver. Although Minxcon accepts the QAQC for silver, one sample (2999) plotted outside two standard deviations (recommended by the manufacturer) but within three standard deviations.

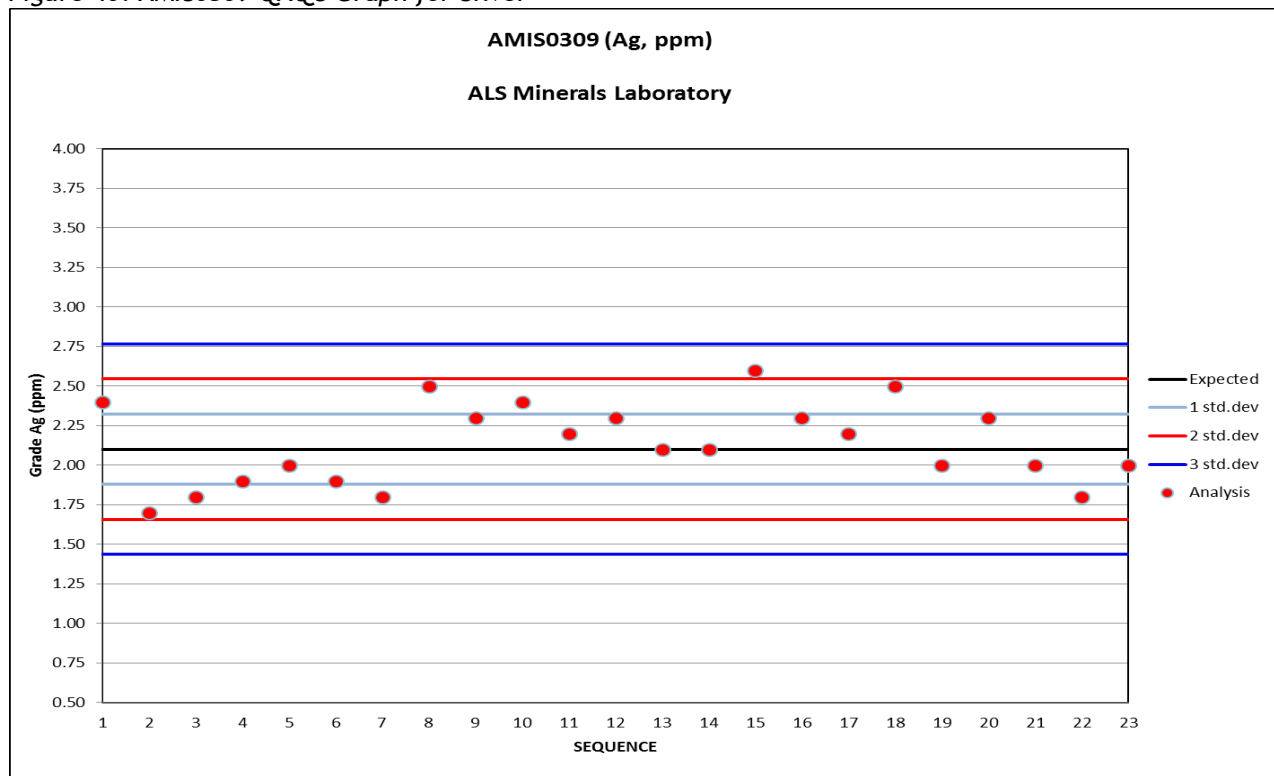Figure 40: AMIS0309 QAQC Graph for Silver



AMIS0424


A total of 24 AMIS0424 CRMs were inserted in the sampling sequence and dispatched to the laboratory and were analysed for copper. Table 11 below presents certified concentration of AMIS0424. It must be noted that AMIS0424 is only certified for Cu and not lead and silver.

Table 11: Details of AMIS0424 CRM.

ID	Cu Fus	Cu M/ICP	Cu P	Specific Gravity	Au Pb Collection	Co M/ICP	Co P
	%	%	%		g/t	ppm	ppm
AMIS0424	1.145 ± 0.053	1.145 ± 0.058	1.135 ± 0.044	3.07 ± 0.08	0.1 ± 0.012	78 ± 16	75 ± 9

Two samples (2641 and 2686) plotted outside three standard deviations. Minxcon is of the opinion that the batches containing those samples which failed the QAQC should have been re-assayed. It is not known whether this was done. Figure 41 below depicts the QAQC graph for copper analysis.

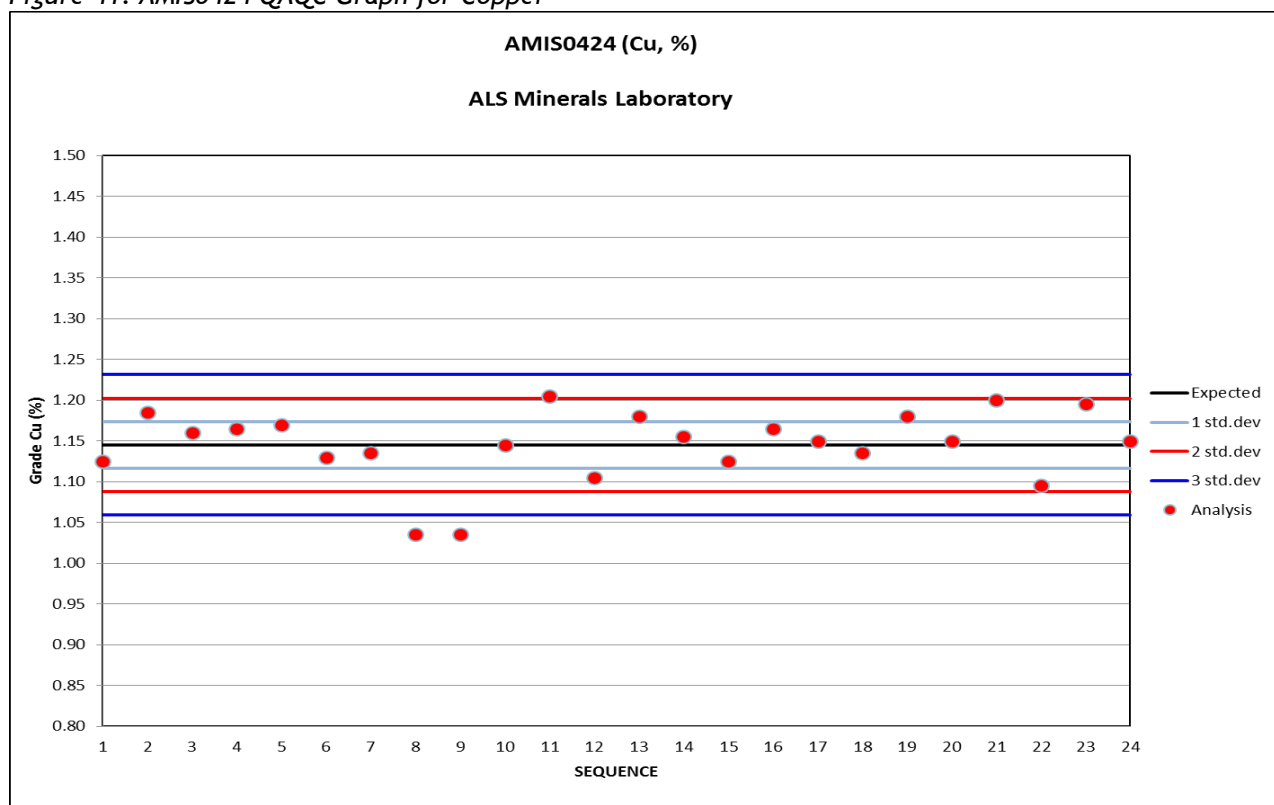Figure 41: AMIS0424 QAQC Graph for Copper



Core Duplicates

A total of 24 core duplicates were selected during sampling and dispatched to the laboratory for copper, lead and silver analysis. Correlation plots for copper, lead and silver were generated to check the repeatability. It was noted that lead had a good correlation or repeatability with a correlation coefficient (R^2) of 0.9855, whereas copper and silver had reasonable correlation coefficients (R^2) of 0.8031 and 0.8505 respectively.

Figure 42 presents the core duplicates graph for copper analysis.

Figure 42: Core Duplicates QAQC Graph for Copper Analysis

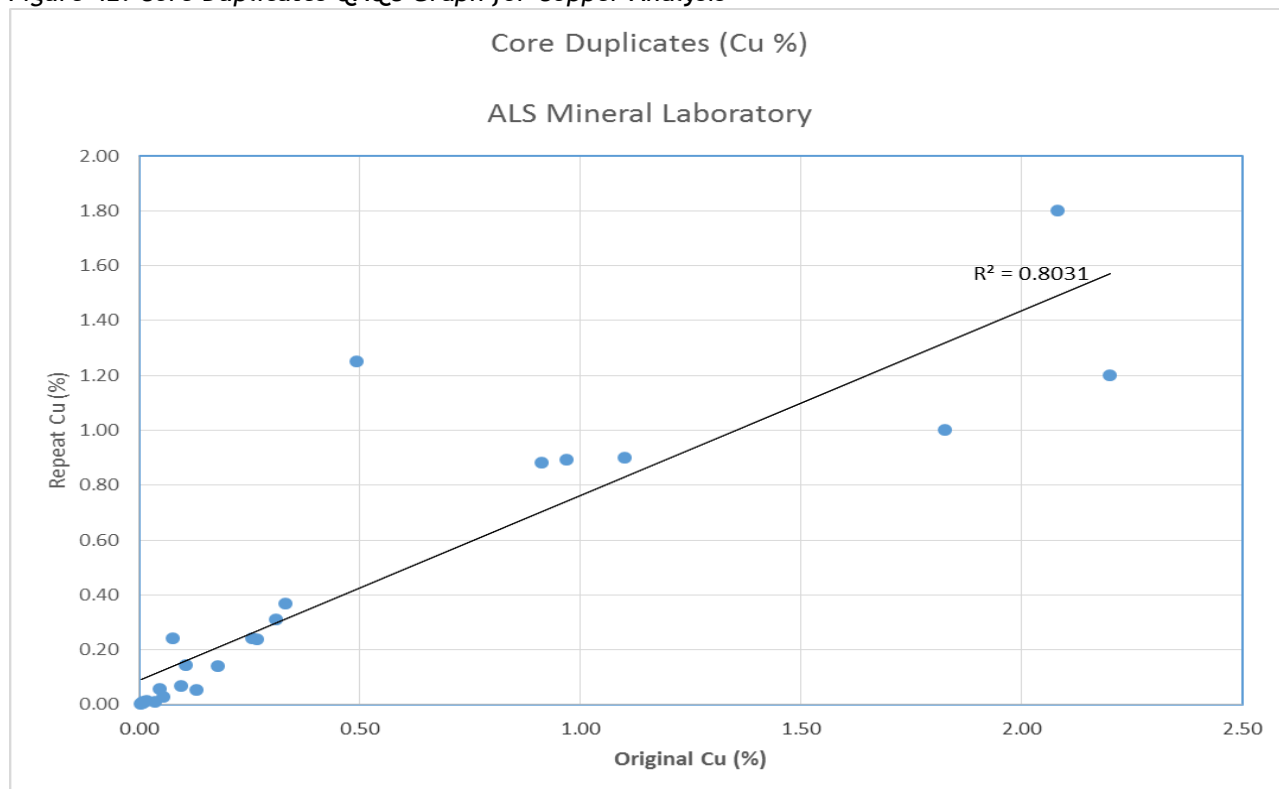


Figure 43 below presents the core duplicates QAQC graph for lead analysis.

Figure 43: Core Duplicates QAQC Graph for Lead analysis.

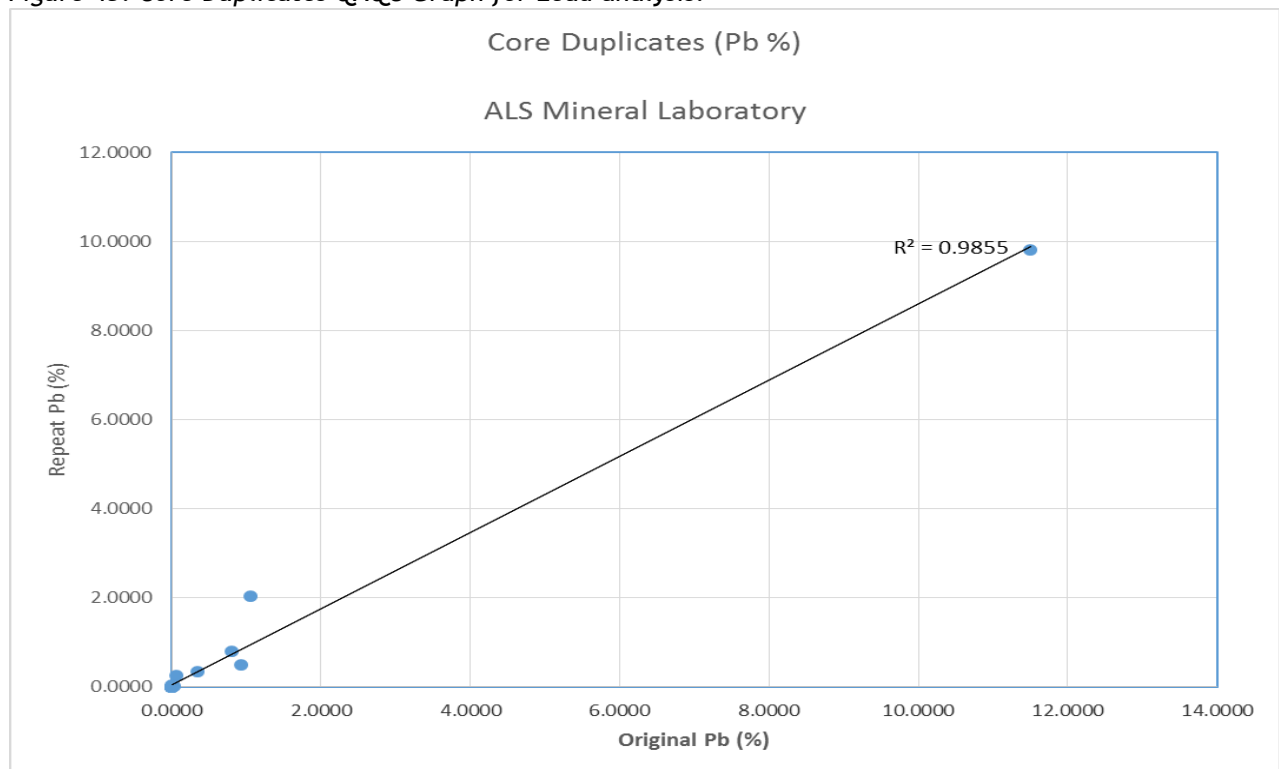
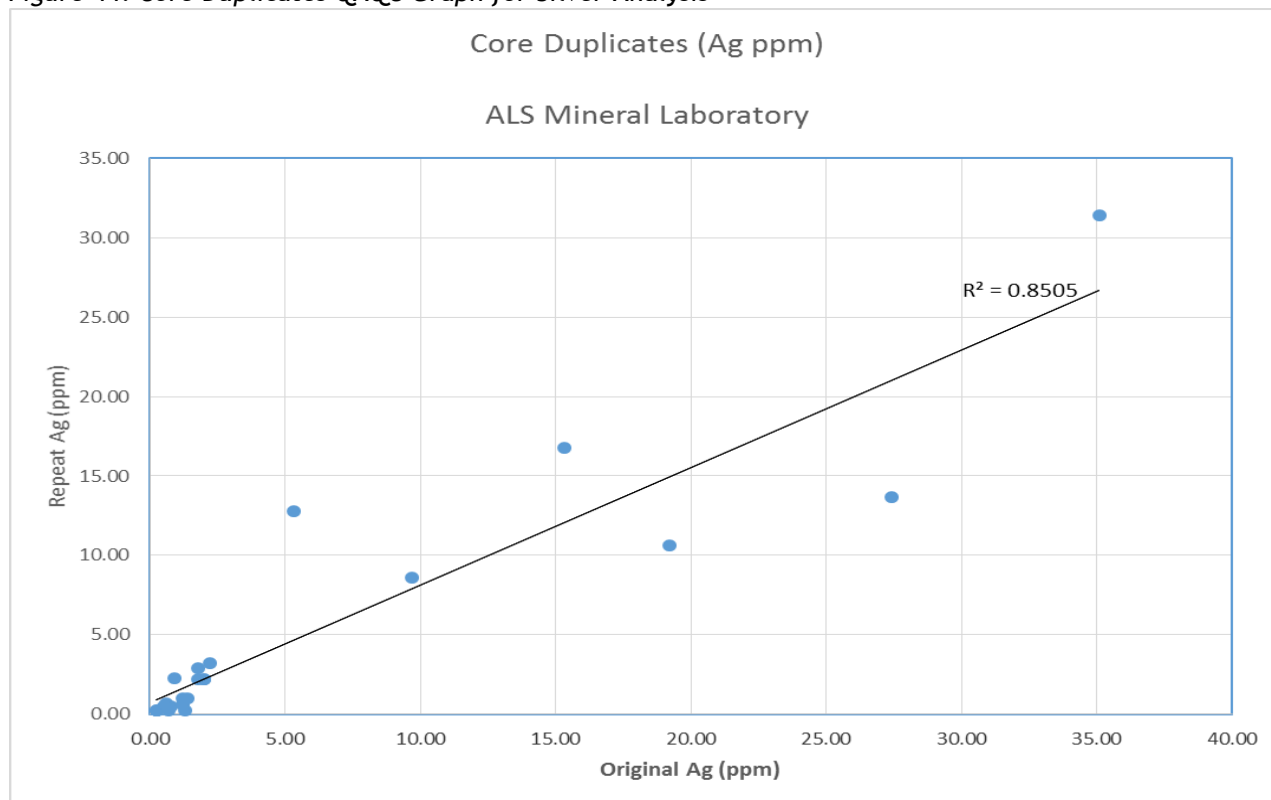


Figure 44 presents the core duplicates QAQC graph for silver analysis.

Figure 44: Core Duplicates QAQC Graph for Silver Analysis

Pulp Duplicates

A total of 23 pulp duplicates were selected and analysed for copper, lead and silver at ALS Mineral Laboratory at the time of sampling during 2015. Correlation plots for copper, lead and silver were generated to check the repeatability. It was noted that silver had a good correlation or repeatability with a correlation coefficient (R^2) of 0.9874 whereas copper and lead had reasonable correlation coefficients (R^2) of 0.8929 and 0.8927 respectively.

Figure 45 presents the pulp duplicates QAQC graph for copper analysis.

Figure 45: Pulp Duplicates QAQC Graph for Copper Analysis

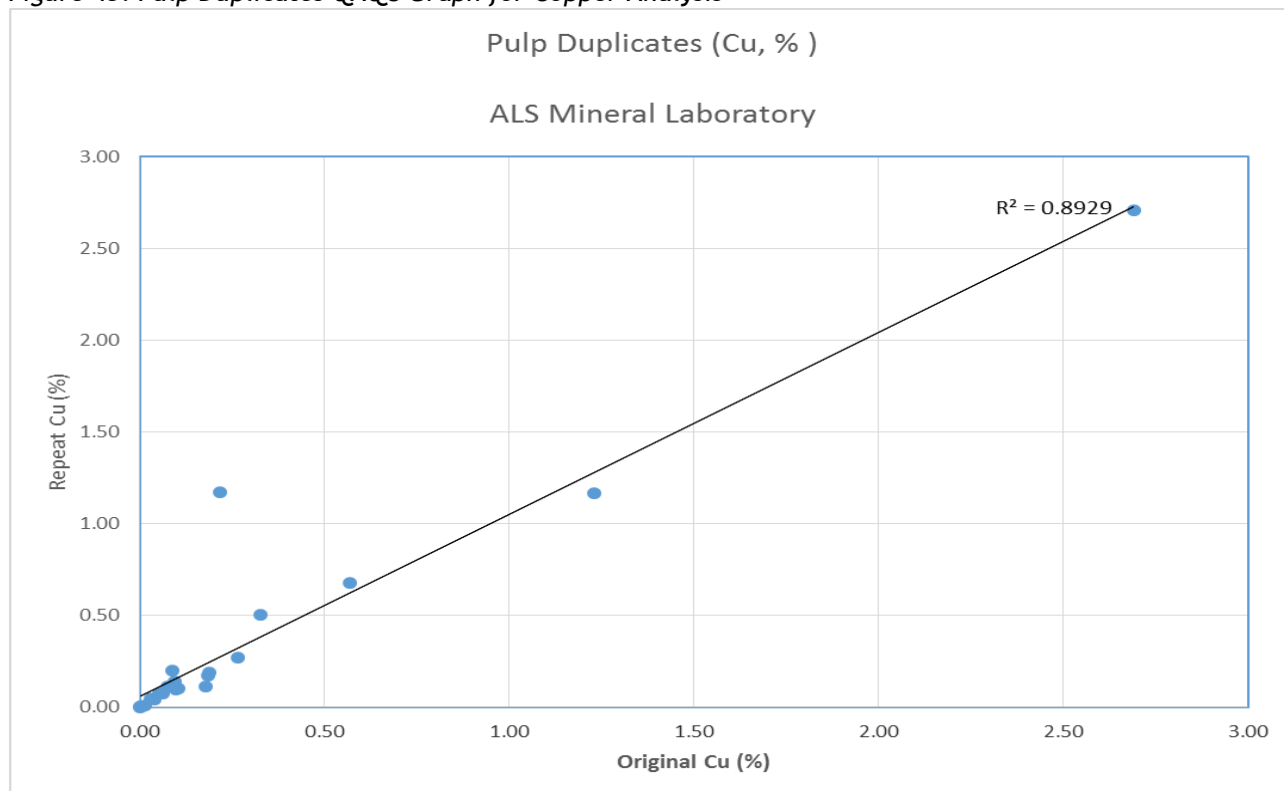


Figure 46 below presents the pulp duplicates QAQC graph for lead analysis.

Figure 46: Pulp Duplicates QAQC Graph for Lead Analysis

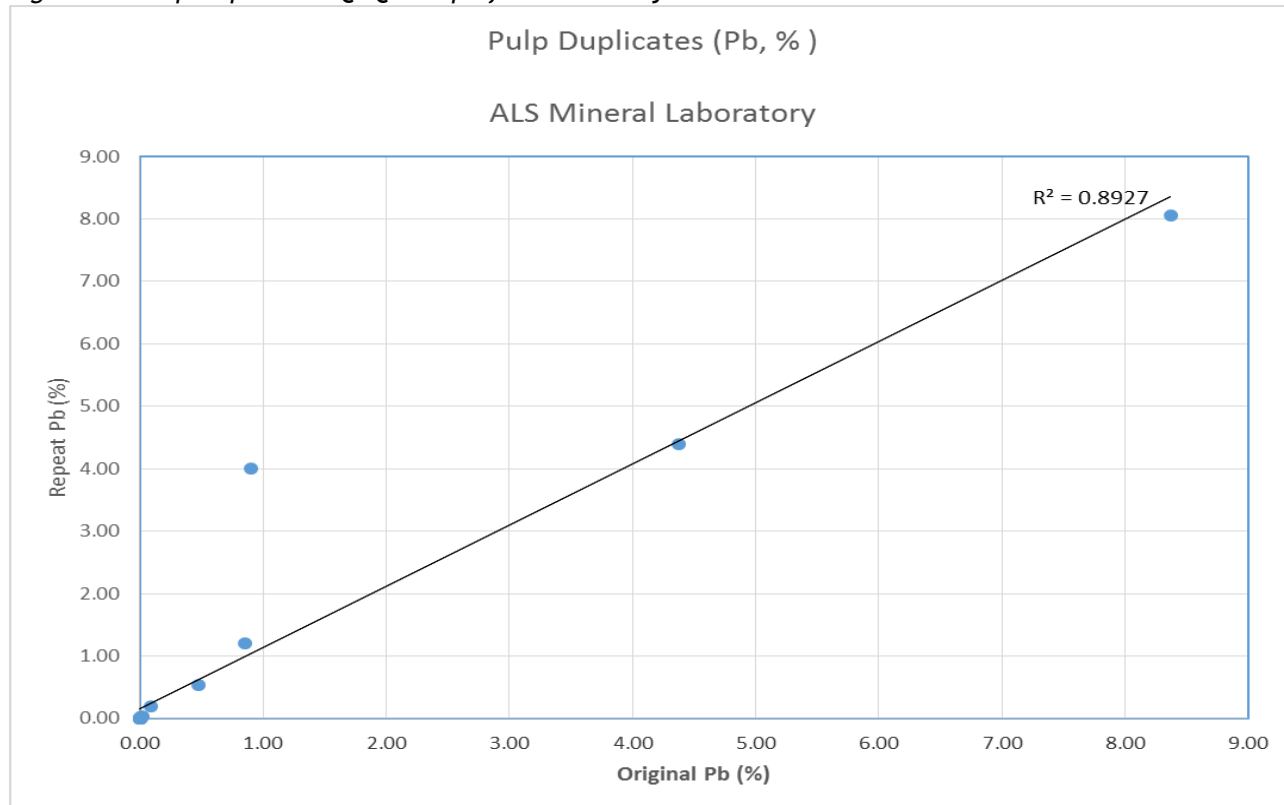
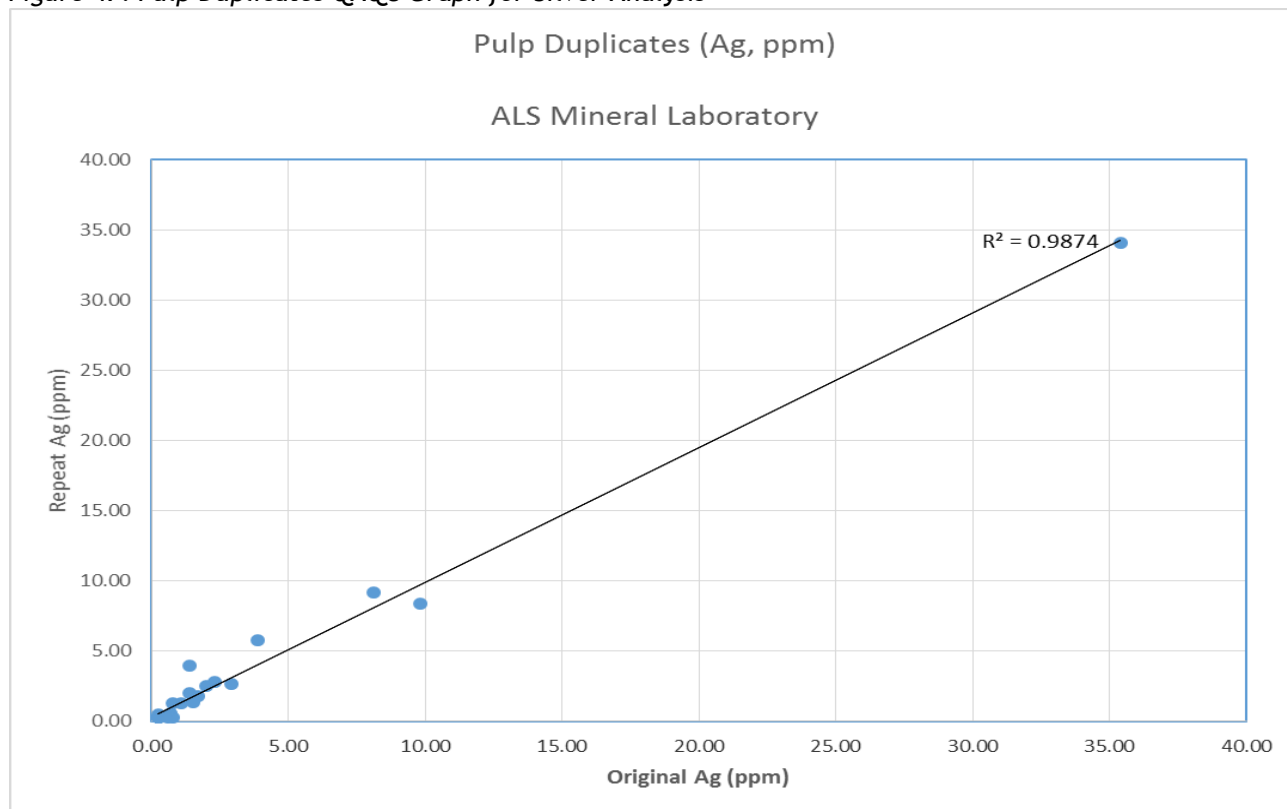


Figure 47 presents the pulp duplicates QAQC graph for silver analysis.

Figure 47: Pulp Duplicates QAQC Graph for Silver Analysis**Item 11 (d) - ADEQUACY OF SAMPLE PREPARATION**

Although there was evidence of sample contamination (blank 2990, 3336 and 2779) at the ALS Mineral Laboratory, due to the small number of sample failures Minxcon accepts the sample preparation conducted at ALS Mineral Laboratory during 2015.

ITEM 12 - DATA VERIFICATION

Item 12 (a) - DATA VERIFICATION PROCEDURES

For the purposes of the 2017 Mineral Resource estimate, Minxcon reviewed and verified the following data types relative to historical files and records (digital and manual):-


- Drillhole collars, surveys and assays;
- Orebody wireframes;
- Mining voids;
- Historical depletion of the orebodies mining; and
- Review of the manual block listings.

Drillhole Collars and Assay Discussion

Minxcon reviewed the captured drillhole collar and assay data. Minxcon conducted random checks of collar locations by means of comparing the captured drillhole collars to collars which were recorded on scanned copies of original hardcopy drillhole logs.

Minxcon also checked the assay files for all the holes for gaps and overlaps: when encountered, these were resolved. Some drillholes within the digital database were found to render composted stretch values (r Figure 48), without the individual original sample intervals and assays. The drillholes were discarded for the purposes of Mineral Resource estimation, but were utilised for geological modelling.

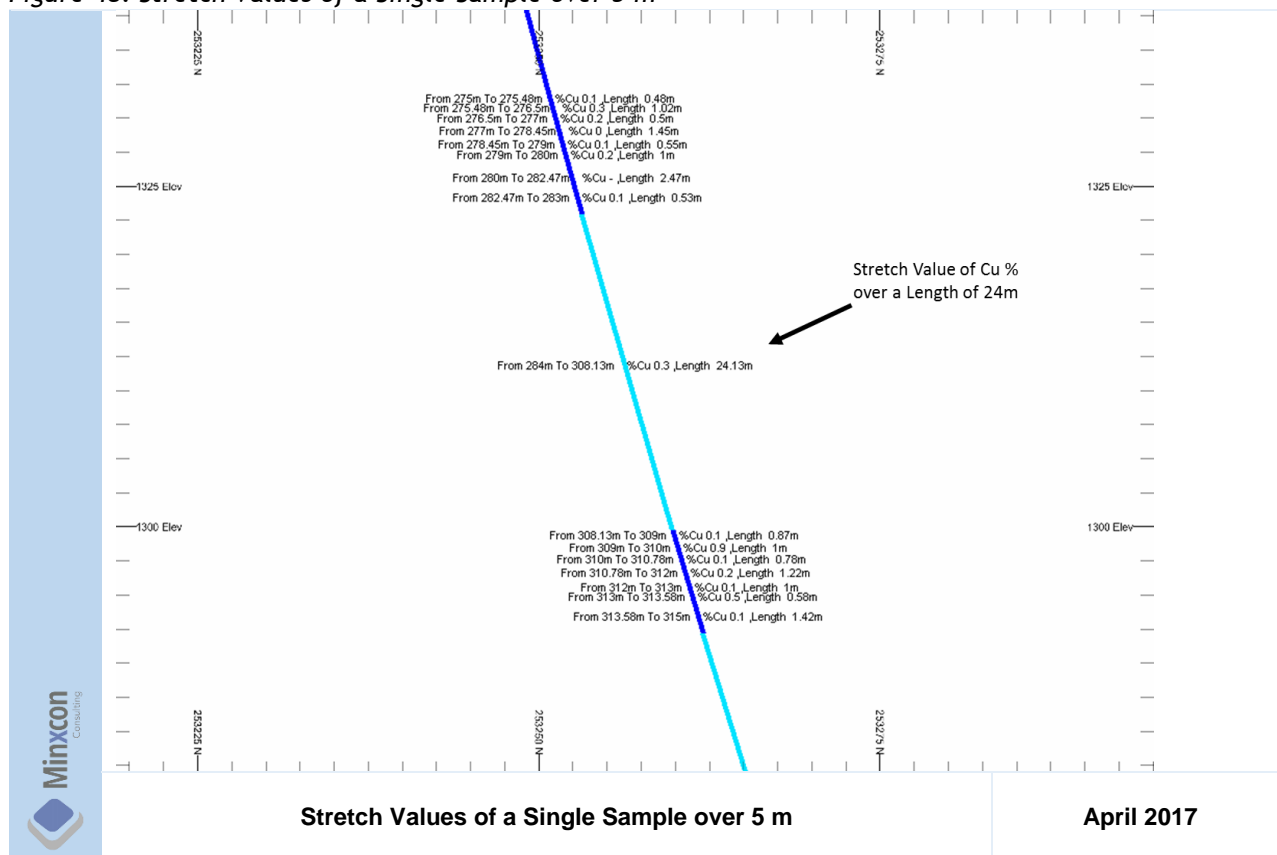
Figure 48: Stretch Values of a Single Sample over 5 m



Orebody Wireframes

No digital orebody models were available for the Kombat section. The historical wireframes generated for Asis West and Asis Far West were available and these were reviewed for spatiality and appropriateness. This was done using the desurveyed drillhole database in conjunction with the wireframes. The interpreted geometry of the wireframes was compared to mined orebodies elsewhere on the properties. These wireframes were found to mostly have the incorrect orientation relative to historical mapping and mining and represented Mineral Resource wireframes and not grade shells with internal mineralisation and therefore were discarded. Minxcon generated new grade shell wireframes for this area in line with the rest of the areas. The historical Mineral Resource wireframes for Asis West and Asis Far West are presented below in Figure 49.

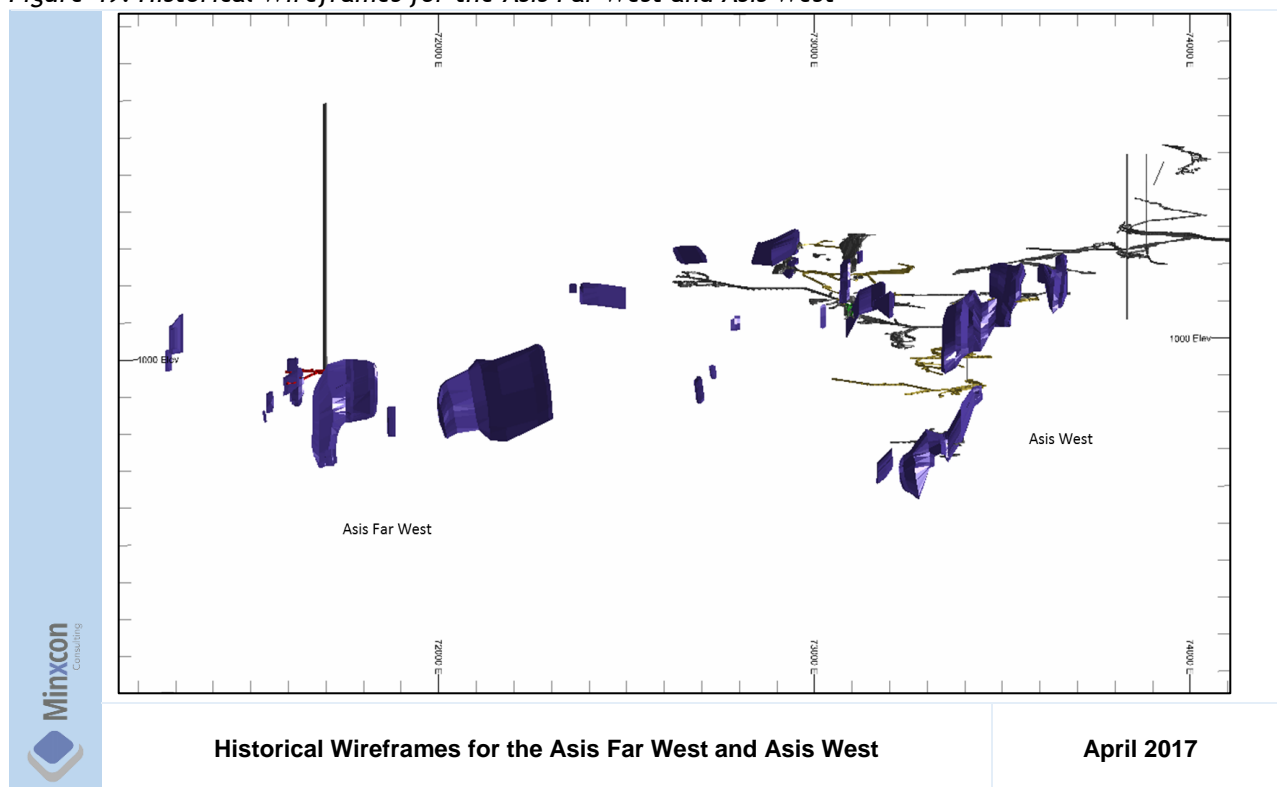
Figure 49: Historical Wireframes for the Asis Far West and Asis West



Mining Voids and Depletions

Long sections of all the mining areas were compared to the provided 3D digital files. The 3D development wireframes were found to be adequate for the purposes of conducting accurate Mineral Resource depletion. However, the stope voids were found to be highly incomplete. Owing to this, Minxcon digitising longitudinal sections of all the stoping and extended these in and out of the mineralised orebody plane in order to maximise the depletion by the stoping voids. This accounts for one of the reasons why only Inferred Mineral Resources are reported for the underground areas. The position of the surface open-pits were verified relative to a surveyed topography and were used for the depletion of the open pit Mineral Resources.

A view of the final digitised historical voids for Kombat and Asis sections is presented in Figure 50.

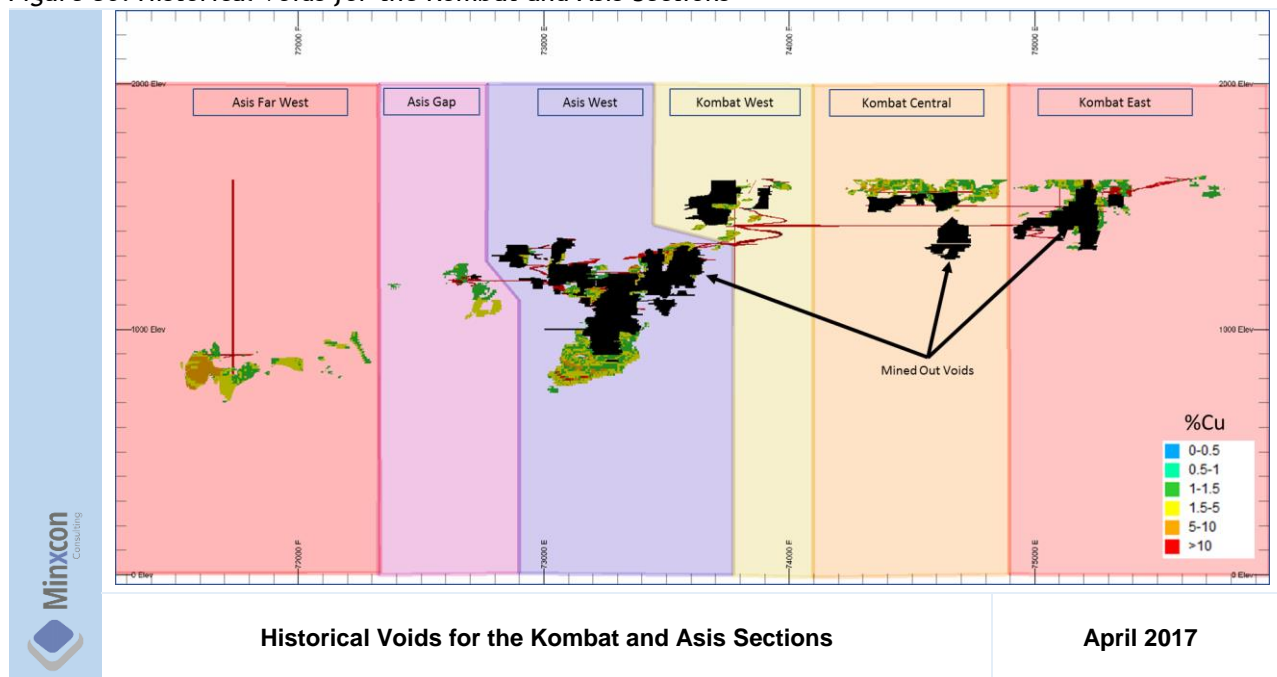Figure 50: Historical Voids for the Kombat and Asis Sections

Manual Block Listing

A large number of the older underground workings were surrounded by pillars or unmined sections of orebodies. These had historically been captured in the form of an MS Excel™ spreadsheet for the historical non-compliant Mineral Resources for the old mining areas. Minxcon attempted to endorse the block-listing by following the documentation audit trail, in order to make the estimate compliant in terms of NI 43-101. However, Minxcon was not able to locate any scans of hand drawn (or even hard-copy) plans which supported the blocklisting. In addition, block listing plans which were found could not be correlated to the block listing and drillhole intersection plotted on these plans were not annotated, nor the assays recorded making up the mineralised intersections.

Owing to not being able to follow the audit trail back to the source plans and data, Minxcon discarded the historical block listing Mineral Resource estimate in favour of conducting an auditable digital Mineral Resource estimate from verified drillholes.

Item 12 (b) - LIMITATIONS ON/FAILURE TO CONDUCT DATA VERIFICATION

Minxcon was not able to review the sampling, drilling, core sampling or QAQC practices utilised on the mine by the sampling and geology crews as the operations are currently not operational with no dedicated geology or sampling teams employed. Mapping standards and onsite geological interpretation could also not be verified for the same reason.

Historical drillhole data pre-dating 2012 did not have assay QAQC records as is to be expected with regards historical operations, thus assay values could not be verified relative to assay records. However, during 2014, P&E conducted a historical core re-sampling program on selected intersections. Minxcon reviewed this data and found (in agreement with P&E) that the historical assays were reasonably reproduceable.

Minxcon utilised the findings of historical Mineral Resource estimations in order to achieve a well-rounded view of the quality of historical data collection methods. The assumption used was that due to the historic

operation was pre code reporting that the geological drilling was of adequate quality and due care was used with regards the historic sampling and geological logging.

Item 12 (c) - ADEQUACY OF DATA

A total of 2,183 drillholes covering the Kombat project area including the Otavi project area were reviewed with regards the spatiality and checking of assay anomalies. From this drillhole database, only 470 drillholes were utilised in the Mineral Resource estimate due to the criteria outlined in the paragraphs above. Holes were discarded based on the findings of the data reviews as described above and due to not intersecting mineralisation. Discarded holes were however utilised in the geological modelling in order to validate and generate lithological and boundaries.

It is Minxcon's view that the volume, quality and density of all the reviewed data (including drilling depletion voids, assay QAQC and geology mapping and interpretation) used in the Mineral Resource are adequate for the purposes of conducting Mineral Resource estimation and for the declaration of an Inferred Mineral Resource.

ITEM 13 - MINERAL PROCESSING AND METALLURGICAL TESTING

This Report is intended as a Mineral Resource Report. As such, mineral processing and metallurgical testing were not investigated.

ITEM 14 - MINERAL RESOURCE ESTIMATES

Item 14 (a) - ASSUMPTIONS, PARAMETERS AND METHODS USED FOR RESOURCE ESTIMATES

The stated Mineral Resource presented herein represents the copper, lead and silver estimation of the Kombat and Asis West to Far West mining properties as well as the Gross Otavi orebody.

The historic tailings were also evaluated, but are not discussed in detail in this Report as they do not meet the requirements of possible eventual economic extraction in terms of the NI 43-101 definition of a Mineral Resource, under the current cut-off grades. Minxcon has only included the tailings evaluation in Item 24 a)-Upside Potential, as the tailings may later prove to be payable in terms of metallurgical processes and economics.

The Mineral Resource estimate considered the total dataset of 2,183 drillholes (comprising percussion, RC and diamond drillholes) for the construction of the geological model. The estimation, however, only considered diamond and RC drillholes (470 drillholes) that were eventually used in the generation of the grade shells and the Mineral Resource estimate.

This section describes the Mineral Resource estimation process utilised by Minxcon and summarises the key assumptions considered in the estimation. The Mineral Resource has been estimated in conformity to the accepted CIM “Estimation of Mineral Resources and Mineral Reserves Best Practices” guidelines and are reported in accordance with the Canadian Securities Administrators’ NI 43-101. Mineral Resources are not Mineral Reserves and do not have demonstrated economic viability. There is no certainty that all or any part of the Mineral Resources will be converted into Mineral Reserves.

It is Minxcon’s opinion that the database used in the estimate is of suitable reliability to interpret the geological boundaries and of suitable assay quality to estimate the Mineral Resources for the Project. Only Inferred Mineral Resources have been declared by Minxcon in 2017 due to the lack of historical assay QAQC, uncertainty with respect to the underground depletion voids and underground control sampling, as well as general data spacing.

Leapfrog Geo™ 3.1.1 software was used to construct the geological wireframes/grade shells, while Datamine™ was used to conduct statistical and geostatistical analyses, conduct variography and generate the estimated grade block model.

Mineral Resource Estimation Procedures

The Mineral Resource Estimation methodology involved the following procedures:-

- Database compilation and verification;
- Geological modelling (discussed in Item 8 b));
- Statistical analysis;
- Domaining;
- Data conditioning (compositing and capping);
- Geostatistical analysis and variography;
- Bulk density determination;
- Block modelling and grade interpolation;
- Mineral Resource classification and validation;
- Assessment of “reasonable prospects for economic extraction” and selection of appropriate cut-off grades; and
- Preparation of the Mineral Resource Statement.

Database Compilation

The drillhole database utilised by Minxcon consisted of a total of 2,183 drillholes, including percussion, RC and diamond drillholes. The percussion holes were discarded from the Mineral Resources database due to concerns pertaining to sample cross-contamination. Only holes intersecting the mineralised grade shells generated from the geological modelling process were used in the estimation, resulting in a net 470 drillhole Mineral Resource estimation dataset. A large number of these drillholes did not have silver values, thus a regression slope of the relationship of silver to copper had to be utilised to evaluate blocks in the block model which were not informed by the drillholes with silver assays. Approximately only 18.1% of all valid samples had valid silver values useable in the Mineral Resource estimation.

Geological Modelling

The construction of the Kombat geological models is comprehensively discussed in Item 8 b) of this Report.

Statistical Analysis

Statistical analysis of the drillholes falling within the mineralised halos was conducted on the metal content of Cu, Pb, Zn, Ag and relative density and length of samples in these drillholes. A total of 13,367 samples over the three sections were available. The mean of the sample lengths show an average sample length of 1 m which was then used as the composite length. Owing to the fact that no clear domains could be defined with regards grade or lithology, the project areas were separated into three domains. The Kombat section and Asis section were split from each other on the Kombat West Fault, while Otavi was domained separately due to being geographically separated from Kombat and Asis sections. The domaining is discussed in detail in the next paragraph.

Table 12 below presents the statistics for the Kombat operations drillhole data.

Table 12: Kombat Drillhole Statistics

Section	FIELD	No Samples	Minimum	Maximum	Range	Mean	Variance	STDev	Geo Mean	Log Est Mean
Kombat Section	LENGTH	8,340	0.02	1.48	1.46	1.00	0.00	0.03	1.00	1.00
	Cu	8,340	0.01	33.02	33.01	1.05	4.37	2.09	0.36	1.38
	Pb	8,340	0.01	42.35	42.34	1.30	8.09	2.84	0.21	2.81
	Zn	8,340	0.01	14.09	14.09	0.21	0.35	0.59	0.04	0.28
	Ag_ppm	8,340	0.01	147.89	147.88	0.85	12.52	3.54	0.52	0.66
	RD	8,340	2.78	4.21	1.43	2.83	0.01	0.08	2.83	2.83

Table 13 presents the statistics for the Asis West, Asis Gap and Asis Far West operations drillhole data.

Table 13: Asis Drillhole Statistics

Section	FIELD	No Samples	Minimum	Maximum	Range	Mean	Variance	STDev	Geo Mean	Log Est Mean
Asis Section	LENGTH	3,948	0.01	1.11	1.11	1.00	0.00	0.02	1.00	1.00
	Cu	3,948	0.01	58.00	58.00	1.81	19.54	4.42	0.38	2.52
	Pb	3,948	0.01	65.45	65.45	1.12	12.54	3.54	0.22	1.33
	Zn	3,948	0.01	9.23	9.23	0.06	0.13	0.36	0.01	0.03
	Ag_ppm	3,948	0.01	580.00	579.99	4.69	398.08	19.95	1.11	2.70
	RD	3,948	2.78	5.45	2.67	2.84	0.03	0.16	2.84	2.84

Table 14 presents the statistics for the Gross Otavi operations drillhole data.

Table 14: Otavi Drillhole Statistics

Section	FIELD	No Samples	Minimum	Maximum	Range	Mean	Variance	STDev	Geo Mean	Log Est Mean
Otavi Section	LENGTH	1,079	0.18	1.08	0.90	1.00	0.00	0.04	1.00	1.00
	Cu	1,079	0.01	25.00	25.00	0.92	3.90	1.98	0.34	0.94
	Pb	1,079	0.01	51.00	51.00	2.89	31.34	5.60	0.70	4.54
	Zn	1,079	0.00	12.20	12.20	0.30	0.47	0.68	0.11	0.36
	Ag_ppm	1,079	0.01	124.00	124.00	1.83	52.69	7.26	0.55	1.44
	RD	1,079	2.78	4.77	1.99	2.86	0.03	0.17	2.86	2.86

The Figure 51, Figure 52 and Figure 53 show the histograms of the copper content from the un-composited drillhole data. The figures depict the normal and log normal distribution of the Cu values. Multiple populations are seen and this is possibly due to the use of multiple laboratories (evident from the multiple recorded detection limits) over the production history of Kombat mine as the different population are not correlated to discreet zones and cannot be domained separately.

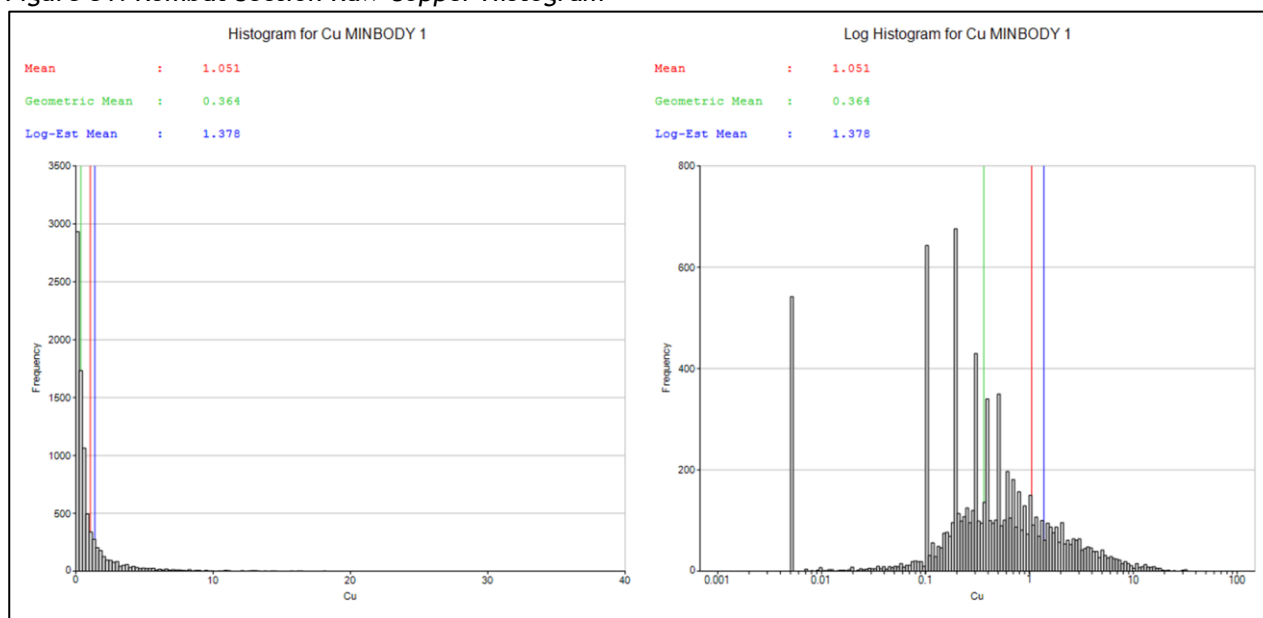
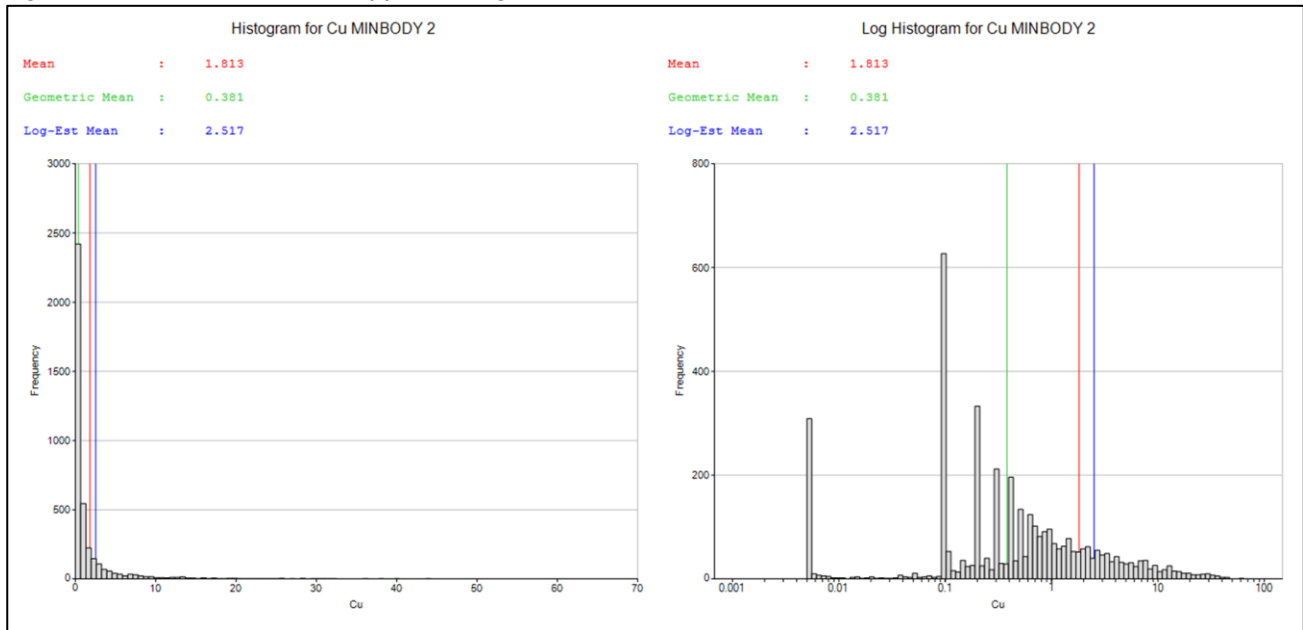
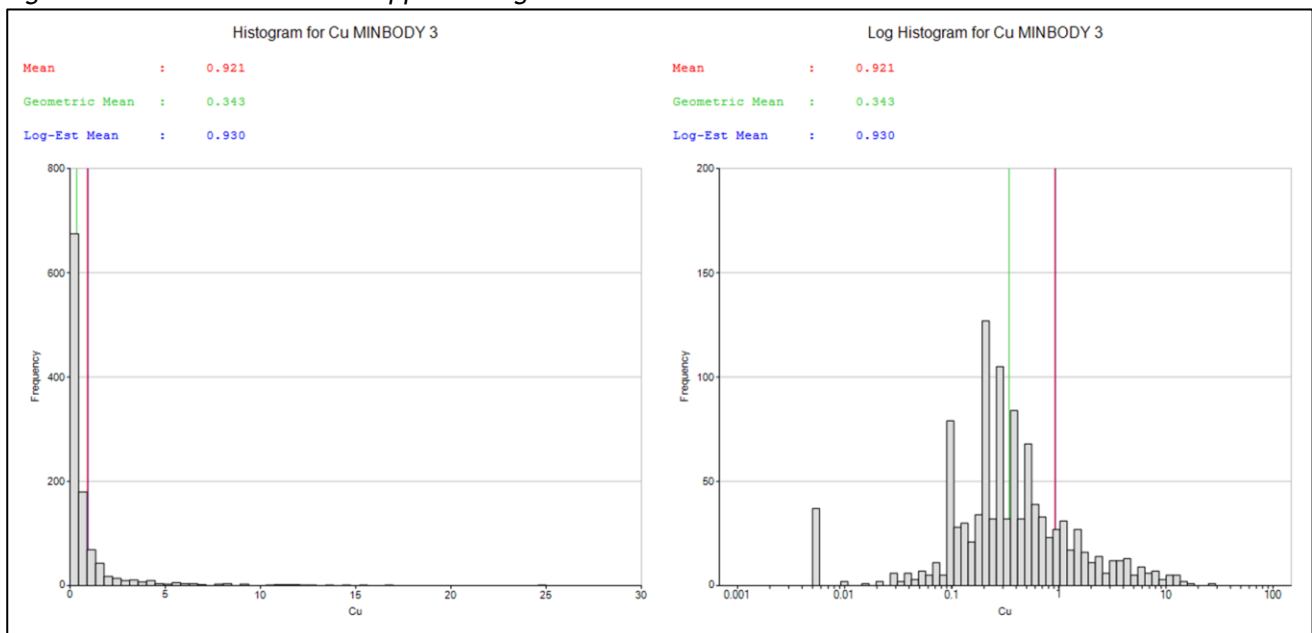
Figure 51: Kombat Section Raw Copper Histogram

Figure 52: Asis Section Raw Copper Histogram**Figure 53: Otavi Section Raw Copper Histogram**


Domining

Domain boundaries were defined based on two basic factors, namely geology and grade. A domain boundary, which segregates the data during interpolation, is typically applied to separate geological units, which are then sub-domained further in the event that the average grade in one domain is significantly different from that of another domain within the same geological unit.

At Kombat the mineralisation occurs in the dolomites in the form of typical fracture regulated boxwork mineralisation. No clear domains could be defined with regards grade or lithology. Domining was thus split into three areas, namely 1) Kombat section, 2) Asis section and 3) the Otavi section. The Asis and Kombat sections are separated by the Kombat West Fault with a downthrow to the West.

This structure serves as a hinge point to the observed dolomite contact strike and dip changes and forms a natural structural domain limit. The Otavi domain is located away from the other areas and is thus treated as a separate domain. Figure 54 below depicts the dip and strike change of the dolomite contact across the Kombat West Fault.

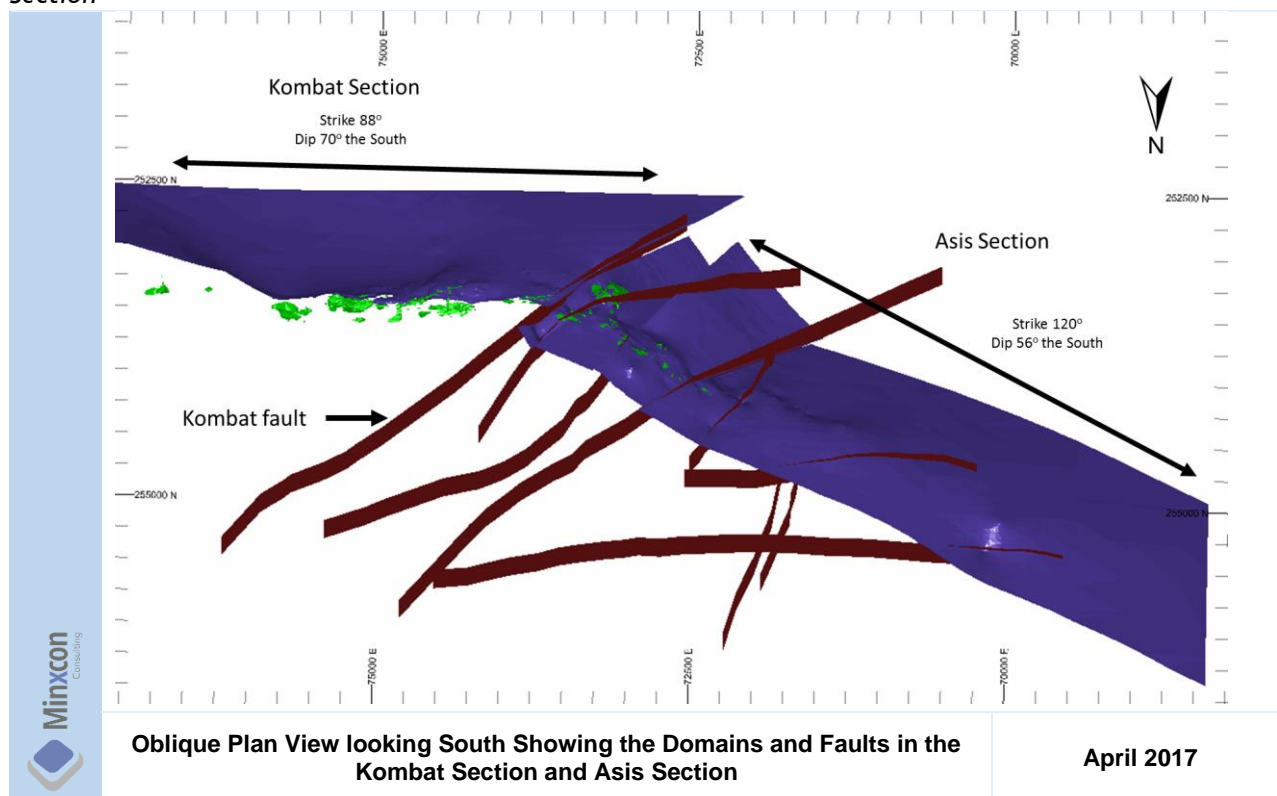Figure 54: Oblique Plan View looking South Showing the Domains and Faults in the Kombat Section and Asis Section



Data Conditioning (Compositing and Capping)

An investigation into high values in the sampling results was conducted on the copper, lead, zinc and silver. Log probability plots were utilised to determine each metals' capping strategy. Capping was set to 24.2% Cu, 23.8% Pb, 10.5% Zn and 53ppm Ag, for the Kombat Section; 40.3% Cu, 44.11% Pb, 7.7% Zn and 180 ppm Ag for the Asis Section and 16.7% Cu, 32.23% Pb, 5.37% Zn and 50ppm Ag for the Otavi Section. The capping strategy for each of the three areas is presented below in Table 15.

Table 15: Capping of the Metal Content for Each Section

Section	Cu %		Pb %		Zn %		Ag ppm	
	Capped	Maximum	Capped	Maximum	Capped	Maximum	Capped	Maximum
Kombat Section	24.20	33.02	23.80	42.35	10.50	14.09	53	147.89
Asis Section	40.30	58.00	44.11	65.45	7.70	9.23	180	580.00
Otavi Section	16.70	25.00	32.23	51.00	5.37	12.20	50	124.00

The capping represents a capping of the 99th percentile and would not advertly affect the estimation. Capping is intended to reduce the influence of excessively high sample values to prevent local over-estimation.

Figure 55, Figure 56 and Figure 57 below depict the Copper (Cu) log probability plots for each area as well as the selected capped value applied to each of these domains.

Figure 55: Log Probability Plot of the Cu Values with the Capping Indicated for the Kombat Section

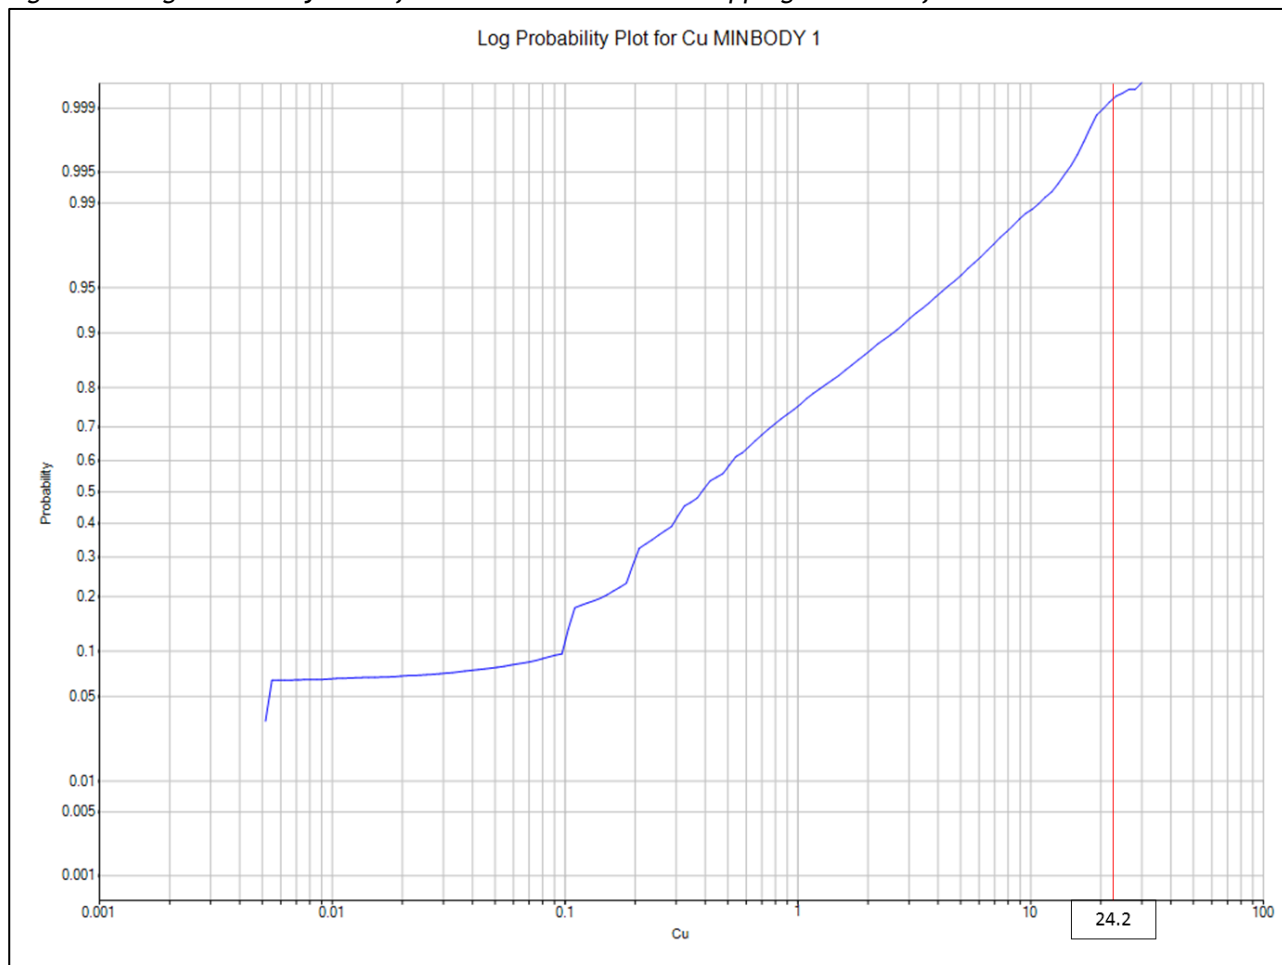


Figure 56: Log Probability Plot of the Cu Values with the Capping Indicated for the Asis Section

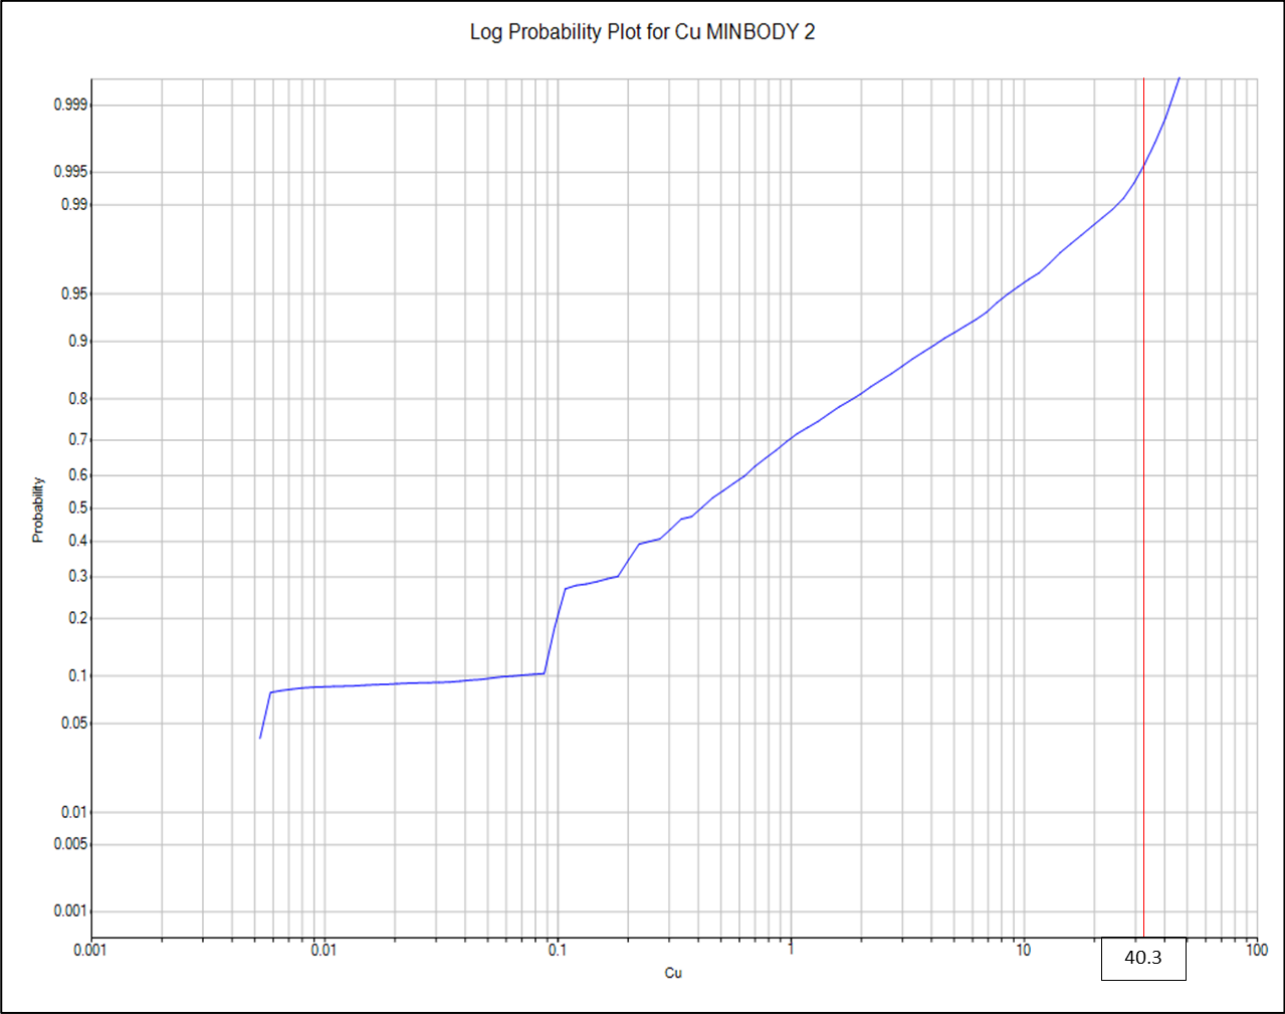


Figure 57: Log Probability Plot of the Cu Values with the Capping Indicated for the Otavi Section

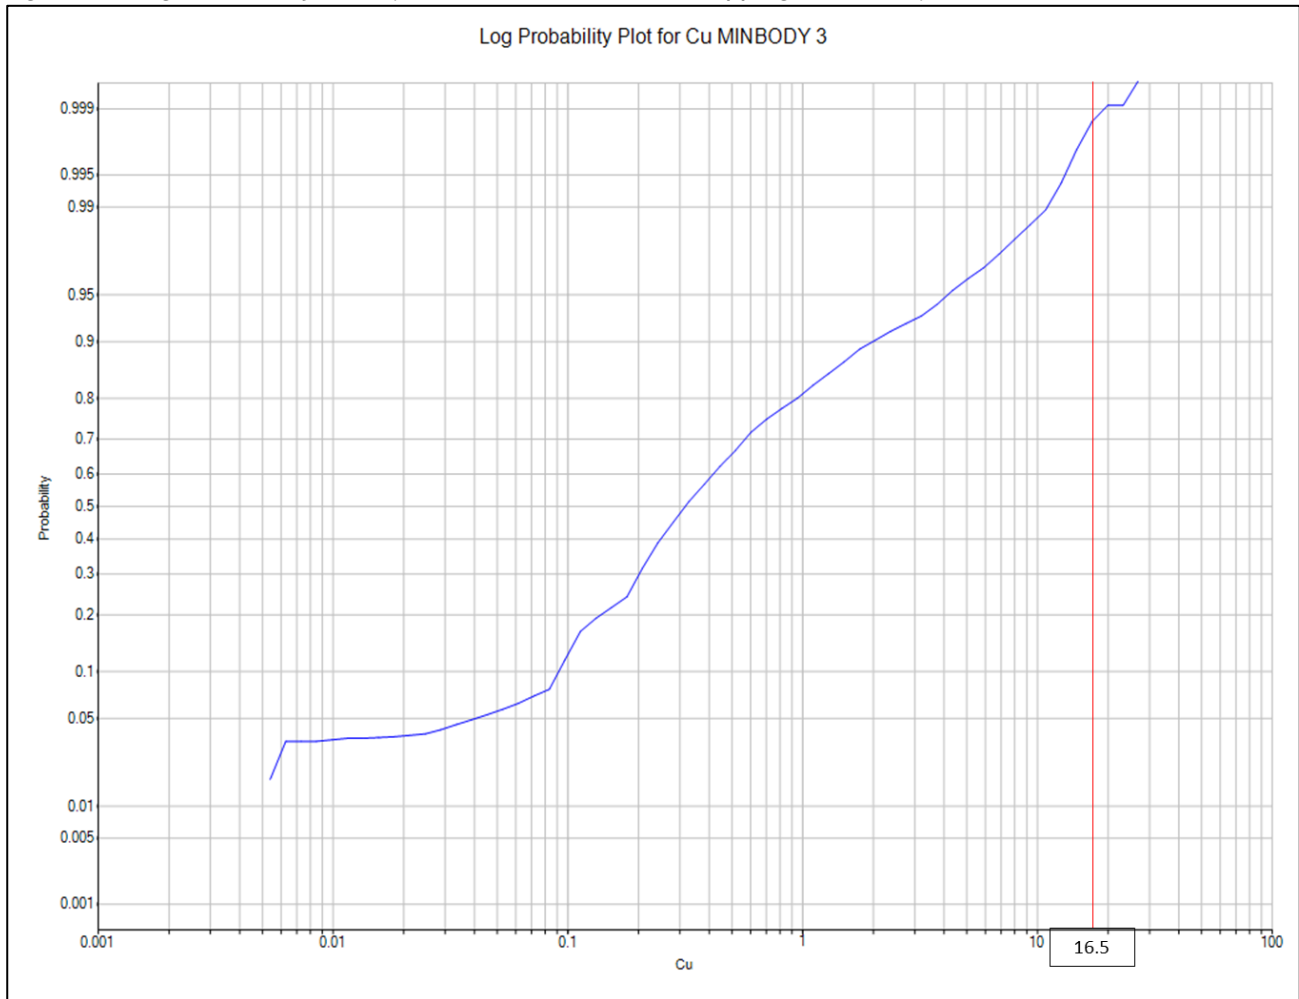


Figure 58, Figure 59 and Figure 60 below depict the Lead (Pb) log probability plots for each area as well as the selected capped value applied to each of these domains.

Figure 58: Log Probability Plot of the Pb Values with the Capping Indicated for the Kombat Section

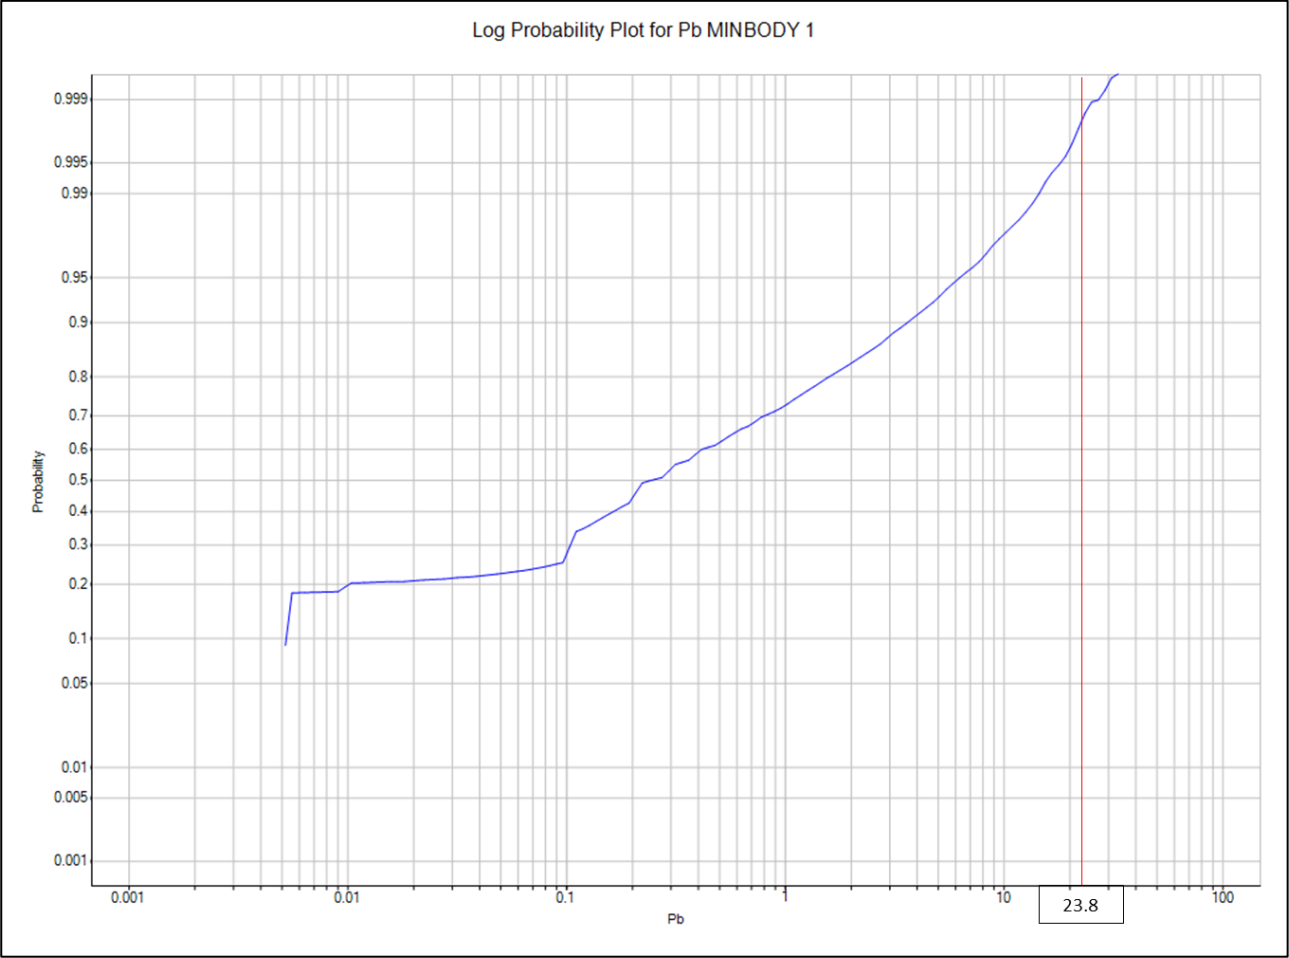


Figure 59: Log Probability Plot of the Pb Values with the Capping Indicated for the Asis Section

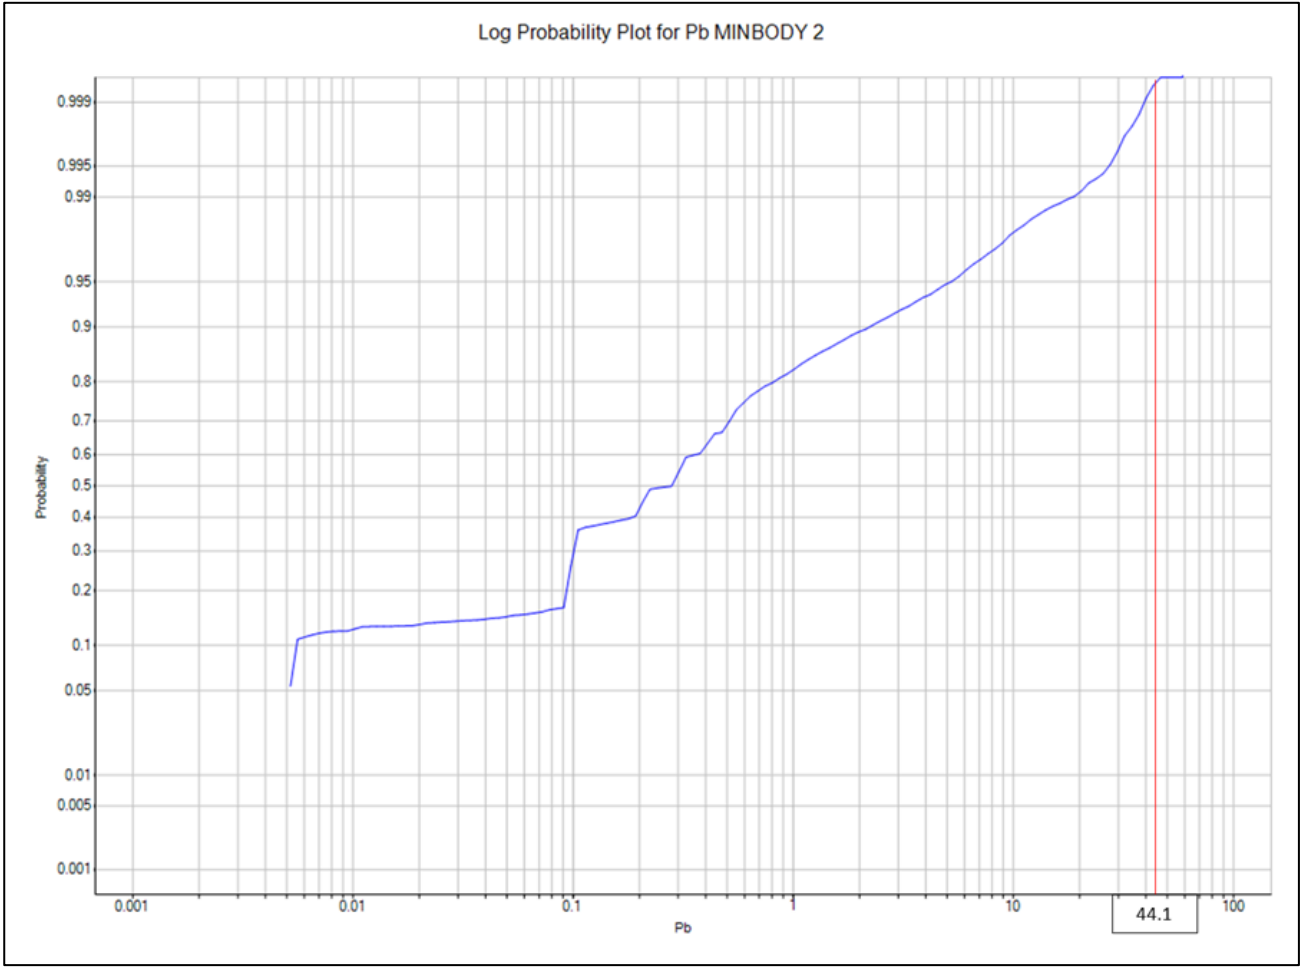
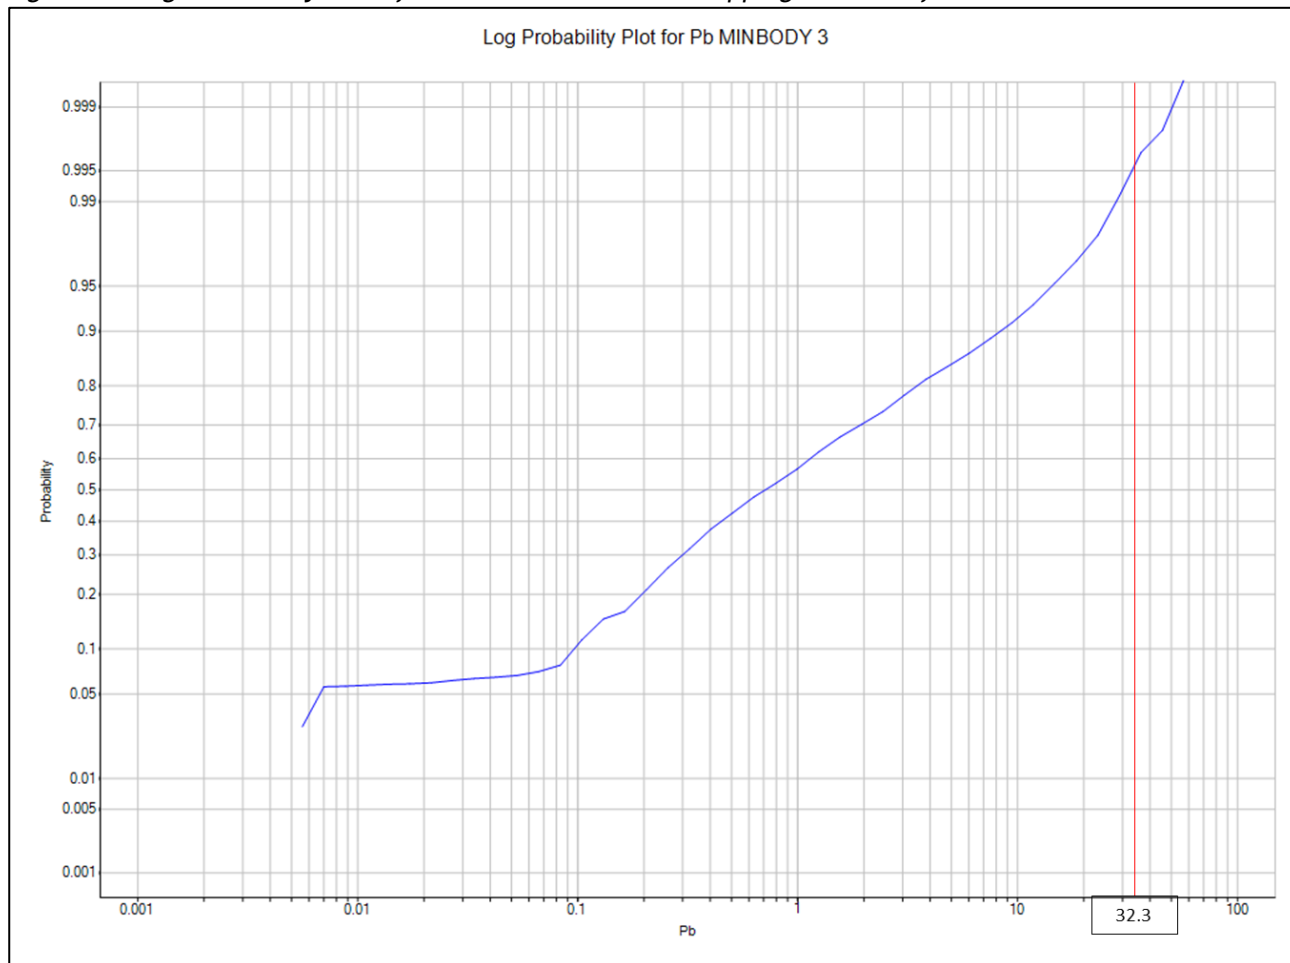
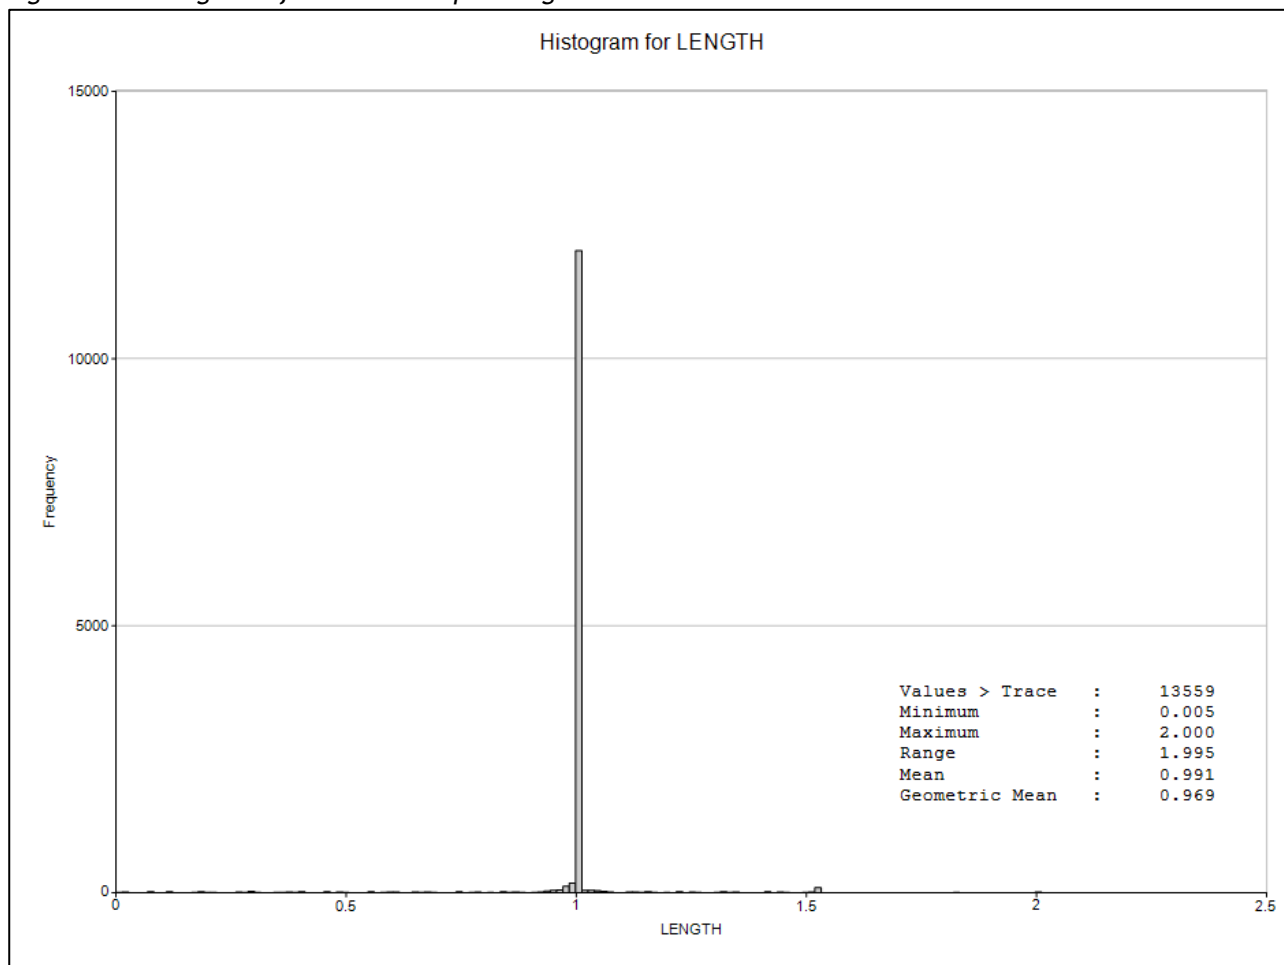


Figure 60: Log Probability Plot of the Pb Values with the Capping Indicated for the Otavi Section

Data Compositing

An analysis of the average sample length was conducted as shown in Figure 61. The Mean of the samples and geometric mean all fall very close to 1m. Based on this analysis the compositing was set to 1 m.

Figure 61: Histogram of the Raw Sample Lengths

Geostatistical Analysis and Variography

Variogram analysis of the domains was carried out on the primary metal (Cu, Pb, Ag and Zn) grades. The investigation showed that the strike relationship of the copper for Kombat section is 126 m, Asis 110 m and Otavi at only 18 m. A summary of the variograms is given in Table 16.

Table 16: Variogram Summary for the Different Areas for Cu, Pb, Ag and Zn

Section	Metal	Direction			Range			Nugget	Variance
		X	Y	Z	X	Y	Z		
Kombat	Cu	2	110	0	126	126	9.5	0.368	2.663
	Pb	2	110	0	130	130	7	0.396	5.193
	ZN	2	110	0	162	162	4.5	0.393	3.749
	Ag	2	110	0	71	71	9.5	0.005	0.482
Asis	Cu	30	146	0	110	110	10	1.447	3.776
	Pb	30	146	0	63	63	5	1.227	3.627
	ZN	30	146	0	125	125	7	0.172	1.912
	Ag	30	146	0	32	32	9.5	67.321	398.178
Otavi	Cu	0	56	0	18	18	4	0.200	2.003
	Pb	0	56	0	51	51	7	0.374	3.740
	ZN	0	56	0	21	21	8	0.084	2.411
	Ag	0	56	0	8	8	4.8	0.025	1.920

The variograms below depict the log variograms produced in Datamine Studio™. Only the copper variograms for the three sections are depicted for illustration purposes.

Figure 62 depicts the Cu log variogram for Kombat section.

Figure 62: Log Variogram for Copper for the Kombat Section

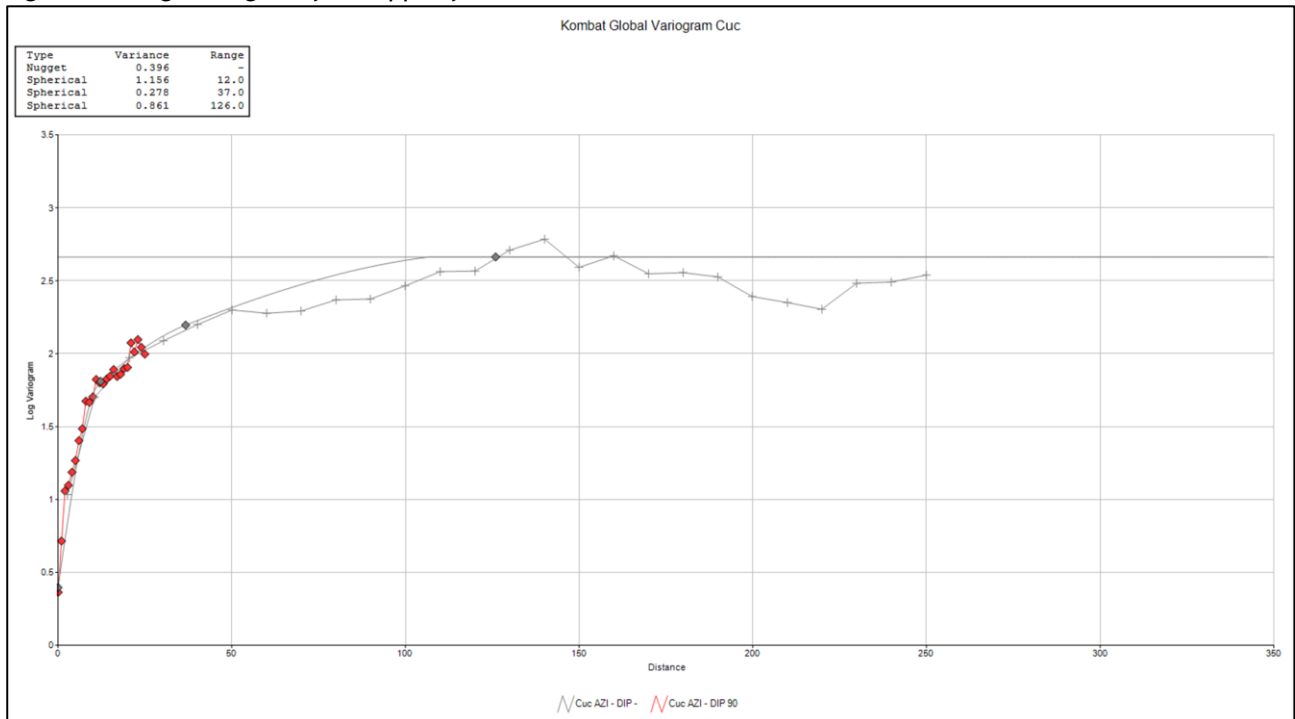


Figure 63 depicts the Cu log variogram for Asis section.

Figure 63: Log Variogram for Copper for the Asis Section

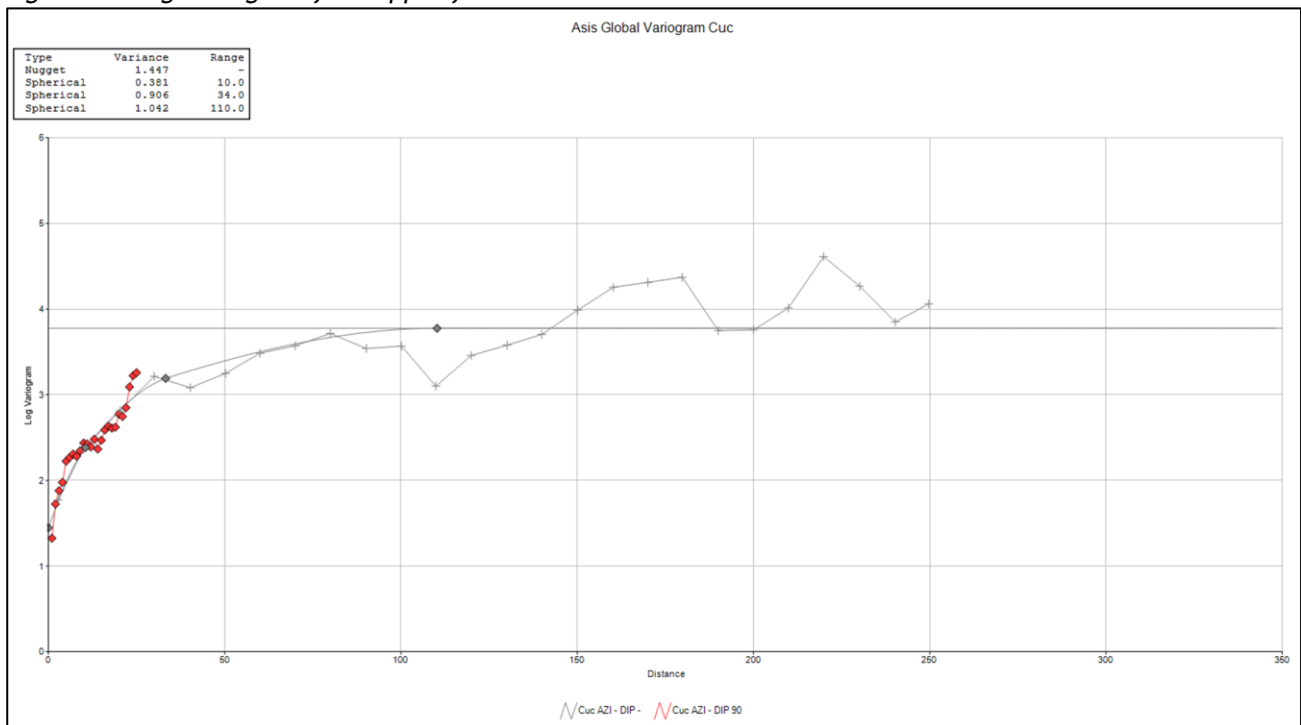
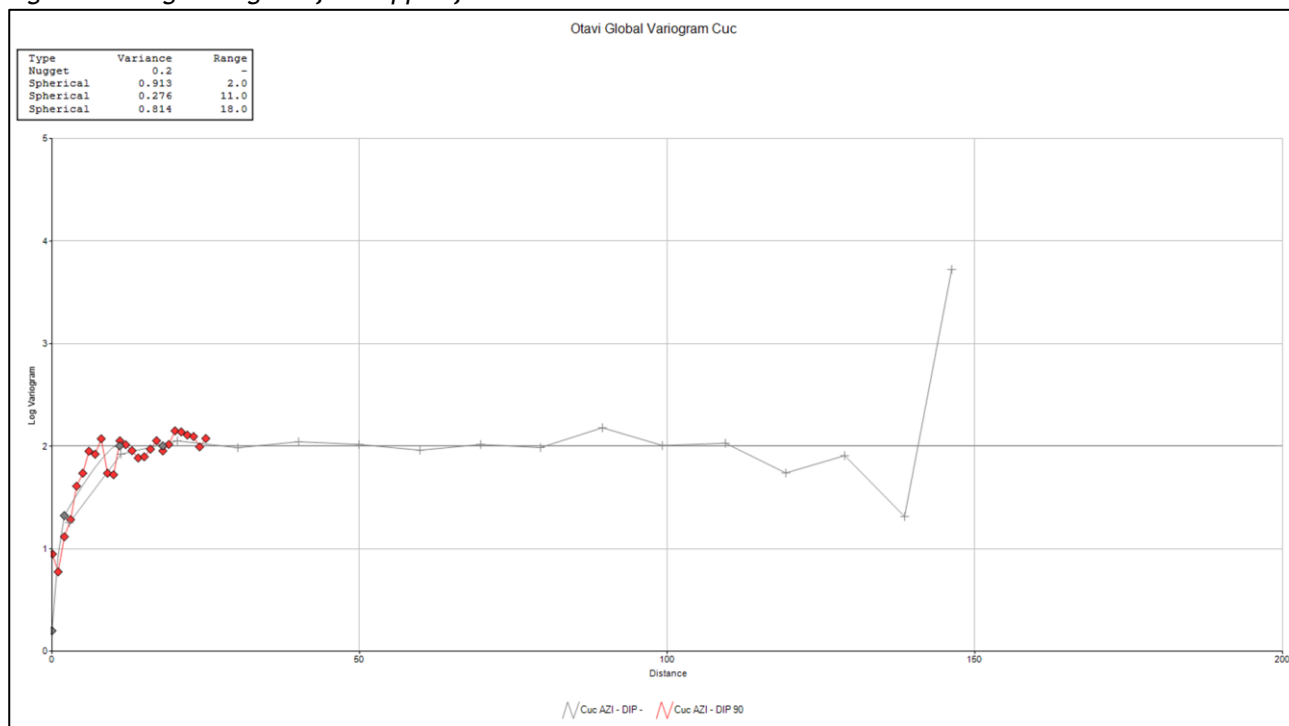


Figure 64 depicts the Cu log variogram for Otavi section.

Figure 64: Log Variogram for Copper for the Otavi Section

Bulk Density

The Asis Far West replacement and fracture fill sulphide mineralisation ranges from disseminated to massive with accompanying grade and mass increases. P&E had water immersion tests performed on the 12 verification core samples obtained on site; SRK also conducted water immersion bulk density tests. P&E reviewed the bulk density tests data and noted a positive correlation between bulk density tests and grade.

The Kombat Mine used the “revised Tsumeb formula” for historic reserves estimates as per the following equation.

Equation 1: Revised Tsumeb Formula

$$\text{Bulk Density (t/m}^3\text{)} = \frac{363}{130 - (0.874 * (\text{Cu}\% + \text{Pb}\%))}$$

P&E compared the calculated Tsumeb bulk densities to actual bulk densities and concluded that the Tsumeb formula provides a smoothed result that corresponds better to the grade data than simple linear or polynomial regression.

Minxcon applied the same formula above for a combined Cu% +Pb% to the estimated block model cells on a per block basis to account for density changes through the deposit. This is reflected as a variable bulk density in the block model.

Block Model Creation and Grade Interpolation

An empty block model was created in Datamine Studio™ which covered both the Kombat and Asis sections. A separate block model was created to cover the Otavi Section. The Kombat/Asis model was generated on a parent block size of 100 m x 100 m x 10 m which reflects the ranges of the variograms. The Otavi Section

block model utilised a parent cell size of 10 m x 2 m x 10 m which reflects the extremely short ranges of its informing variogram. The block model parameters for the areas are summarised in Table 17.

Table 17: Block Model Origin and Cell Size

Section	Origin			Block Size			Number of Cells		
	X	Y	Z	X	Y	Z	X	Y	Z
Kombat/Asis	71260	253150	660	10	2	10	563	616	101
Otavi	62840	258430	1430	10	2	10	20	96	22

The block model was filled using the orebody grade shell wireframes and only these blocks were estimated. A regime of subcell splitting was used to ensure that the true volumetrics of the grade shells were honoured as best possible. The primary cells were allowed to split to a minimum dimension of 1 m in the X, Y and Z.

The block model was estimated utilising ordinary kriging for all three sections to the extent of two search volumes. Search volume 1 (usually for Measured Mineral Resources) equated to 2/3 times the variogram range for each commodity, while search volume 2 (usually for Indicated Mineral Resources) equated to 1.5 times the variogram range. The third search volume was not calculated in order to assist with restriction of the estimate. Check estimates in the form of inverse distance squared and nearest neighbour were also carried out as a means of validating the ordinary kriged estimation.


Individual grade shells were estimated to ensure that no cross estimation occurred between grade shells. A minimum of three samples and a maximum of 10 samples from a minimum of two drillholes were used as estimation parameters in the estimation. The minimum of 2 drillholes is used to reduce the potential bias of a single drillhole influencing the block estimation. This would most likely occur in areas where the block model is poorly informed due to sparse local data distribution. The search parameters utilised during the grade interpolation are listed below in Table 18 for each of the sections and the relevant metal estimates.

Table 18: Search Parameters for the Kombat, Asis and Otavi Sections

Section	Metal	Direction			Range			Min Samples	Max Samples	Min Drillholes
		X	Y	Z	X	Y	Z			
Kombat	Cu	2	110	0	126	126	3	3	10	2
	Pb	2	110	0	130	130	3	3	10	2
	Zn	2	110	0	162	162	3	3	10	2
	Ag	2	110	0	71	71	3	3	10	2
Asis	Cu	30	146	0	110	110	3	3	10	2
	Pb	30	146	0	63	63	3	3	10	2
	Zn	30	146	0	125	125	3	3	10	2
	Ag	30	146	0	32	32	3	3	10	2
Otavi	Cu	0	56	0	18	18	3	3	10	2
	Pb	0	56	0	51	51	3	3	10	2
	Zn	0	56	0	21	21	3	3	10	2
	Ag	0	56	0	8	8	3	3	10	2

Smearing of grade up and down the holes as well as across strike was reduced by means of limiting the downhole search radius to 2 m. The search parameters used in the estimation were restricted in the Z direction to also reduce the effect of smearing of grade over the larger volumetric. Figure 65 shows how the search restrictions reduced the effect of over estimating grade throughout the grade shell.

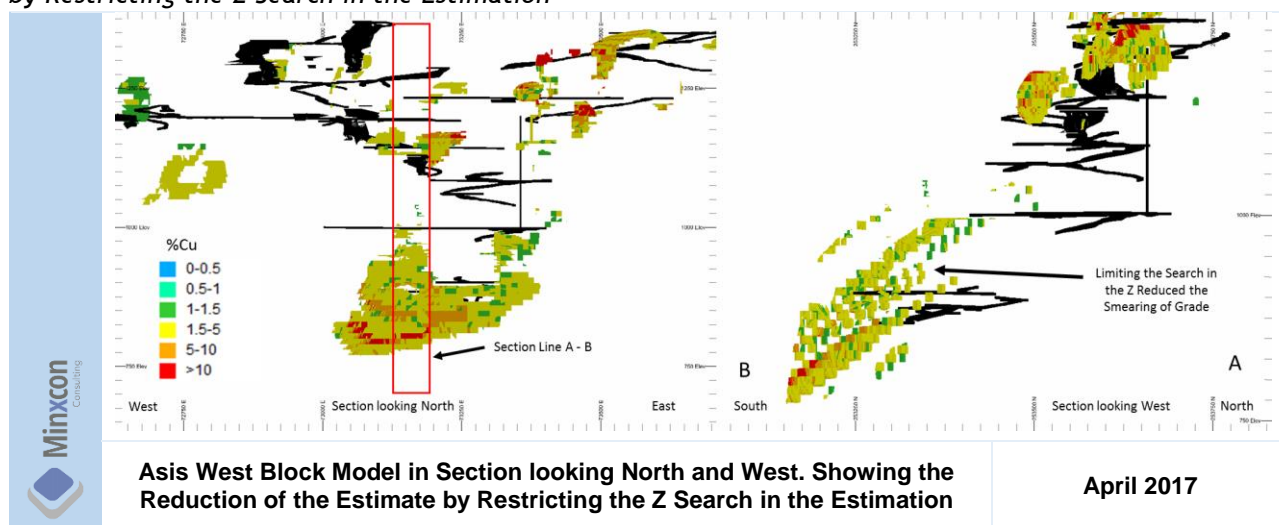Figure 65: Asis West Block Model in Section looking North and West. Showing the Reduction of the Estimate by Restricting the Z Search in the Estimation



The final volume of the final block model was reduced to reflect only estimates where both copper and lead were estimated. Cells that only contained a copper or lead estimate were discarded due to the fact that the Kombat orebodies constitute mixed metal mineralisation and metallurgical processing currently only processes mixed ores.

Owing to the slightly longer variogram ranges of the lead estimate in the Kombat Section and the corresponding shorter ranges for lead in the Asis section, this trimming was conducted to ensure that both metal estimates are required to be present before the block was seen as a valid estimation. A similar block validation was conducted on the Otavi section. Two search volumes were used in the reporting of the Mineral Resources. However, regardless of the fact that all Mineral Resource reported to Measured and Indicated Mineral Resource search volumes, all Mineral Resources were downgraded to Inferred Mineral Resources due to factors discussed in Item 14 (a).

Figure 66 to follow shows the estimated copper mineral resource block model where no cut-off grade has been applied as a filter, prior to depletions being conducted.


Figure 66: Kombat Mine Mineral Resource with no Cut-off Applied and no Historical Voids Removed

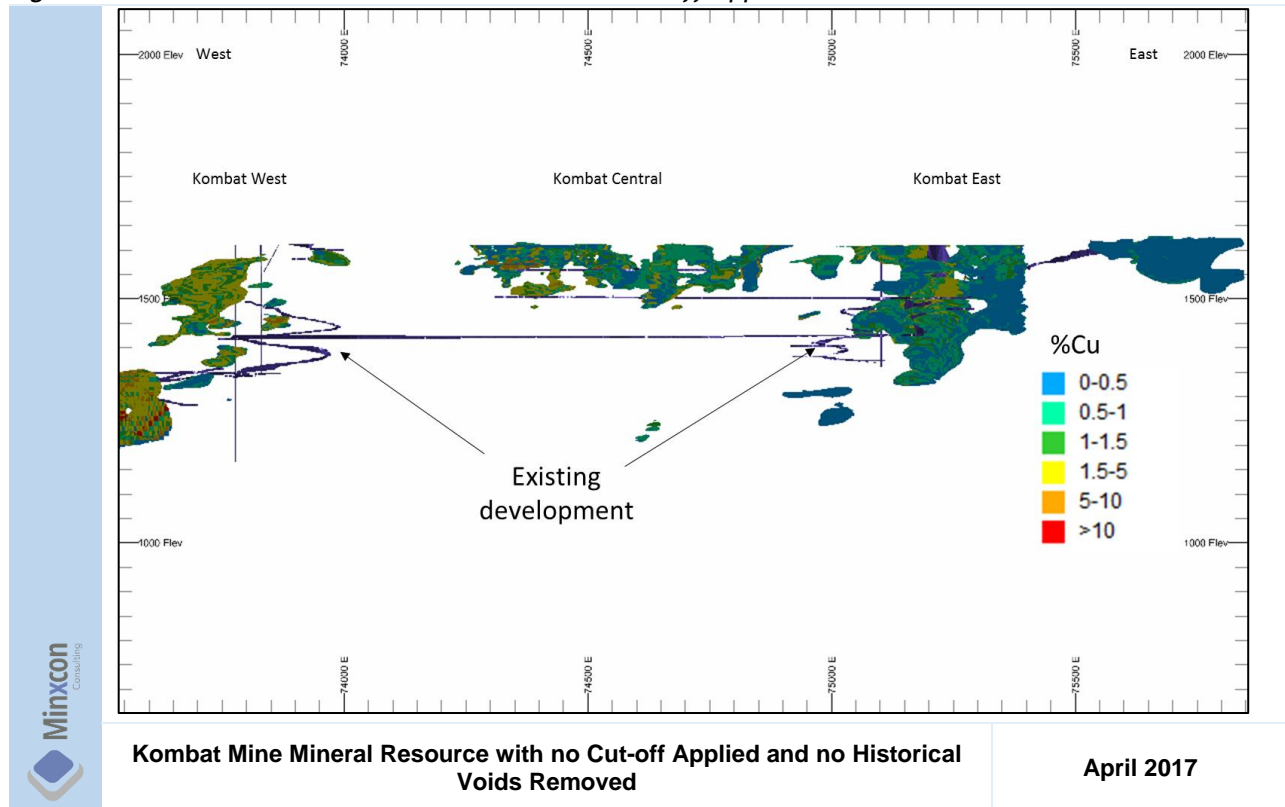Figure 67 shows the Mineral Resource block model after the historic mining voids have been removed (ore depleted) and a copper equivalent cut-off of 1.4% has been applied.

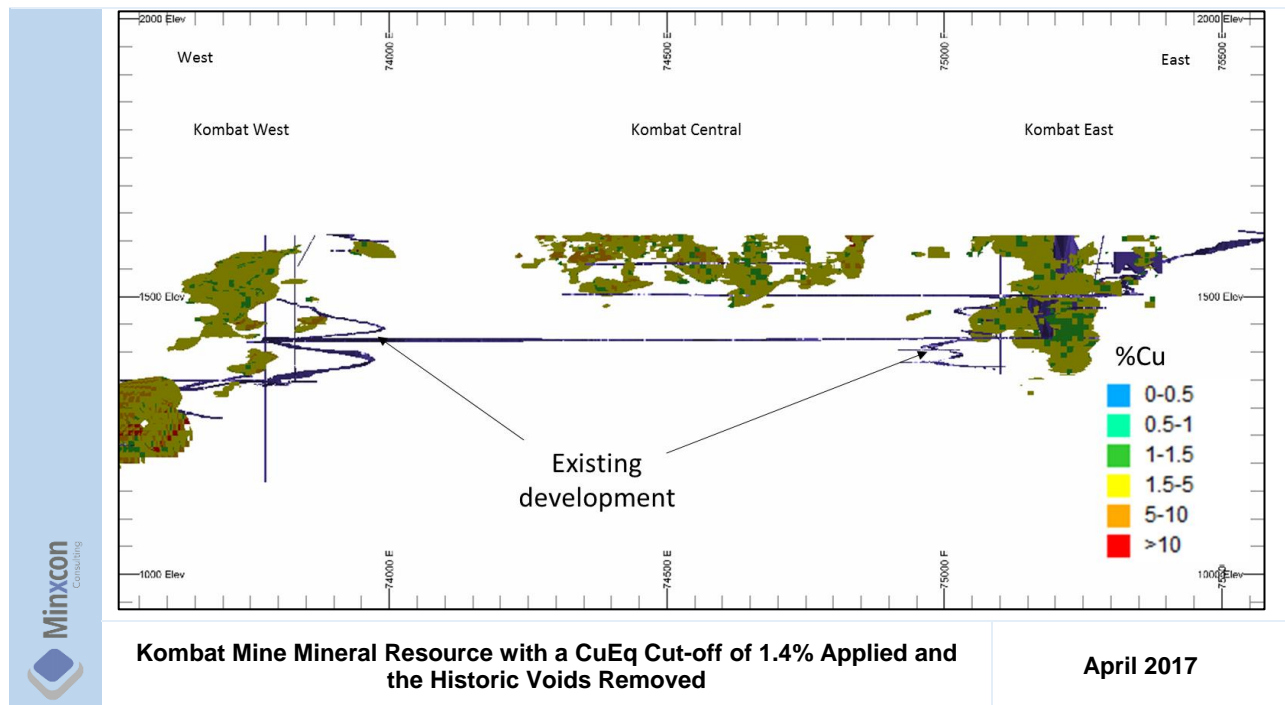
Figure 67: Kombat Mine Mineral Resource with a CuEq Cut-off of 1.4% Applied and the Historical Voids Removed

Figure 68 shows the estimated copper Mineral Resource block model for Asis mine with no cut-off applied. The model has also not been depleted.

Figure 68: Asis Mine Mineral Resource with No Cut-off Applied and no Historical Voids Removed


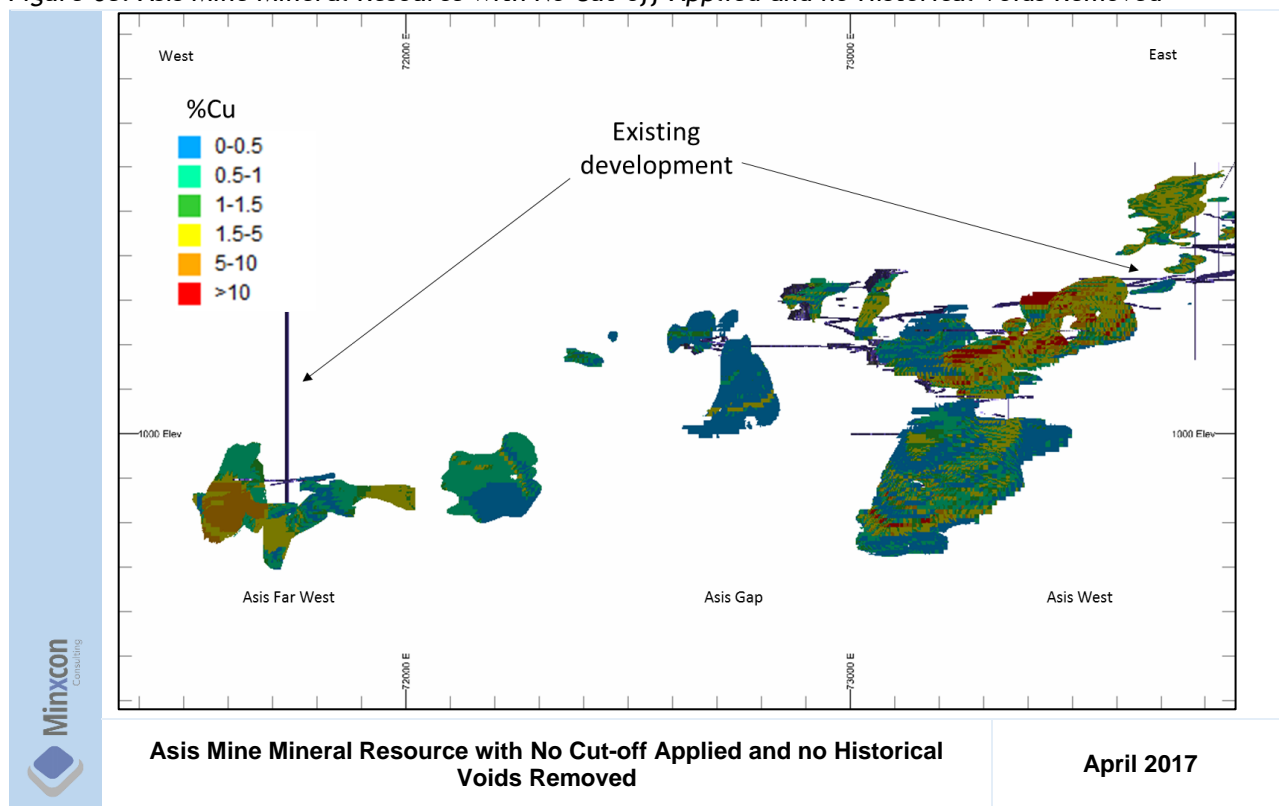


Figure 69 depicts the Mineral Resource block model after the historic mining voids have been depleted and a CuEq cut-off of 1.4% has been applied.

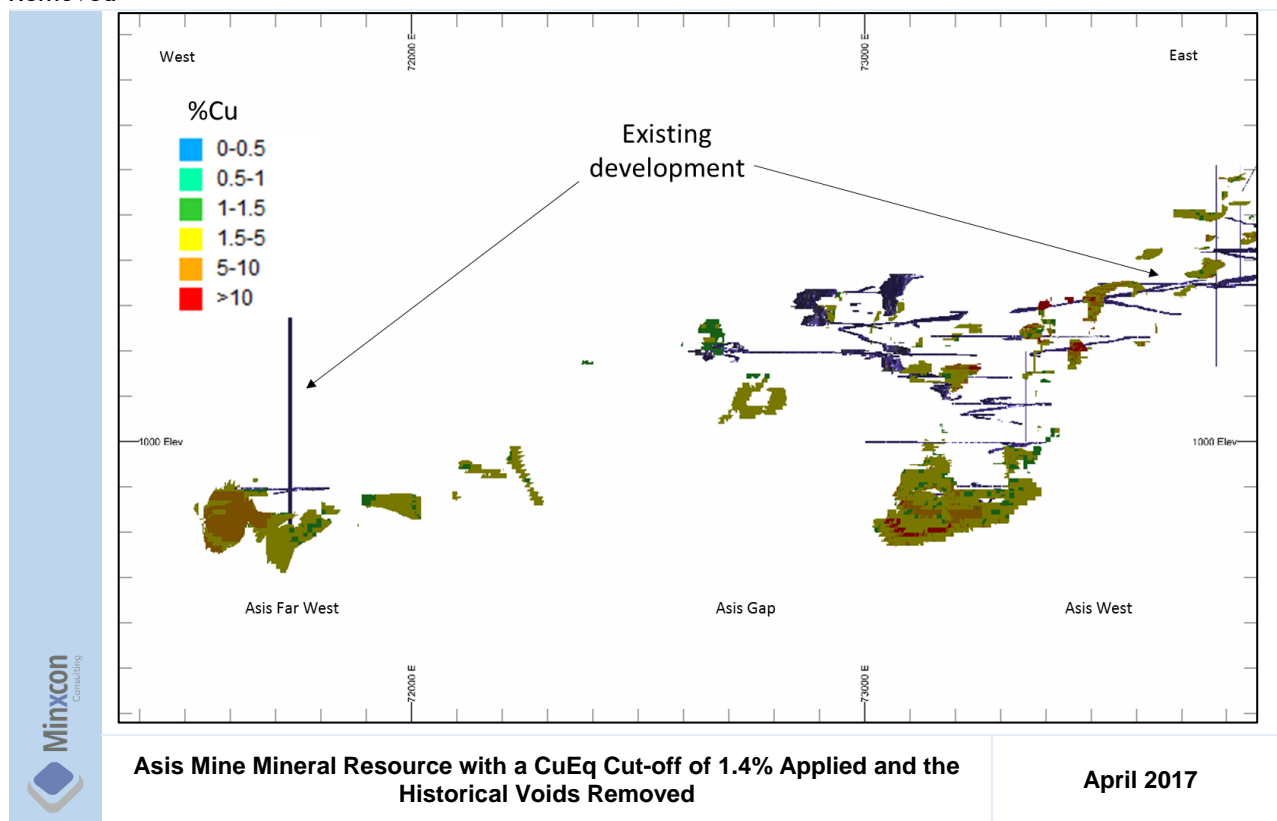Figure 69: Asis Mine Mineral Resource with a CuEq Cut-off of 1.4% Cu Applied and the Historical Voids Removed



The Otavi orebody is depicted in Figure 70 looking to the east. The interpolated block model on the left is shown with no cut-off applied, while the one on the right has had a CuEq cut-off of 0.77% applied.

Figure 70: Otavi Mine Mineral Resource Looking East with no Cut-off Applied and a CuEq Cut-off of 0.77% Applied

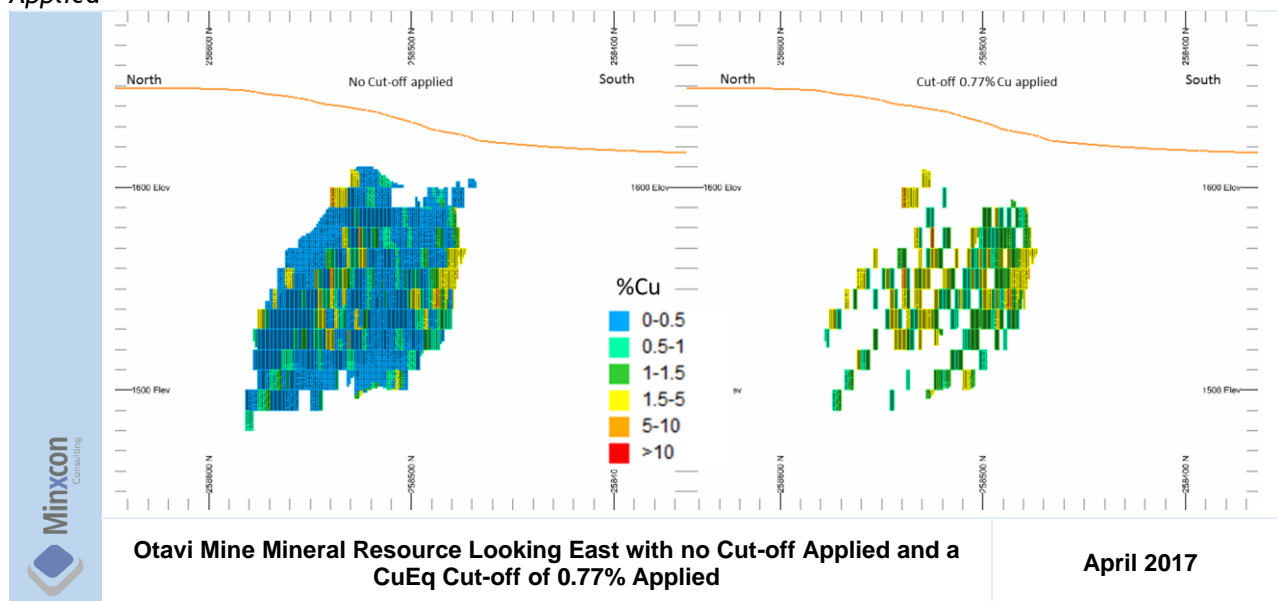
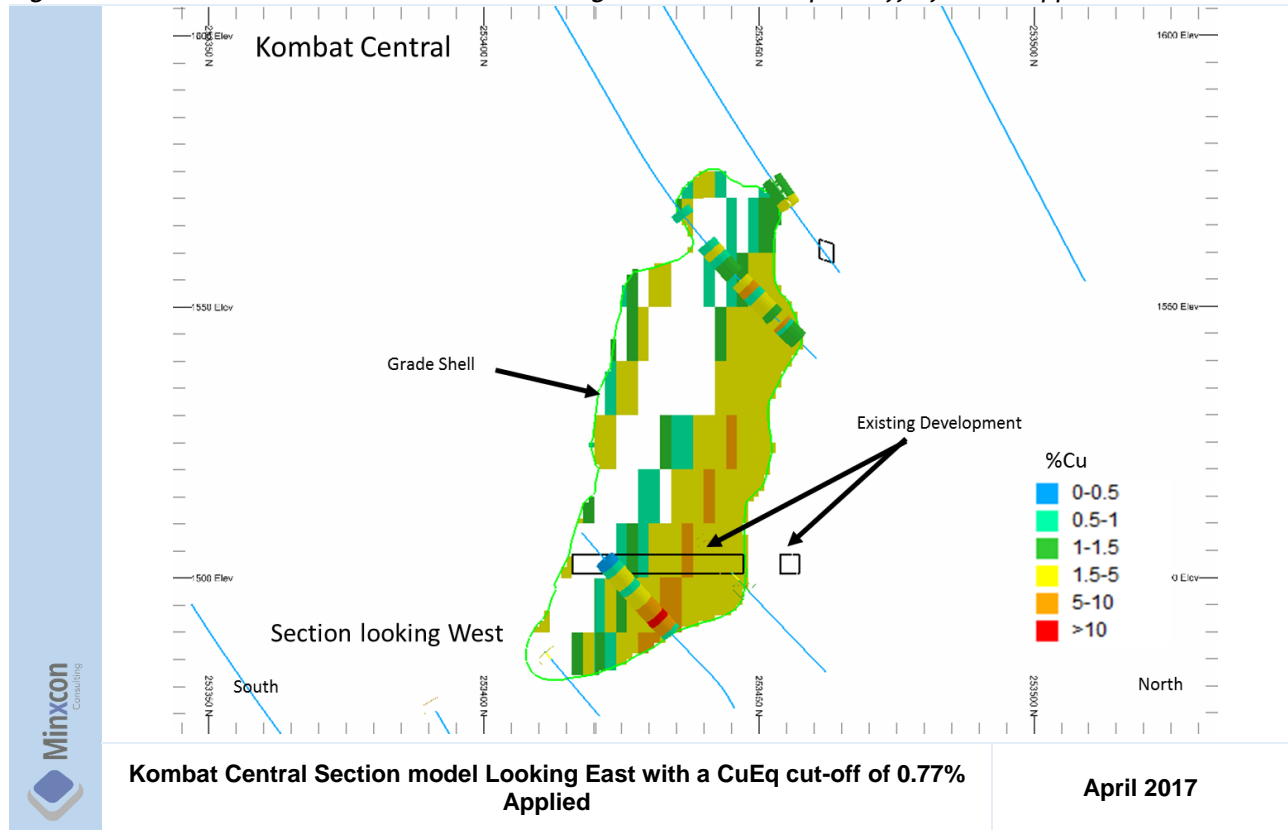


Figure 71 depicts the Kombat Estimation with the Cut-off of 0.77 CuEq applied in section view.

Figure 71: Kombat Central Section model Looking East with a CuEq cut-off of 0.77% Applied

The following sections show the Asis West and Far West with the CuEq of 1.4%. The grade shells are shown where the natural cut-off of 0.3% is shown in green and the estimate falls within this grade shell (Figure 72 and Figure 73).

Figure 72: Asis West Section Model Looking East with a CuEq Cut-off of 1.4% Applied

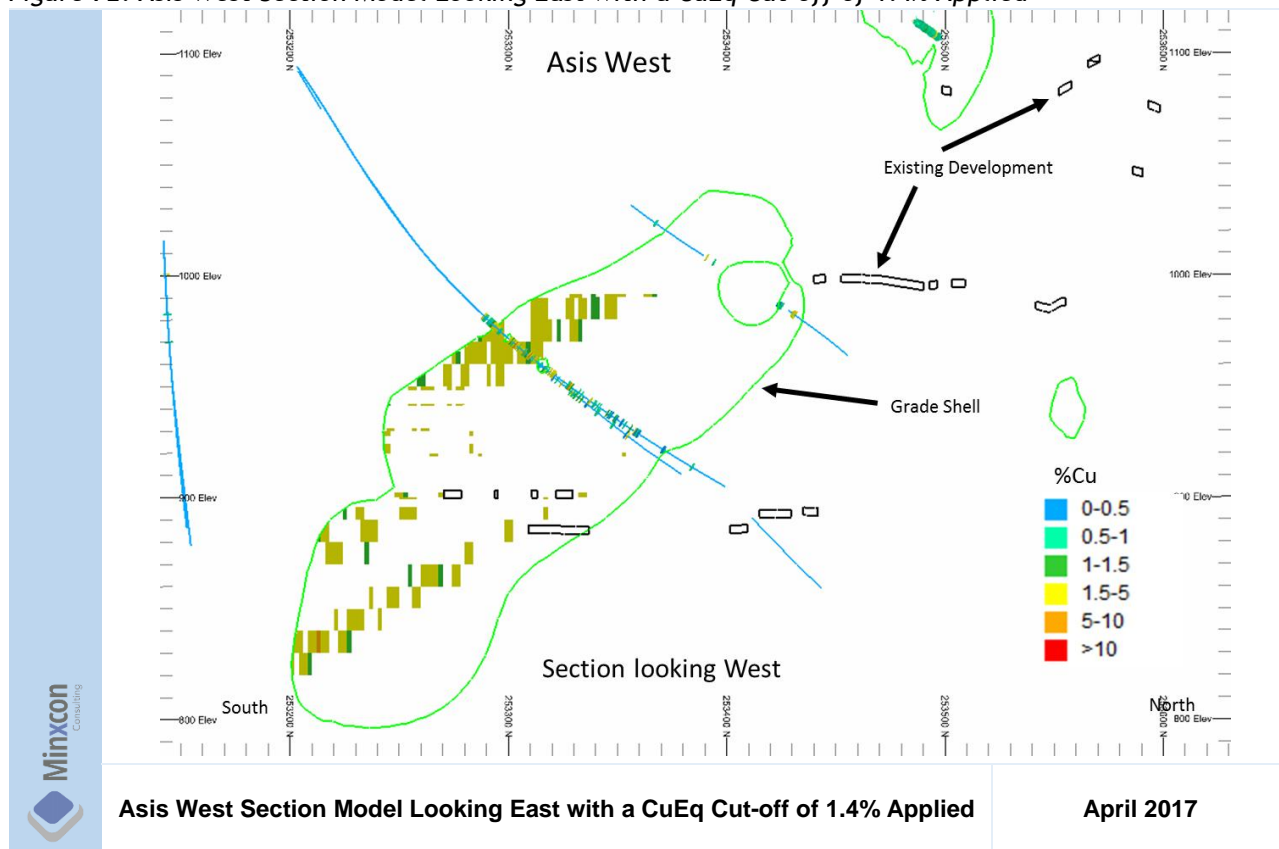


Figure 73: Asis Far West Section Model Looking East with a CuEq Cut-off of 1.4% Applied

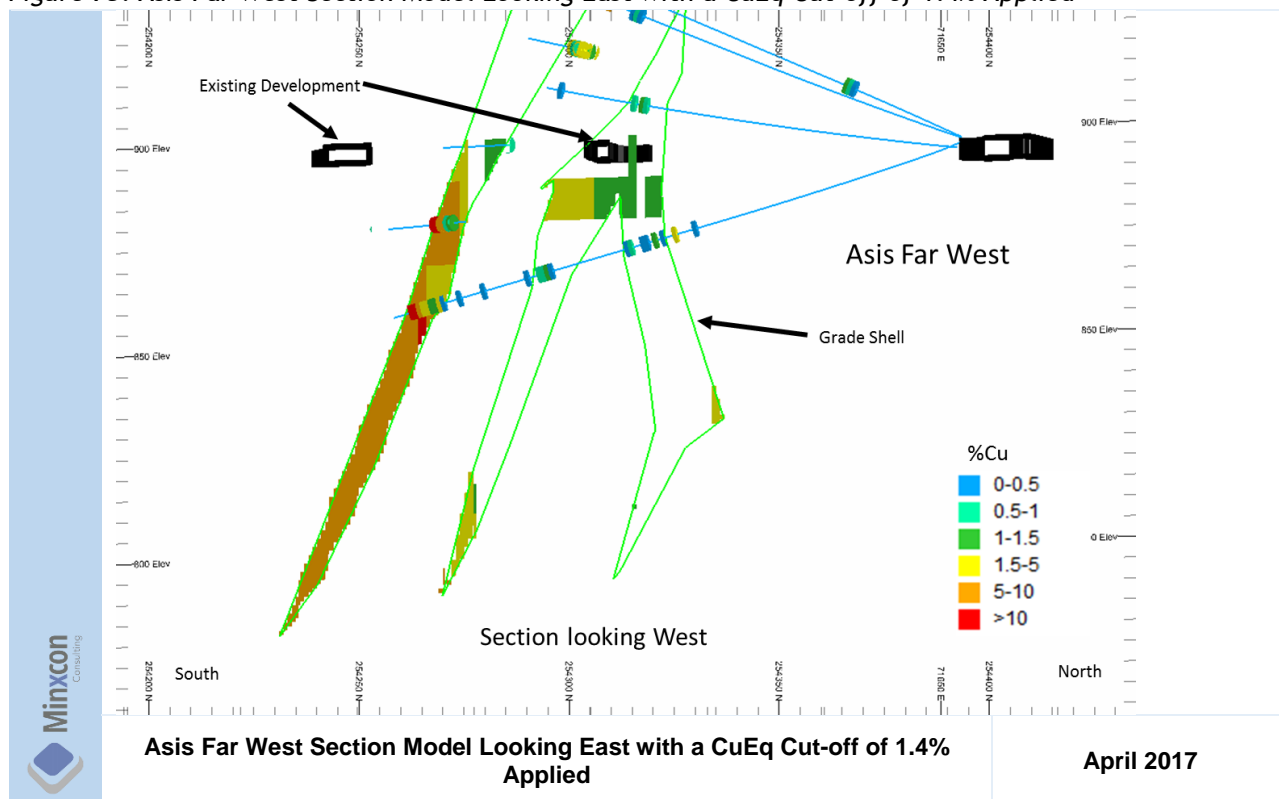


Figure 74 to Figure 78 show zoomed in figures of the grade estimation models the various project areas at CuEq cut-offs in relation the historical mining.

Figure 74: Kombat East Estimation Model at a CuEq Cut-Off of 0.77 % with Historical Mining Voids

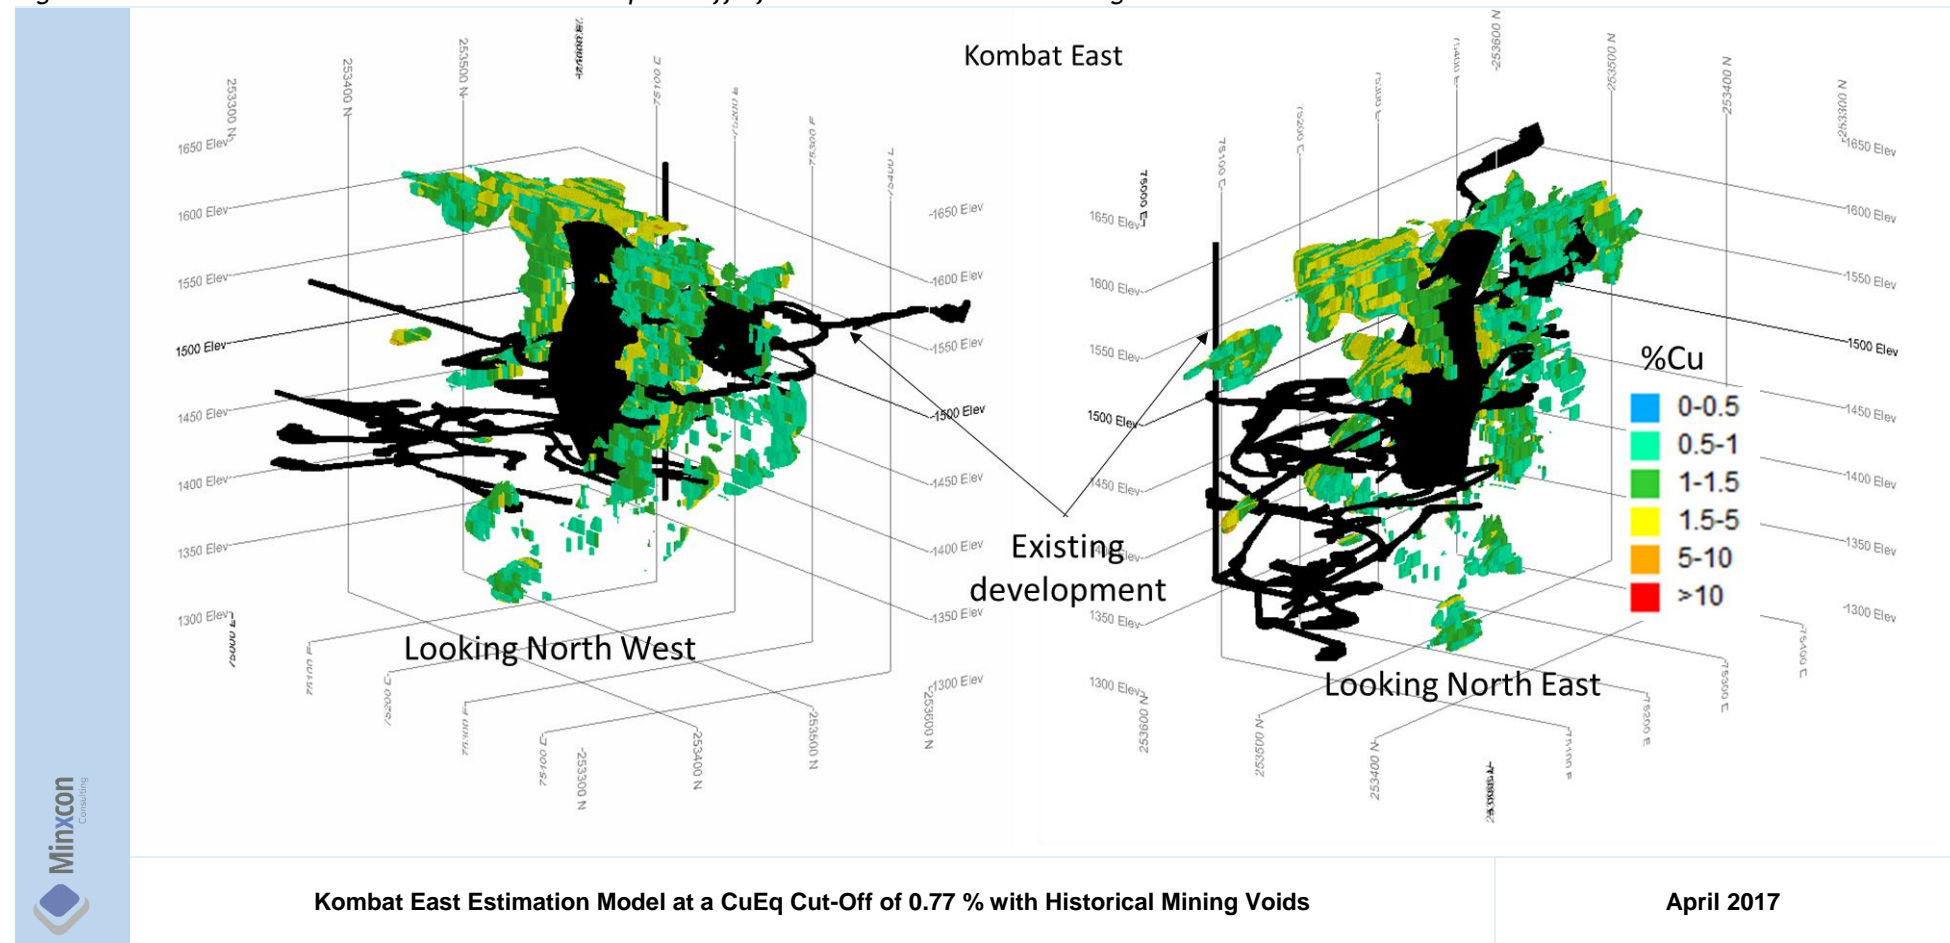


Figure 75: Kombat Central Estimation Model at a CuEq cut-off of 0.77 % with Historical Mining Voids

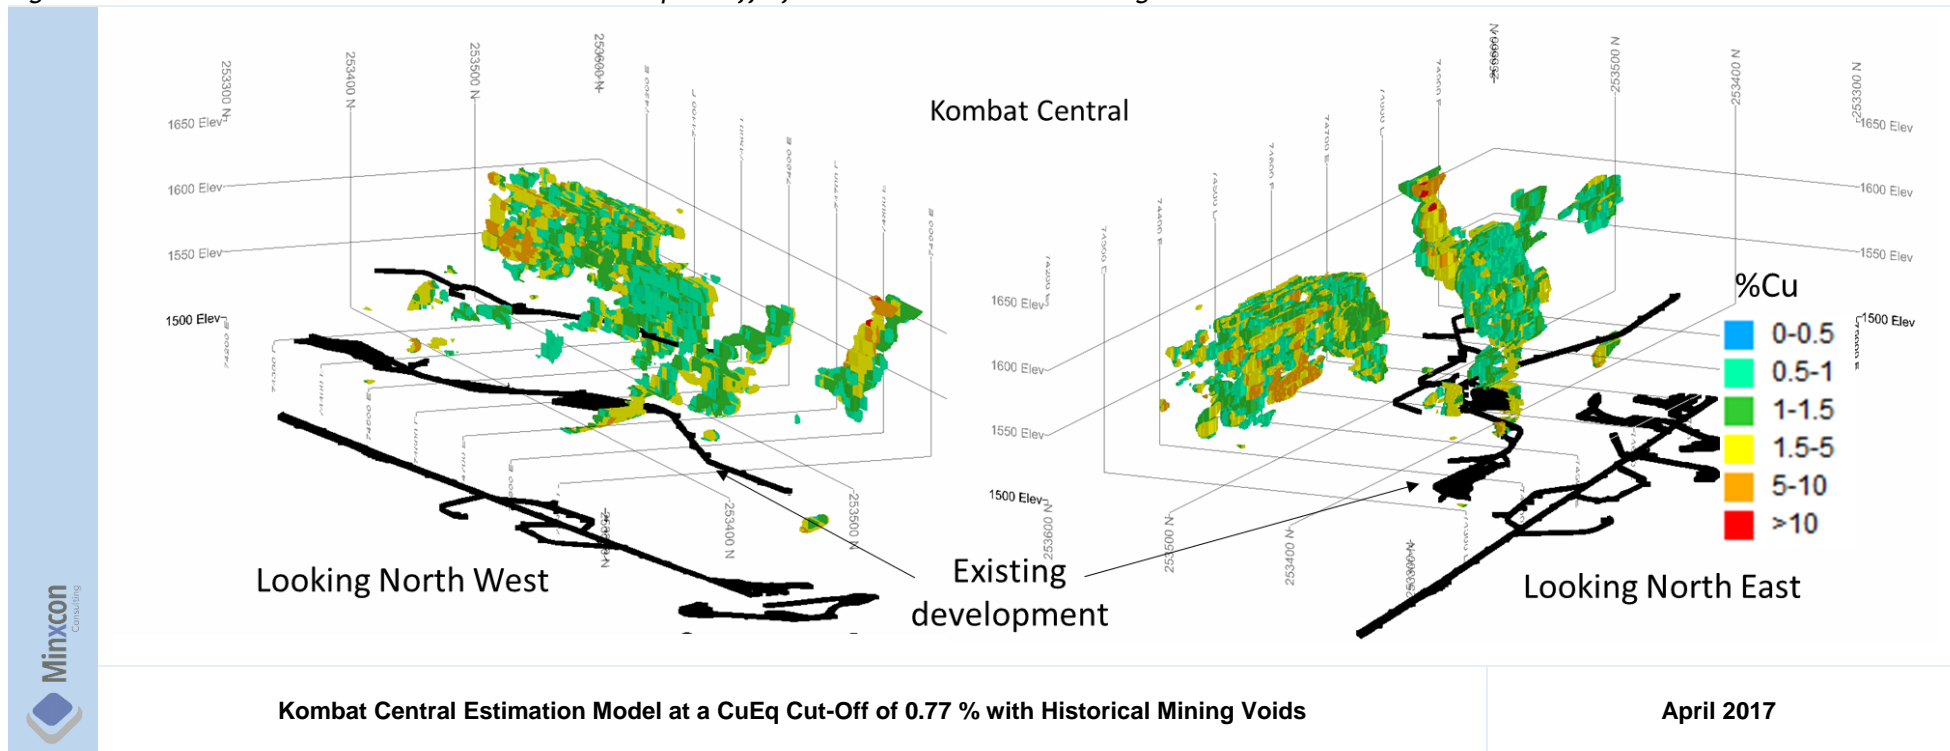


Figure 76: Kombat West Estimation Model at a CuEq cut-off of 0.77 % with Historical Mining Voids

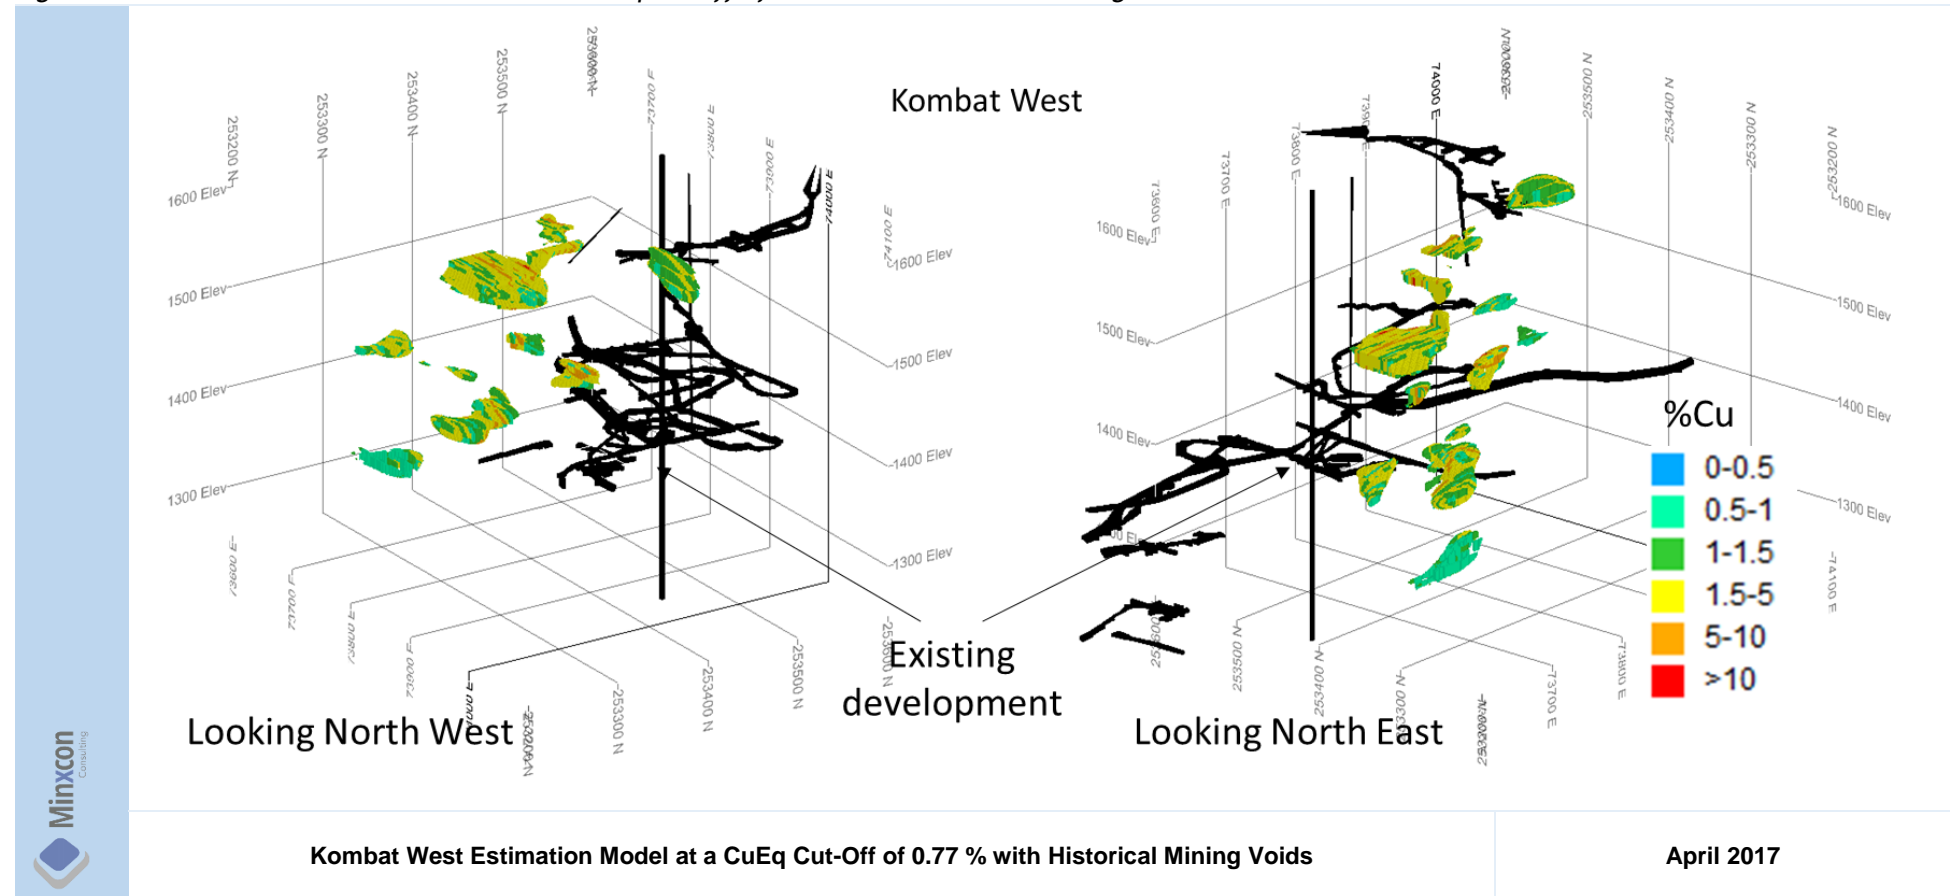


Figure 77: Asis West Estimation Model at a CuEq cut-off of 1.40 % with Historical Mining Voids


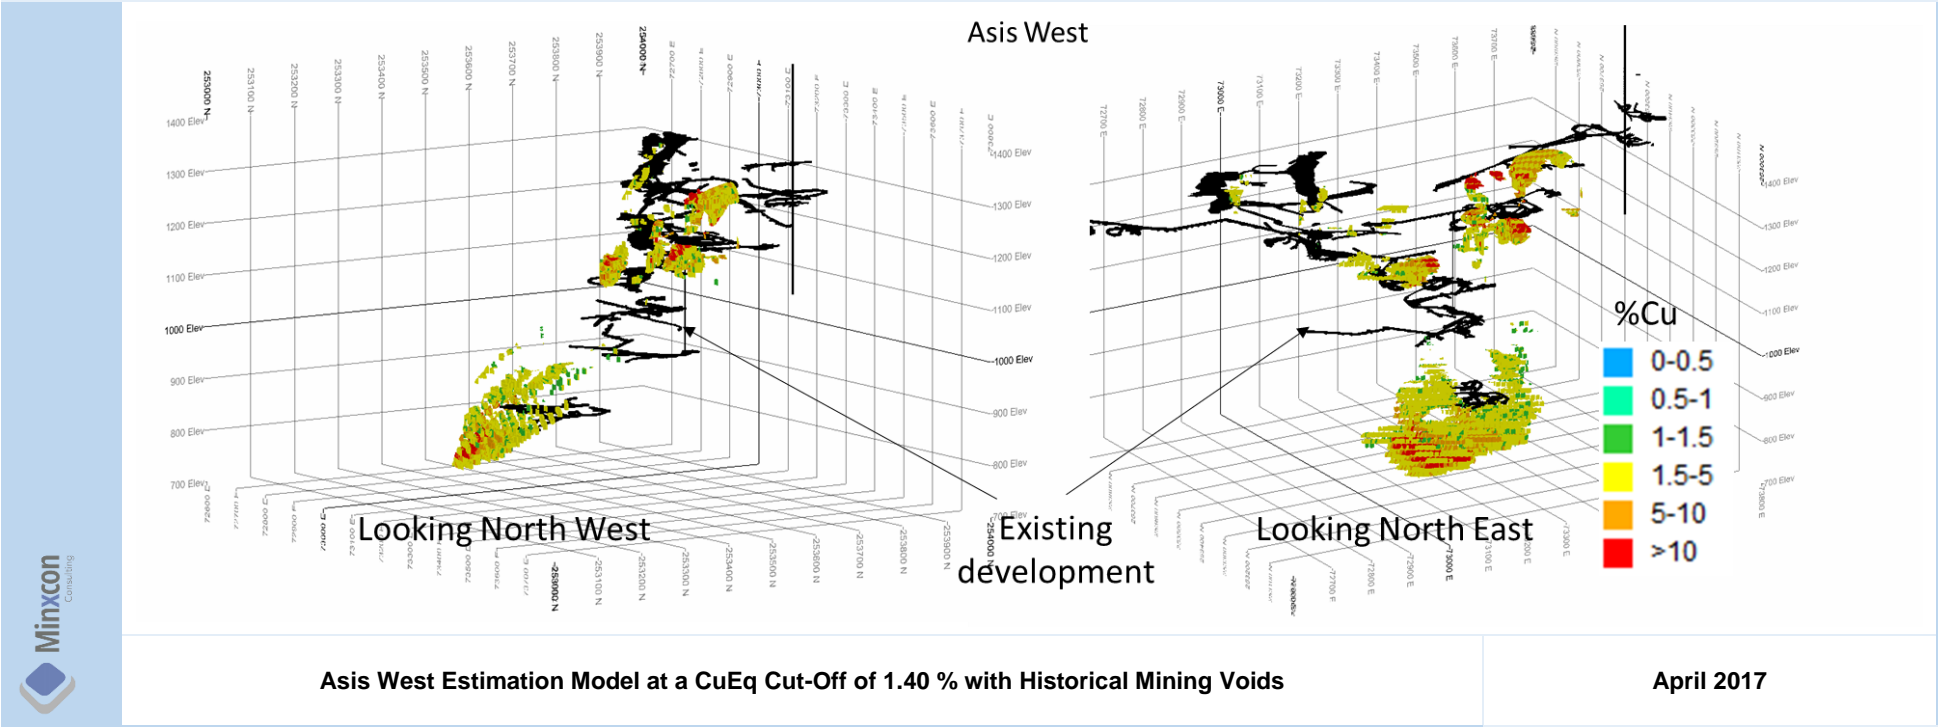


Figure 78: Asis Far West Estimation Model at a CuEq cut-off of 1.40 % with Historical Mining Voids

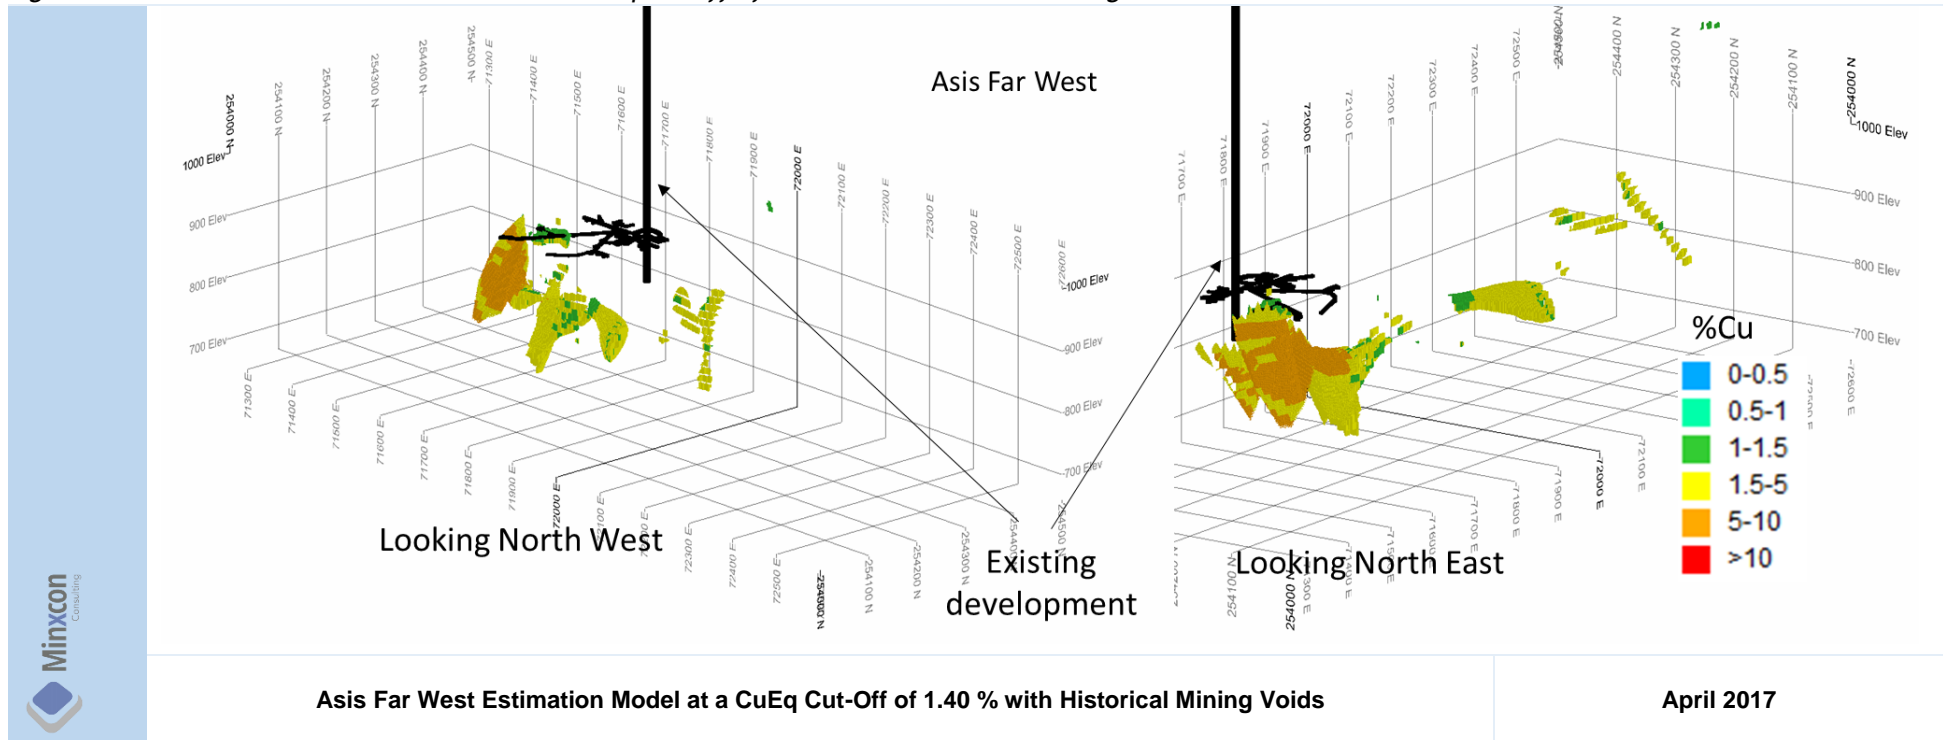

Mining Depletions

The Mineral Resources for the Kombat operations were depleted based upon the available digital historical voids with regards the stoping and development. Review of Mine longitudinal sections however demonstrated that the stoping voids are largely incomplete. Minxcon thus digitized the most extensive stope outlines on longitudinal section on a per mine shaft basis and projected these through the entire project area towards the north in order to remove all mineralisation within the presented profile so as not to over-estimate the Mineral Resources.

Figure 79 below shows an example of one of the scanned longitudinal mine sections over Asis West which was digitised to conduct the additional depletions.

Figure 79: Historical Longitudinal Sections Showing the Mined-out Areas

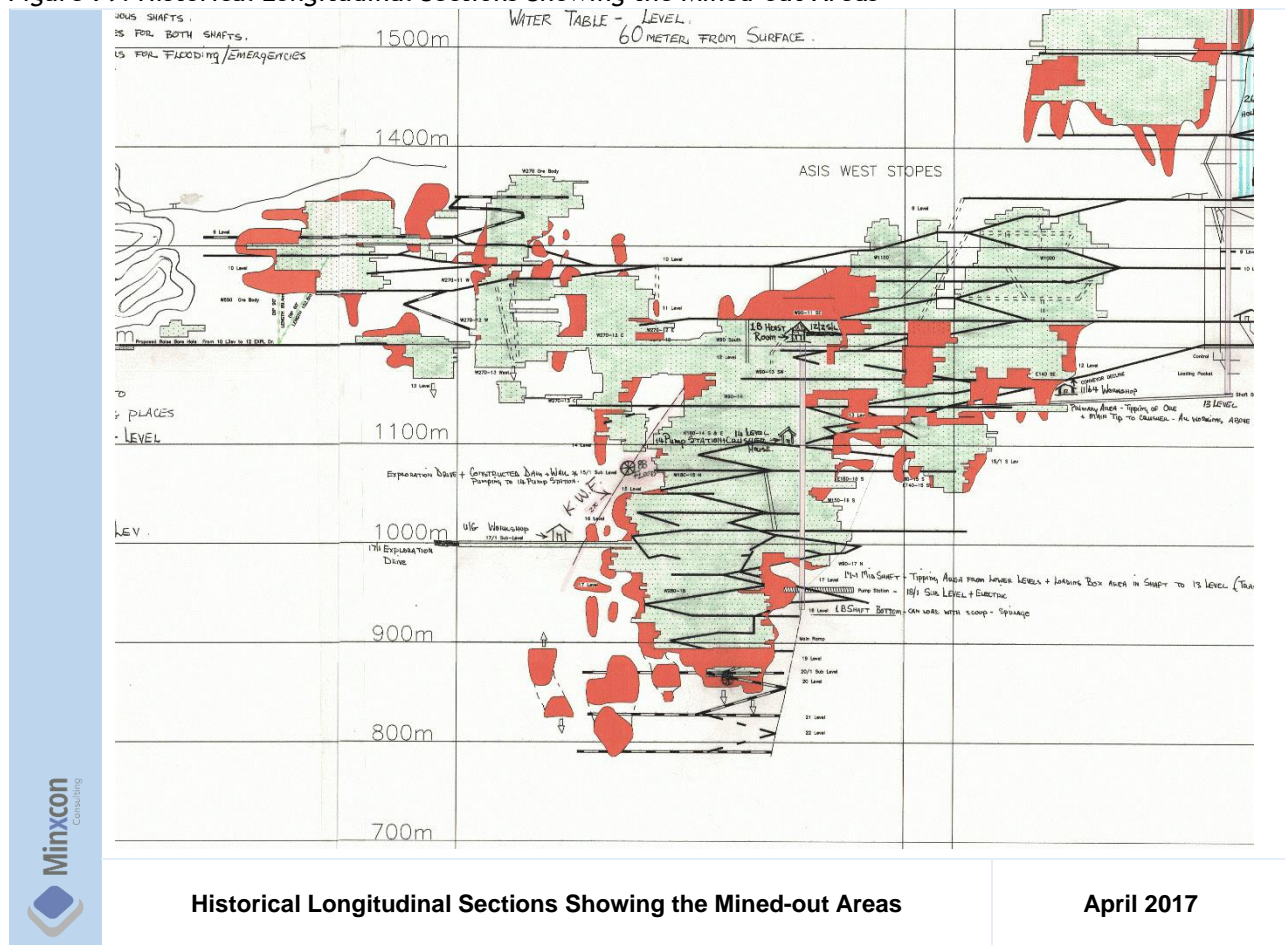
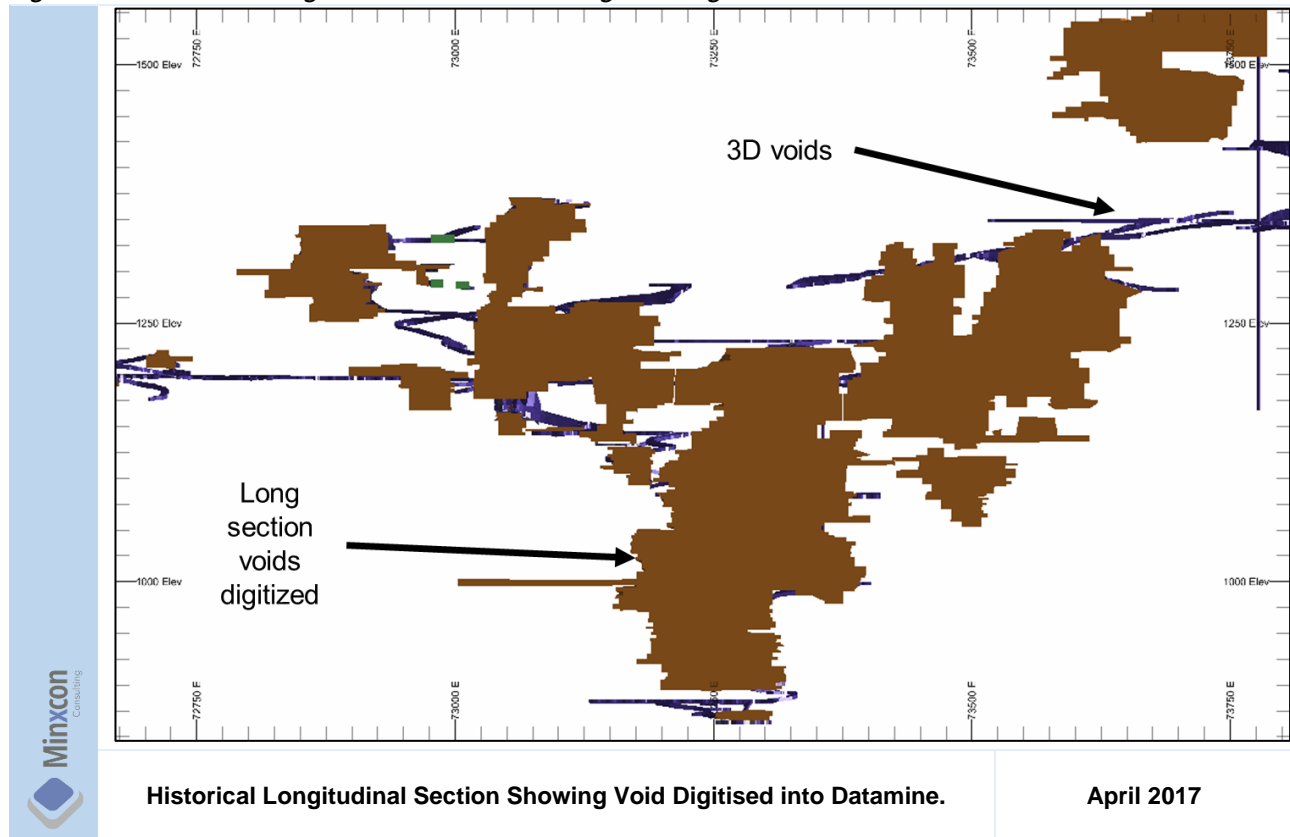


Figure 80 depicts the comparative final digital constructed voids to the scanned section in Figure 79 with all the final development and stoping areas included.

Figure 80: Historical Longitudinal Section Showing Void Digitised into Datamine


Block Model Validation

Visual Model Validation

The block model validation was carried out with regards a number of checks. During the block model grade interpolation, Minxcon conducted parallel Inverse Distance Squared (ID^2) and nearest neighbour estimates. A visual check and comparison with regard estimated block model values and drillhole values was also carried out on sections to ensure the estimate reflected the drillhole values.

Figure 81 depicts a clipped section showing the high grade and low grade modelled areas corresponding with those of the drillholes.

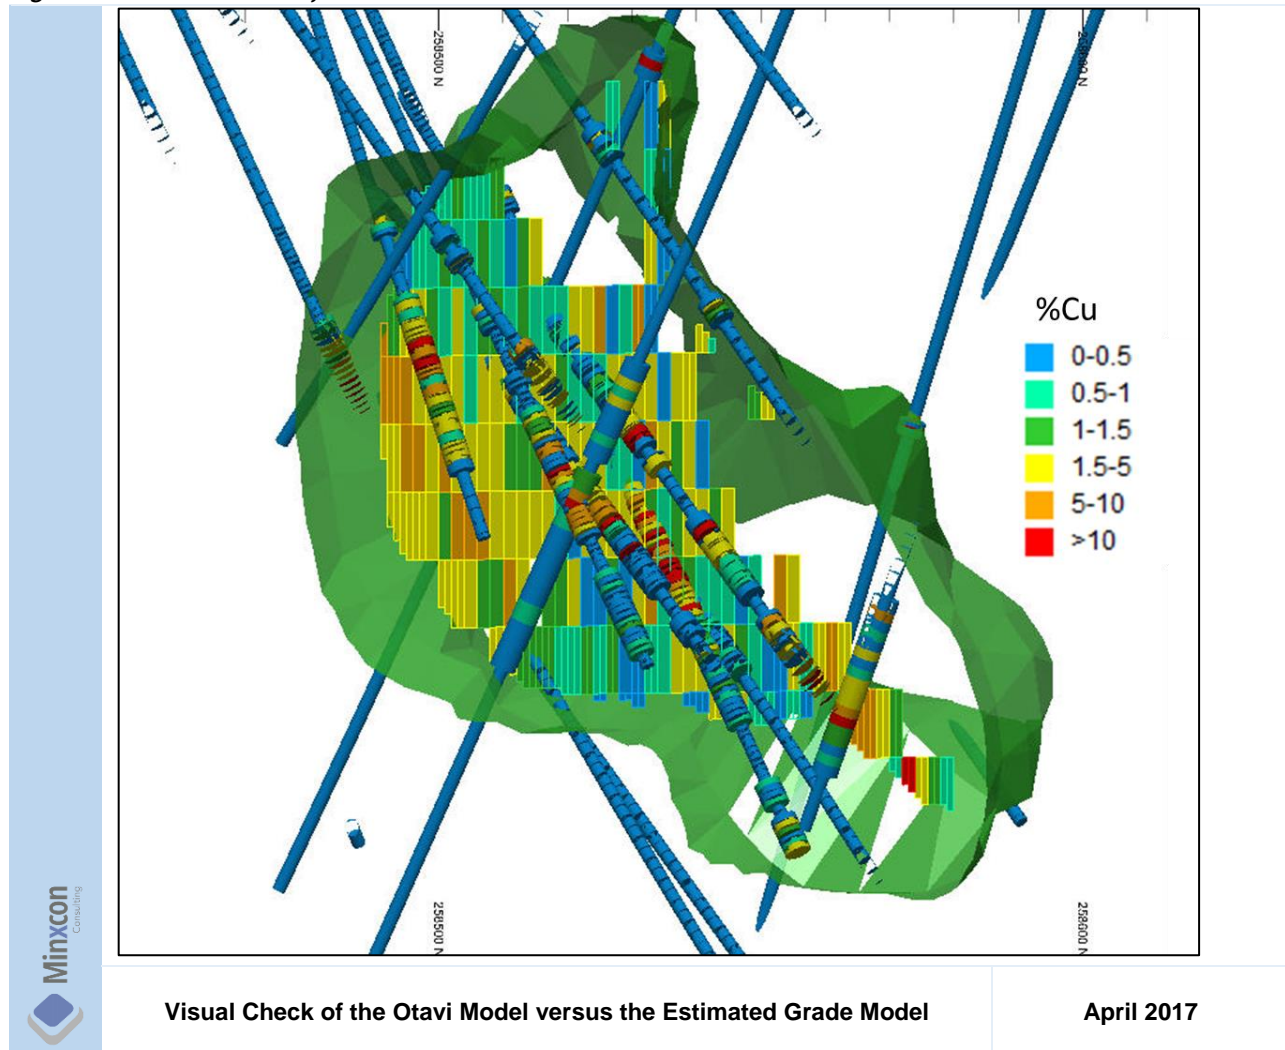Figure 81: Visual Check of the Otavi Model versus the Estimated Grade Model



Scatterplot Model Validation

In addition, scatter plots of the estimated block value versus the average drillhole value for the models was carried out and show a good correlation between the Ordinary Kriging estimate and the drillhole values. These scatter plots for each of the three areas are presented below for both copper and lead.

Figure 82 shows the correlation between the copper estimate and the drillholes used followed by the same for lead for Kombat section. The copper estimate generated a correlation co-efficient of 0.963, while the lead estimate generated a correlation co-efficient of 0.957.

Figure 82 Kombat Section Scatter Plot of the Copper and Lead Estimation versus the Average Drillhole Values

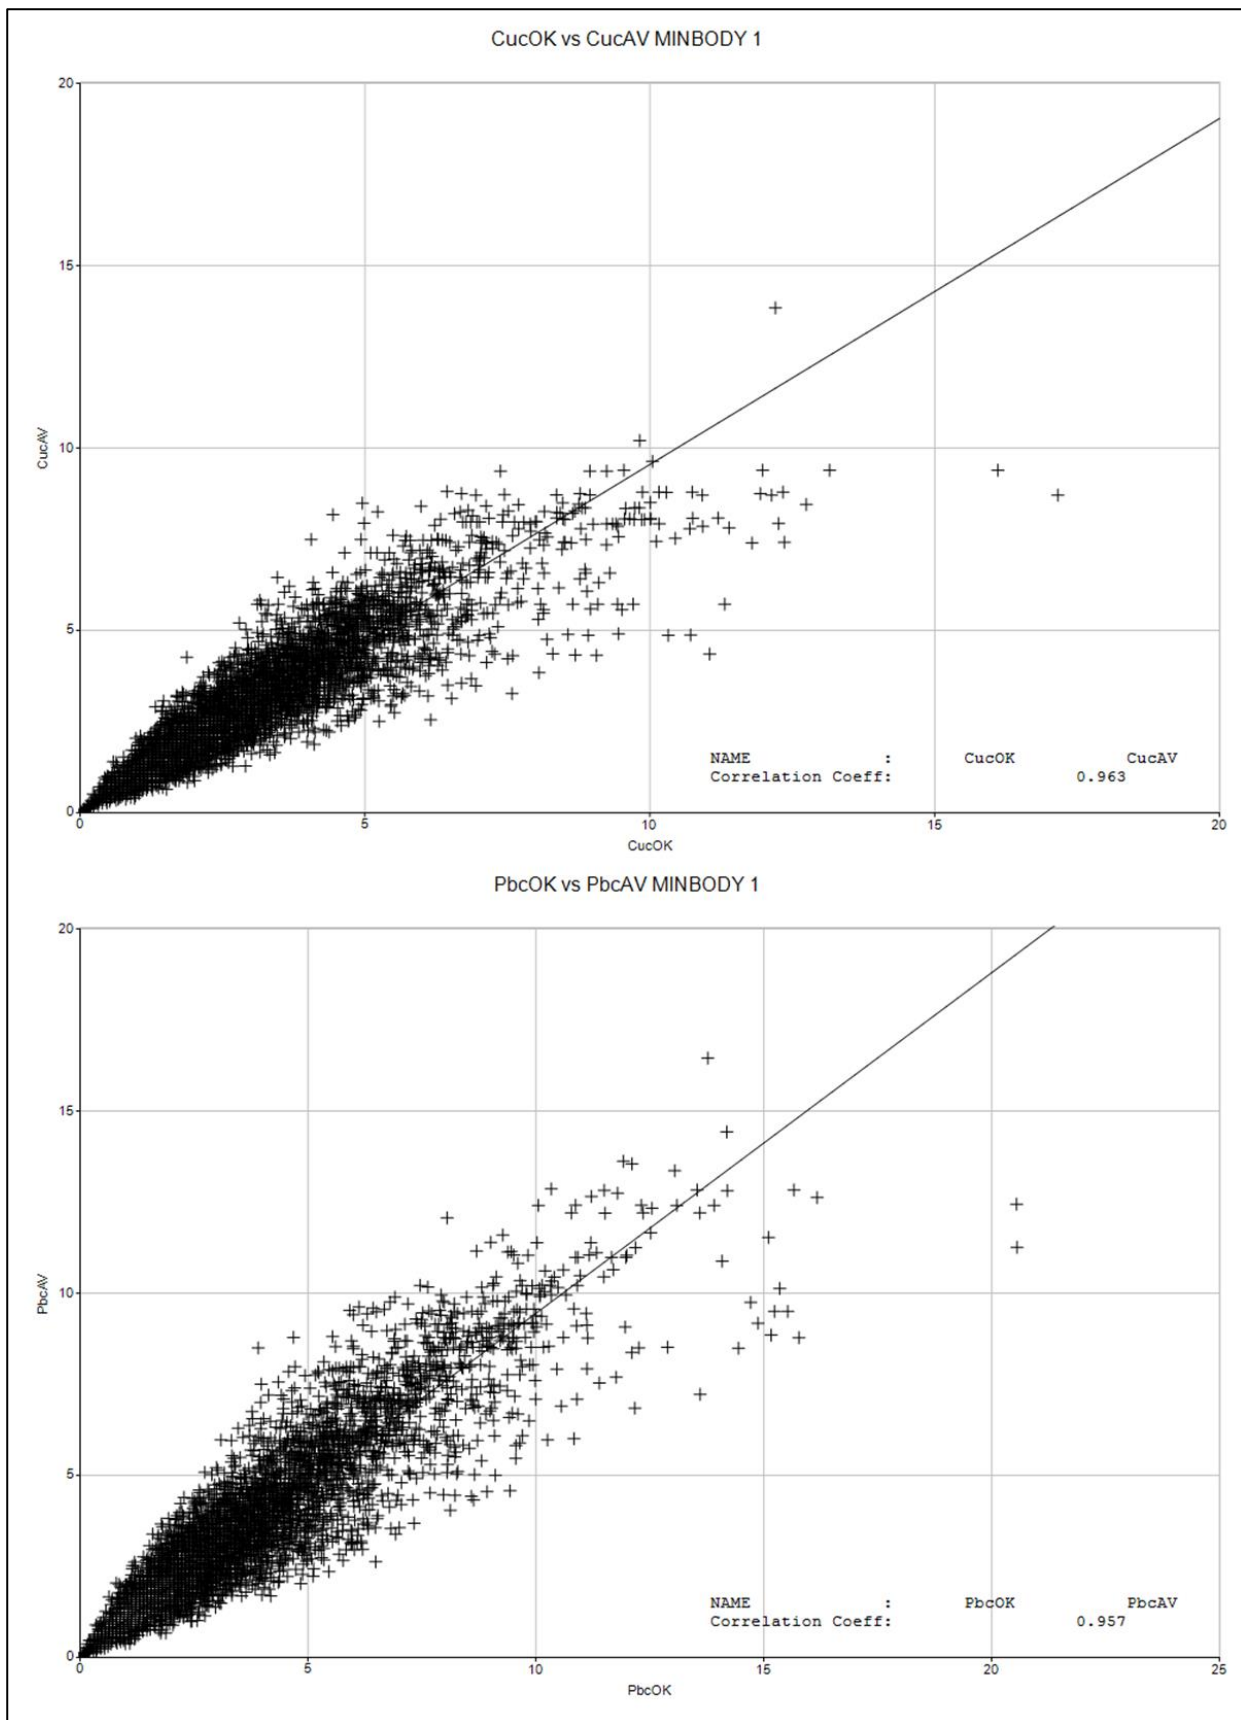


Figure 83 shows the correlation between the copper estimate and the drillholes used followed by the same for lead for the Asis section. The copper estimate generated a correlation co-efficient of 0.980, while the lead estimate generated a correlation co-efficient of 0.986.

Figure 83: Asis Section Scatter Plot of the Copper and Lead Estimation versus the Average Drillhole Values


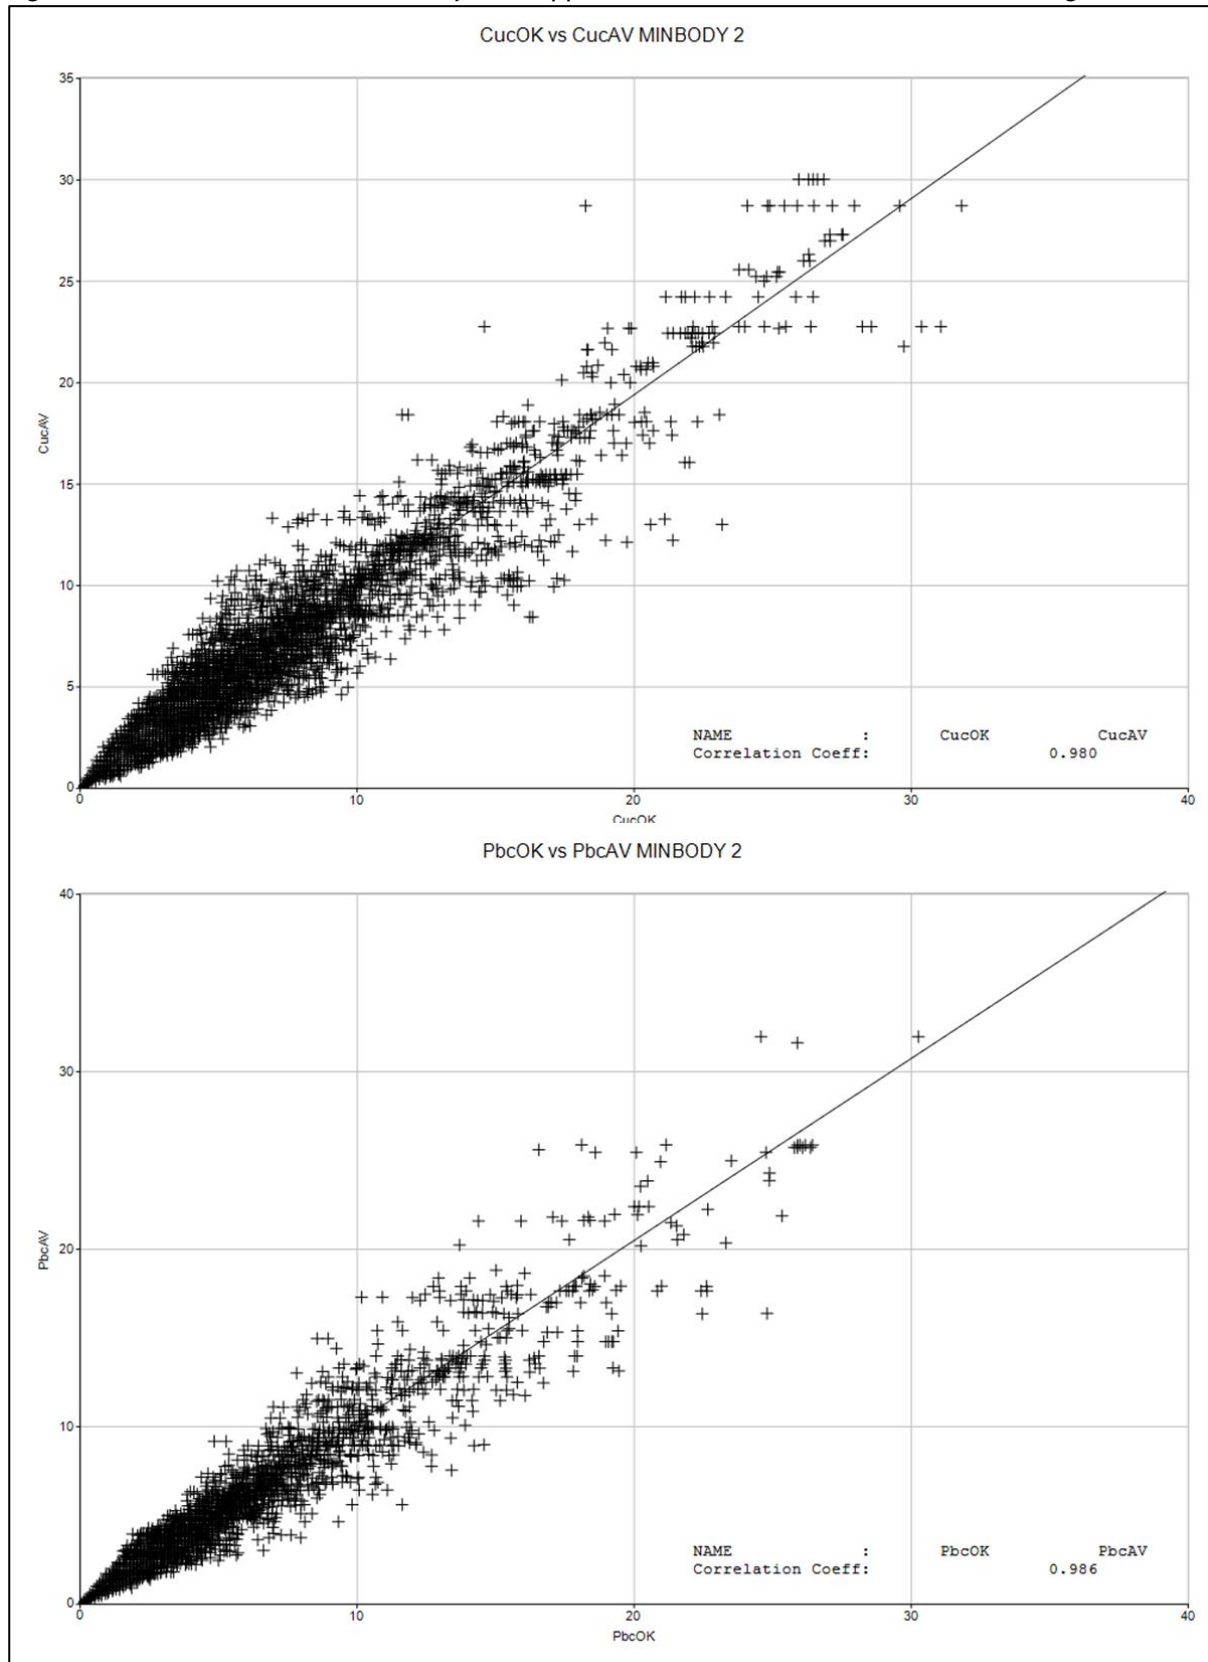


Figure 84 shows the correlation between the copper estimate and the drillholes used followed by the same for lead for the Otavi section. The copper estimate generated a correlation co-efficient of 0.994, while the lead estimate generated a correlation co-efficient of 0.975.

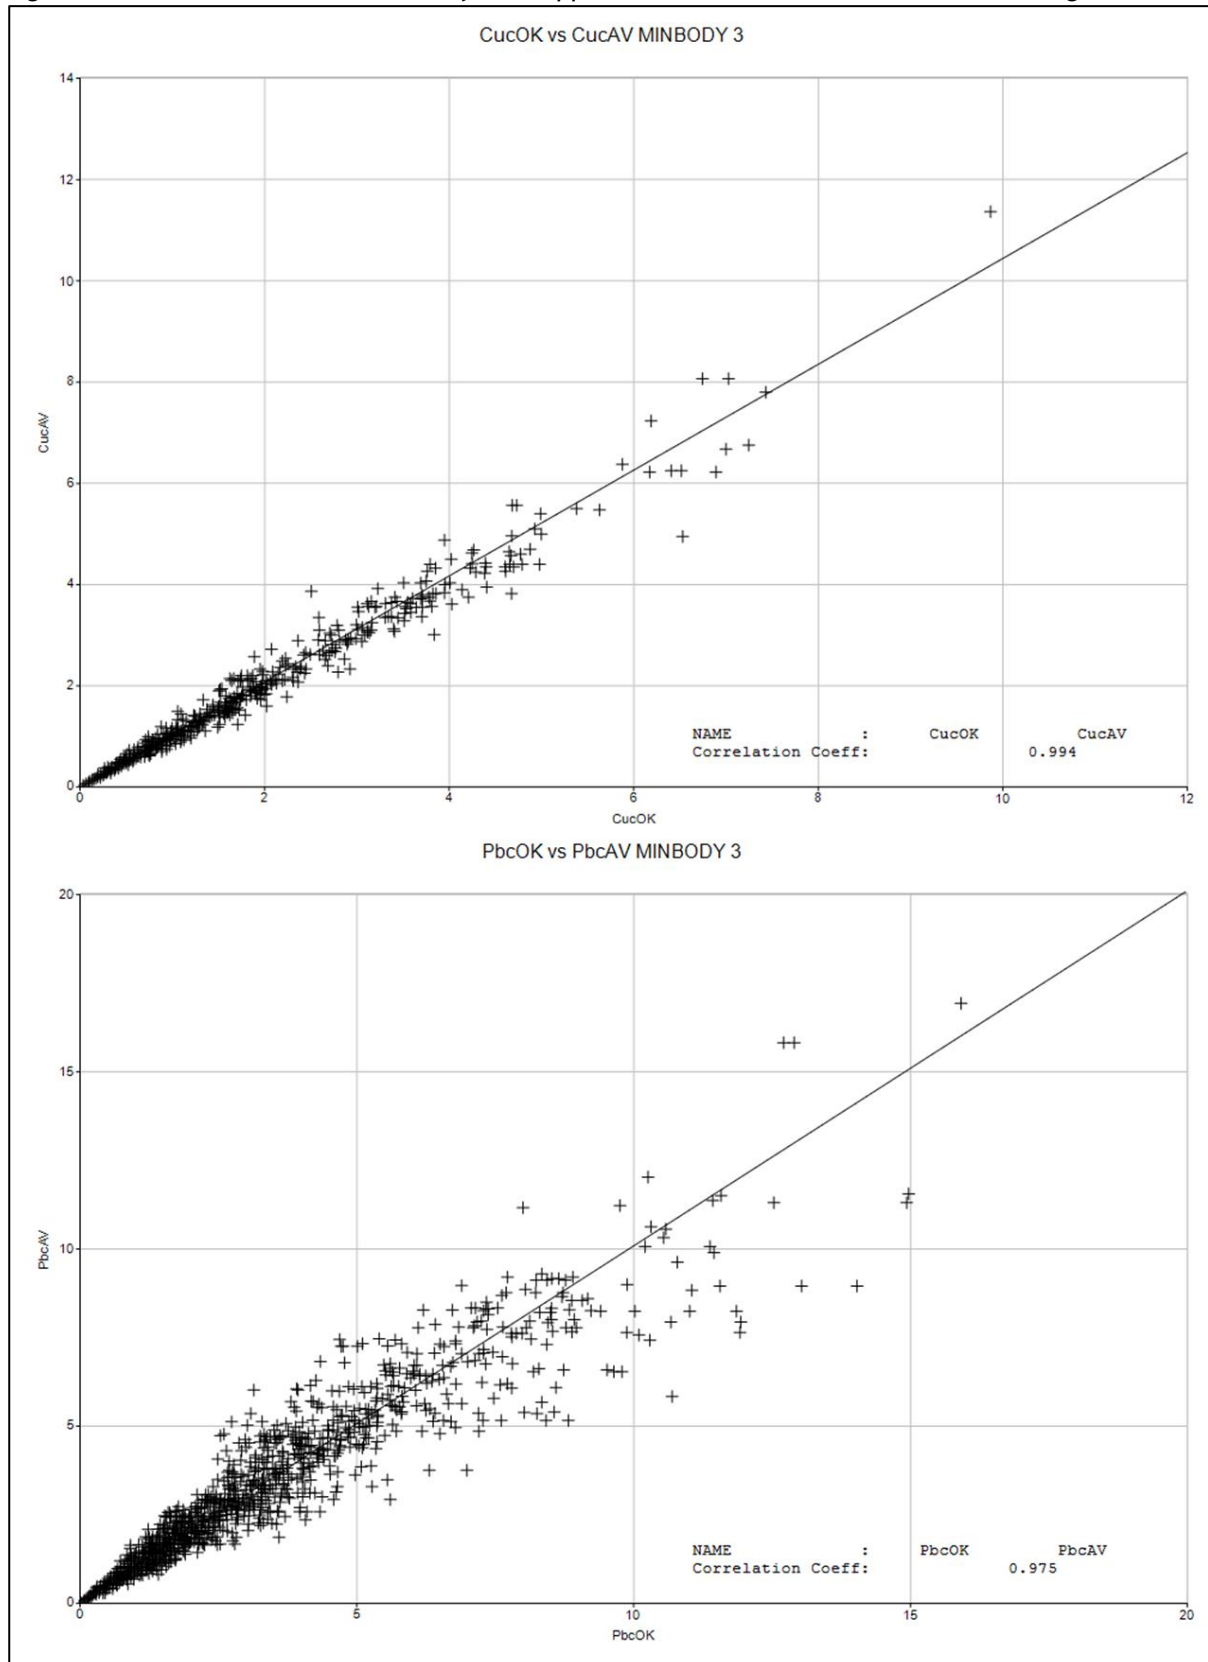Figure 84: Otavi Section Scatter Plot of the Copper and Lead Estimation versus the Average Drillhole Values




Swath Analysis Model Validation

A final validation was carried out by means of swath plots across the block model and the informing drillholes, both in plan view as well as in depth to compare the behaviour and estimation trends of the block model to that of the drillholes used to inform the block model. The swath widths in a north to south orientation for the Kombat and Asis sections were set at 200 m and numbered in sequence from west to east resulting in 21 swaths. The vertical swaths were conducted in 100 m layers from the surface down rendering a total of 10 swaths numbered top-down.


Kombat and Asis sections were considered as one model for the purposes of swath analysis and the overview plan (Figure 85) shows the location of the 21 swaths for the west to east comparison and the relative elevation of the 10 swaths utilised in the vertical analysis.

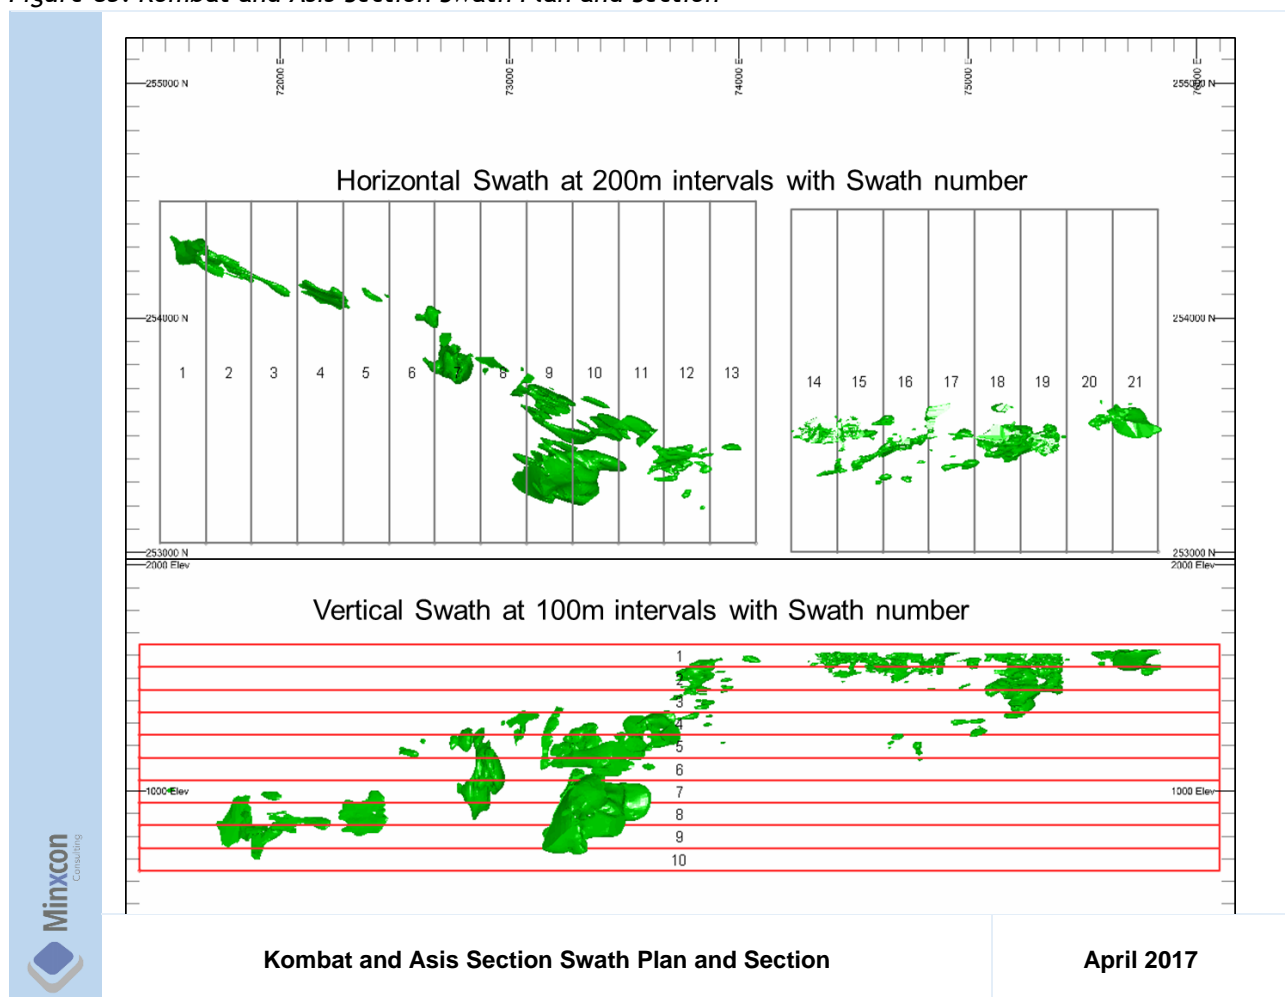Figure 85: Kombat and Asis Section Swath Plan and Section




The result of the west to east swath analysis for copper for Kombat and Asis sections is presented in Figure 86. It is immediately evident that the grade trends of the model largely reflect the trends of the informing drillholes. The vertical swath plot at the bottom of Figure 86 also depicts a close local correlation between the model and the informing drillholes.

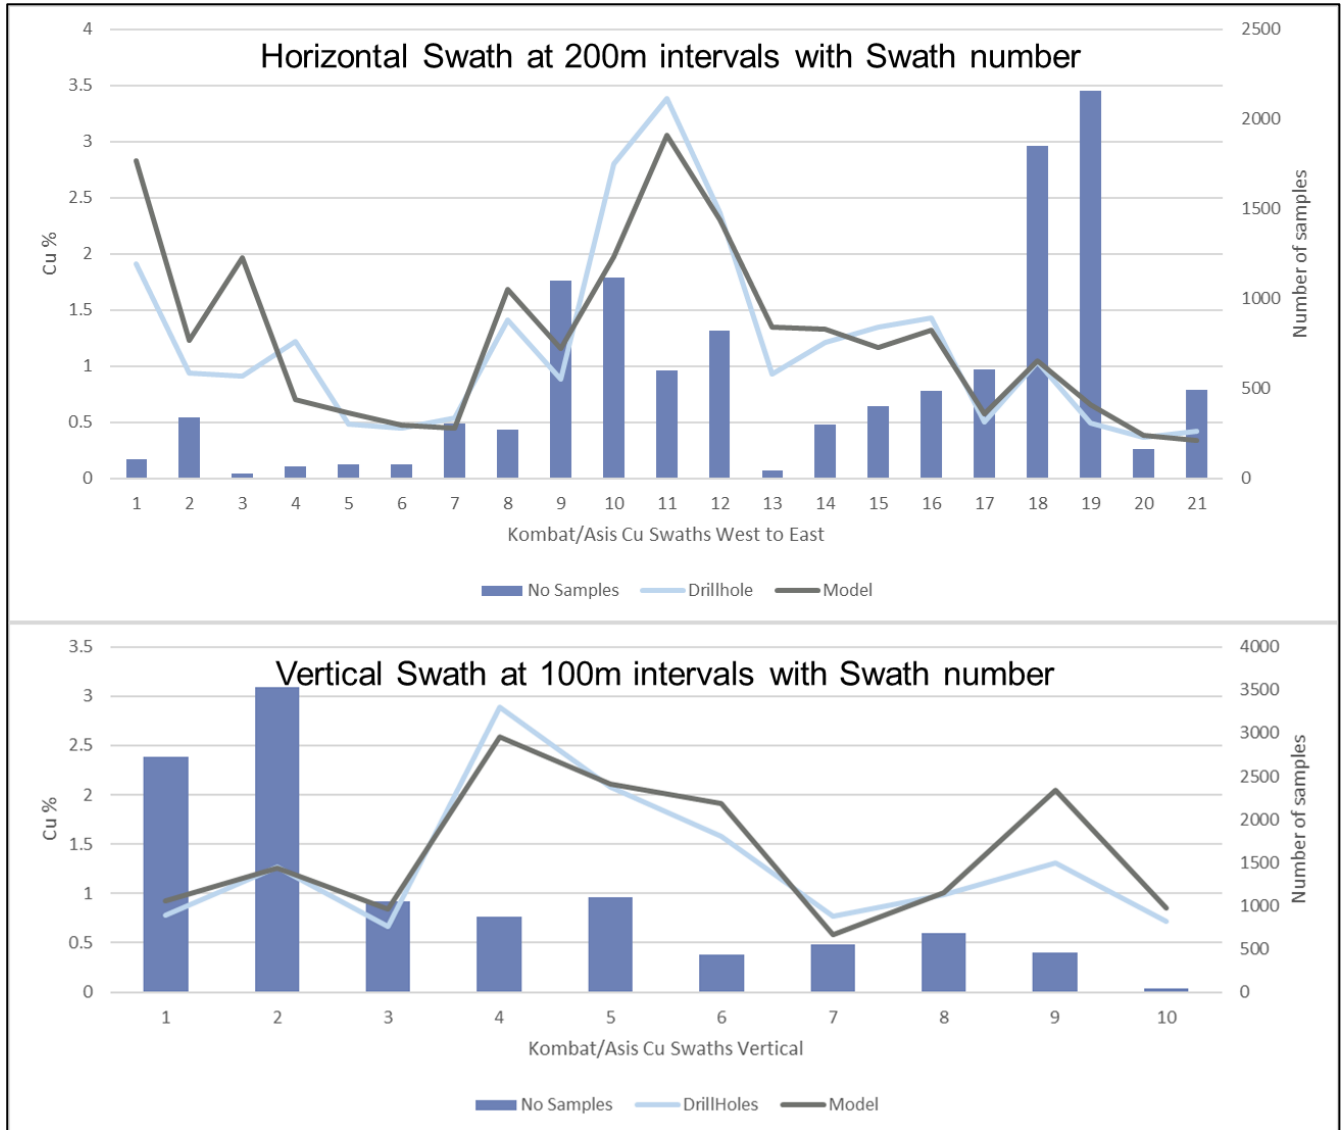Figure 86: Kombat/Asis Section Copper Swath Analysis East to West and Vertically




The result of the west to east swath analysis for lead for Kombat and Asis sections is presented in Figure 87. It is evident that the grade trends of the estimated model largely reflect the trends of the informing drillholes. The vertical swath plot at the bottom of Figure 87 also depicts a close local correlation between the model and the informing drillholes.

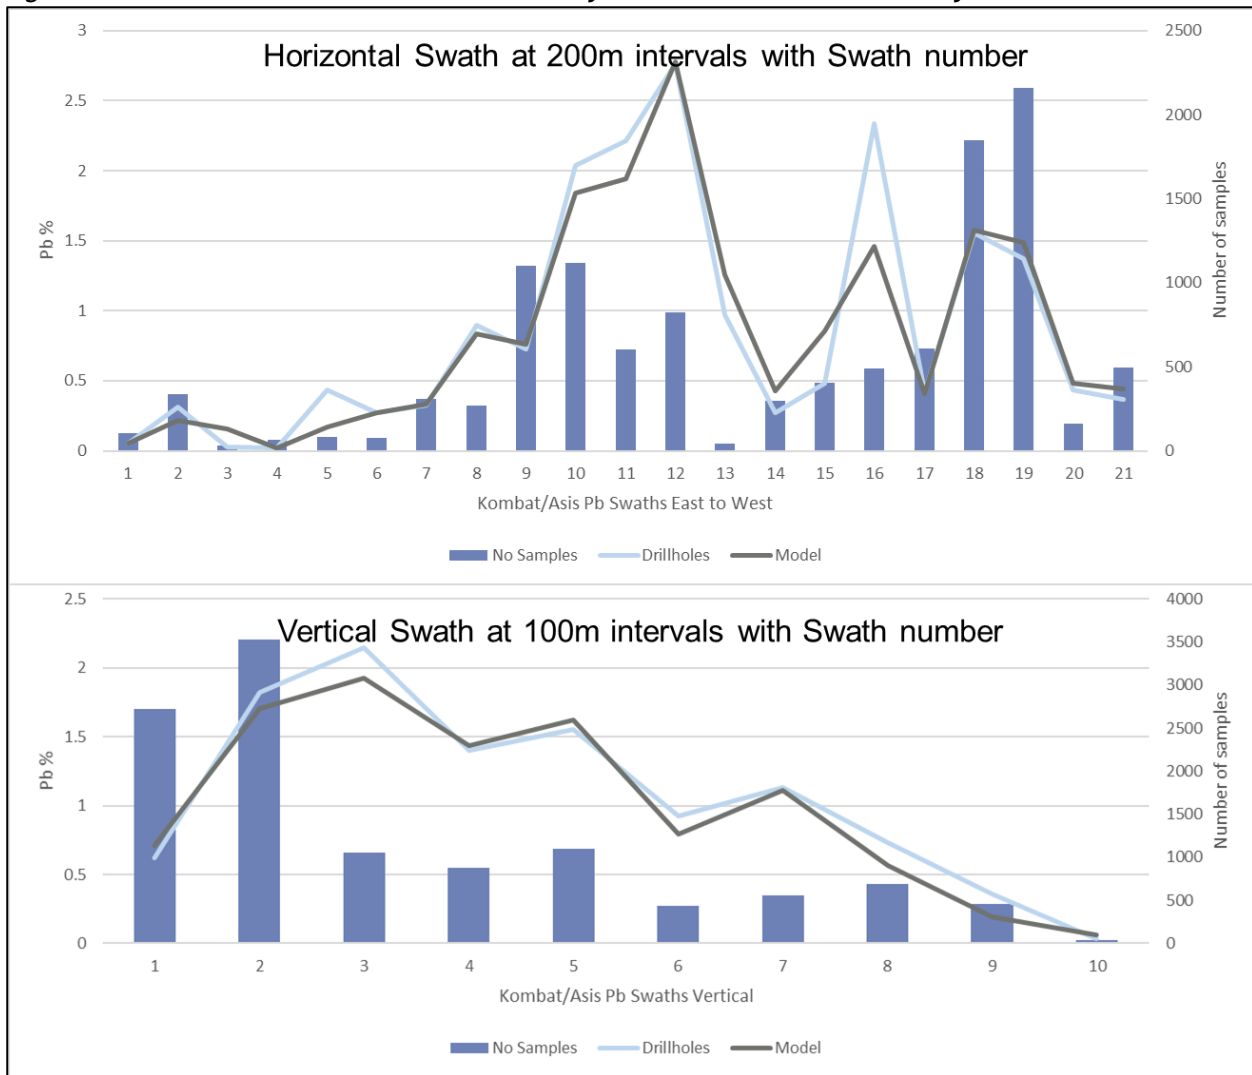Figure 87: Kombat/Asis Section Lead Swath Analysis East to West and Vertically




The Otavi section swath analysis and the overview plan (Figure 88) shows a total of five swaths were conducted at 25 m intervals from west to east on strike while six were generated for the vertical swath analysis which were numbered sequentially top -down. Swath spacing was small due to the relatively small size of the Otavi orebody.

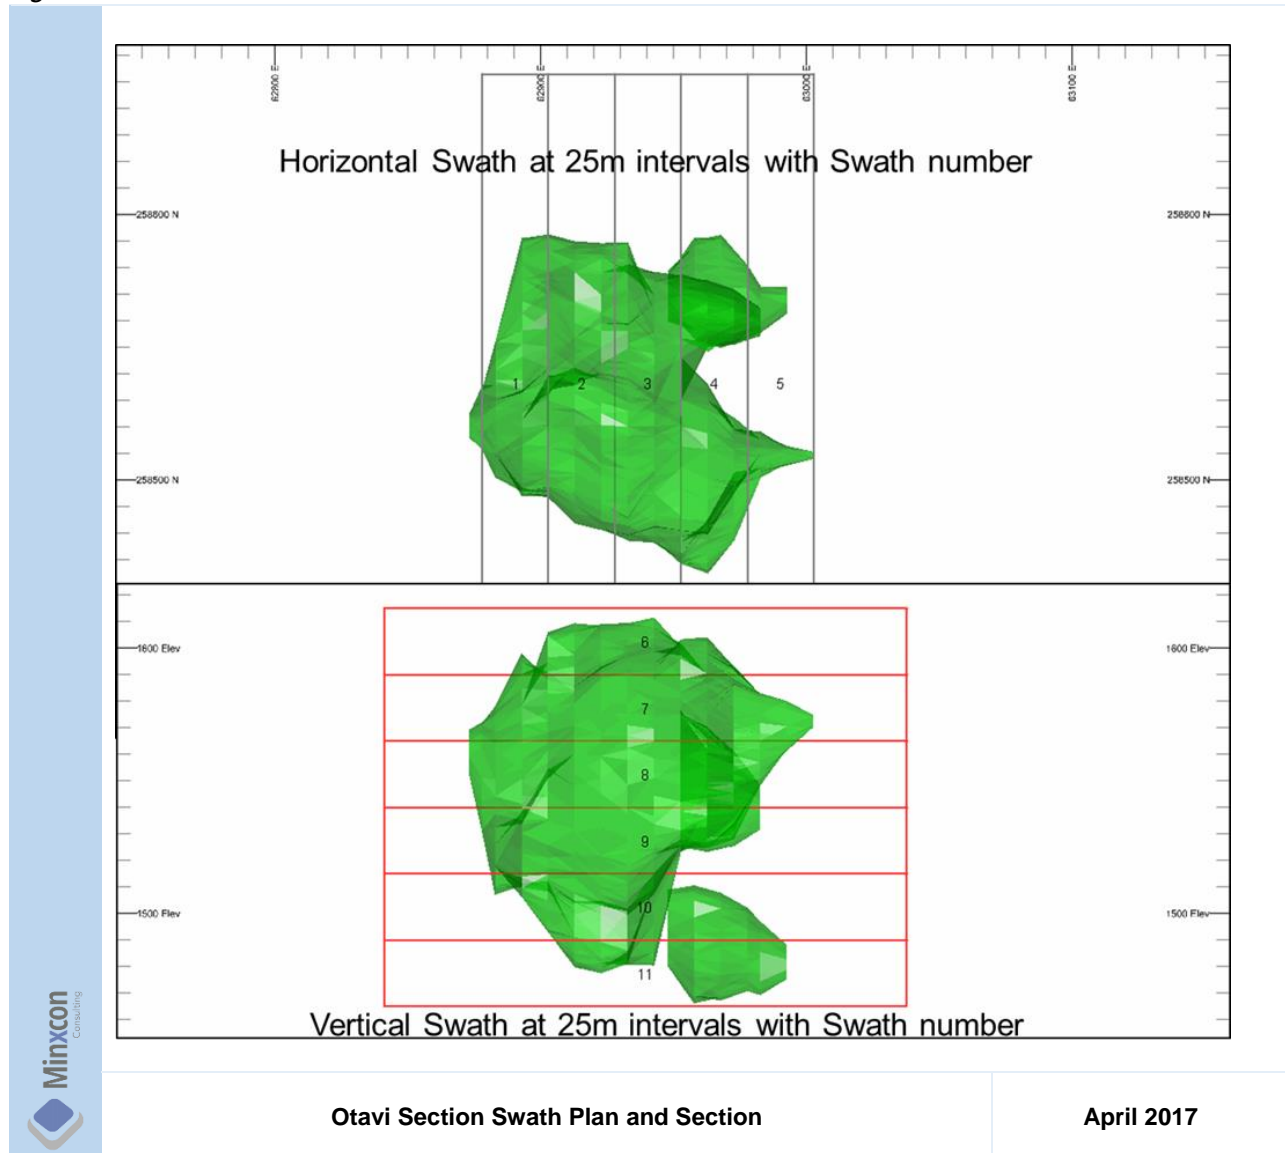Figure 88: Otavi Section Swath Plan and Section




The result of the west to east swath analysis for copper for Otavi is presented in Figure 89. The grade trends of the model largely reflect the trends of the informing drillholes. The vertical swath plot at the bottom of Figure 89 also depicts a close local correlation between the model and the informing drillholes.

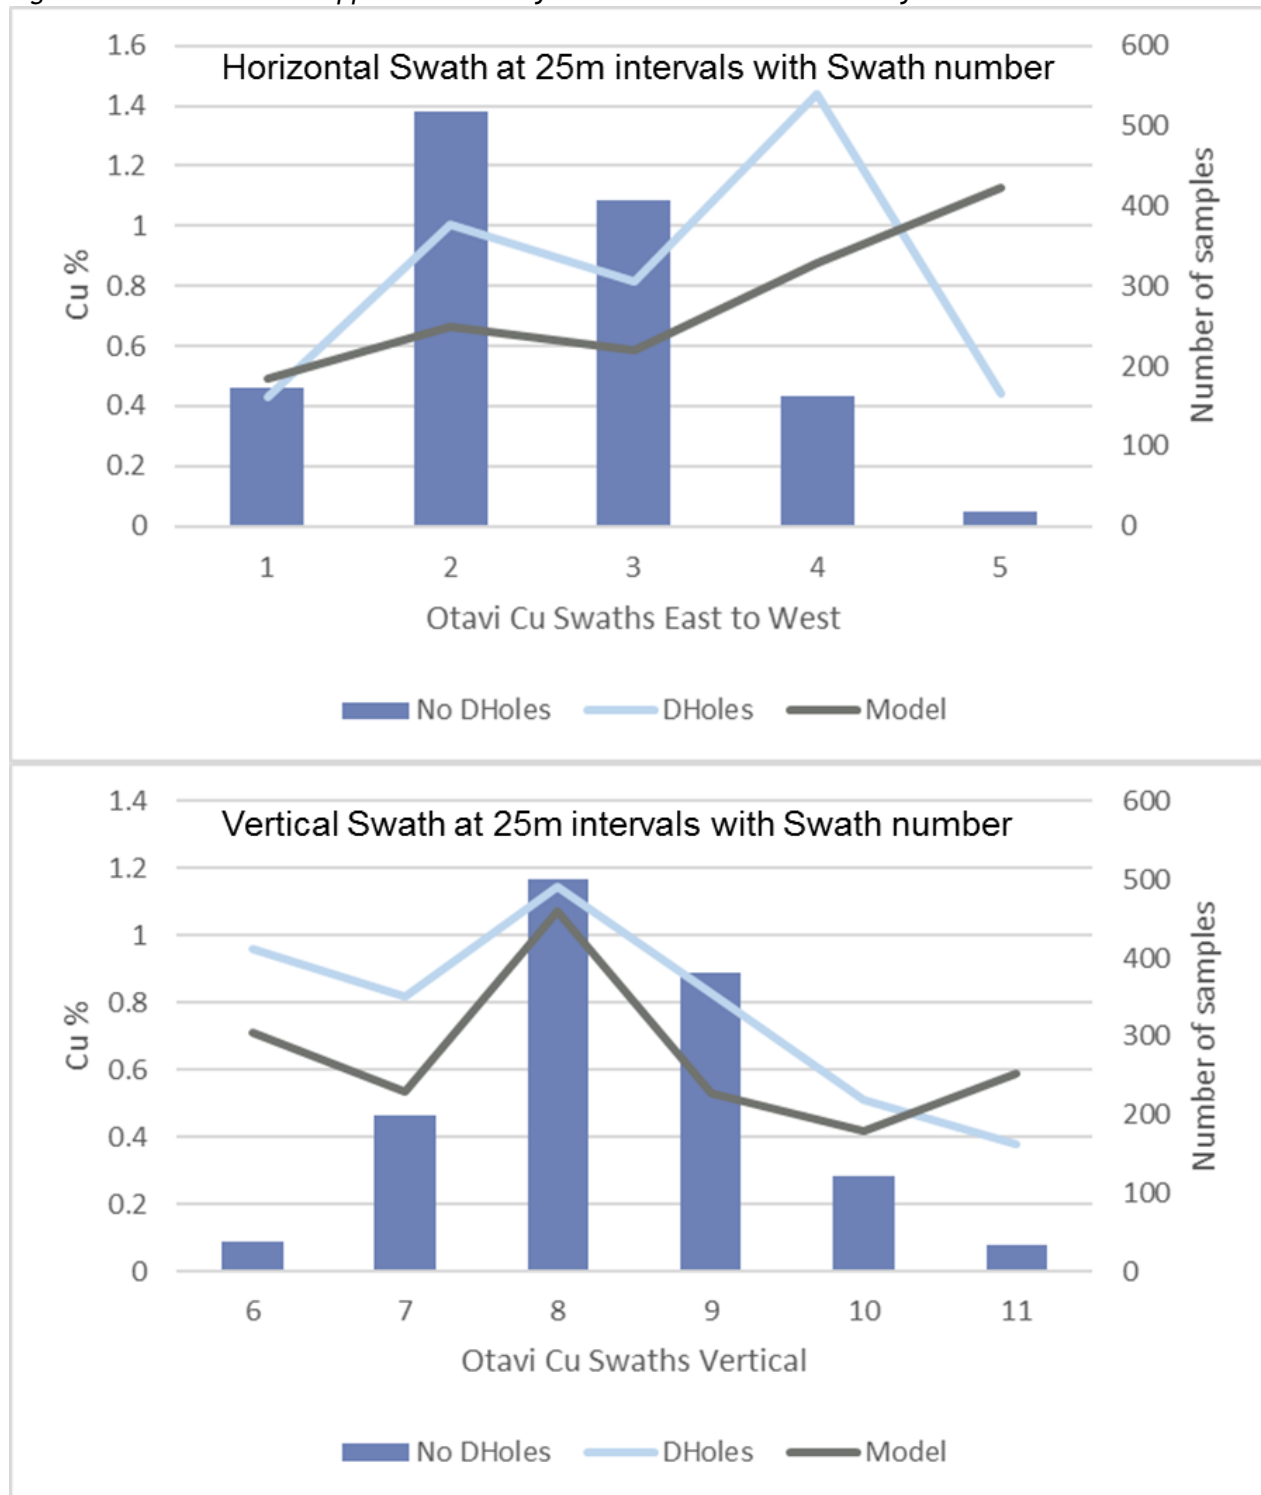Figure 89: Otavi Section Copper Swath Analysis East to West and Vertically



The result of the west to east swath analysis for lead for Otavi is presented in Figure 90. The grade trends of the model largely reflect the trends of the informing drillholes. The vertical swath plot at the bottom of Figure 90 also depicts a close local correlation between the model and the informing drillholes.

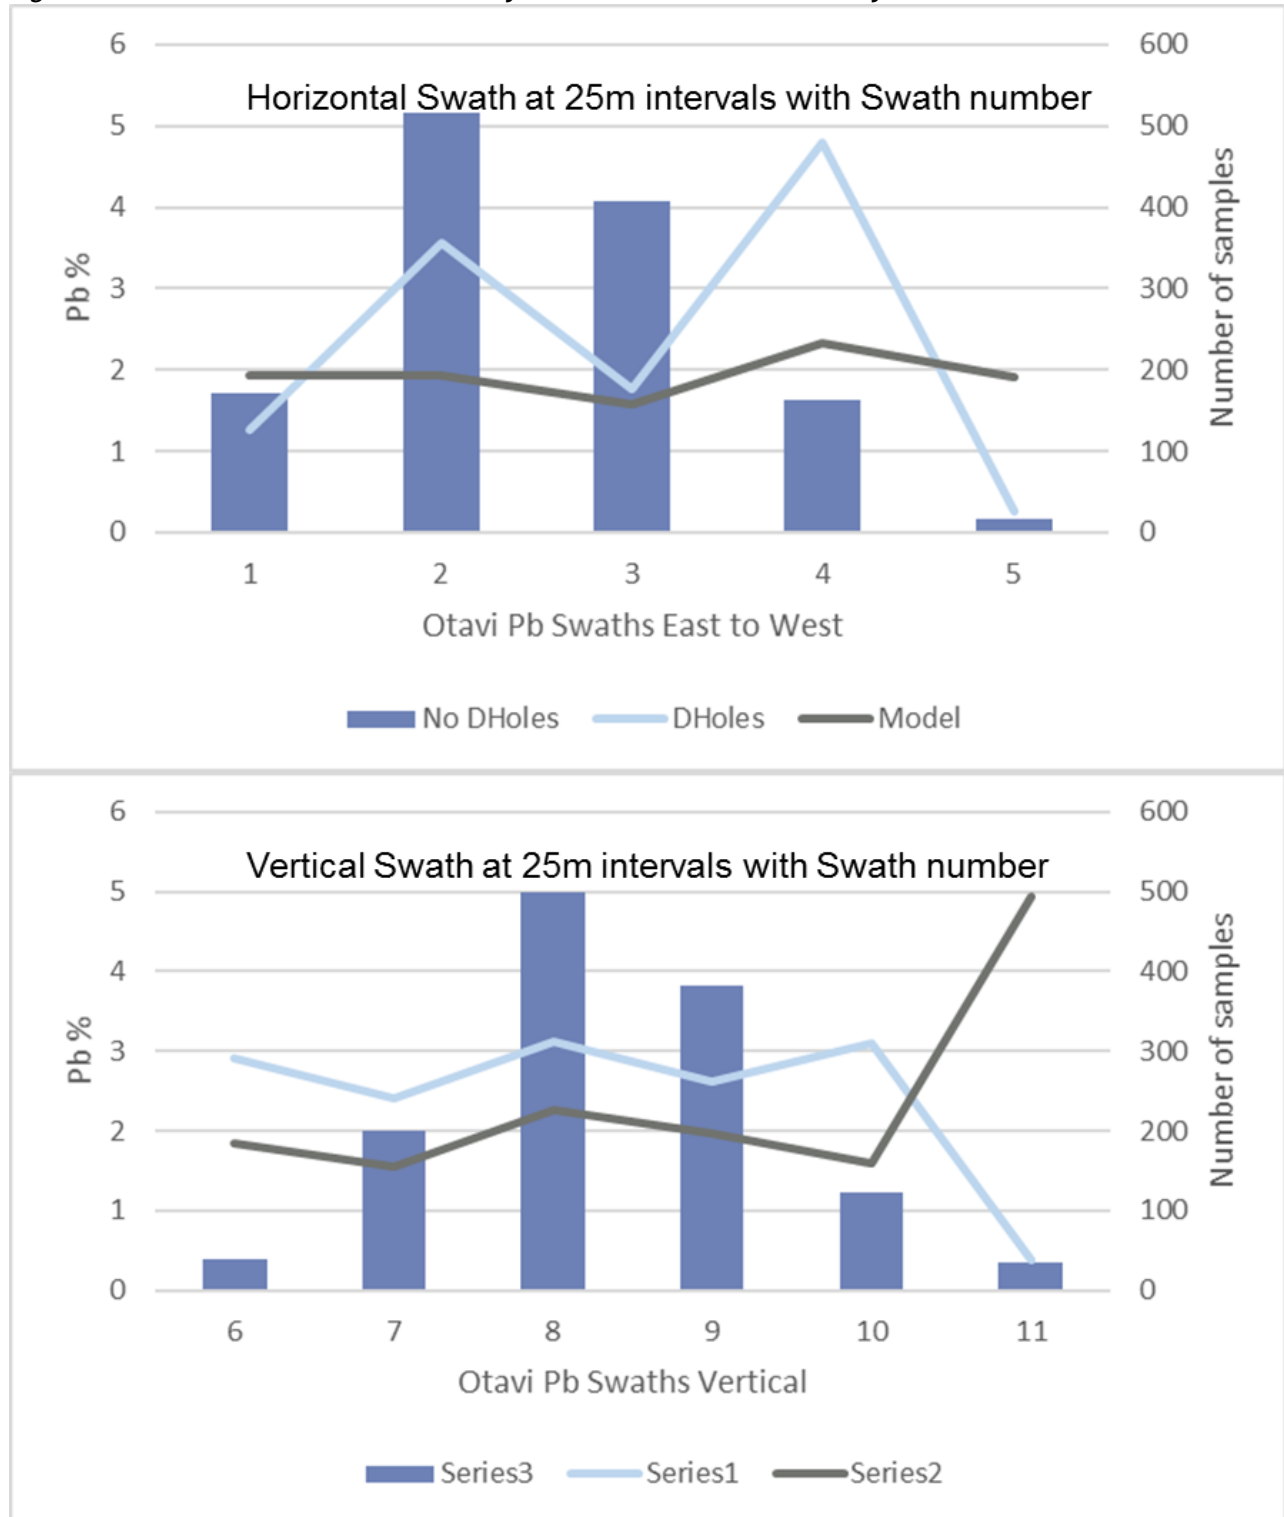Figure 90: Otavi Section Lead Swath Analysis East to West and Vertically



Item 14 (b) - DISCLOSURE REQUIREMENTS FOR RESOURCES

All Mineral Resources have been categorised and reported in compliance with the definitions embodied in the CIM Definition Standards on Mineral Resources and Mineral Reserves adopted by the CIM Council (incorporated into NI 43-101). As per CIM Code specifications, Mineral Resources have been reported separately in the Measured, Indicated and Inferred Mineral Resource categories. Inferred Mineral Resources

have been reported separately and have not been incorporated with the Measured and Indicated Mineral Resources.

Item 14 (c) - INDIVIDUAL GRADE OF METALS

Mineral Resource Classification

The entire Mineral Resource has been classified as an Inferred Mineral Resource, thus no Measured nor Indicated Mineral Resources are reported.

Although QAQC from the 2012-2015 drilling programmes are available and no fatal flaws were identified in these checks, the historical drilling predating the 2012 drilling campaign does not have the robust QAQC required to improve the Mineral Resource classification. In addition, no underground stope sampling was available, nor any detailed stope outlines or stope voids to conduct accurate depletions of the modelled grade shells. In some instances, the grade shells had to be generated and expanded to encompass historic mined out areas where it was assumed that the grade was sufficient to warrant mining.

It is Minxcon's view that due to the reasons cited above, an Inferred Mineral Resource classification is warranted. The Inferred Mineral Resource classification is also warranted (as opposed to only being referred to as an Exploration Target) due to the fact that the dataset is extremely large due to the long mining history. In addition, the drillhole dataset was found to be in good condition and easily traceable back to drillhole hardcopies currently stored on the mine. Previous operational staff were also prepared to vouch for the quality of the data and also expressed agreement with the Minxcon modelled interpretation.

Item 14 (d) - FACTORS AFFECTING MINERAL RESOURCE ESTIMATES

Depletions

Owing to the uncertainty surrounding the exact location of the 3D stoping voids, Minxcon is of the view that the depletion should and does play a significant role in the Mineral Resource classification. It is possible that the final tabulated Mineral Resources might produce a somewhat over-depleted tonnage due to the methodology employed in depleting right through all the mineralised zones, hence the Inferred Mineral Resource classification. It is Minxcon's view that the depletions as conducted might be aggressive in their application, thus resulting in a slightly conservative tonnage estimate.


Pit Optimisation

In order to determine the quantities of material offering "reasonable prospects for eventual economic extraction" by means of an open pit, Minxcon used a pit optimizer together with reasonable mining assumptions to evaluate the proportions of the block models that could be "reasonably expected" to be mined from an open pit. The results are used as a guide to assist in the preparation of a Mineral Resource statement, as well as to select an appropriate Mineral Resource reporting cut-off grade.

The pit optimisation shows that a maximum depth of 150 m at a cut-off grade of 0.77% Cu with 70% Cu recovery (or 6.40% for Pb with a 25% Pb recovery) is possible for the Kombat open pits, while the Otavi area the same depth limit is reached at a Copper cut-off of 0.77% Cu with a 70% recovery (or 2.00% Pb at 80% Pb plant recovery). The 150 m has been used as a Mineral Resource depth cut-off to delineate Mineral Resources exploitable by means of open pit. Mineral Resources deeper than 150 m are declared at a higher cut-off grade due to being only economically exploitable by means of underground mining.

The final optimised pits over the Kombat section are presented in Figure 91 below. The top diagram presents a plan view of the area under consideration, while the underlying diagram presents the corresponding longitudinal section.

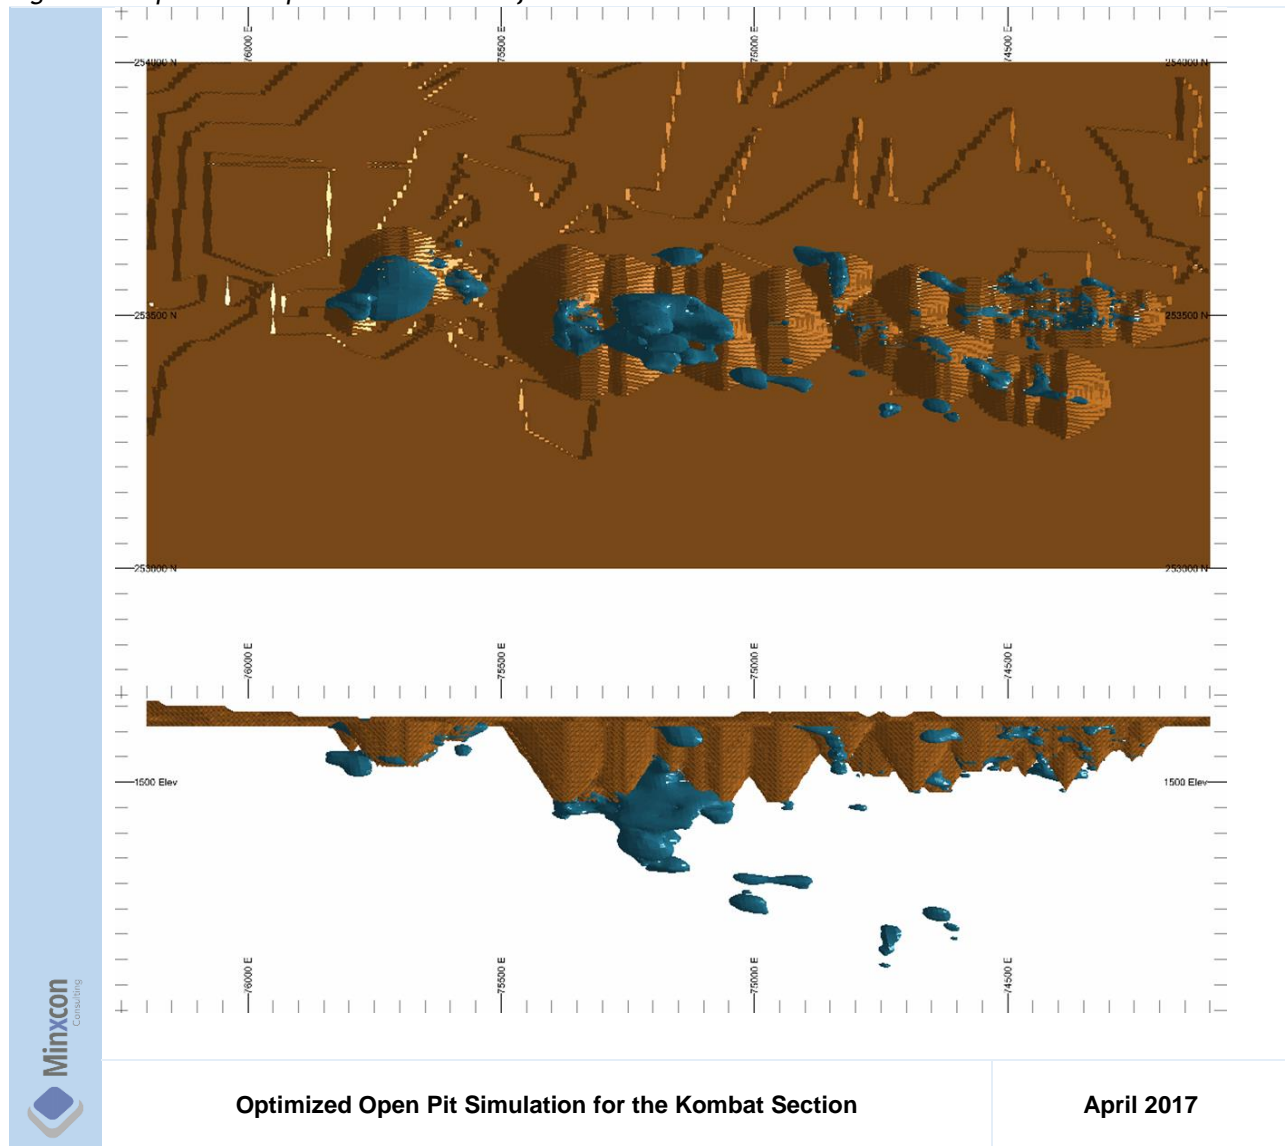Figure 91: Optimised Open Pit Simulation for the Kombat Section




Cut-off Parameters

The Mineral Resource cut-off grades for the respective open pit and underground accessible Mineral Resources were based upon optimistic mining considerations. The Mineral Resource cut-offs should not be considered in terms of Mineral Reserves, but as a long term view based on realistic operational and processing costs, as well as long term projected commodity prices as explained in the paragraph below.

The pay limit for the mining operation is based upon a copper price of USD3.19/lb and a lead price of USD1.05/lb, which represents the 80th percentile of the historical real term commodity prices since 1980 (Figure 92). These commodity prices were rounded to USD3/lb and USD1/lb for copper and lead respectively.

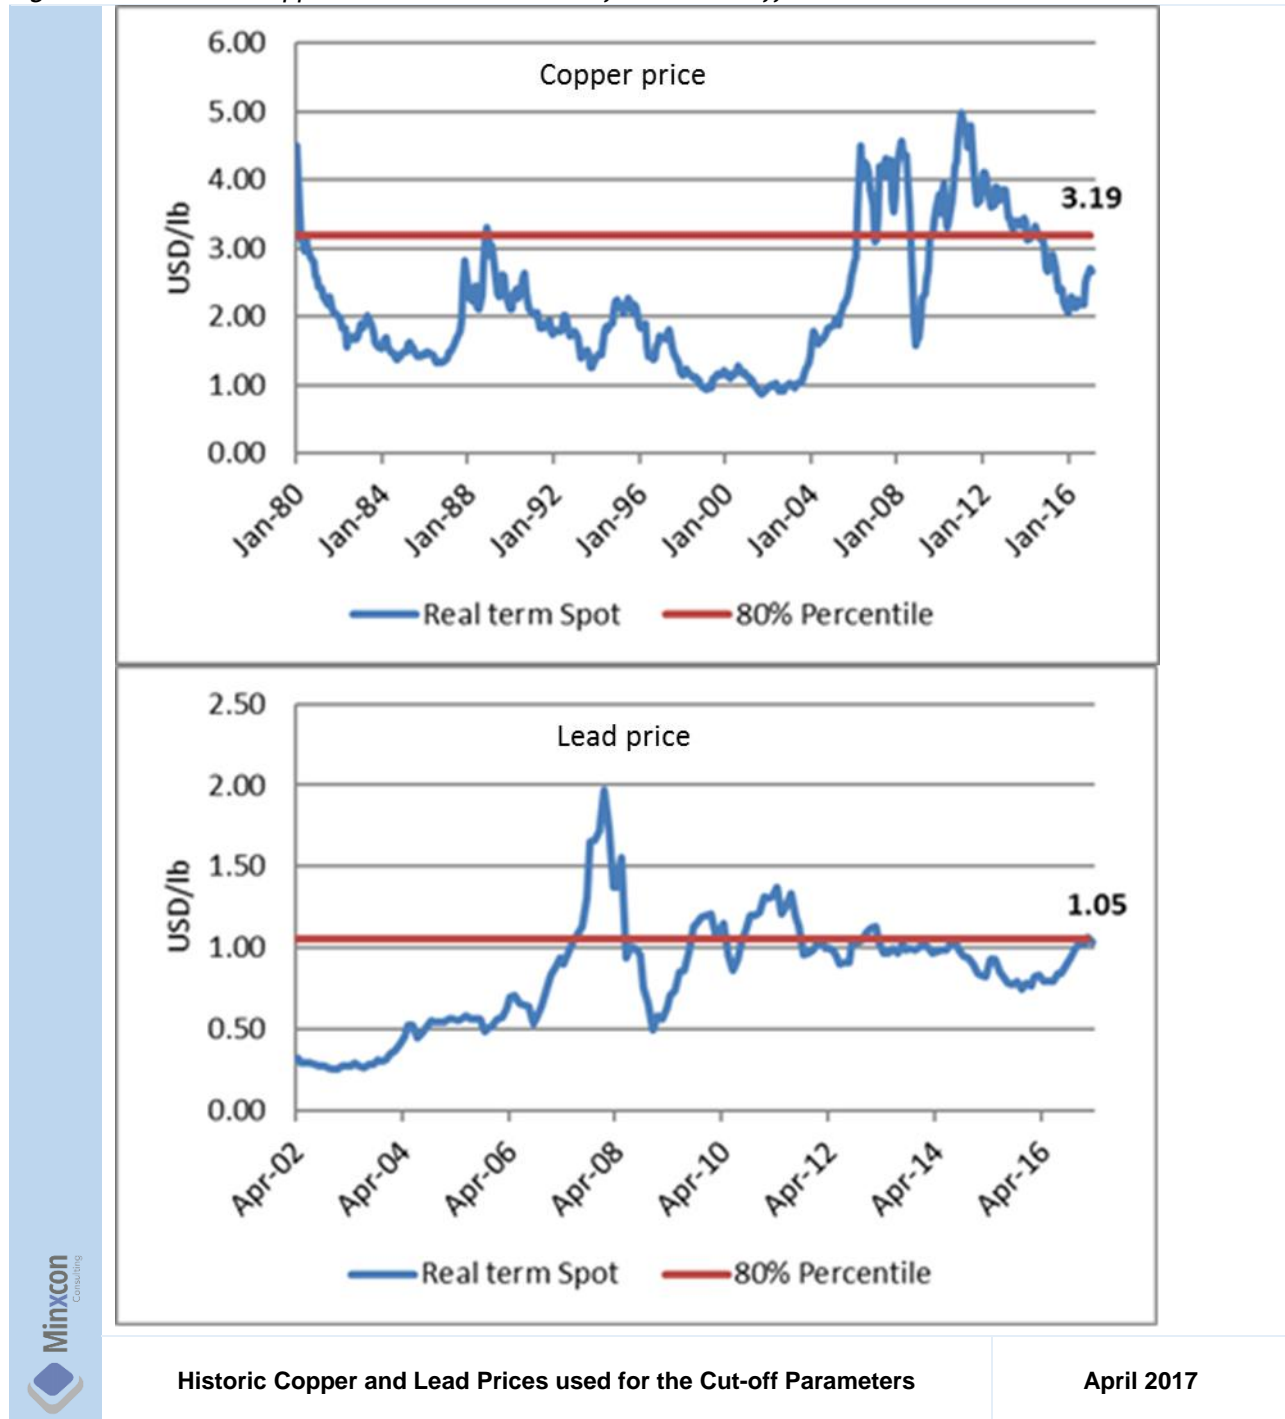Figure 92 Historical Copper and Lead Prices used for the Cut-off Parameters



For the underground mining, a mining cost of USD14.52 per tonne was applied with an overhead mining cost of USD10.21 per tonne. Processing cost for the plant was calculated at USD13.4 per tonne.

For the open pit calculations, the processing cost remained the same while a mining cost of USD1.68 per tonne and plant overhead costs of USD35.51 per tonne were applied.

The recoveries for the copper was calculated at 70% for both Kombat and Otavi. Owing to the nature of the orebodies under consideration Lead recoveries are seen to vary significantly in relation to grade. The lead recoveries were calculated at 25% for Kombat and 80% for Otavi. The relevant %Cu cut-off applicable to the different mining areas are presented in Table 20.

Table 19: Cut-off Values Relative to Cu and Pb Recovery Values as Calculated for Each Mining Area

Description	Cu Recovery	Pb Recovery	Cu Cut-off	Conversion Factor to CuEq
	%	%	%	
Kombat Open Pit	70.00	25.00	0.77	0.12
Otavi Open Pit	70.00	80.00	0.77	0.39
Underground %Cu	90.00	30.00	1.40	1.09

Mineral Resource Statement

The Mineral Resource statement for the Kombat operations is presented relative to the 150 m depth cut-off with respect to the possible employable mining strategy. The open pittable Mineral Resources are stated at copper equivalent ("CuEq") value of CuEq 0.77%, the underground mineable Mineral Resources are stated at the value of CuEq 1.4%. The conversion factor to copper equivalent is indicated in Table 19 above.

The Mineral Resources have been depleted for the Kombat and Asis Sections as described in the sections above. No historical voids are available for the Otavi section, but it was indicated by mine personnel that very little development has taken place. This was evidenced by Minxcon personnel upon the site visit to Otavi. The Otavi section in the Mineral Resource has been discounted by 1% in order to account for historical mining with an additional 7.5% as a porosity factor due to the presence of karst voids. An additional 15% geological loss has been applied to the Mineral Resources for all sections. Density for the hard rock has been estimated.

Only Inferred Mineral Resources have been calculated for the Kombat operations as indicated above.

Table 20 presents the estimated Mineral Resources for the potential open pit areas.

Table 20: Open Pittable Mineral Resources for the Kombat Operations at a Copper Equivalent Cut-off of CuEq 0.77% as at April 2017

Section	Mineral Resource Classification	Tonnes	Density	Cu	Pb	Ag	Cu Content	Pb Content	Ag Content
		Mt	t/m ³	%	%	ppm	t	t	kg
Kombat East	Inferred	1.208	2.82	1.36	1.01	1.72	16,465	12,187	2,074
Kombat Central	Inferred	0.848	2.82	1.79	0.33	6.90	15,135	2,767	5,848
Kombat West	Inferred	0.354	2.88	2.76	2.63	2.20	9,785	9,303	780
Kombat Total	Inferred	2.410	2.83	1.72	1.01	3.61	41,385	24,257	8,702
Gross Otavi	Inferred	0.643	2.84	0.93	2.50	0.85	6,006	16,053	546
Gross Otavi Total	Inferred	0.643	2.84	0.93	2.50	0.85	6,006	16,053	546
Total Open Pit	Inferred	3.053	2.83	1.54	1.35	2.98	47,391	40,310	9,248

Note:

1. Historical mine voids have been depleted from the Mineral Resource.
2. Historical mine voids were not available for Otavi so the tonnage has been reduced by 1% for historical mining.
3. Additional 7.5 % porosity factor has been applied to Otavi for the karst voids.
4. The open pit Mineral Resource is declared to a depth of 150 m with a CuEq cut off of 0.77 %.
5. The underground Mineral Resource (below 150m) is declared at a CuEq cut off of 1.4 %.
6. No tailings have been declared at a 0.4 % Cu cut off (upside potential at 0.3 % Cu cut-off).
7. Densities for the hard rock material have been modelled.
8. A geological loss of 15 % has been applied to the Mineral Resource.
9. All reported Mineral Resources are limited to fall within the property boundaries of the project area.
10. Columns may not add up due to rounding.
11. The Inferred Mineral Resources have a large degree of uncertainty as to their existence and whether they can be mined economically. It cannot be assumed that all or any part of the Inferred Mineral Resource will be upgraded to a higher confidence category.

Table 21 presents the estimated Mineral Resources for the potential underground areas.

Table 21 Underground Mineral Resources for the Kombat Operations at a Copper equivalent Cut-off of CuEq 0.77% as at April 2017

Section	Mineral Resource Classification	Tonnes	Density	Cu	Pb	Ag	Cu Content	Pb Content	Ag Content
		Mt	t/m ³	%	%	ppm	Tonnes	Tonnes	Kg
Kombat East	Inferred	0.024	2.87	1.90	2.94	0.61	459	708	15
Kombat Central	Inferred	-	-	-	-	-	-	-	-
Kombat West	Inferred	0.104	2.91	2.79	4.15	3.27	2,899	4,307	339
Kombat Total	Inferred	0.128	2.90	2.63	3.92	2.77	3,358	5,015	354
Asis West	Inferred	2.475	2.88	4.05	1.28	32.36	100,214	31,735	80,078
Asis Gap	Inferred	0.166	2.83	2.35	0.35	21.15	3,909	590	3,514
Asis Far West	Inferred	1.082	2.85	3.42	0.10	35.81	37,000	1,036	38,763
Asis Total	Inferred	3.723	2.87	3.79	0.90	32.86	141,122	33,361	122,355
Total Underground	Inferred	3.851	2.87	3.75	1.00	31.86	144,480	38,376	122,709

Note:

1. Historical mine voids have been depleted from the Mineral Resource.
2. Historical mine voids were not available for Otavi so the tonnage has been reduced by 1% for historical mining.
3. Additional 7.5 % porosity factor has been applied to Otavi for the karst voids.
4. The open pit Mineral Resource is declared to a depth of 150 m with a CuEq cut off of 0.77 %.
5. The underground Mineral Resource (below 150m) is declared at a CuEq cut off of 1.4 %.
6. No tailings have been declared at a 0.4 % Cu cut off (upside potential at 0.3 % Cu cut-off).
7. Densities for the hard rock material have been modelled.
8. A geological loss of 15 % has been applied to the Mineral Resource.
9. All reported Mineral Resources are limited to fall within the property boundaries of the project area.
10. Columns may not add up due to rounding.
11. The Inferred Mineral Resources have a large degree of uncertainty as to their existence and whether they can be mined economically. It cannot be assumed that all or any part of the Inferred Mineral Resource will be upgraded to a higher confidence category.

Table 22 below presents the total combined Mineral Resources for the Kombat operations.

Table 22: Combined Mineral Resources for the Kombat Operations as at April 2017

Section	Mineral Resource Classification	Tonnes	Density	Cu	Pb	Ag	Cu Content	Pb Content	Ag Content
		Mt	t/m ³	%	%	ppm	Tonnes	Tonnes	Kg
Kombat East	Inferred	1.232	2.83	1.37	1.05	1.70	16,924	12,895	2,089
Kombat Central	Inferred	0.848	2.82	1.79	0.33	6.90	15,135	2,767	5,848
Kombat West	Inferred	0.458	2.89	2.77	2.97	2.44	12,684	13,610	1,119
Kombat Total	Inferred	2.538	2.83	1.76	1.15	3.57	44,743	29,272	9,056
Gross Otavi	Inferred	0.643	2.84	0.93	2.50	0.85	6,006	16,053	546
Gross Otavi Total	Inferred	0.643	2.84	0.93	2.50	0.85	6,006	16,053	546
Asis West	Inferred	2.475	2.88	4.05	1.28	32.36	100,214	31,735	80,078
Asis Gap	Inferred	0.166	2.83	2.35	0.35	21.15	3,909	590	3,514
Asis Far West	Inferred	1.082	2.85	3.42	0.10	35.81	37,000	1,036	38,763
Asis Total	Inferred	3.723	2.87	3.79	0.90	32.86	141,122	33,361	122,355
Total Mineral Resources	Inferred	6.905	2.85	2.78	1.14	19.11	191,871	78,685	131,957

Note:

1. Historical mine voids have been depleted from the Mineral Resource.
2. Historical mine voids were not available for Otavi so the tonnage has been reduced by 1% for historical mining.
3. Additional 7.5 % porosity factor has been applied to Otavi for the karst voids.
4. The open pit Mineral Resource is declared to a depth of 150 m with a CuEq cut off of 0.77 %.
5. The underground Mineral Resource (below 150m) is declared at a CuEq cut off of 1.4 %.
6. No tailings have been declared at a 0.4 % Cu cut off (upside potential at 0.3 % Cu cut-off).
7. Densities for the hard rock material have been modelled.
8. A geological loss of 15 % has been applied to the Mineral Resource.
9. All reported Mineral Resources are limited to fall within the property boundaries of the project area.
10. Columns may not add up due to rounding.
11. The Inferred Mineral Resources have a large degree of uncertainty as to their existence and whether they can be mined economically. It cannot be assumed that all or any part of the Inferred Mineral Resource will be upgraded to a higher confidence category.

Figure 93 shows the grade tonnage curves for copper for the Kombat section.

Figure 93: Kombat Section Copper Grade Tonnage Curve

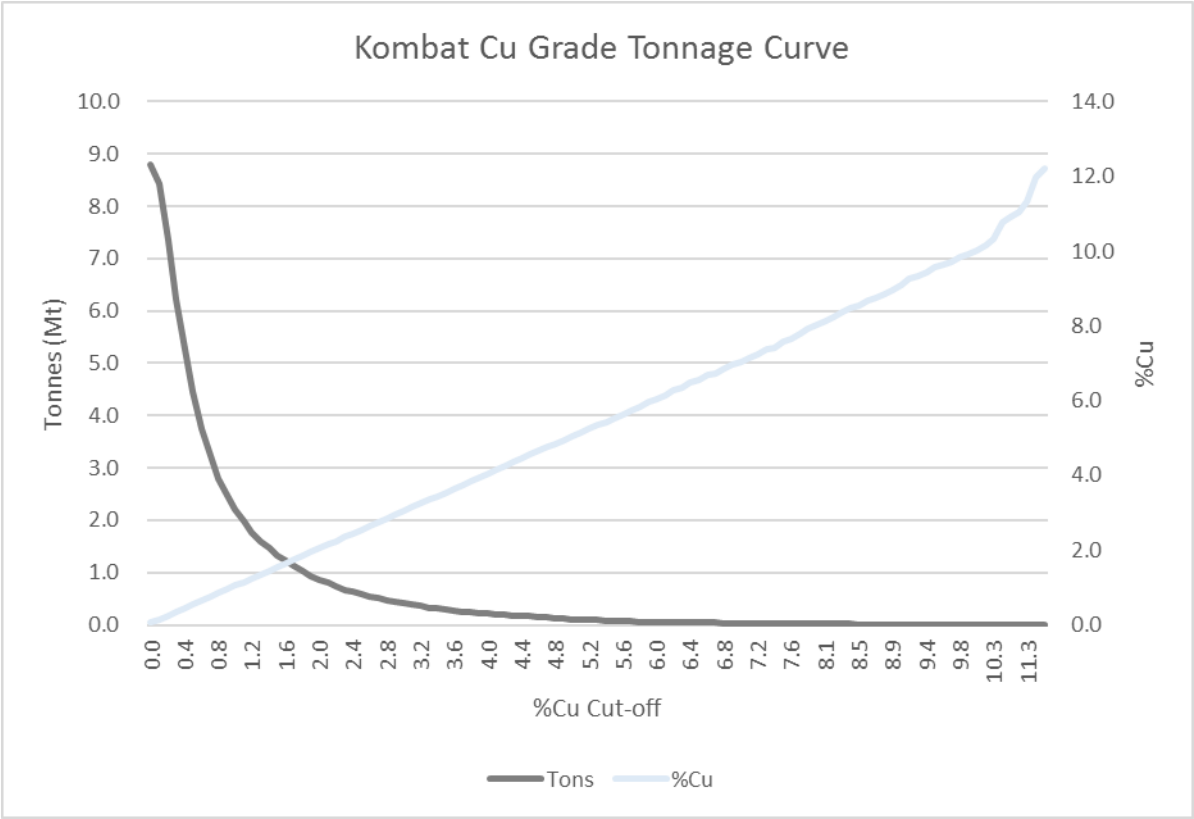


Figure 94 shows the grade tonnage curves for copper for the Asis section.

Figure 94: Asis Mine Copper Grade Tonnage Curve

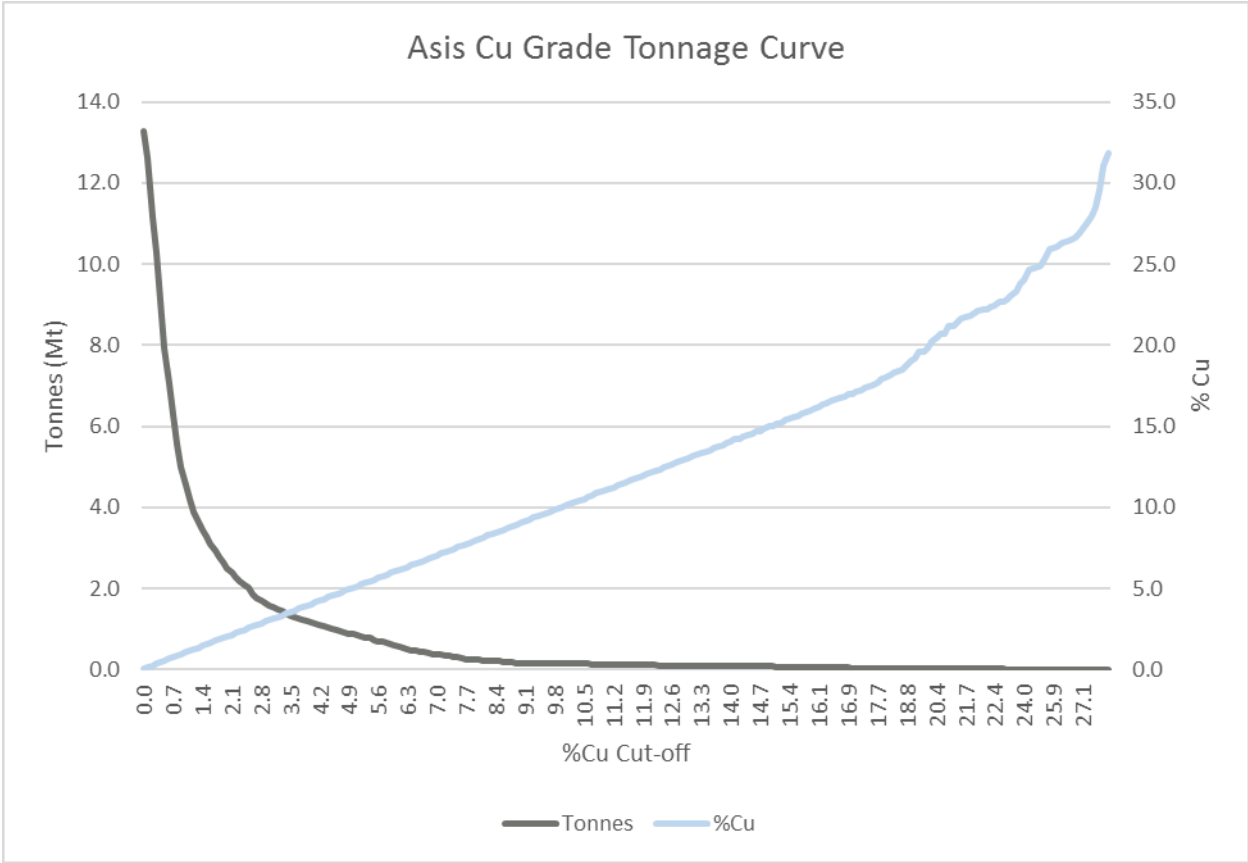


Figure 95 shows the grade tonnage curves for copper for the Gross Otavi section.

Figure 95: Gross Otavi Section Copper Grade Tonnage Curve

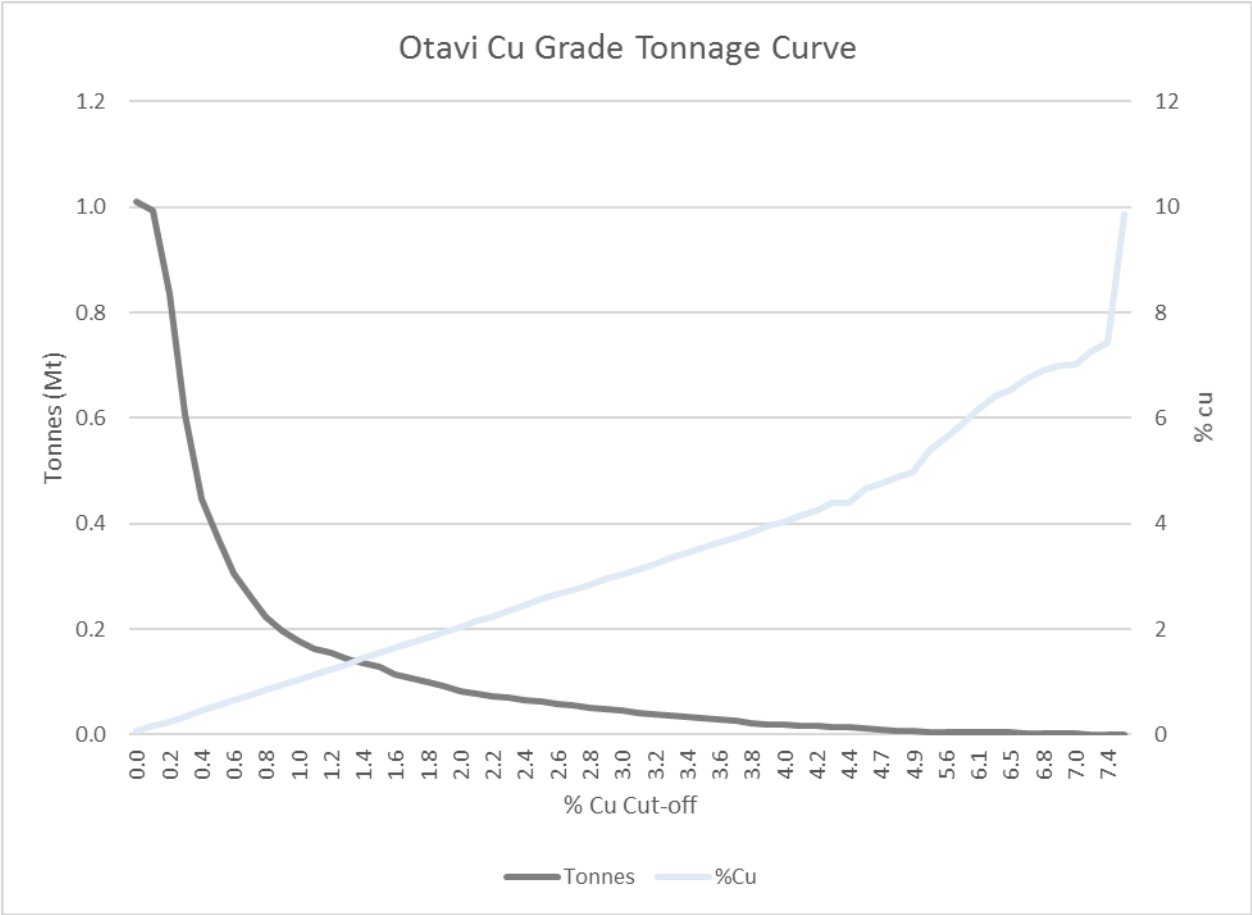


Table 23 details the open pit Mineral Resource for Kombat (at a cut-off of 0.77 % CuEq) in 10 m benches.

Table 23: Open Pit Mineral Resource Split into 10 m Benches

Mine	Top of Bench amsl	Tonnes Mt	Density t/m ³	Cu %	Pb %	Ag ppm	Cu Tonnes	Pb Tonnes	Ag kg
Kombat	1,631	0.004	2.80	1.08	0.15	0.50	41	6	2
	1,621	0.018	2.80	1.11	0.16	2.89	198	28	51
	1,611	0.363	2.82	1.66	0.54	6.42	6 038	1,956	2,333
	1,601	0.308	2.82	1.53	0.77	4.85	4 708	2,383	1,491
	1,591	0.382	2.82	1.54	0.76	4.26	5 875	2,917	1,626
	1,581	0.320	2.83	1.65	0.77	3.77	5 272	2,448	1,204
	1,571	0.142	2.82	1.62	0.37	4.79	2 297	526	681
	1,561	0.110	2.82	1.54	0.48	4.04	1 697	531	445
	1,551	0.087	2.82	1.67	0.66	3.18	1 453	570	277
	1,541	0.061	2.82	1.54	0.82	1.97	935	497	119
	1,531	0.099	2.84	1.78	1.29	1.03	1 756	1,274	102
	1,521	0.078	2.85	1.94	1.83	0.49	1 509	1,430	38
	1,511	0.152	2.88	2.77	2.61	0.49	4 208	3,967	75
	1,501	0.127	2.88	2.57	2.85	0.53	3 274	3,632	68
	1,491	0.058	2.85	1.52	2.10	0.81	887	1,222	47
	1,481	0.031	2.83	1.07	1.63	0.66	336	513	21
	1,471	0.053	2.84	1.40	1.86	1.62	751	995	87
Total		2.394	2.83	1.72	1.04	3.62	41 235	24,895	8,667

Notes:

1. Historical mine voids have been depleted from the Mineral Resource.
2. A geological loss of 15 % has been applied to the Mineral Resource.
3. The open pit Mineral Resource is declared to a depth of 150 m with a CuEq cut off of 0.77 %.
4. The numbers will not be the same as the total table due to rounding.

ITEM 15 - MINERAL RESERVE ESTIMATES

This Report is intended as a Mineral Resource Report. No Mineral Reserves were estimated.

ITEM 16 - MINING METHODS

This Report is intended as a Mineral Resource Report. As such, mining methods were not investigated.

ITEM 17 - RECOVERY METHODS

This Report is intended as a Mineral Resource Report. As such, recovery methods were not investigated.

ITEM 18 - PROJECT INFRASTRUCTURE

This Report is intended as a Mineral Resource Report. As such, project infrastructure was not investigated.

ITEM 19 - MARKET STUDIES AND CONTRACTS

This Report is intended as a Mineral Resource Report. As such, market studies and contracts were not investigated.

ITEM 20 - ENVIRONMENTAL STUDIES, PERMITTING AND SOCIAL OR COMMUNITY IMPACT

Item 20 (a) - RELEVANT ENVIRONMENTAL ISSUES AND RESULTS OF STUDIES DONE

At the Project Areas, the orebodies are hosted in karstic or water-bearing dolomite. Thus, although the local carbonate rocks have low permeability, there is a groundwater influence. Notwithstanding, mining has taken place in this environment for 50 years and the main risks can be mitigated by following sound engineering and mining principles taking cognisance of historical when the past mistakes are considered. The sphere of groundwater influence around the mine is about 120 km² and, due to a limited amount of surface runoff, a relatively high percentage (17%) of the annual rainfall (600 mm) enters two mutually inclusive groundwater flow systems. Groundwater flows along the connectivity via joints, fractures, faults or contact zones, between these two permeability networks and influences the inflows of water into the underground workings (SMS, 2014).

The majority of the inflows from groundwater are associated with northeast-southwest trending faults, with smaller amounts of storage aquifers associated with fractures and the contact of the orebodies with the phyllite. It is along the more continuous faults where mine inflow problems have occurred. It has also been reported that the 270 West Fault generated an inflow of about 320 klph. When Kombat produced in the order of 35 ktpm, an average of 350,000 m³/month water was pumped to surface from a pump station on 14 Level. Of this, 155,000 m³/month was from above 14 Level (SMS, 2014).

There is no active pre-dewatering from surface. The risk of underground inflows of water was previously managed by cover drilling and grouting with plain cement during development. The cement budget was typically 0.4 t to 0.5 t of cement per (planned) cementation drill metre, translating to some 2 t to 3 t of cement per development metre (SMS, 2014).

In addition to groundwater management, environmental management will be required to manage used oil, oil spills, and dust from the TSF.

Item 20 (b) - WASTE DISPOSAL, SITE MONITORING AND WATER MANAGEMENT

The items presented in this section are summarised from SLR Namibia (2016).

There is currently no Waste Management Plan or procedure and will be required in the future. The operational waste management facility (landfill site) is located on the MLs (Nr. 1 Fill Pit). A smaller pit (Nr. 2 Pit) is located next to the Nr. 1 Pit but is not currently in use. The landfill site is used for waste from the mine (domestic waste and waste from Care and Maintenance activities), waste from the town, and from neighbouring farmers. Waste gets burned at the facility. An ECC or permit should be obtained for the landfill site.

There is no provision for disposal of hazardous waste or record of hazardous waste disposal, which is currently stored on site. Historically, hazardous waste was disposed of into the open cast hole (Nr. 1 Shaft Pit). This pit has almost been completely backfilled with tailings, waste rock and other waste.

Waste oil is sent to OilTech, which is a waste oil and tyre recycling plant.

The landfill facility is located on the Kombat Copper mining area and belongs to Trigon through acquisition of Manila. Trigon is therefore accountable for this facility, even though it is also being used by the Kombat

town residents and relevant farmers for the disposal of their waste. The relevant authorisations for this facility should be obtained and a waste management plan should be developed.

The current Wastewater Treatment System is part of Kombat Town. Trigon may consider designing and implementing their own sewerage treatment facility not linked to the town's facility.

Currently no environmental monitoring is undertaken, although a quarterly groundwater monitoring programme was initiated in 2014, but only two quarterly monitoring campaigns were conducted and reports prepared for July and October 2014. Monitoring was stopped thereafter. Mine water levels at the Asis Far West, #1 Shaft and #3 Shaft are measured weekly.

Monitoring plans should be developed and implemented for water quality and water levels, dust, noise and weather.

Item 20 (c) - PERMIT REQUIREMENTS

Trigon is hypothetically working under the old Ongopolo approved Environmental Management Plan ("EMP"). However, it was not formally ever transferred to Manila. If environmental bi-annual reports are filed to MET, then they issue an ECC which is valid for three years - Trigon currently have a valid ECC for the ML areas. The ECC expires on 24 July 2017 and renewal applications have already been submitted. MET may require a new EIA for the EMP to be updated in Manila's name.

Additional environmental permit requirements are discussed in Item 4 (g) and Item 20 (b) .

Item 20 (d) - SOCIAL AND COMMUNITY-RELATED REQUIREMENTS

The mine has been on care and maintenance for nearly a decade. The social responsibility documents as required for mining licences are outdated. A formal updated social and labour plan will be submitted with the mining licence renewal applications in the coming year.

Although Trigon and its subsidiaries do not currently have any legal obligations towards the local communities, water pipelines and bursaries have been supplied ad hoc.

Item 20 (e) - MINE CLOSURE COSTS AND REQUIREMENTS

Currently no Mine Closure Plan or rehabilitation plan exists. Initial rehabilitation has been conducted which included backfilling of the "open cast hole" (Nr. 1 Shaft Pit), planting of trees on the perimeter of the TSF and pushing some garden refuge against the northern slopes, selling of old equipment as scrap metal and demolishing of some old buildings. No rehabilitation trust fund is in place (SLR Namibia, 2016).

A Mine Closure Plan needs to be developed and funding for rehabilitation and ongoing monitoring needs to be implemented.

ITEM 21 - CAPITAL AND OPERATING COSTS

This Report is intended as a Mineral Resource Report. As such, capital and operating costs were not investigated.

ITEM 22 - ECONOMIC ANALYSIS

This Report is intended as a Mineral Resource Report. As such, an economic analysis was not undertaken.


ITEM 23 - ADJACENT PROPERTIES

Item 23 (a) - PUBLIC DOMAIN INFORMATION

A number of historic mines are scattered in the immediate and regional vicinity.

Sabre Resources Limited (“Sabre”) currently holds majority interest in the Otavi Mountain Land Exploration Project that comprises two tenements, EPL 3540 and EPL 3542, over some 700 km². The 220 km² EPL 3540 is over 40 km of the strike extents of the Kombat Copper Trend and entirely encompasses the Kombat Mine and Gross Otavi licence areas, located on the Kombat Copper Trend. Exploration is focused some 10 km east of Kombat Mine at the Guchab South Prospect. Geochemical drilling at Guchab South has identified visible chalcocite and malachite over an 850 m by 100 m zone along trend east of the Kombat Copper Mine. The EPL 3542 entirely surrounds the Harasib licence area and is located on the Border-Toggenburg Lead-zinc Corridor (Sabre, 2016) (Refer to Figure 96).

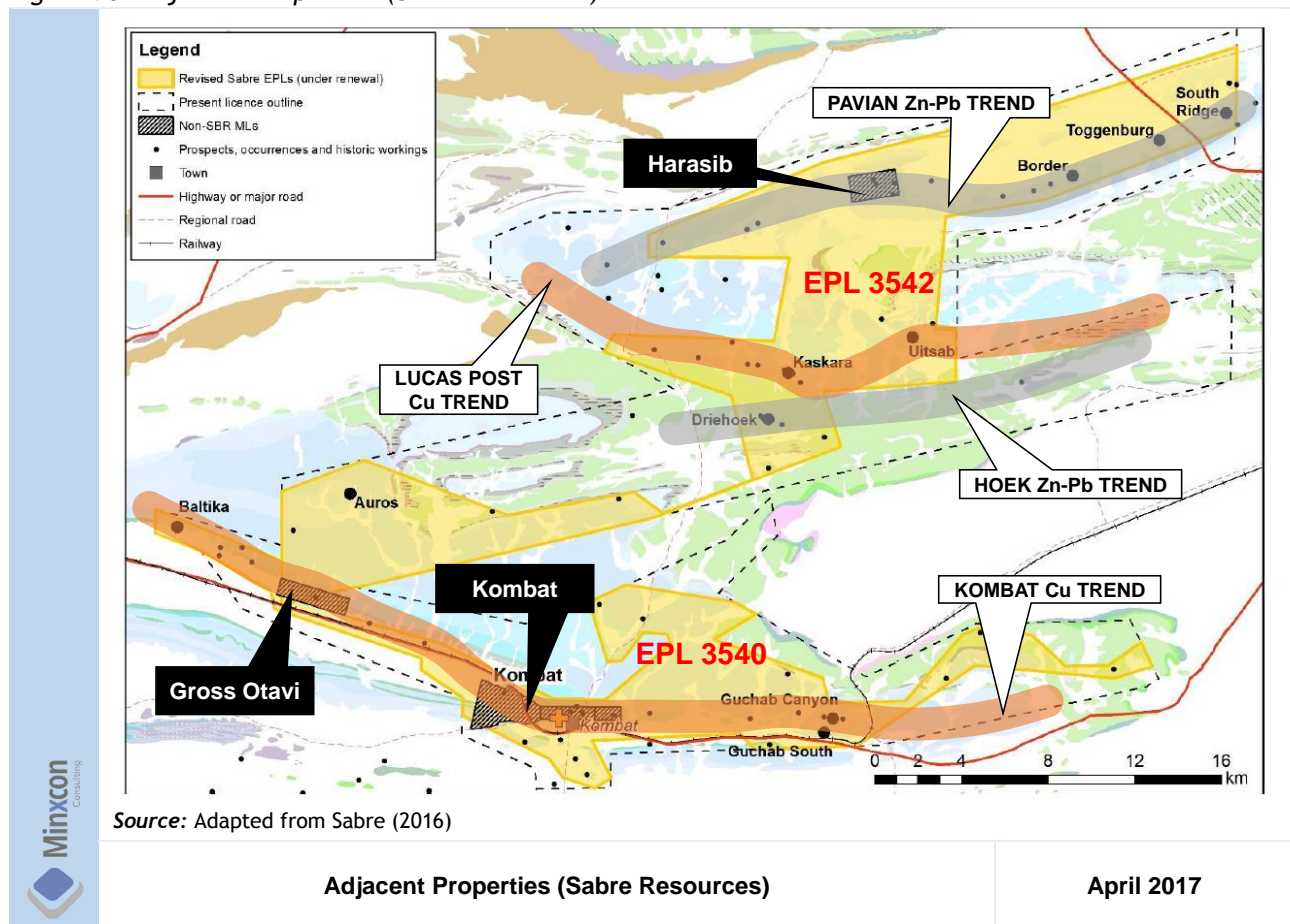Figure 96: Adjacent Properties (Sabre Resources)




Further north lies the old Tsumeb Mine, as well as the only operational mine in the region, namely the open pit Tschudi copper mine of Weatherly International PLC, which is located some 55 km north-northwest of Gross Otavi on a ML125 granted mining licence. The mine has an 11 year life and production commenced in October 2015. Oxidised copper ore is mined at a rate of 2.0-2.6 Mtpa using conventional drill and blast methods. The ore is treated through heap-leach, solvent extraction and electro-winning to produce an average of 17,000 tpa copper (mining-technology.com). Tschudi contains JORC-compliant Measured and Indicated Mineral Resources of 27.5 Mt at 0.87% Cu for 239,900 t Cu, Inferred Mineral Resources at 22.2 Mt

at 0.80% Cu for 399,900 t Cu, and Mineral Reserves of 22.7 Mt at 0.85% Cu, for some 185,000 t Cu as at 30 June 2016 (weatherlyplc.com).

The nearby mines are illustrated in

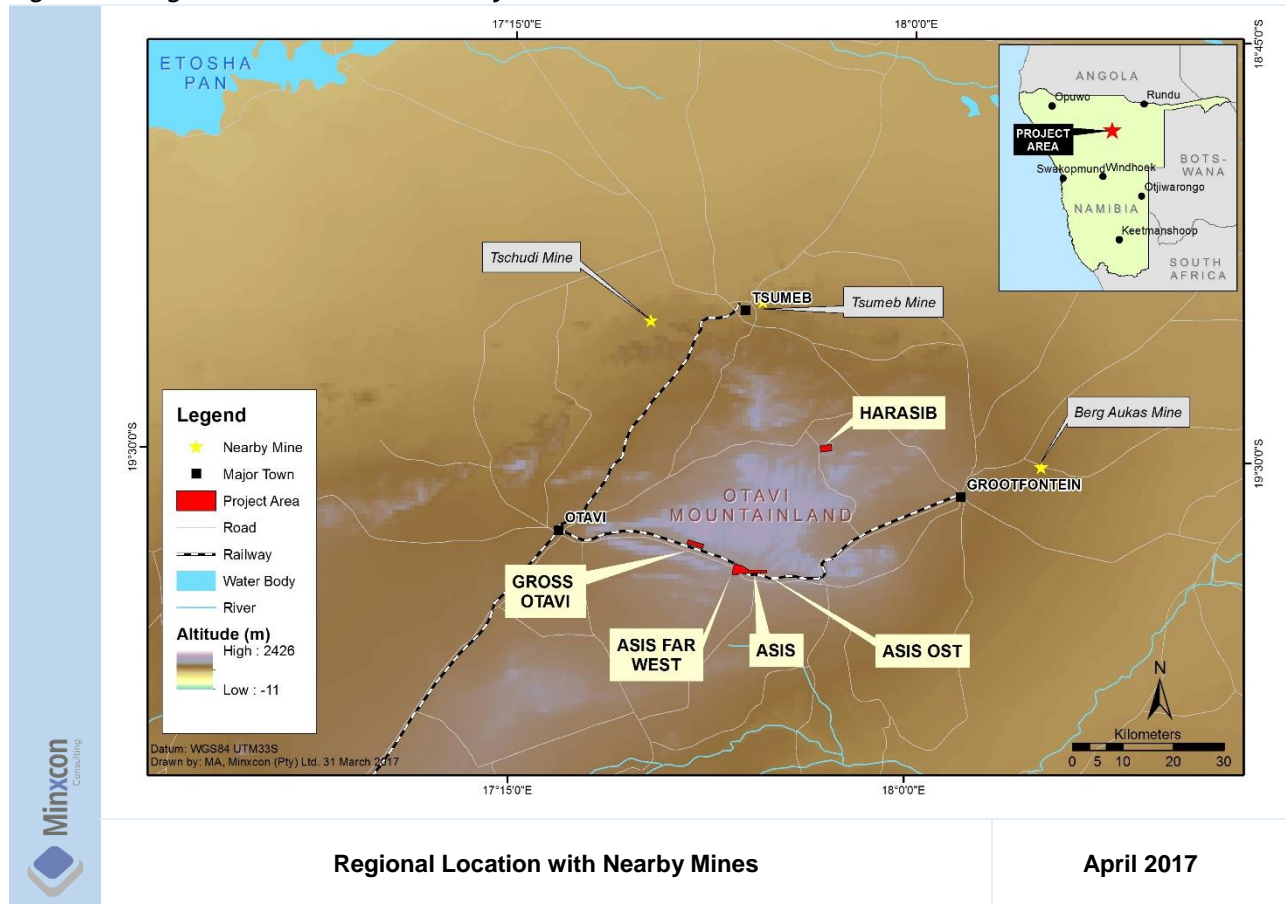Figure 97: Regional Location with Nearby Mines



Item 23 (b) - SOURCES OF INFORMATION

All information as used in this Section is sourced from public sources as follows:-

- Sabre Resources Limited - Annual Report 2016
- <http://www.mining-technology.com/projects/tschudi-copper-project/>
- <http://weatherlyplc.com/operations/tschudi/>

Item 23 (c) - VERIFICATION OF INFORMATION

Minxcon has relied on the information as is presented by the above sources. Verification has been limited to that data which is made available publicly and has been limited to cross-referencing information presented by the individual sources.


Item 23 (d) - APPLICABILITY OF ADJACENT PROPERTY'S MINERAL DEPOSIT TO PROJECT

The licence areas of Sabre entirely surround the Kombat Mine, Gross Otavi and Harasib prospects of Trigon, and are situated along the same mineralised trends within a few kilometres of each other. As such, the style of mineralisation at Sabre's targets is applicable to that of Trigon's Project Areas.

Item 23 (e) - HISTORICAL ESTIMATES OF MINERAL RESOURCES OR MINERAL RESERVES

No historical Mineral Resource or Mineral Reserve estimates have been declared for any areas lying immediately adjacent to the Kombat Project Areas.

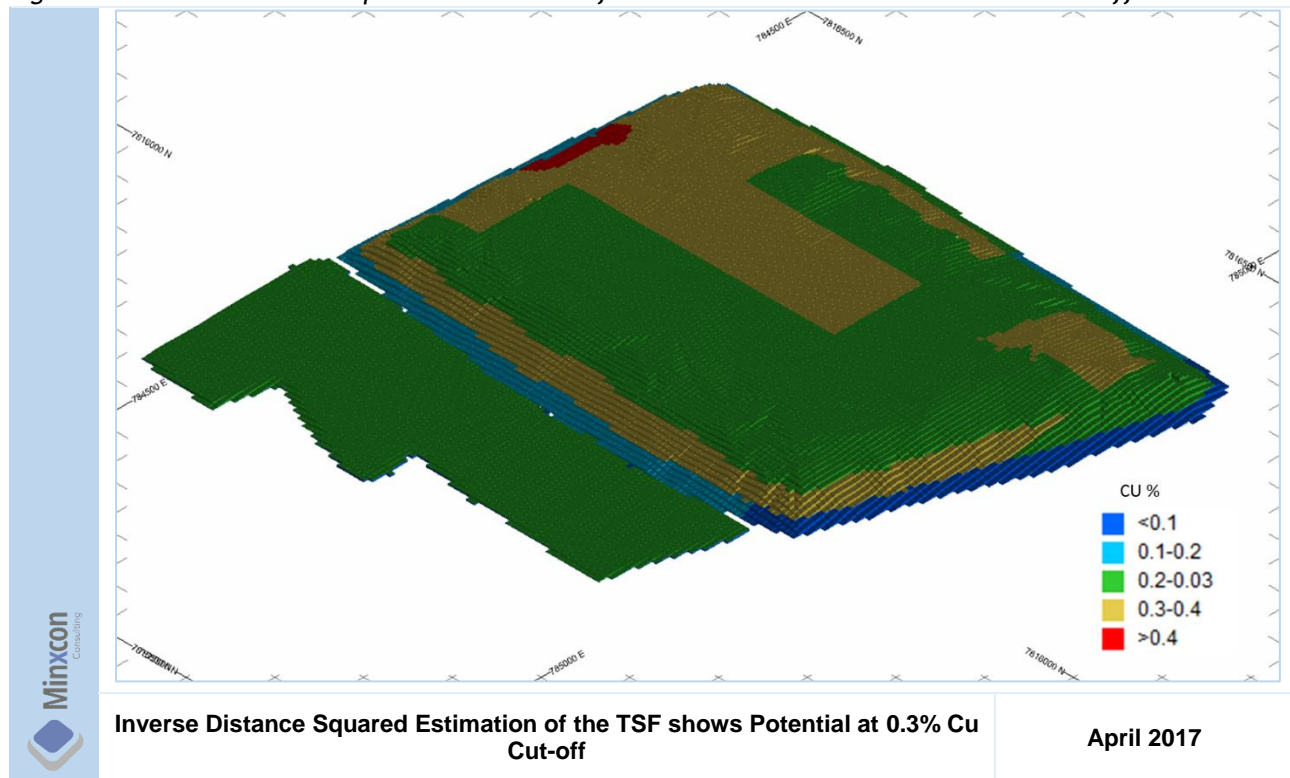Figure 99: Inverse Distance Squared Estimation of the TSF shows Potential at 0.3% Cu Cut-off



The copper is viewed as being the only economic metal and a costing with regards the processing and mining of the dump was conducted by Minxcon. The economic cut-off for the dump was calculated at 0.4% copper, and when applied to the TSF estimated block model, it cannot be deemed economically viable as only approximately 55 000 t out of a total of some 3.078 Mt reporting above a 0.3% cut-off. In the event that the copper price significantly improves such that a pay limit of 0.3% Cu is possible, the tonnages attributable to the TSF could potentially be added to the current Mineral Resources as presented below in Table 24.


Table 24: Potential Mineral Resources for the TSF at a 0.3 % Cu and 0.4 % Cu Cut off

Mine	Cu Cut-off %	Tonnes Mt	Density	Cu %	Pb %	Ag ppm	Cu t	Pb t	Ag kg
TSF	0.3	3.078	1.45	0.35	0.34	1.27	10,668	10,584	3,900
TSF	0.4	0.055	1.45	0.40	0.40	1.00	220	218	54

Asis West Gap Area

Additional upside potential may be attributed to the Asis West Gap area (which has limited drilling) and extends on plunge and dip from the current Asis West workings, westwards towards Asis Far West. Minxcon recommends that focussed exploration drilling be conducted from surface, or at a later stage, dewatered underground drilling platforms.

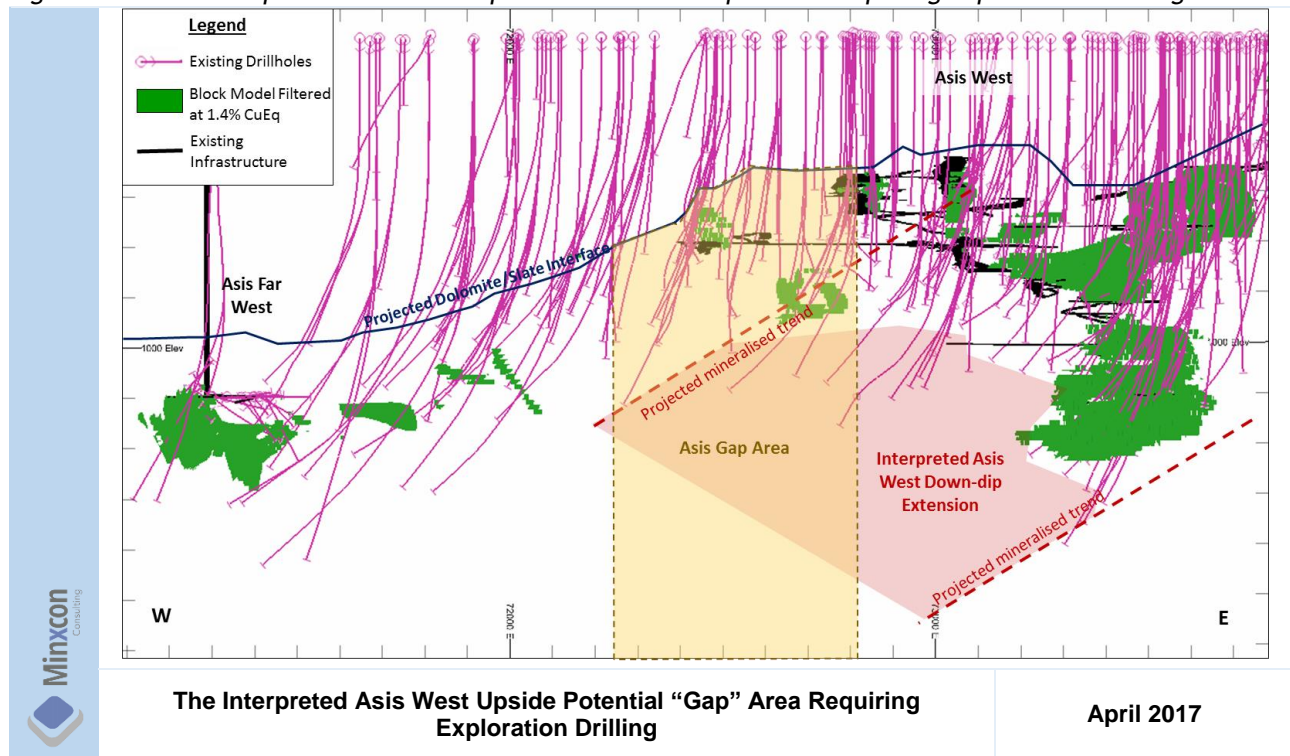Figure 100: The Interpreted Asis West Upside Potential “Gap” Area Requiring Exploration Drilling



Gross Otavi

At Gross Otavi, only a single orebody has currently been identified and evaluated. Upside potential could exist along strike and at depth as the property is located on the Kombat Copper Trend (Refer to Figure 96). Exploration drilling would assist in testing the possibility of upside potential.

Harasib

The Harasib property belonging to Kombat is located on the Pavian Zinc-Lead Trend (Figure 96) and is located approximately 20 km to the north of the Kombat operations but did not form part of the current scope of work. Harasib has a lot of historical data. Minxcon recommends that a proper assessment be conducted of the available data in order to assess the potential for additional Mineral Resources.

PRELIMINARY ECONOMIC ASSESSMENT

Introduction

Minxcon was commissioned by Trigon in April 2017 to complete a scoping level study on the Kombat Project. This Report details a scoping-level study in the form of a Preliminary Economic Assessment (“PEA”) conforming to NI 43-101 standards and requirements.

The PEA includes Inferred Mineral Resources that are considered too speculative geologically to have the economic considerations applied to them that would enable them to be categorised as Mineral Reserves (the “PEA Study”), and there is no certainty that the PEA will be realised.

Study Purpose

The purpose of the PEA is to investigate the economic viability of the open pit and underground mining potential targeting the copper and lead resources at Kombat East, Kombat Central, Asis Far West, Asis West and Gross Otavi areas.

The PEA investigated mining methods, treatment methods and development of additional infrastructure. The study focussed on the total Inferred Mineral Resource to determine the economic viability, upside potential as well as future exploration requirements.

A discounted cash flow (“DCF”) valuation was carried out on the PEA Study areas includes only Inferred Resources. The value derived from the PEA is considered to represent the upside potential value of the current copper and lead resources.

Study Status

The PEA includes Inferred Mineral Resources that are considered too speculative geologically to have the economic considerations applied to them that would enable them to be categorised as Mineral Reserves, and there is no certainty that the PEA will be realised. The mining operating costs for the open pit operation were sourced from a contract with an industry known mining contractor and are regarded as accurate. The underground mining cost was sourced from a previous concept study and inflated to current monetary terms. The capital estimate is based on benchmarking with similar sized projects and conceptual designs conducted by Minxcon. The capital is deemed sufficient and all major infrastructure costs have been accounted for.

Strategic Considerations

Mining at Kombat will commence at a throughput of 30 ktpm to ensure the plant is fully utilised. The current processing plant requires some revamping and will be able to produce the required throughput. The production rate is planned to be doubled.

The Kombat Project consists of open pittable resources within the Kombat East, Kombat Central, Kombat West and Gross Otavi areas and underground mineable resources at Asis Far and Asis Far West.

Each mining area was analysed separately to determine the most economically viable sequence of extraction. Open pit mining was given preference due to the lead times required to recommission the underground mines. Mining will commence at a rate of 30 ktpm with Kombat East due to its lower stripping ratio followed by Kombat Central

Asis Far West has a higher copper grade and is also easier to de-water and re-establish underground, compared to Asis West. As a result, development of underground mining at Asis Far West will commence while Kombat Central is being mined. The processing plant will then be expanded to 60 ktpm in time to treat material from Asis Far West once Kombat Central is depleted. Development at Asis West will take place to ensure stoping can commence once Asis Far West is depleted.

Open pit mining operations will be relocated to Gross Otavi when Kombat Central is depleted. Pre-stripping will then commence to ensure that production at Gross Otavi commences after mining at Asis West ceases.

Kombat East and Kombat Central open pits require minimal establishment and will thus be less capital intensive. The underground sections of Asis Far West and Asis West will, however, be more capital intensive to re-establish than the surface open pit operations. Thus, a decision has been made to schedule these operations after the open pit mining in order to allow time for the re-establishment process and to defer some of the larger capital intensive processes.

Mining

Open Pits

The open pit mining method is conventional open pit mining with drilling and blasting followed by loading and hauling activities conducted by a mining contractor.

The open pit mine designs for Kombat East and Kombat Central with a depth ranging from 45 m to 90 m for Kombat East and a depth ranging from 65 m to 85 m for Kombat Central are shown in Figure 101. Kombat East has the lowest stripping ratio at 4.78 with 0.66 Mt ore at a copper grade of 1.68%. Kombat Central has a stripping ratio compared to Kombat East, namely 9.48, with 0.73 Mt ore at a copper grade of 1.85%.

The open pit mine design for Gross Otavi with a depth ranging from 100 m to 150 m; this depth difference is attributed to the location of Gross Otavi on a hill. The stripping ratio is at 10.18, with total ore tonnes of 0.52 Mt at a copper grade of 1.18% and a lead grade of 3.46%.

Underground

The underground mining method selected is cut-and-fill with backfilling utilising the existing underground infrastructure. The underground stopes were generated in the software program Mineable Stope Optimiser and were deemed sufficient to be utilised as final stope shapes.

The underground development and stoping for Asis Far West is shown in Figure 102. The total development required is 6,865 m and the contained material in the stopes is 0.85 Mt ore at 3.67% Cu.

The underground development and stoping for Asis West is shown in Figure 102. The total development required is 11,153 m and the contained material in the stopes is 1.74 Mt ore at 4.08% Cu.

Figure 101: Pit Designs: Kombat East and Kombat Central


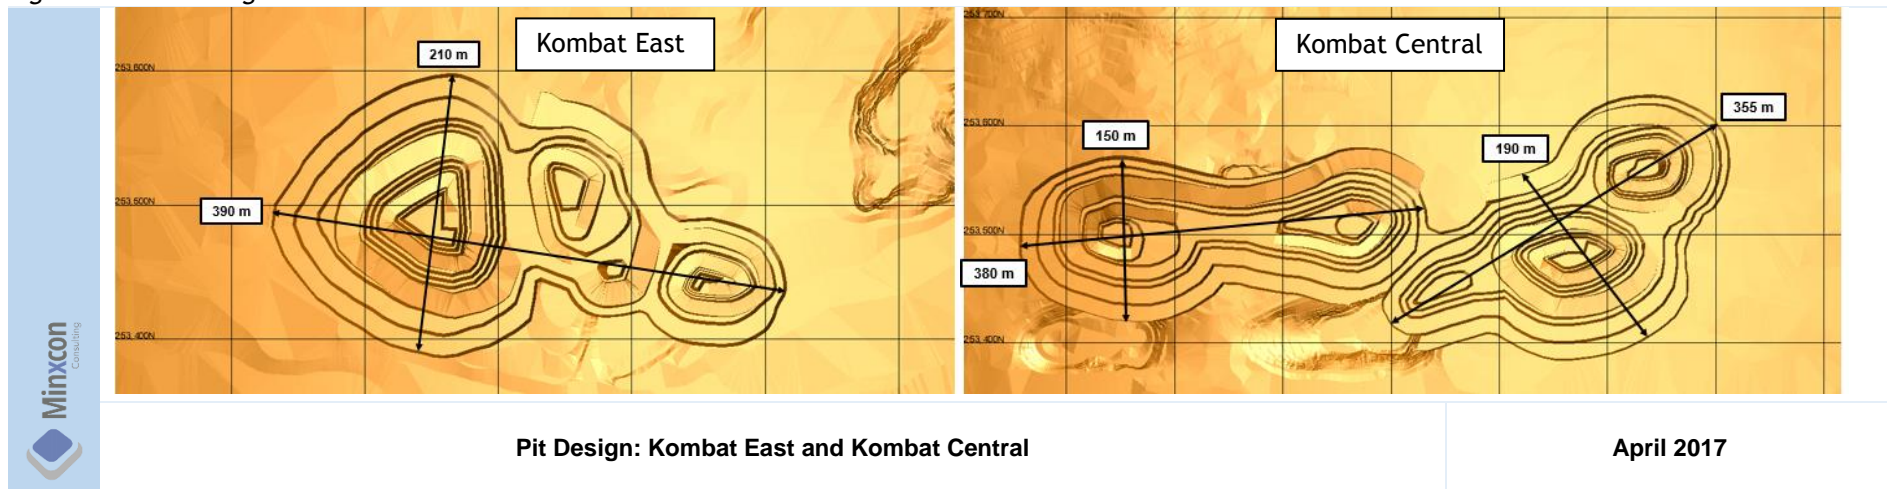


Figure 102: Underground Designs: Asis Far West and Asis West

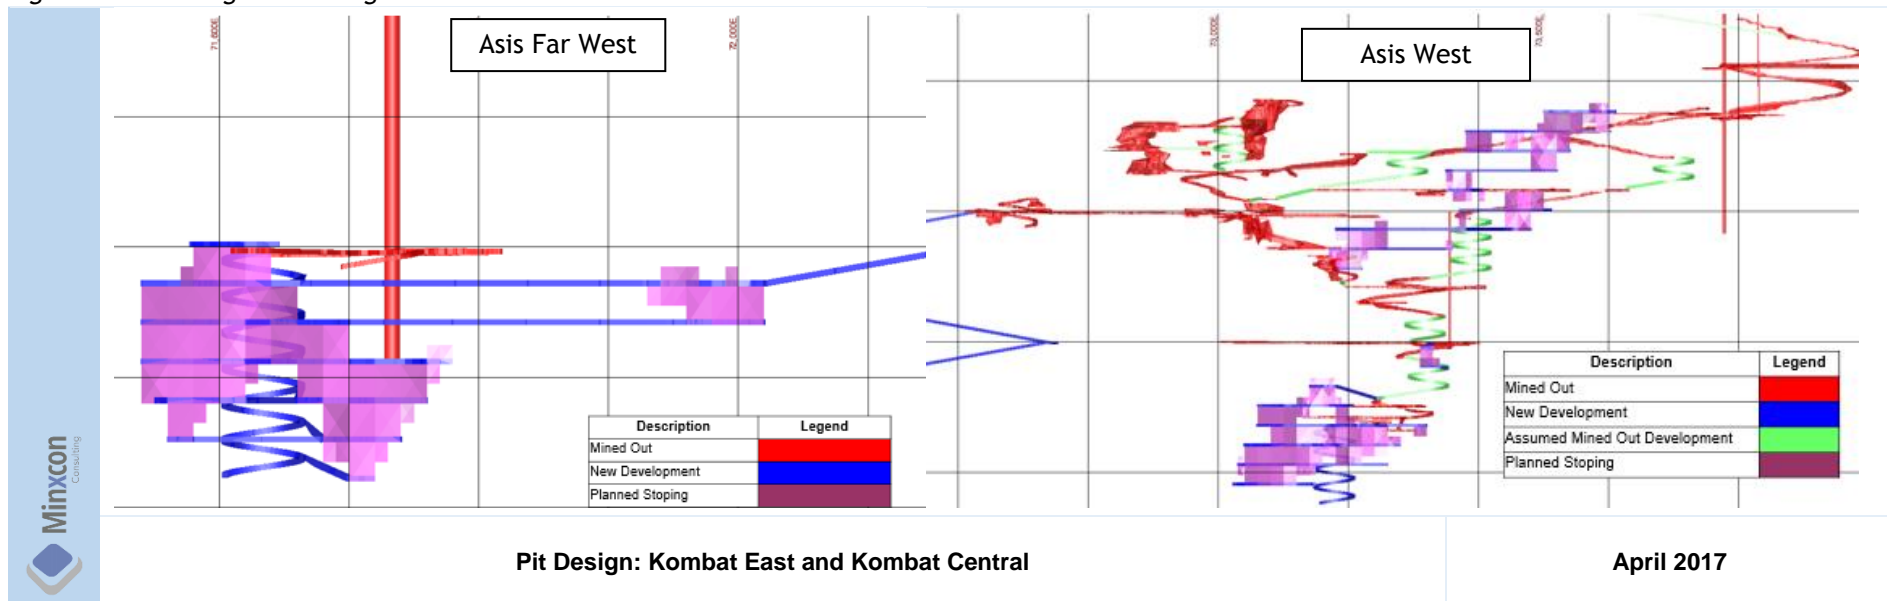


PEA Production

The modifying factors for the open pit operations are comprised of 1% ore losses and 2% dilution and for the underground operations comprise of 5% ore losses and 10% dilution. Minor geological losses of 5% and a mine call factor of 100% were applied to both the open pit and underground operations.

The diluted plant feed tonnes are shown in Figure 103.

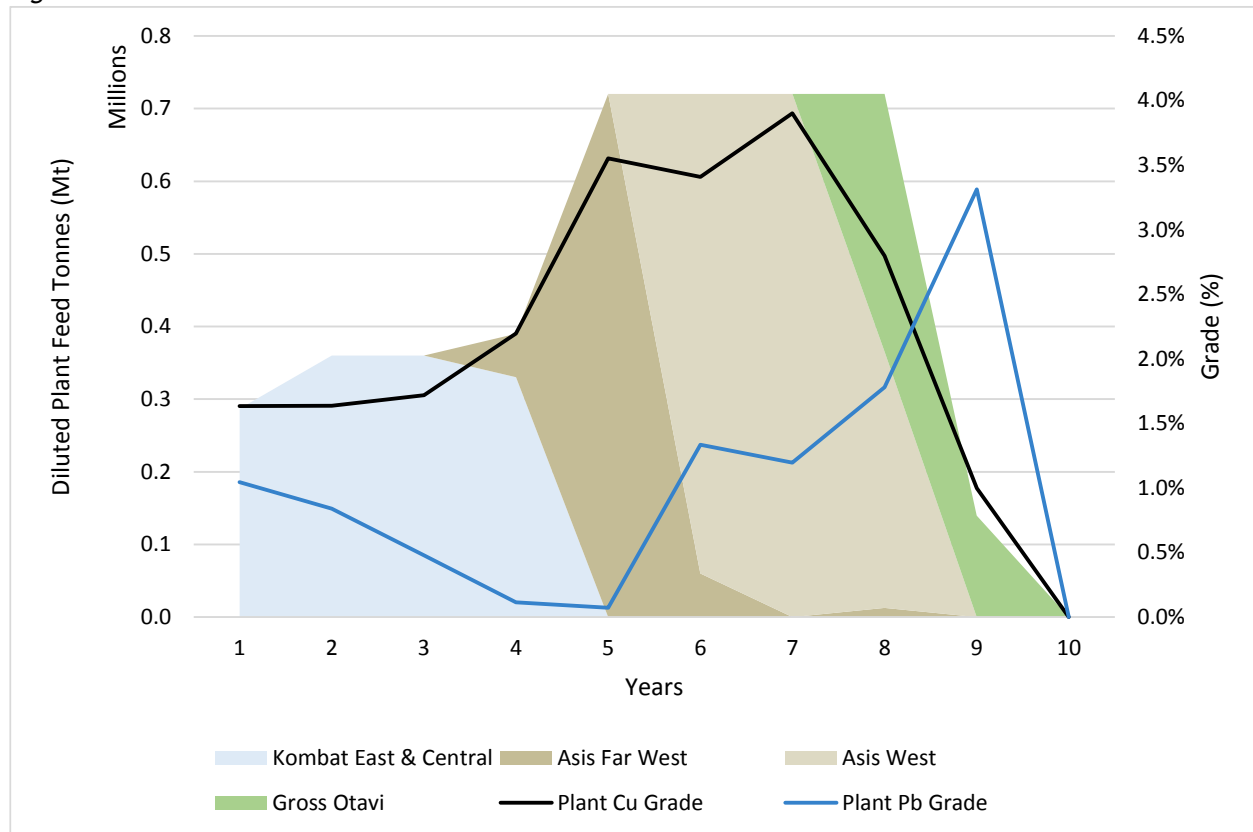Figure 103: Diluted Plant Feed Tonnes




The plant feed tonnes shown highlight the increase in production rate from year five onwards to 60 ktpm. The copper grade also increases in year five due to the higher grade of the underground stopes. During year nine and year ten the lead grade increases due to the ore feed from Gross Otavi.

Processing

Referring to the block flow schematic below (Figure 104), the existing Kombat plant has a capacity of 30 ktpm and consists of a three-stage crushing, rod and ball milling, flotation, concentrate thickening and filtering plant which is capable of producing separate copper and lead concentrates.

Kombat has not conducted recent metallurgical testwork. As a result, historic production efficiencies were used to estimate plant recoveries. The plant will produce a copper concentrate when treating material from Kombat, Asis and Asis Far West areas at recoveries of between 87% and 93%. Lead and copper concentrates will be produced when treating Gross Otavi material at recoveries of 70% and 80% respectively.

For the purpose of this assessment, it was assumed that all concentrate produced will be sold to the smelter at Tsumeb while the lead concentrate will be sold to the export market. The concentrates will be thickened and filtered before loading onto rail and trucks.

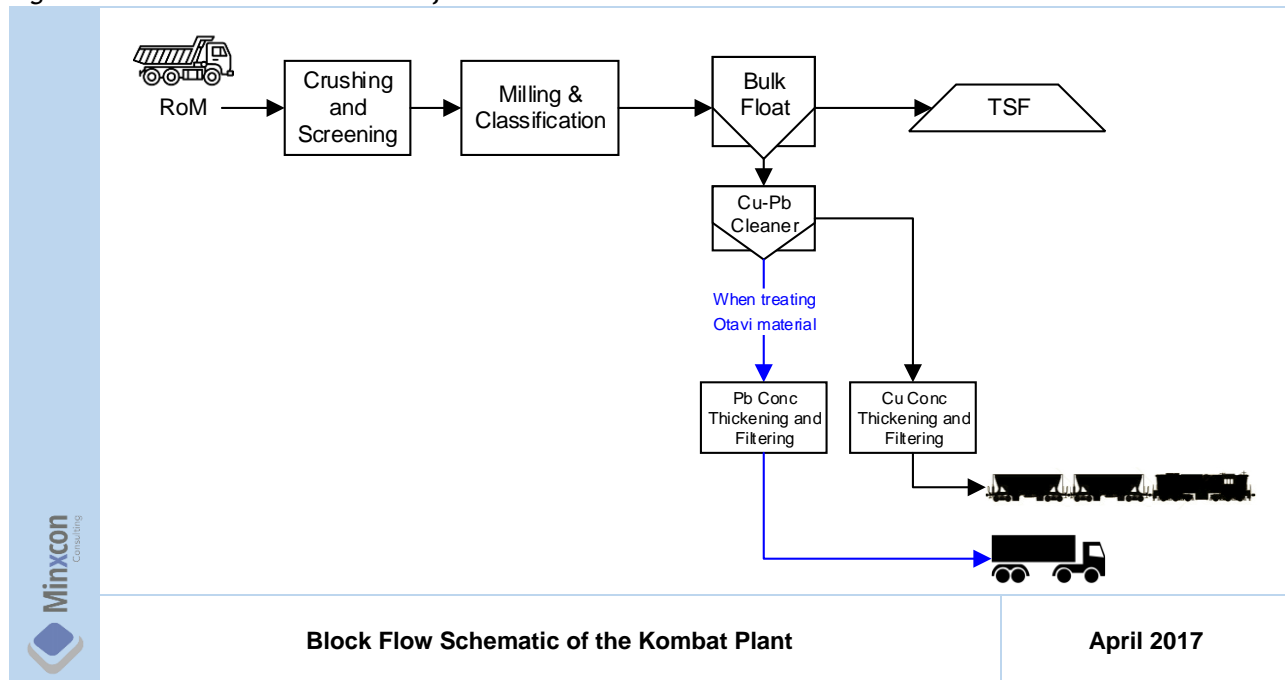Figure 104: Block Flow Schematic of the Kombat Plant

The owner-operated plant will be refurbished before it is recommissioned to treat open pit material from the Kombat area at a throughput of 30 ktpm. The plant will then be expanded to 60 ktpm in year four before underground production commences in year five at Asis Far West.

PEA Infrastructure


The Kombat operation is well established and easily accessible via the existing road and rail network in the area. All major infrastructure such as power supply, water supply, shaft and associated equipment and infrastructure, buildings and amenities are already in place and sufficient for the operation of the mining areas.

Minor repairs and upgrades will be required to the available infrastructure on surface in order to fully re-establish the mining operation. This will mainly include the upgrading of the Kombat substation. The underground workings will require more extensive upgrades and repairs especially at the Asis West operation. In effect the entire shaft below bank level and the total underground section will have to be refurbished once it has been completely dewatered.

The open pit operation will require minimal additional infrastructure as contractor mining will be conducted. Minor repairs will be required to existing buildings as well as the re-equipping of areas such as workshops. The Gross Otavi operation will be operated as a satellite operation to the main Kombat operation, thus minimal infrastructure will be required for the establishment of the operation. A modular approach has been taken in that as far possible all infrastructure deployed at Gross Otavi will be portable or prefabricated.

The layout indicating some of this infrastructure is illustrated in Figure 105.

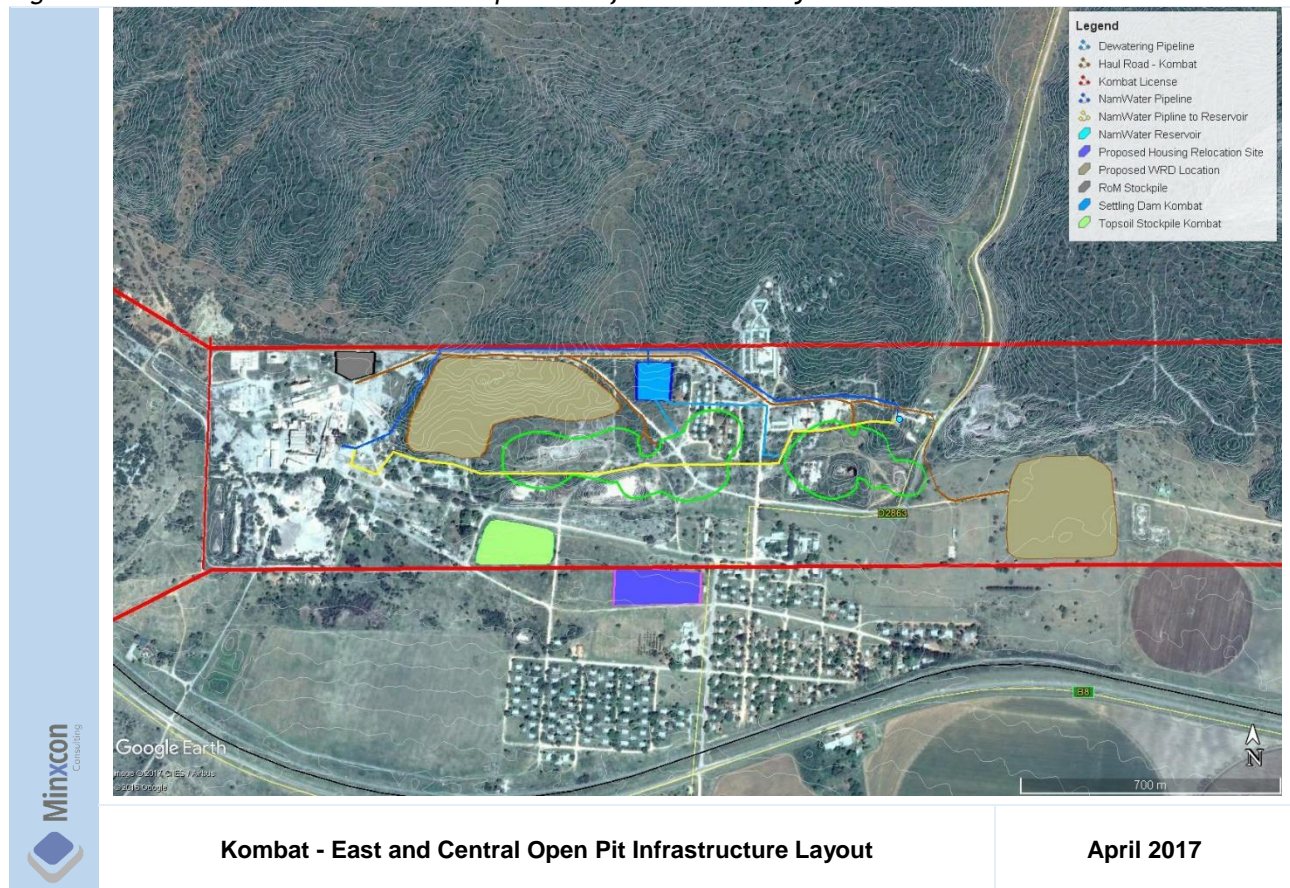Figure 105: Kombat - East and Central Open Pit Infrastructure Layout



Mining of Kombat dates back to 1960 with some 12 Mt of ore being extracted despite continual inflow of water and various periods of disruption due to flooding. A large inflow of groundwater occurred at the end of 2006 due to a 24hr power outage from NamPower. The mine did not have sufficient backup generation capacity and the pumping system could not be utilized to its full potential. As a result, the mine was flooded. Considering metal prices at the time and the cost to dewater the operations, the mine was placed under care and maintenance in January 2007. Most of the flooding events throughout Kombat's history occurred as a result of the following:-

- Power outage from NamPower;
- Insufficient backup generation capacity at Kombat Mine; and
- Knowingly holding into major fault systems - this event occurred concurrently with labour action at the mine.

The company is continuously assessing best practices going forward and has learnt from past mistakes in order to successfully mitigate the risk of potential groundwater inflows. In addition to allow for sufficient backup generating capacity (approximately 3 MVA) and avoiding major fault systems, the mining method is also being considered. An extract of the 2014 Concept Study completed by Sound Mining is shown below:

Geohydrology: "Sound Mining understands that the sphere of ground water influence around the mine is about 120km² (Department of Water Affairs Report 12/5/G2, February 1990) and that, due to a limited amount of surface runoff, a relatively high percentage (17%) of the annual rainfall (600mm) enters two mutually inclusive groundwater flow systems (Henry Mutafela Mukendwa, MSc. Thesis - November 2009). Ground water flows along the connectivity via joints, fractures, faults or contact zones, between these two permeability networks and influences the inflows of water into the underground workings. The majority of the inflows from ground water are associated with the NE-SW trending faults, with smaller

amounts of storage aquifers associated with fractures and the contact of the orebodies with the phyllite. It is along the more continuous faults, especially the Kombat West, 270 West, 271 West and 550 West where mine inflow problems have occurred (DWA Report 12/5/G2, 1990). It has also been reported that the 270 West fault generated an inflow of about 320 klph. On mine records reveal that, when Kombat produced in the order of 35 ktpm, an average of 350,000 m³/month was pumped to surface from a pump station on 14 Level, of which 155,000 m³/month of this was from above 14 Level.”

Cementation: *“The risk of underground inflows of water was previously competently managed by cover drilling and grouting with plain cement during development, and this approach will form an integral part of the operations going forward. A series of 36m long horizontal pilot holes will be drilled ahead of all advancing faces to create a ‘halo’ of cement within which development can be advanced. They will extend beyond the advancing faces and will also serve to identify faults and fractures early, and to assist in planning for continuity of the underground operations. When a water bearing feature is intercepted, cement will be pumped into the hole to seal it off. The pumping will start with a mix of thin grout at high pressure (21 MPa to 25 MPa) until sufficient back pressure develops. The mix is then thickened and the pressure reduced to avoid destruction of the early partial sealing from the primary effort. In the past, the holes were drilled for the length of a rod, cemented and the redrilled, for a length of two rods and again cemented. This was repeated until a the hole length of 36 m was achieved and fully sealed. Development will proceed for a distance of 30m before cover drilling process is repeated, allowing a 6m safety overlap. This procedure reduces inflows and any residual water left flowing will be redirected to sumps for pumping to surface. Development should remain as far ahead of the stopes as possible to provide room to “buffer” the effect of any major inflows. Backfilling will help to reduce the impact of water flowing in the stoped out areas, but will also reduce volume for temporary water storage. Water doors can be considered in development that links different working areas to enable specific areas to be sealed off.”*

Surface Pumping: *“Vertical aquifers may be better intercepted with horizontal drain holes. The site visit revealed that there are detailed maps of the geology and structures. Sections plots of past diamond drilling from surface and underground show the position and approximate flow rates of water intersected. Pumping from surface boreholes to remove water from high storage aquifers will form some pressure relief as the average depth of mining increases. This will reduce the risk of flooding which is associated with high pressure gradients. This would be a more proactive measure to complement the barrier system of water control through cementation alone.”*


Surface pumping will be a viable option should the boreholes be in a condition allowing for such pumping.

PEA Capital Estimation Summary

The capital schedule for the Kombat mining operations for the life of mine is illustrated in Figure 106. The plant sustaining capital expenditure is based on 12.0% of the plant operating costs and the underground sustaining capital is based on 3.5% of the mining operating costs. The underground sustaining capital is mainly to do repairs in the shaft. Both the open pit and underground mining will be done by contractors who include the sustaining capital of the mining fleet in their total costs.

The start-up capital required for first production of the open pit amounts to USD7.73 million. Total direct capital expenditure over the life of mine is USD67.21 million (excluding contingency) with the peak capital expenditure during years 2021 and 2022 and peak funding requirement of USD46 million during 2022. The pre-development that takes place before stoping was all capitalised, thereafter it was treated as operating expenditure.

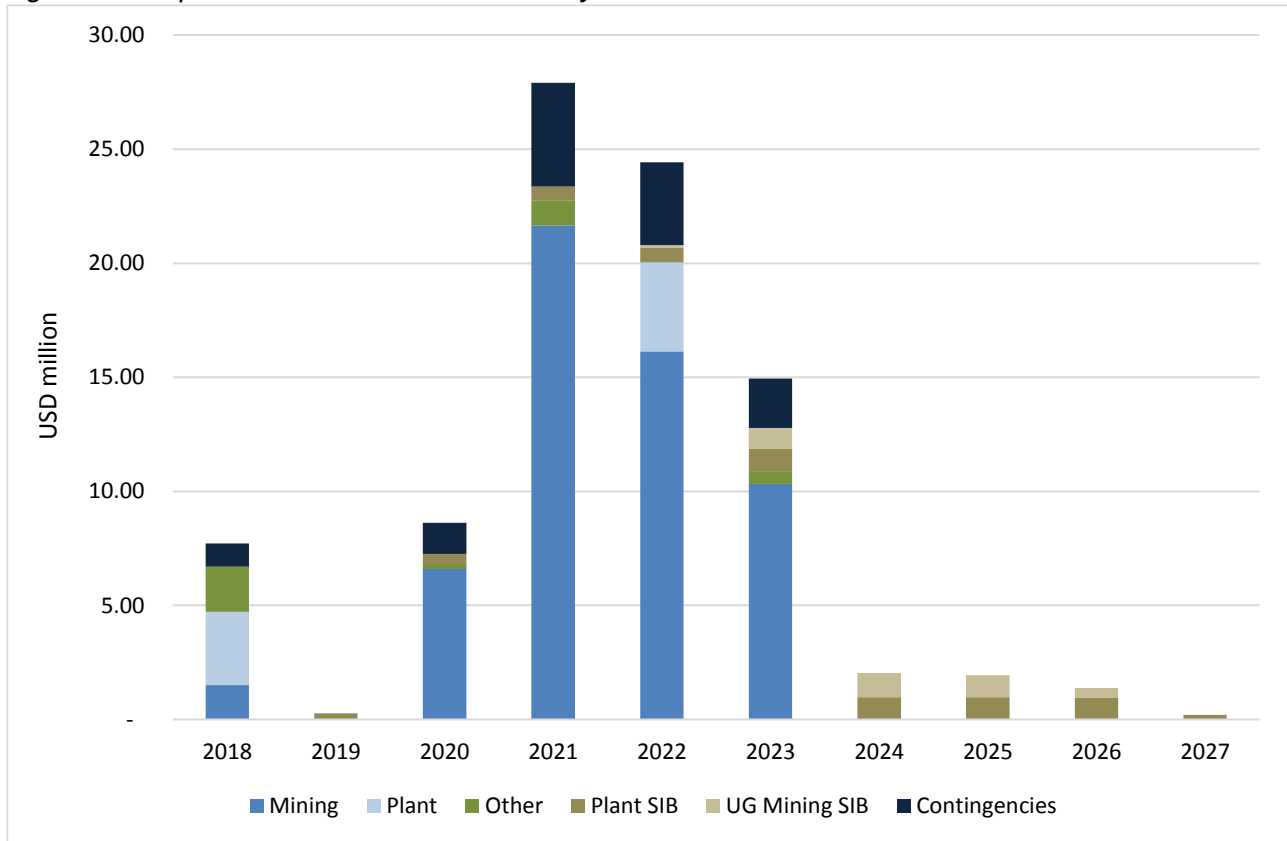Figure 106: Capital Schedule Based on PEA Study



PEA Operating Costs

The open pit mining operating cost for the PEA was sourced from a previously submitted proposal from a reputable industry known mining contractor and benchmarked against Minxcon's operating cost model. Formal tendering processes will follow. The variable cost for Kombat East and Kombat Central was taken at an average depth of 40 m, and for Gross Otavi it was taken at an average depth of 50 m. The underground mining operating cost was sourced from a previous study and inflated. The fixed cost utilised for the open pits was sourced from Minxcon's operating cost model including the owner's fixed costs component to produce an all in mining cost.

The plant operating costs at treatment rates of 30 ktpm and 60 ktpm are summarised in Table 25. The processing costs include the disposal of tailings.

Table 25: Mining and Processing Operating Cost Summary

Item	Area	Description	Type	Unit	Value	
Mining	Open Pit	Drill & Blast	Variable	USD/t	1.21	
	Open Pit	Load and Haul Waste Kombat East and Kombat Central	Variable	USD/t	1.04	
	Open Pit	Load and Haul Ore Kombat East and Kombat Central	Variable	USD/t	1.21	
	Open Pit	Load and Haul Waste Gross Otavi	Variable	USD/t	1.10	
	Open Pit	Load and Haul Ore Gross Otavi	Variable	USD/t	1.14	
	Underground	Total (excluding development)	Variable	USD/RoM t	30.89	
	Underground	Development Cost	Variable	USD/m	2,309.61	
	Total Operation	Overheads	Fixed	USD'000/month	306.22	
Item	Area	Description	Type	Unit	30 ktpm	60 ktpm
Processing	Plant and Tailings	Plant labour, reagents, consumables, power, tailings disposal	Variable	USD/t	7.46	7.66
			Fixed	USD'000/month	152.48	156.39
			Total	USD/t	12.54	10.27

Costs reported for the Kombat operations, which consist of plant and mining operating costs, are displayed in Table 26. Other costs (C1) include concentrate transport costs, treatment costs and refining costs. Other cash costs (C3) include the corporate overheads cost. The royalty amount includes the Namibian revenue royalty of 3%. The costs are displayed per milled tonne as well as per recovered copper equivalent pound. Kombat has an all-in sustainable cost of USD109/milled tonne that equates to USD1.77/copper equivalent pound.

Table 26: Financial Cost Indicators

Item	Unit	Kombat Copper PEA
Net Turnover	USD/Milled tonne	172
Mine Cost	USD/Milled tonne	34
Plant Costs	USD/Milled tonne	12
Other Costs	USD/Milled tonne	35
Direct Cash Costs (C1)	USD/Milled tonne	81
Capex	USD/Milled tonne	20
Production Costs (C2)	USD/Milled tonne	101
Royalties	USD/Milled tonne	5
Corporate Overheads	USD/Milled tonne	3
All-in Sustainable Costs (C3)	USD/Milled tonne	109
All-in Sustainable Cost Margin	%	36%
EBITDA*	USD/Milled tonne	83
EBITDA Margin	%	48%
Copper Product Recovered	t	108,377
Copper Equivalent	tonnes	122,106
Net Turnover	USD/Copper Equivalent lb	2.82
Mine Cost	USD/Copper Equivalent lb	0.56
Plant Costs	USD/Copper Equivalent lb	0.20
Other Costs	USD/Copper Equivalent lb	0.57
Direct Cash Costs (C1)	USD/Copper Equivalent lb	1.33
Capex	USD/Copper Equivalent lb	0.31
Production Costs (C2)	USD/Copper Equivalent lb	1.64
Royalties	USD/Copper Equivalent lb	0.08
Corporate Overheads	USD/Copper Equivalent lb	0.05
All-in Sustainable Costs (C3)	USD/Copper Equivalent lb	1.77
EBITDA*	USD/Copper Equivalent lb	1.36

Saleable Product

The saleable product tonnes per area are displayed in Table 27. The first area mined is the combined East and Central pits which deliver a total of 113 kt of concentrate with 18% copper content to the smelter. The combined pits have a life of four years delivering an average copper grade of 1.74% at an average of 30 ktpm.

After the completion of the east and central open pit operations, the underground mines are in a position to start treating ore at 60 ktpm at an average copper grade of 3.72%. The underground mines will deliver a total of 284 kt of concentrate with approximately 30% copper content to the smelter. The combined underground mines have a life of five years when mining at an average rate of 60 ktpm.

The final area to be mined is Gross Otavi that targets high grade lead of 3.39%. The pit will deliver a total of 30 kt of concentrate with 45% lead content to the smelter, which will be further treated to also deliver a secondary product of 22 kt of 18% copper concentrate.


The combined open pits and underground mines have a life of nine years mining 4,418 kt at an average mined grade of 2.83% copper.

Table 27: Combined Production Breakdown in Life of Mine

Item	Unit	
Ore Tonnes Mined	kt	4,418
Average Cu Grade Mined	%	2.83%
Average Ag Grade Mined	g/t	20.63
Total Cu Concentrate	kt	420
Total 45% Pb Concentrate	kt	30
Total Cu Metal Paid For by Smelter	kt	108
Cu Payability (Including Refining and Lead penalties)	%	91.4%
Cu Payability (Including Refining, Smelter Treatment and Lead penalties)	%	79.9%
Total Silver Ounces Paid For by Smelter	koz	2,443
LoM	Years	9

The saleable product tonnes paid for by the smelter after taking into account the deductions per year are illustrated in Figure 107. The 18% copper concentrate tonnes from the open pits and approximately 30% Cu concentrate tonnes from the underground are also displayed in Figure 107. The majority (91%) of the total revenue generated is from copper, while the silver credits contribute approximately 5% of the revenue stream. The lead produced from Gross Otavi contributes 4% of the total revenue.

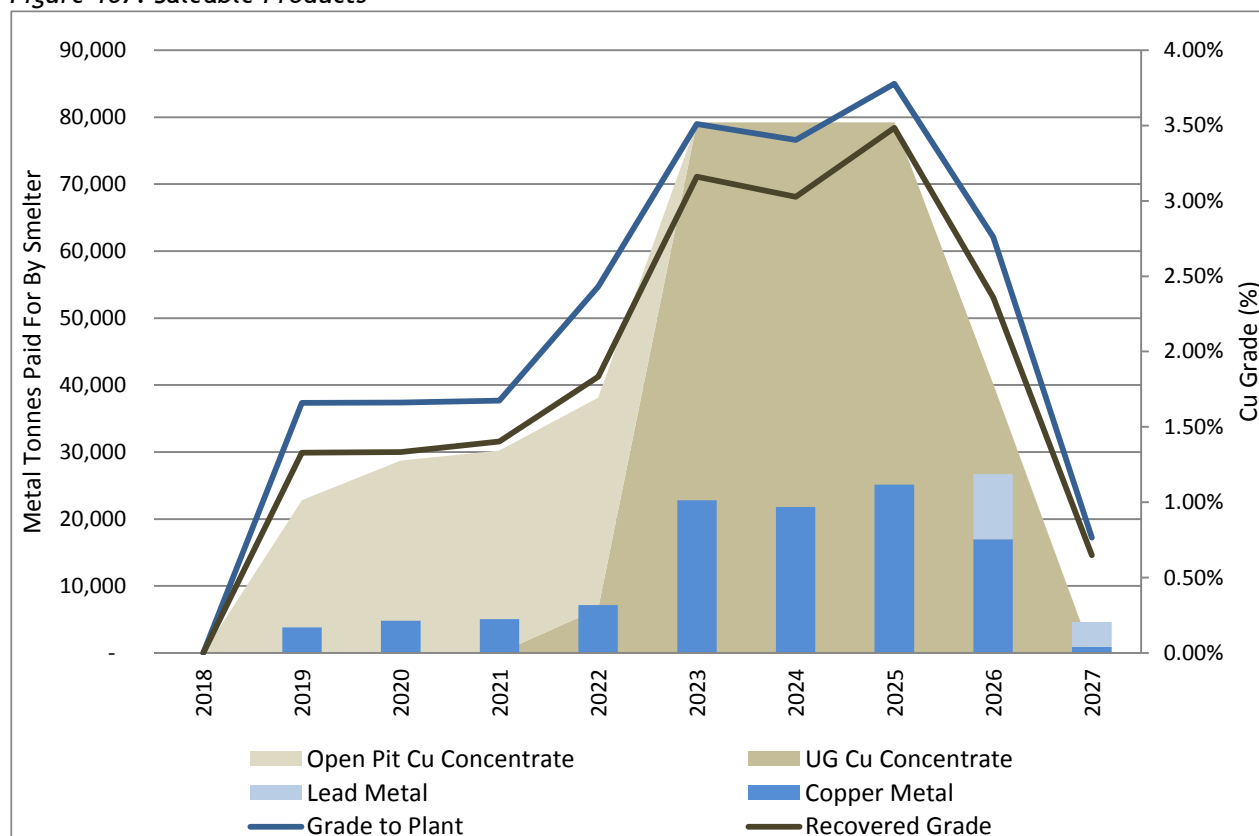Figure 107: Saleable Products



Valuation Results

The scope of this valuation exercise was to determine the financial viability of the Project. This was done by using the discounted cash flow method on a Free Cash Flow to the Firm (“FCFF”) basis, to calculate the nett present value (“NPV”) and the intrinsic value (fundamental value based on the technical inputs, and a cash flow projection that creates an NPV) of the Project in real terms. The discounted cash flow model is based on the total Mineral Resource, including Inferred, to determine the potential value of the Project.

The NPV is derived using post-royalties and tax and pre-debt real cash flows, after taking into account operating costs, treatment and refining fees paid to the smelter, corporate overheads, capital expenditures for the mining operations and the processing plant, and using forecast macro-economic parameters. The valuation reflects the full value of the operation and no attributable values were calculated. The model was set up in financial years with the first year 2018 starting in April 2017 and ending March 2018. The following macro-economic and commodity price forecasts were used in the discounted cash flow model.

Table 28: Macro-Economic Forecasts and Commodity Prices over the LoM (Real Terms)

Item	Unit	2017	2018	2019	2020	Long-term
Silver	USD/oz.	17.42	17.76	18.20	18.14	18.16
Copper	USD/tonne	5,624	5,510	5,628	5,733	6,507
Copper	USD/lb	2.55	2.50	2.55	2.60	2.95
Lead	USD/tonne	2,193	2,071	2,006	1,930	1,878
Lead	USD/lb	0.99	0.94	0.91	0.88	0.85

Source: Various Bank and Broker Forecasts (March 2017), Minxcon.

Note: Conversion: 1 Pound = 2,204.62 tonnes.

Table 29 illustrates the Project NPV at various discount rates with a best-estimated value of USD72 million at a real discount rate of 11.02% and a healthy internal rate of return (“IRR”) of 45.5%.

Table 29: Valuation Summary

Item	Unit	Kombat Copper PEA
NPV @ 0%	USD million	172
NPV @ 5%	USD million	117
NPV @ 10%	USD million	81
NPV @ 11.02%	USD million	72
NPV @ 15%	USD million	55
NPV @ 20%	USD million	37
IRR	%	45.5%
All-in Sustainable Cost Margin	%	37.1%
Peak Funding Requirement*	USD million	-46.1
Payback Period	Years	4.81
Break-even Copper Price	USD/Copper Equivalent t.	3,906

Note: * The Peak Funding Requirement is the maximum cumulative cash flow needed for the Project.


Monte Carlo Simulation

In order to evaluate risk, a Monte Carlo simulation was developed using a population of 5,000 simulations. This is a tool which allows the simulation of random scenarios to determine the effect thereof. Minxcon simulated various input parameters using a range in which a parameter is expected to vary (see Table 30). The current commodity prices is based on the average prices over the life of mine of the Project. The minimum and maximum price range are based on the real term historic copper price's 50th and 80th percentile over the past 37 years.

Table 30: Monte Carlo Input Ranges

Input	Min	Max	Current	Min	Max
Copper Price (USD/t)	69%	113%	6,213	4,300	7,036
Lead Price (USD/t)	90%	120%	1,994	1,794	2,393
Silver Price (USD/oz.)	90%	120%	18.96	17.07	22.76
Grade (%)	90%	110%	2.83%	2.55%	3.12%
Fixed Costs (USD/Milled t)	90%	110%	11	10	13
Variable Cost (USD/Milled t)	90%	110%	68	62	75
Mining Capex (USDm)	85%	115%	60	51	69
Plant Capex (USDm)	85%	115%	7	6	8

The simulation was done on the life of mine model. The results of the simulation are depicted in Figure 108. Using these figures in the Monte Carlo model, the value range of the Kombat operation plots between USD22.00 million (Quartile 25%) and USD76.37 million (Quartile 75%). The analysis shows a positive distribution with a medium deviation from the mean. The operation is therefore somewhat robust operation and moderately sensitive to change in the input parameters - an indication of medium risk. The best-estimated value of USD72 million is also related to the mean value of USD50 million derived from the Monte Carlo simulation.

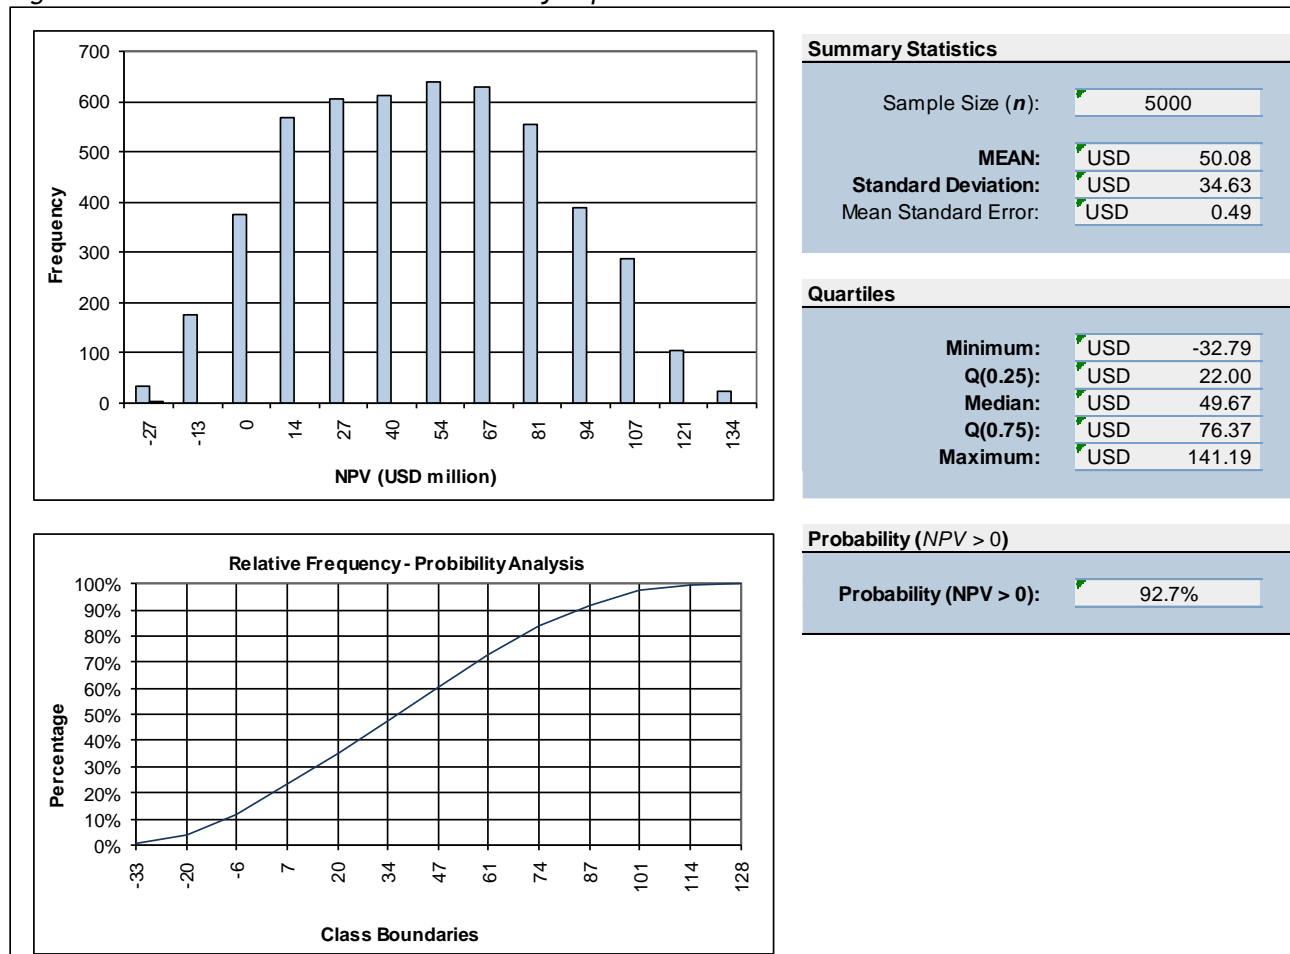Figure 108: Monte Carlo Simulation Summary Report

PEA Cash Flows

The annual cash flow before capital expenditure, total capital expenditure and cumulative cash flow forecast for the combined project over the life of mine is displayed in the figures to follow. The open pits will require the least work and time before it they can go into operation. While the open pits are being mined it enables the combined Project to pay back the initial infrastructure and plant capital and make a small return while at the same time generates the time for the underground Project to complete the studies, exploration, refurbishment, dewatering and development required to come into full production.

The cash flow of the initial east and central pits as a stand-alone model (excluding the underground capital requirement) is displayed in Figure 109, to better indicate the advantage that the open pits have. The pits pay back the plant and other capital in 3.7 years and generate cash that is utilised for the underground mines.


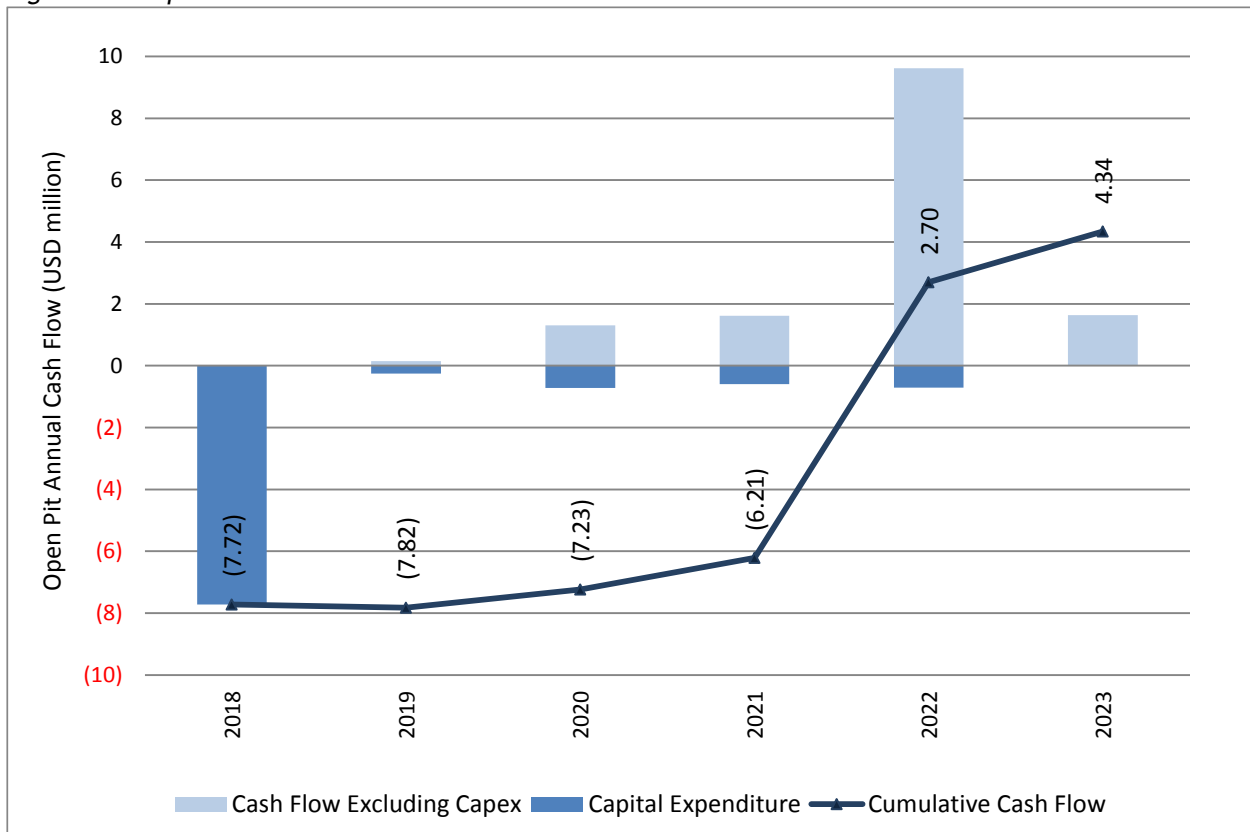
Figure 109: Open Pit Stand-alone Annual and Cumulative Cash Flow


Figure 109 indicates that the funding required to start the open pit production amounts to USD7.7 million. Including the underground mines into the cash flow the peak funding requirement, which is the maximum cumulative cash flow needed for the Project, increases by the capital expenditure of the underground mines. The peak funding requirement of the combined project per annum is displayed in Figure 110.

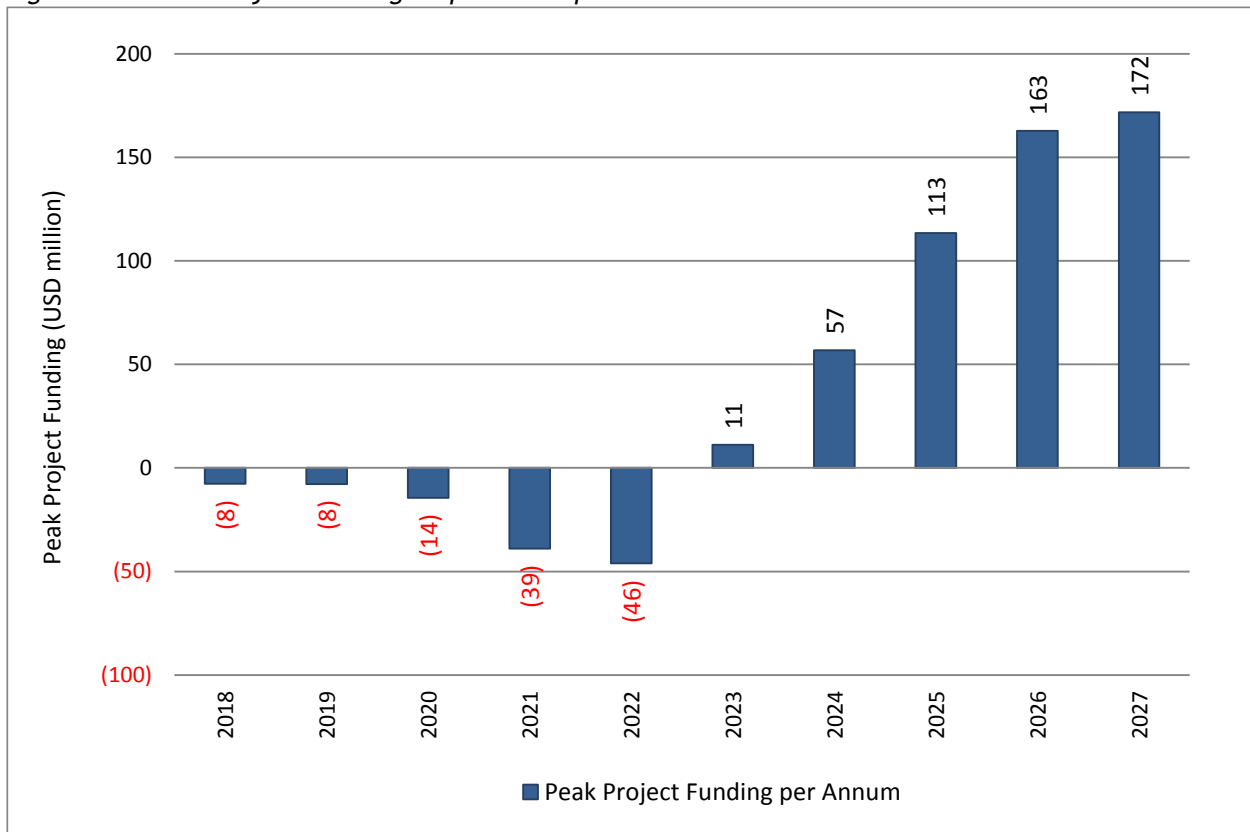Figure 110: Peak Project Funding Requirement per Annum



This maximum combined cash flow required amounts to USD46 million in 2022, thereafter the business is cash positive and no additional funding is required.

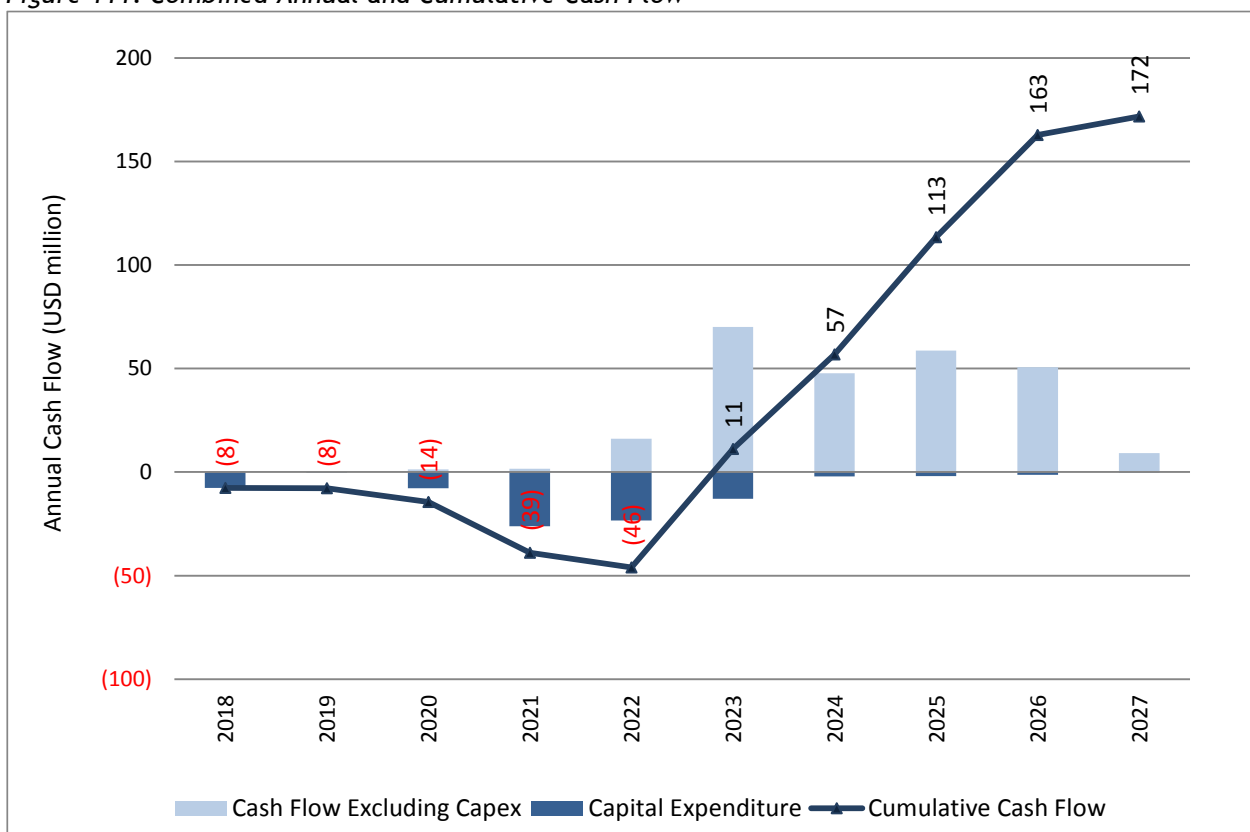Figure 111: Combined Annual and Cumulative Cash Flow




The current valuation is based on the current existing Mineral Resource that has been drilled to date. It is important to note that throughout the history of Kombat the mine rarely had a reserve inventory of more than three to five years due to the fact that exploration drilling was not carried out well in advance. One of the reasons for this is the nature of the orebody and the manner in which exploration was done at Kombat in the past. The short life of mine of each of the areas is thus an indication of what the current known Mineral Resource offers. The potential exists for the areas to increase the Mineral Resources and the life of the operations as the production commences which will extend the cash flows far beyond the current model valued.

PEA Sensitivity Analysis

Based on the real cash flow calculated in the financial model, Minxcon performed single-parameter sensitivity analyses to ascertain the impact on the NPV. The bars in Figure 112 represent various inputs into the model, each being increased or decreased by 2.5%, *i.e.*, the left side of graph shows lower NPVs because of lower prices and lower grades, higher Opex and Capex and the opposite on the right hand. The red line and black line respectively represent the least sensitive and most sensitive impacts to the NPV. For the DCF, the commodity prices and grade have the biggest impact on the sensitivity of the Project followed by the variable operating cost.

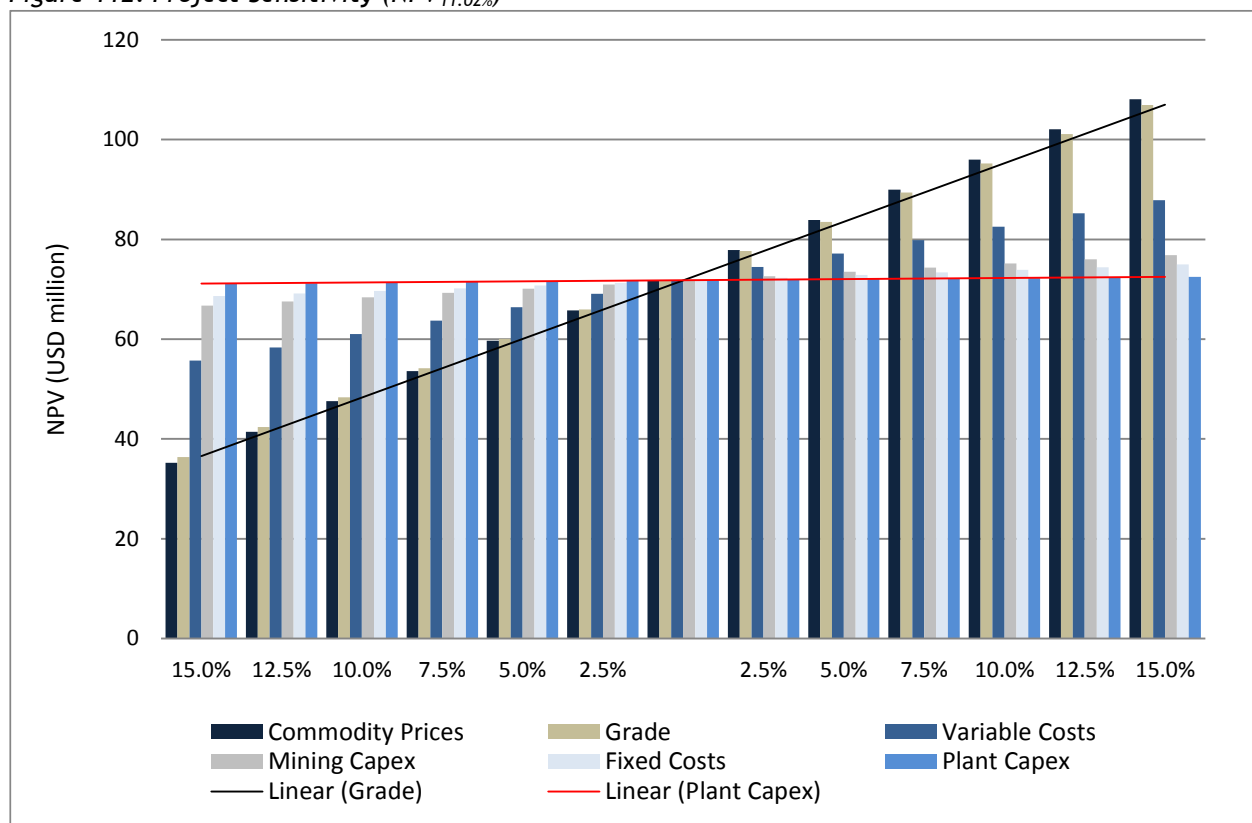Figure 112: Project Sensitivity (NPV_{11.02%})



To further demonstrate the sensitivities on the most sensitive impacts to the NPV, Minxcon included the following tables below. Table 31 displays the NPV sensitivity to net turnover and average copper grade while Table 32 displays the NPV sensitivity to the Project cash cost and average copper grade.

Table 31: NPV_{11.02%} Sensitivity to Net Turnover and Average Copper Grade (USD million)

	Cu Grade	2.41%	2.48%	2.55%	2.62%	2.69%	2.76%	2.83%	2.90%	2.97%	3.04%	3.12%	3.19%	3.26%
Net Turnover (USD/Copper Equivalent t)	Change %	85.0%	87.5%	90.0%	92.5%	95.0%	97.5%	100.0%	102.5%	105.0%	107.5%	110.0%	112.5%	115.0%
5,281	85.0%	5	10	15	20	25	30	35	40	45	50	55	60	65
5,436	87.5%	10	15	21	26	31	36	41	47	52	57	62	67	72
5,591	90.0%	15	21	26	32	37	42	48	53	58	63	69	74	79
5,747	92.5%	21	26	32	37	43	48	54	59	64	70	75	81	86
5,902	95.0%	26	32	37	43	49	54	60	65	71	76	82	87	93
6,057	97.5%	31	37	43	49	54	60	66	71	77	83	89	94	100
6,213	100.0%	36	42	48	54	60	66	72	78	84	89	95	101	107
6,368	102.5%	42	48	54	60	66	72	78	84	90	96	102	108	114
6,523	105.0%	47	53	59	65	72	78	84	90	96	102	109	115	121
6,678	107.5%	52	58	65	71	77	84	90	96	103	109	115	122	128
6,834	110.0%	57	64	70	77	83	90	96	102	109	115	122	128	135
6,989	112.5%	62	69	75	82	89	95	102	109	115	122	129	135	142
7,144	115.0%	67	74	81	88	95	101	108	115	122	128	135	142	149
7,455	120.0%	78	85	92	99	106	113	120	127	134	141	149	156	163

Table 32: NPV_{11.02%} Sensitivity to Cash Cost and Average Copper Grade (USD million)

	Cu Grade	2.41%	2.48%	2.55%	2.62%	2.69%	2.76%	2.83%	2.90%	2.97%	3.04%	3.12%	3.19%	3.26%
Cash Cost (USD/Milled t)	Change %	85.0%	87.5%	90.0%	92.5%	95.0%	97.5%	100.0%	102.5%	105.0%	107.5%	110.0%	112.5%	115.0%
104	130.0%	-3	3	9	15	21	27	33	39	45	50	56	62	68
100	125.0%	4	10	16	22	28	34	39	45	51	57	63	68	74
96	120.0%	10	16	22	28	34	40	46	52	58	63	69	75	81
92	115.0%	17	23	29	35	41	47	53	58	64	70	76	82	87
88	110.0%	23	29	35	41	47	53	59	65	71	76	82	88	94
84	105.0%	30	36	42	48	54	60	65	71	77	83	89	95	100
80	100.0%	36	42	48	54	60	66	72	78	84	89	95	101	107
76	95.0%	43	49	55	61	66	72	78	84	90	96	102	108	113
72	90.0%	49	55	61	67	73	79	85	91	96	102	108	114	120
68	85.0%	56	61	67	73	79	85	91	97	103	109	115	121	126
64	80.0%	62	68	74	80	86	92	97	103	109	115	121	127	133
60	75.0%	68	74	80	86	92	98	104	110	116	122	128	133	139
56	70.0%	74	80	86	92	98	104	110	116	122	128	134	140	146

ITEM 25 - INTERPRETATION AND CONCLUSIONS

Minxcon reviewed all the information and has made the following observations regarding the Project:-

NI43-101 CONCLUSIONS

- The geological controls and mineralisation mechanisms pertaining to the Kombat operations are well understood and documented, regardless of their complexity.
- Though the apparent oxide zone is very thin, however a good understanding of this interface is required.
- The Inferred confidence in the Mineral Resource classification for the Kombat operations is based on a combination of factors such as:-
 - Low local drillhole data density in some areas.
 - The lack of QAQC on the historical drillholes (pre-2012), regardless of the check sampling conducted by P&E.
 - The inability to accurately deplete the Mineral Resources due to lack of digital underground voids relative to the block model and
 - The fact that underground stope sampling data was not available to assist in constraining the mineralised halos.
- A considerable wealth of historical geological mapping and interpretation and drillhole core exists in the mine archives in various fireproof strong rooms or the coreshed that has not been included which may serve to significantly increase the confidence in the Mineral Resource estimate.
- Due to the care and maintenance status of the Kombat operations, standard operating procedures and protocols are not easily available and need to be documented or found.
- Minimal measured bulk density values are available to support the current estimate contributing to the Inferred Mineral Resource classification, regardless of the use of the Tsumeb Formula.
- Upside potential for the Kombat operations exists in the form of the already-evaluated TSF, the Gap area at Asis West (which has limited drilling) and possible strike extension of the copper corridor at Gross Otavi and the possible addition of Harasib, which is not part of the scope of this Report.

PEA CONCLUSIONS

The purpose of the PEA is to investigate the economic viability of the open pit and underground mining potential targeting the copper and lead resources at Kombat East, Kombat Central, Asis Far West, Asis West and Gross Otavi areas. The PEA investigated mining methods, treatment methods and development of additional infrastructure. The study focussed on the total Inferred Mineral Resource to determine the economic viability, upside potential as well as future exploration requirements. A DCF valuation was carried out on the PEA Study areas includes only Inferred Resources. The value derived from the PEA is considered to represent the upside potential value of the current copper and lead resources.

Mining

The orebody analysis showed that the shallow orebodies situated at Kombat East, Kombat Central and Gross Otavi are open pitable. Pit optimisations were conducted whereby the ultimate pits were selected for pit designs. The deeper orebodies' extraction require underground mining methods, and the current infrastructure will provide access to the workings. Mineable Stope Optimiser generated stope shapes utilised for the underground designs. The current underground infrastructure wireframes were incomplete and it was assumed that all connections were in place. This needs to be verified in the next study phase. The mine designs were based on geotechnical assumptions and a detailed study is required in the next study phase.

The mineable portion of the combined project, namely open pits and underground, comprises 4.5 Mt at a copper grade of 2.82%. This represents about 65% of the estimated Mineral Resource. The open pits comprise of 1.9 Mt at a copper grade of 1.61% and the underground comprises of 2.59 Mt at a copper grade of 3.94%. All the mining areas produce copper only as a product, except for Gross Otavi producing copper and lead. The current reserve inventory is based on Inferred Mineral Resources only. In order to convert to a formal Mineral Reserve, a pre-feasibility study needs to be conducted.

The optimal extraction sequence was determined by evaluating each mining area individually. The final sequence starts with Kombat East at 30 ktpm followed by Kombat Central at 30 ktpm. Gross Otavi commences with pre-stripping once Komabt Central is depleted. During the extraction of Kombat Central development at Asis Far West commences followed by development at Asis West. As production declines at Kombat Central, stoping at 60 ktpm commences at Asis Far West followed by stoping at Asis West. Gross Otavi ore extraction commences once Asis West is depleted at 60 ktpm.

This mining sequence enables ore extraction in the initial years from the open pits providing revenue to pay back the initial capital. From year three underground development commences simultaneously with open pit mining. This enables the mine to generate cash while opening up underground mining faces. The underground stopes are extracted once the required development is complete. The underground stopes provide the larger return and are extracted as soon as possible. Gross Otavi is processed at the tail of the mine plan due to the high stripping ratio and due to the processing of two products.

Processing

The existing processing plant will employ conventional well-tested flotation processing methods and is capable of producing copper and lead concentrates. The plant, once refurbished, will be capable of treating the planned 30 ktpm from the Kombat open pit areas. The plant will then need to be expanded to a capacity of 60 ktpm as mining production ramps up from underground.

The plant will initially produce only a copper concentrate at recoveries of between 87% and 93% when treating material from the Kombat, Asis and Asis Far West areas. Thereafter, the plant will produce copper and lead concentrates from the high-lead Otavi material at copper and lead recoveries of 70% and 80% respectively.

Engineering and Infrastructure

The Kombat operation is a well-established operation with all main infrastructure required already in place. Some maintenance, repairs and refurbishment will be required especially at the Asis West and Asis Far West underground operations. The existing infrastructure as well as the power and water supply will be capable and sufficient to accommodate the production rates planned as part of this PEA.

The Kombat East open pit comes within close proximity to the No. 3 shaft and its associated infrastructure. This may constitute a risk to the project. Dewatering of the underground workings is the most important requirement with regards to re-establishment of the underground operation and will require detailed assessment and planning. The size of the vertical shaft at Asis Far West may constitute a risk in term of transporting mining equipment underground.

Financial Valuation

Minxcon, together with the Client, derived a mining strategy to outfit the Project financially and practically in the best way. Although the majority of the Project value lies within the underground operation, the open pits will require the least work and time before they can go into operation. While the open pits are being mined it enables the combined Project to pay back the initial infrastructure and plant capital and make a

small return, while at the same time generating the time for the underground Project to complete the studies, exploration, refurbishment, dewatering and development required to come into full production.

The following conclusions were reached regarding the Project PEA:-

- The Project investigated is financially feasible at an 11.02% real discount rate.
- The best-estimated value of the PEA was calculated at USD72 million at a real discount rate of 11.02% and the Project has a healthy IRR that was calculated at 45.5%.
- By using the Monte Carlo model for the PEA, the positive distribution value range of the Project plots between USD47 million and USD96 million.
- The Monte Carlo analysis has a relatively small deviation from the mean and is therefore a robust operation and not very sensitive to change in the input parameters - an indication of lower risk.
- The PEA is most sensitive to commodity prices and grade.
- The PEA has a break-even copper price of USD1.77/copper equivalent pound, including capital.

ITEM 26 - RECOMMENDATIONS

Minxcon recommends the following for the Project:-

NI43-101 RECOMMENDATIONS

- All sections and plans with historical stope face positions should be digitised for incorporation into the mine void model in order to increase the confidence in the depletion of the Mineral Resource estimate.
- Historical, as well as recent processes and protocols pertaining to any sampling data should be updated and standardised in line with current accepted industry best practice in order to assist in future Mineral Resource assessments.
- The wealth of core in the coreshed should be utilised to add to a re-assay programme, over and above the one conducted by P&E, and should consider a wide spread of data over the historical life of the mine.
- The wealth of historical core available can be used to better inform the measured bulk density database. In future the mine should also consider the purchase of a scale to conduct routine raw bulk density measurements in order to support the Tsumeb Formula and save cost.
- Historical geological mapping (underground and surface) should be digitally captured and elevated in order to lend further integrity to the digital Mineral Resource estimation process.
- It is strongly recommended that drillhole assays and check assays are sent to accredited laboratories for sample preparation and analysis.
- Additional drilling is recommended to improve confidence in the orebody and Mineral Resources and should also consider the oxide sulphide transition.
- In future, all drilling should be sampled for silver due to the current low silver data density.

PEA RECOMMENDATIONS

In order to declare Mineral Reserves, a pre-feasibility study should be completed. As part of the pre-feasibility, processing assumptions and plant recoveries should be updated. Mine planning, schedule optimisation, operating cost and capital estimations should be updated to the required level of detail. The production rate and extraction sequence should be investigated in detail.

Mining

During the pre-feasibility study, a geotechnical study and geohydrological study is recommended to recommend the rock engineering parameters for all mine designs. The optimal return air strategy for Asis Far West should be investigated in the pre-feasibility study. The optimal extraction methodology for Gross Otavi should be investigated in the pre-feasibility study.

Processing

Metallurgical testwork will be required to verify the expected processing recoveries and the plant design. The tests should also serve to confirm reagent requirements and reagent consumptions to better estimate plant operating costs.

Engineering and Infrastructure

It is recommended that during the next study level a complete and detailed assessment and plan be conducted with regards to the dewatering of the underground operation as well as the refurbishment of the main hoisting shafts. These areas will be critical in terms of re-establishment of the operation.

According to a water balance conducted, it can be expected that both during initial dewater and dewater during steady state production an excess of water will be present at the operation. Although NamWater utilises the majority of the excess water there may still be excess water remaining that will have to be discarded. A clear plan needs to be set out in terms of how and where excess water can be discarded/released.

A detailed trade-off study will be required to select mining equipment that will be able to be transported down the vertical shaft and still meet the required production.

Financial Valuation

The assumptions made and strategy followed should be further investigated in the pre-feasibility study. The Project valuation is sensitive to the treatment and smelter charges and it is imperative for Trigon to get certainty with regards to off-take agreements and the actual costs associated with delivering a concentrate to the Tsumeb smelter.

ITEM 27 - REFERENCES

- Awmack, H.J. (2012). Technical (NI43-101) Report on the Kombat Project, Prepared for Pan Terra Industries Inc., January 31, 2012.
- <http://www.mining-technology.com/projects/tschudi-copper-project/>. Accessed on 31 March 2017.
- <https://en.climate-data.org/location/171570/>. Accessed on 31 March 2017.
- Deane, J.G. (1995) The structural evolution of the Kombat deposits Otavi Mountainland, Namibia. Communications of the Geological Survey of Namibia, 10 (1995), 99-107.
- Gray, D. R.; Foster, D. A.; Meert, J. G.; Goscombe, B. D.; Armstrong, R.; Trouw, R. A. J.; Passchier, C. W. (2008). "A Damara orogen perspective on the assembly of southwestern Gondwana" (PDF). Geological Society, London, Special Publications. 294 (1): 257-278. doi:10.1144/SP294.14. Retrieved 7 May 2017.
- Kamona, A.F., Günzel, A. (2007) Stratigraphy and base metal mineralisation in the Otavi Mountain Land, Northern Namibia - a review and regional interpretation. Gondwana Research Vol. 3, 396 - 413.
- Kruger, T.M., and Kisters, A. (2016) Magma accumulation and segregation during regional-scale folding: The Holland's dome granite injection complex, Damara belt, Namibia. Journal of Structural Geology, 89, 1-18.
- Laukamp, C. (2007) Structural and fluid system evolution in the Otavi Mountainland (Namibia) and its significance for the genesis of sulphide and nonsulphide mineralisation, Ph.D. Inaugural Dissertation, Ruprecht-Karls University, Heidelberg, Germany. 167 pp.
- Meert, J.G. and Lieberman, B.S. (2008) The Neoproterozoic assembly of Gondwana and its relationship to the Ediacaran- Cambrian radiation. Gondwana Research, 14, pp. 5-21.
- Minz, F., (2008) The Kombat ore deposit, Otavi Mountainland (Northern Namibia). Advanced Seminars, Institute for Geology, Technical University Berg Academy, Freiberg. 18 pp.
- Mughongora, A. 2007: Kombat metallurgy laboratory. Weatherly Mining Namibia internal report, October 31, 2007, 10 p.
- P&E Mining Consultants Inc. (2014). Technical Report and Resource Estimate on the Kombat Copper Project, Grootfontein District, Otjozondjupa Region, Namibia. Latitude 19° 42' 35"S Longitude 17° 42' 09"E UTM Zone 33K 783301 m E 7818395 m S for Kombat Copper Inc. Effective Date 20 May 2014. Authored by Puritch, E., Routledge, R., Sutcliffe, R., Burga, D. and Hayden, A. 114pp.
- Sabre Resources Limited (2015). ASX Announcement and Media Release, 30 October 2015. Quarterly Activities for the quarter ended 30 September 2015. 8pp.
- Sabre Resources Limited (2016). Annual Report 2016. 73pp.
- SLR Namibia (2016). Manila Investments (Pty) Ltd, Kombat Copper Mine - Environmental Gap Analysis. Report No.: 01. September 2016. 19pp.
- Sound Mining Solutions (Pty) Ltd (2014). Conceptual Mining Study for Underground Mining at AFW Shaft for Kombat Copper Inc. Report No: SM/138/14. October 2014. 136pp.

APPENDIX

Appendix 1: Qualified Persons' Certificates

CERTIFICATE of QUALIFIED PERSON

I, Uwe Engelmann, do hereby certify that:-

1. I am a Director of **Minxcon (Pty) Ltd**
Suite 5, Coldstream Office Park,
2 Coldstream Street,
Little Falls, Roodepoort, South Africa
2. I graduated with a BSc Honours (Geology) degree from the University of the Witwatersrand in 1991.
3. I have more than 18 years' experience in the mining and exploration industry. This includes eight years as an Ore Resource Manager at the Randfontein Estates Projects on the West Rand. I have completed a number of assessments and technical reports pertaining to various commodities, including copper, using approaches described by the National Instrument 43-101 (Standards of Disclosure for Mineral Projects), Form 43-101F1 and the Companion Policy Document 43-101CP ("NI 43-101").
4. I am affiliated with the following professional associations, which meet all the attributes of a Professional Association or a Self-Regulatory Professional Association, as applicable (as those terms are defined in NI 43-101):-

Class	Professional Society	Year of Registration
Member	Geological Society of South Africa (MGSSA No. 966310)	2010
Professional Natural Scientist	South African Council for Natural Scientific Professions (Pr.Sci.Nat. Reg. No. 400058/08)	2008

5. I am responsible for all Items of the technical report titled "NI 43-101 Technical Report on the Kombat Copper Project, Namibia - Mineral Resource Report" prepared for Trigon Metals Inc. with an effective date of 1 April 2017 ("the Report").
6. I have read the definition of "Qualified Person" set out in NI 43-101 and certify that by reason of my education, affiliation with professional associations and past relevant work experience, I fulfil the requirements to be a Qualified Person for the purposes of the Report.
7. I have read NI 43-101 and the Report has been prepared in compliance with it.
8. As of the effective date, to the best of my knowledge, information and belief, the Report contains all scientific and technical information required to be disclosed to make the Report not misleading.
9. I am independent of Trigon Metals Inc. as such term is defined in Section 1.5 of NI 43-101. My compensation, employment or contractual relationship with Trigon Metals Inc. is not contingent on any aspect of the Report.
10. I undertook a personal inspection of the property on 9 to 10 April 2017 to inspect the core storage facilities and other areas of interest on the Kombat Project Areas.

Signed at Little Falls, Roodepoort on 02 June 2017.



U ENGELMANN

BSc (Zoo. & Bot.), BSc Hons (Geol.)

Pr.Sci.Nat., MGSSA

DIRECTOR, MINXCON

KEY AUTHORS

Mr Daniel (Daan) van Heerden (Director, Minxcon): B Eng (Min.), MCom (Bus. Admin.), MMC, Pr.Eng. (Reg. No. 20050318), FSAIMM (Reg. No.37309), AMMSA.

Daan has worked in the mining industry for over 30 years. He has a vast amount of experience in managing underground and open cast mining operations in South Africa and abroad for world-class mining majors and junior mining companies. He was responsible for new business development for two major mining companies and has experience in mining mergers and acquisitions. He is currently heading the Mining Engineering division of Minxcon, where he is integrally involved in activities such as valuation, due diligence, finance structuring, change management required post the event, feasibility studies, life of mine plans, technical reviews and writing of technical reports for various commodities.

Mr Johan Odendaal (Director, Minxcon): BSc (Geol.), BSc Hons (Min. Econ.), MSc (Min. Eng.), Pr.Sci.Nat. (Reg. No. 400024/04), FSAIMM (Reg. No. 702615), MGSSA (Reg. No. 965119).

Johan Odendaal has over 30 years' experience in the mining and financial industry. This includes 12 years as independent mining consultant specialising in the valuation of Mining Projects and 12 years as a mining analyst at two major stockbroking firms and investment bank. During this time he was rated one of the top platinum and gold mining analysts and became a globally recognised industry specialist in a various commodities. Regular contact with the mining, corporate and investment community allowed him to build an extensive network of contacts around the globe specialising in valuation of mining companies. He commands a wide range of knowledge on both local and international mining companies. As a former employee of a Global Investment Bank, he was actively involved in Financial Analysis and advising mining companies and investment bankers on corporate mining transactions. Johan has a vast experience in fundamental analysis of commodity markets. His experience with regard to Mineral Asset Valuations, Concept Studies, Competent Persons Reports, Due Diligence and Technical Reports includes precious metals, ferrous and non-ferrous metals, coal, diamonds and a number of minor metals and commodities. Johan also serves on the JSE Issuer Regulation Advisory Committee and SAMVAL Working Group.

Mr Dario Clemente (Director, Minxcon Projects SA): NHD (Ext. Met.), GCC, BLDP (WBS), MMMA (Reg. No. M000948), FSAIMM (Reg. No. 701139)

Dario has over 40 years' experience in the metallurgical industry, including five years abroad working for large international companies - as a Metallurgical Manager at a tungsten and tin base metal mine; and as a Technical Consultant at a polymetallic copper operation. He has extensive experience in base metal and platinum group metals refining, as well as gold and uranium metallurgy. He has also co-authored technical papers and presented his findings locally and abroad. He is currently heading the Metallurgy division of Minxcon Projects.

Mr Paul Obermeyer (Mineral Resource Manager, Minxcon): BSc Hons (Geol.), Pr.Sci.Nat. (Reg. No. 400114/06).

Paul has 19 years' experience in the mining industry, where he has gained extensive experience in data processing and orebody modelling using Datamine™, and the fields of sedimentology, stratigraphy, gold exploration and QAQC. He has been involved in projects with commodities such as of gold, platinum, coal and base metals. He was a Chief Geologist on one of South Africa's most complex mines for four years. He has worked in a production environment for 13 years, as well as in exploration. Owing to his experience, Paul is also well-equipped to conduct due diligence exercises on operations for different commodities and to conduct audits.

Mr Laurence Hope (Senior Resource Geologist, Minxcon): NHD (Econ. Geol.), Pr.Sci.Nat. (Reg. No. 200010/11).

Laurence has been involved in the mining industry for over 25 years in both production and consulting. As a geologist, he has held managerial level positions for over 12 years, leading teams in numerous work environments. He has extensive experience of over 18 years in 3D geological modeling and Mineral Resource estimation for a variety of deposit types. He is proficient in many geological modeling software programs, including Vulcan, Surpac, Datamine, Micromine and Leapfrog3D. He has worked as a production geologist on a variety of mines and conducted exploration programmes in the field. As a consultant, a main function of his career has been in mine database management and QAQC.

Miss Maria Antoniadis (Geologist, Minxcon): BSc Hons (Geol.), Cand.Sci.Nat. (Reg. No. 114426), MGSSA.

Maria obtained her Honours Degree in Geology in 2006. She started her career as a Mineral Projects Analyst, where she gained experience in the assessment of mineral projects across a variety of commodities. She has worked as a sole in-house geologist, setting up company standards and assessing geological terrains. Maria has Minxcon as geologist, forming an integral part of the team undertaking roles including geological interpretations, editing and mining project co-ordination. She is actively involved in the compilation of technical documentation in compliance with the main reporting codes requirements and performs reviews of various mining and exploration projects to indicate their viability.

Mr Sherlock Rathogwa (Exploration Geologist, Minxcon): BSc (Geol. & Math.), BSc Hons (Geol.), MGSSA.

Sherlock has over five years' experience in the mining industry. He graduated with a B.Sc. in Geology and Mathematics from the University of Johannesburg in 2008. In 2009 he obtained his B.Sc. Honours in Geology from the University of Johannesburg. His experience includes extensive field exploration geology in a wide range of minerals and geological settings, GIS application in geology, 3D geological modelling. Sherlock has gained excellent proficiency in geological field work as well as the associated and relevant office work. He has worked on drilling projects where he monitored and supervised diamond drilling campaigns.

Mr Jaco Burger (Mining Engineer, Minxcon): B Eng (Min.), PG Dip. (Fin. Man.), MMC, Pr.Eng. (Reg. No. 20130533), MSAIMM.

Jaco joined the team of Mining Engineers and the financial side at Minxcon in March 2012. He is currently working on a wide range of projects involved in mine design, mine operating cost and capital cost evaluation and financial estimations. While working for Anglo Platinum on Rustenburg Platinum Mines, he gained production and management experience while working in various positions in production in both the conventional breast and up-dip mining. He obtained his Mine Managers Certificate for Metalliferous Mines in October 2012.

Mr Wilhelm Warschkuhl (Mining Engineer, Minxcon): B Eng (Min.), B Eng Hons (Min.), MSAIMM.

Wilhelm is a mining engineer with seven years' experience in the mining industry. He has had the privilege to gain a respectable amount of experience from two different mining environments. He worked for various internationally acclaimed companies. Wilhelm has completed his underground coal blasting certificate and gained coal mining experience as a miner at Khutala Colliery. He then joined Hatch Goba whereby he gained experience in mine planning, supplier engagement, production scheduling and operational cost estimating. During his time with Hatch Goba he was involved with Order of Magnitude Studies, Pre-Feasibility Studies and Feasibility Study. During his time with VBKOM Consulting Engineers he gained experience in open pit mine design and scheduling. Wilhelm has experience in operating various mining software, namely Mine 2-4D, Studio Planner, EPS Scheduler, Deswik and Deswik Scheduler, Surpac and Mineshed.

Mr Julian Knight (Senior Process Engineer, Minxcon): B Eng (Chem.), B Eng Hons (MOT), Pr.Eng. (Reg. No. 20150289), MSAIMM.

Julian has experience in process control and optimisation as well as project management of platinum and base metals commercial projects. Furthermore, Julian has an R&D background in process control in the PGM and BM industries. As a Process Engineer at Minxcon, he is responsible for leading process engineering work with his skills directed at the metallurgical discipline in all projects that involve processing from metallurgical accounting reviews to feasibility studies and onsite optimisation. He is currently working on a wide range of projects in various commodities and forms part of Junior Management and the Executive Committee.

Mr Jano Visser (Mechanical Engineer, Minxcon): B Eng (Min.), GCC.

Jano obtained his B.Eng. (Mechanical) degree from the North West University in 2009. From 2010 he was an employee of Anglo American Platinum on the Engineer in Training Programme. During a two and a half year period he gained exposure and experience in the different company fields including shafts, underground mining (conventional and trackless), concentrators, smelters and refineries. As part of the programme he acted in various Foreman, Senior Foreman and Section Engineer roles. Jano obtained his Government Certificate of Competency -Mines and Works (Mechanical) in June 2012. In October 2012 he was appointed as Section Engineer (Production) within Anglo American Platinum. Jano joined Minxcon in November 2015 as a mechanical engineer, consulting on various mining projects and a variety of commodities. He has valuable experience in mine infrastructure design and operating and capital cost estimations.

Appendix 2: Historical QAQC Results

2012 Re-sampling Programme (Gross Otavi)

During the 2012 core re-sampling programme, the protocol included the insertion of six certified reference materials within 117 core samples to be submitted to Bureau Veritas. CRMs were purchased from Canadian Resource Laboratories Ltd. The table below presents all CRMs used during the 2012 core re-sampling programme.

Summary of CRMs used During 2012 Core Re-sampling programme.

CRMID	Provisional	Certified Concentration			
	Au	Ag	Cu	Pb	Zn
	g/t	g/t	%	%	%
CND-ME-13	0.148 ± 0.024	76.5 ± 6.8	2.69 ± 0.2	1.70 ± 0.09	18.48 ± 1.83
CDN-ME-19	0.62 ± 0.062	103 ± 7	0.474 ± 0.018	0.98 ± 0.06	0.75 ± 0.04


Analytical performance is judged by warning limits of +/- two standard deviations from the mean of the between-lab round robin characterisation, and tolerance limits of +/- three standard deviations from the certified mean. Values should remain between +/- two standard deviations nine times out of ten. Any values falling outside the tolerance limits are failures and must be examined on a case-by-case basis.

The table below presents a summary of performance of all CRMs used during the 2012 core re-sampling programme.

Summary of Performance of CRMs Analysis

Standard	Acceptance	Remarks
CDN-ME-13 Cu%	Pass	Values at or slightly below mean value
CDN-ME-13 Pb%	Pass	Slightly low but within one standard deviation
CDN-ME-13 Ag g/t	Fail	All values lower than three standard deviations
CDN-ME-19 Cu%	Marginal	Sample #10107 fail; Samples 10027 & 10067 warnings
CDN-ME-19 Pb%	Pass	Sample #10107 warning
CDN-ME-19 Ag g/t	Fail	All values lower than three standard deviations

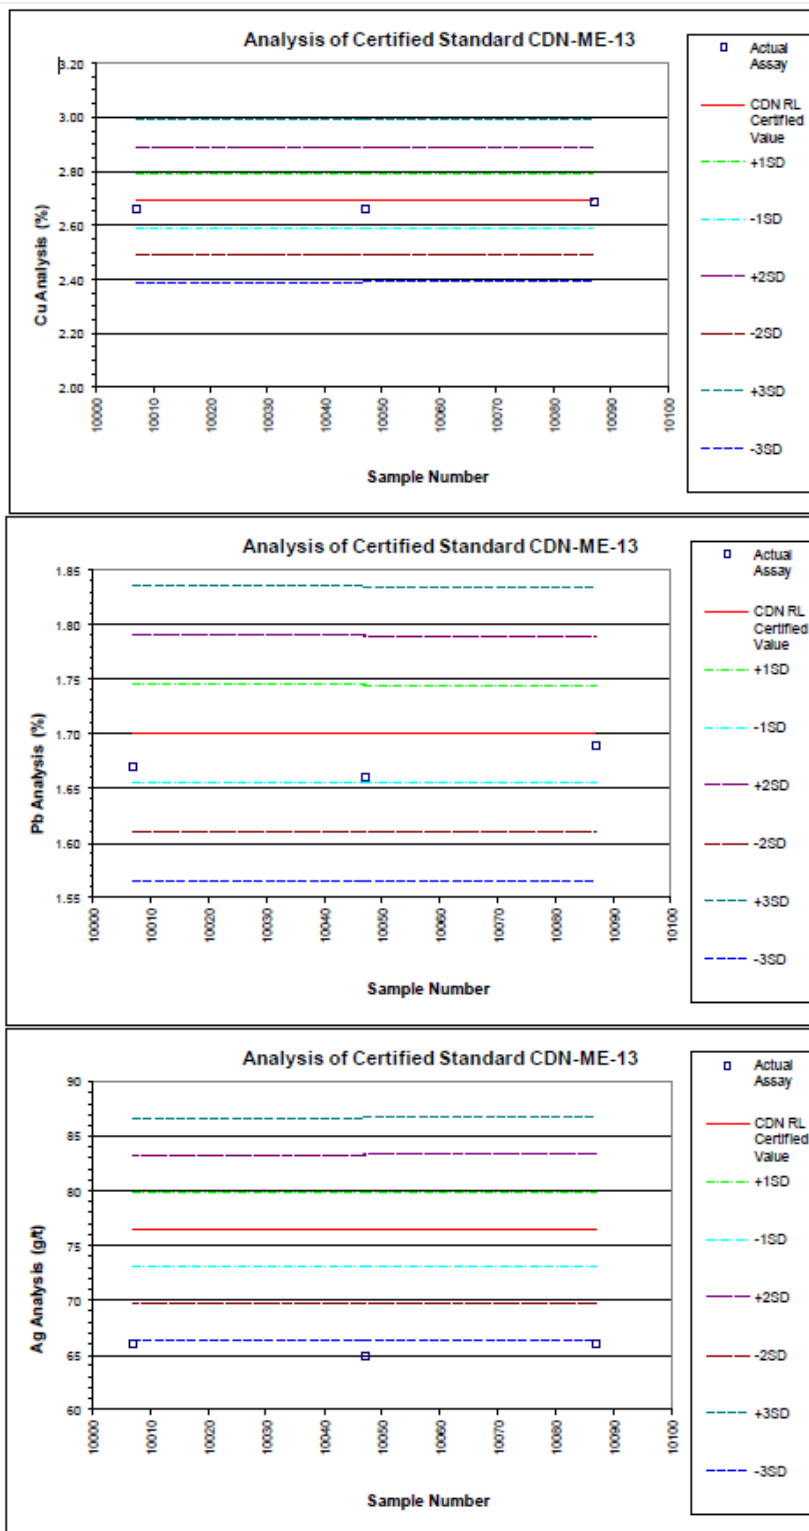
Figure below depicts the CND-ME-13 CRM performance. Three samples failed Silver analysis, and the batch containing these samples should have been re-assayed. It is not known whether this was conducted or not.

Performance of CND-ME-13

Source: P&E Mining, 2014

Performance of CND-ME-13**April 2017**

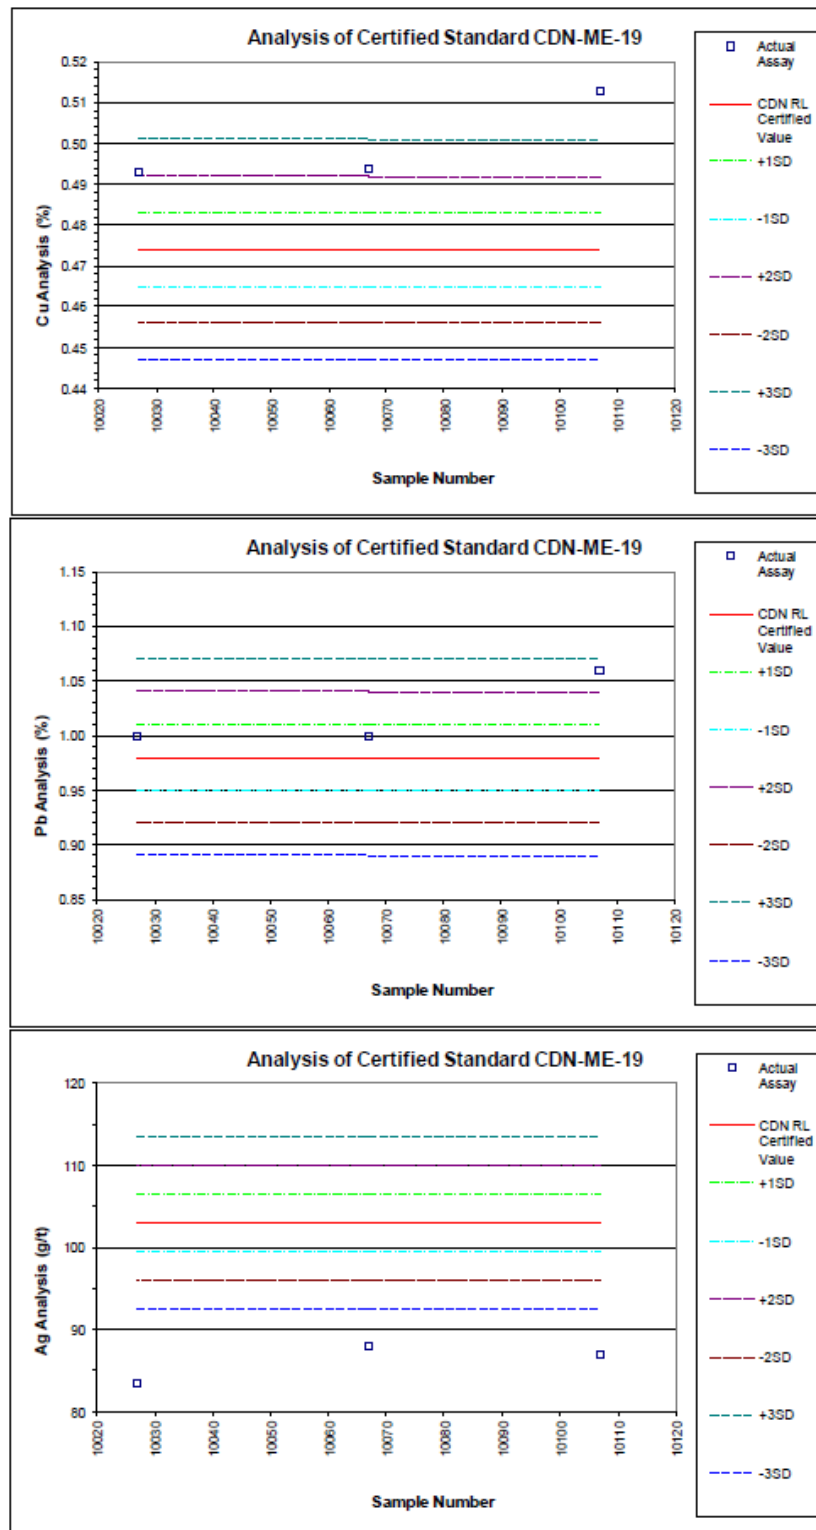Lead analyses are acceptable. The batches containing the CDN-ME-19 standard, i.e. samples 10107, 10027 and 10067, are likely to have analysed high for copper and should have been rerun for copper. Silver analysed unacceptably low for all six standards submitted and all samples should have been rerun for silver.

Performance of CND-ME-19

Source: P&E Mining, 2014

Performance of CND-ME-19**April 2017**

Blank Material

Analytical blank, CDN-BL-10 was utilised during the 2012 re-sampling programme. The blank material was purchased from CDN Resource Laboratory in Langley, BC. And it was prepared from granitic rock. CDN-BL-10 was certified for gold, platinum and palladium only and had no certified or recommended values for copper, lead and silver. Table below presents details of the certified blank that was utilised during 2012 re-sampling programme.


Detailed Summary of CDN-BL-10

ID	Type	Certified Concentration						
		Au	Pt	Pd	Ag	Cu	Pb	Zn
		g/t	g/t	g/t	g/t	%	%	%
CDN-BL-10	Pulp Blank	<0.01	<0.01	<0.01	-	-	-	-

The blanks were pre-pulverized to -53 µm and as such did not pass through the crushing and pulverizing stages of the sample preparation, which are most at risk for contamination.

Six blanks were analysed during the re-sampling program, and results indicated that contamination post-preparation was not an issue for Pb and Ag. Cu blanks returned less than 25 ppm but all exceeded the expected threshold of 6 ppm, which is three times the lower detection limit of 2 ppm. This level of Cu may represent background values in the blank material.

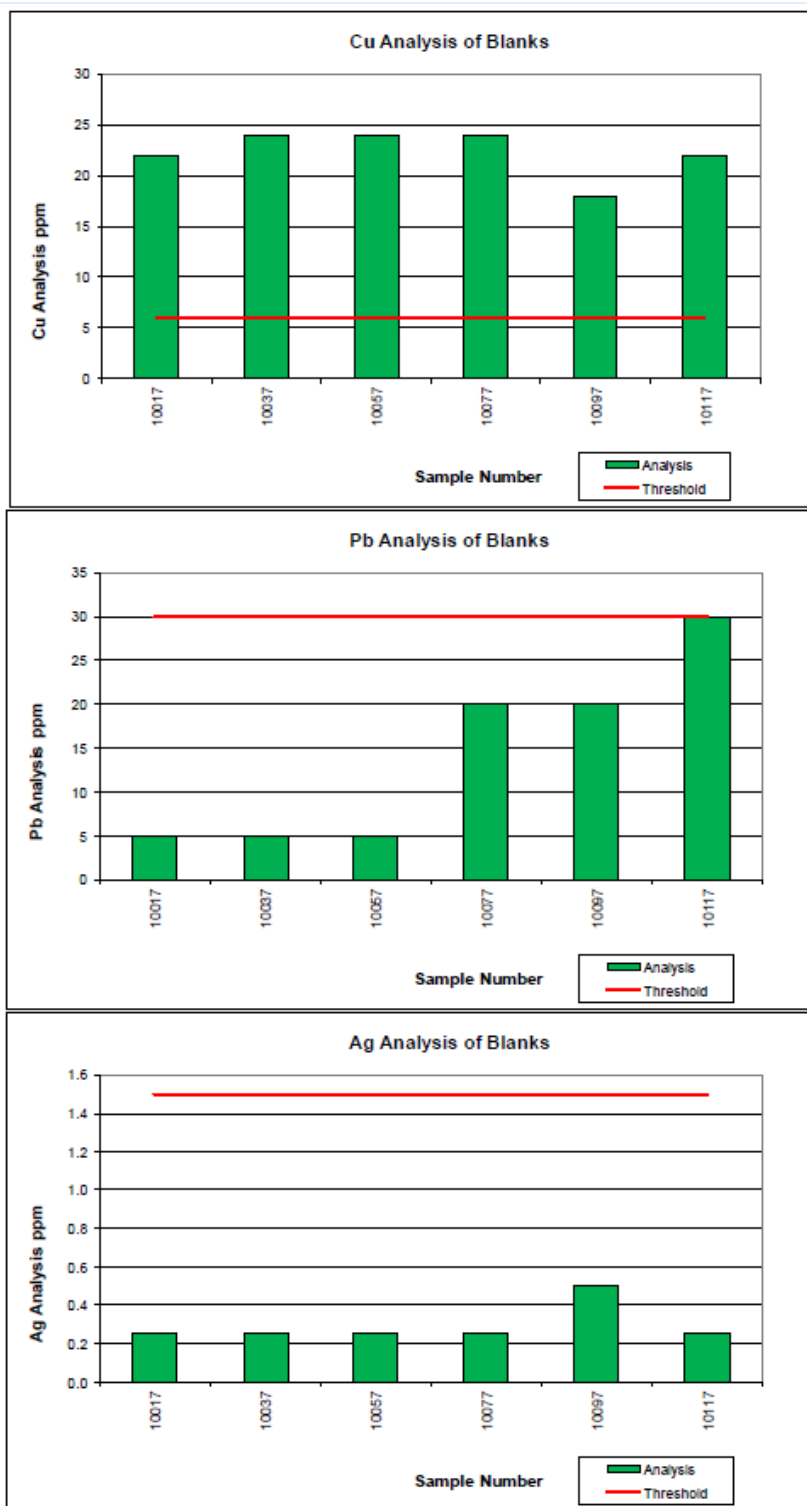Performance of Certified Blanks



Source: P&E Mining, 2014

Performance of Certified Blanks


April 2017

Core Duplicates

The re-sampling program samples are essentially core duplicates and outside lab check samples since the analytical laboratory is Bureau Veritas and not the original Kombat Mine or Tsumeb laboratories. As such, sampling variance and inter-laboratory analytical variance are combined into higher overall variance.

There were 102 field duplicate pairs, comprised of a quarter core splits sent for analysis at Bureau Veritas. Scatter plots of paired analyses for copper, silver and lead are shown in the figure below. The scatter is considerable with linear correlation coefficients (R^2) of <0.5 with the relative standard deviation ("RSD") of 147 % indicating poor reproducibility with a bias to higher grades for the original assays. At the 95% confidence limit the expected difference between assays is ± 200 %. The cause for this lack of combined accuracy and precision is likely contamination at the Kombat Mine laboratory and/or poor (selective) core sampling practice. Bureau Veritas analysed two pulp duplicate pairs as part of their internal quality control. Precision was acceptable for Cu, Pb and Ag.

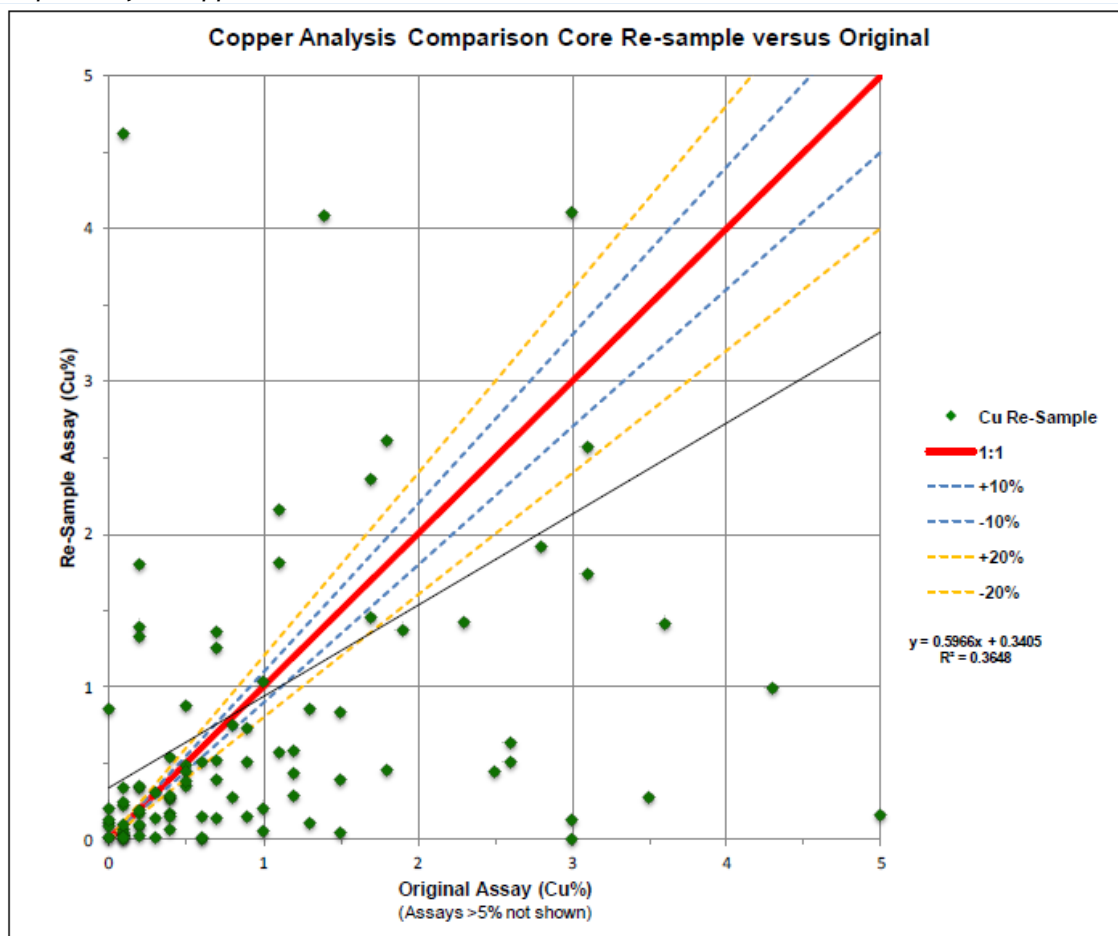
AFW Core Duplicate for Copper.



Source: P&E Mining, 2014


AFW Core Duplicate for Copper

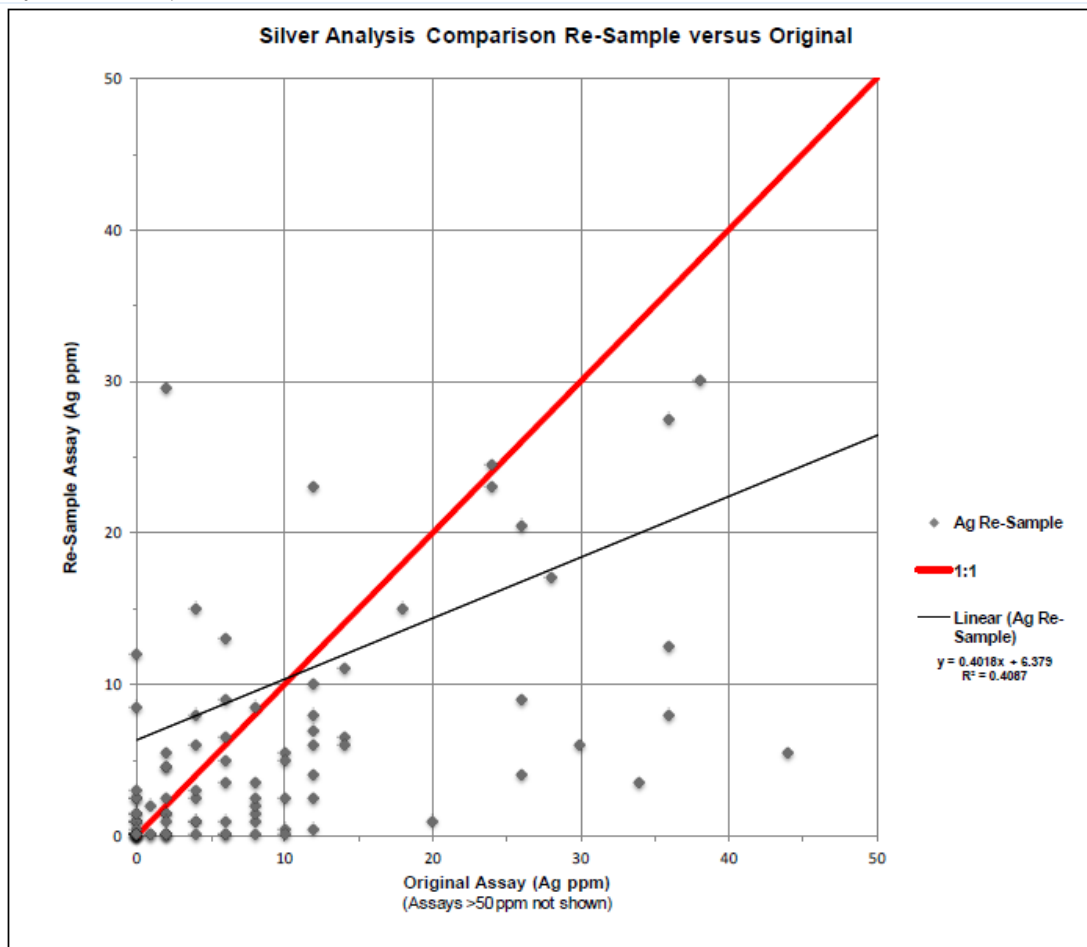April 2017

AFW Core Duplicate Pair for Silver


Source: P&E Mining, 2014

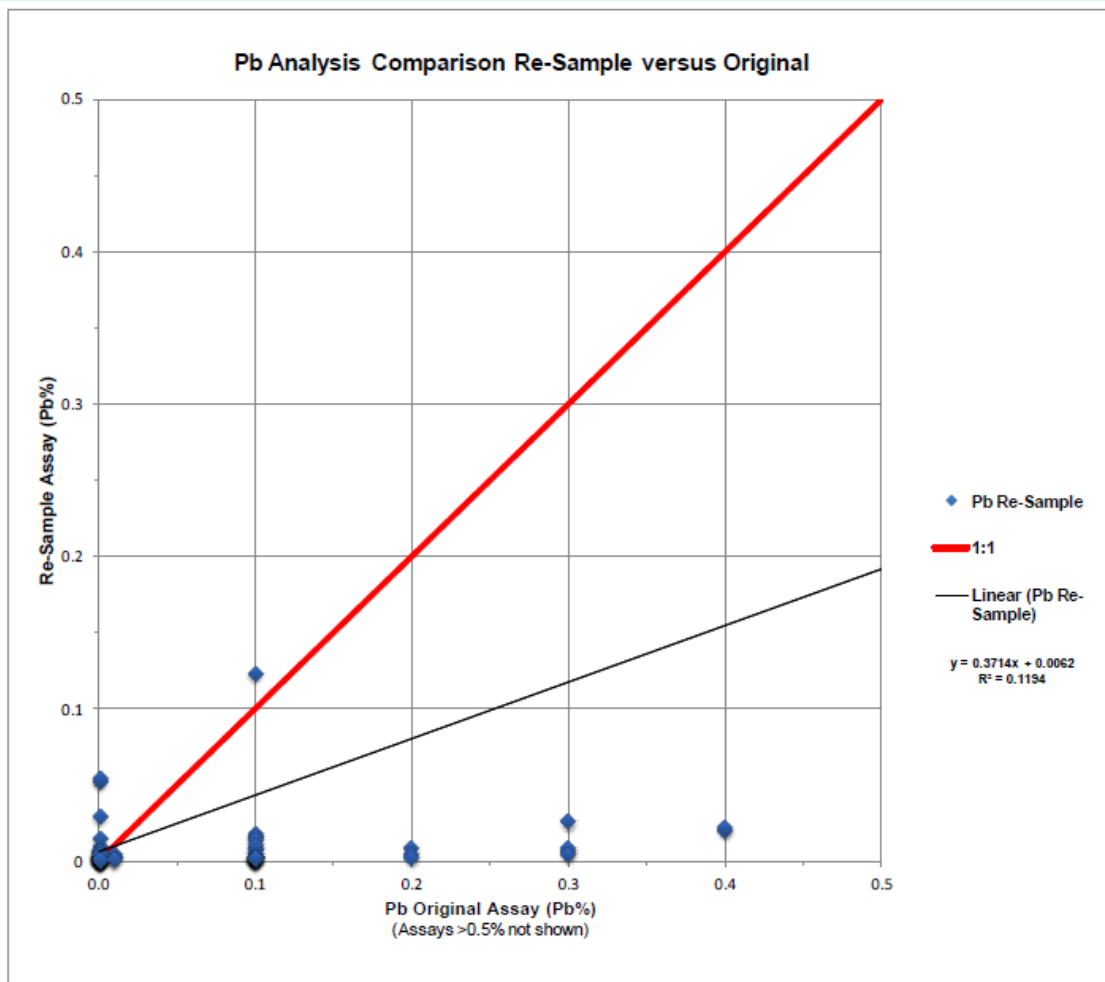AFW Core Duplicate Pair for Silver**April 2017**

AFW Core Duplicate Pair for Lead

Source: P&E Mining, 2014

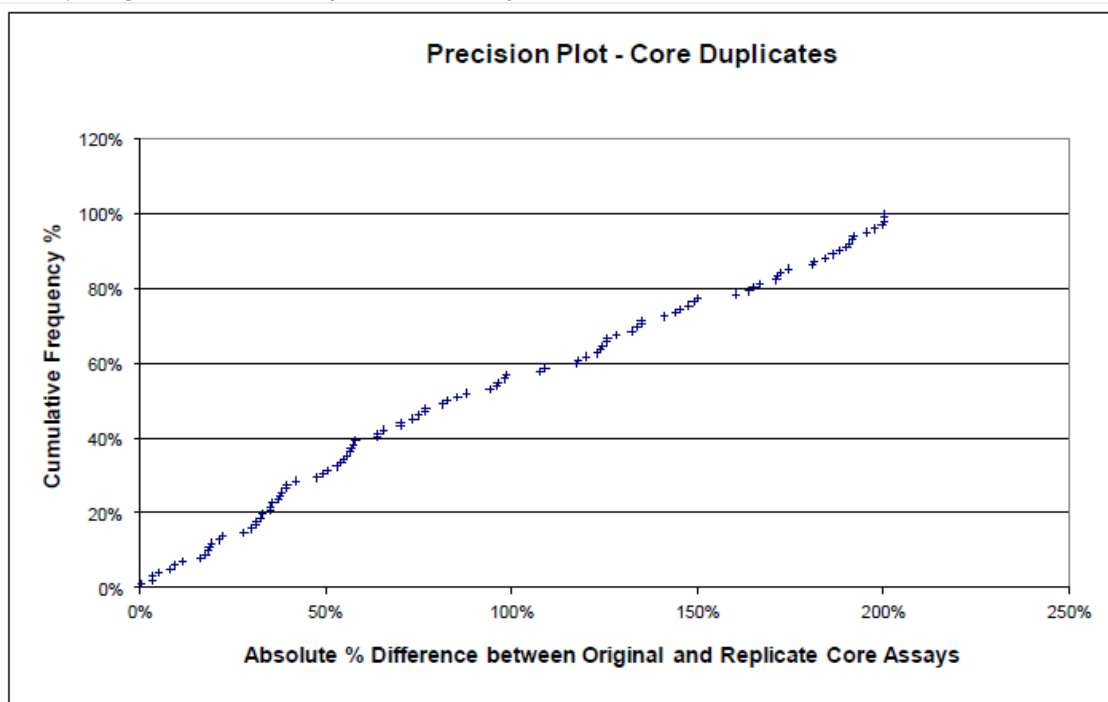AFW Core Duplicate Pair for Lead**April 2017**

AFW Precision of Original and Re-Sampled Core Assays

Source: P&E Mining, 2014

AFW Precision of Original and Re-Sampled Core Assays**April 2017****2013 Drilling Campaign (Asis Far West)**

A total of 118 samples including reference material were dispatched to Bureau Veritas for sample preparation and the pulps were analysed at Acme Analytical Laboratories. Blanks and CRMs were purchased from Canadian Resource Laboratories Ltd. The details of the CRMs utilised during 2013 Drilling Campaign are presented in the table below.

Summary of CRMs used During 2013 Drilling Campaign

ID	Type	Certified Concentration						
		Au	Pt	Pd	Ag	Cu	Pb	Zn
		g/t	g/t	g/t	g/t	%	%	%
CND-BL-10	Pulp Blank	<0.01	<0.01	<0.01	-	-	-	-
CDN-ME-19	CRM	0.62 ± 0.062	-	-	103 ± 7	0.474 ± 0.018	0.98 ± 0.06	0.75 ± 0.04
CDN-ME-1201	CRM	0.125 ± 0.03	-	-	37.6 ± 3.4	1.572 ± 0.086	0.465 ± 0.032	4.99 ± 0.29

The table below presents a summary of all the quality control samples for 2013 drilling campaign.


Summary of the Quality Control Samples for 2013 Drilling Campaign.

Sample ID	QC Sample	Remarks
12480	CDN-BL-10	Pulp Blank
12489	CDN-ME-19	CRM Pulp
12498	Core Duplicate	
2009	CDN-ME-1201	CRM Pulp
2018	Prep Duplicate	2 nd Pulp from 2017 Sample
2027	CDN-BL-10	Pulp Blank
2036	CDN-ME-19	CRM Pulp
2045	Core Duplicate	
2054	CDN-ME-1201	CRM Pulp
2063	Prep Duplicate	of 2062 Sample

Sample ID	QC Sample	Remarks
2072	CDN-BL-10	Pulp Blank
2081	CDN-ME-19	CRM Pulp
2090	Core Duplicate	
2099	CDN-ME-1201	CRM Pulp
2108	Prep Duplicate	of 2107 Sample
2118	CDN-BL-10	Pulp Blank
2127	CDN-ME-19	CRM Pulp
2137	Core Duplicate	
2146	CDN-ME-1201	CRM Pulp
2155	Prep Duplicate	of 2154 Sample
2164	CDN-BL-10	Pulp Blank

Blanks

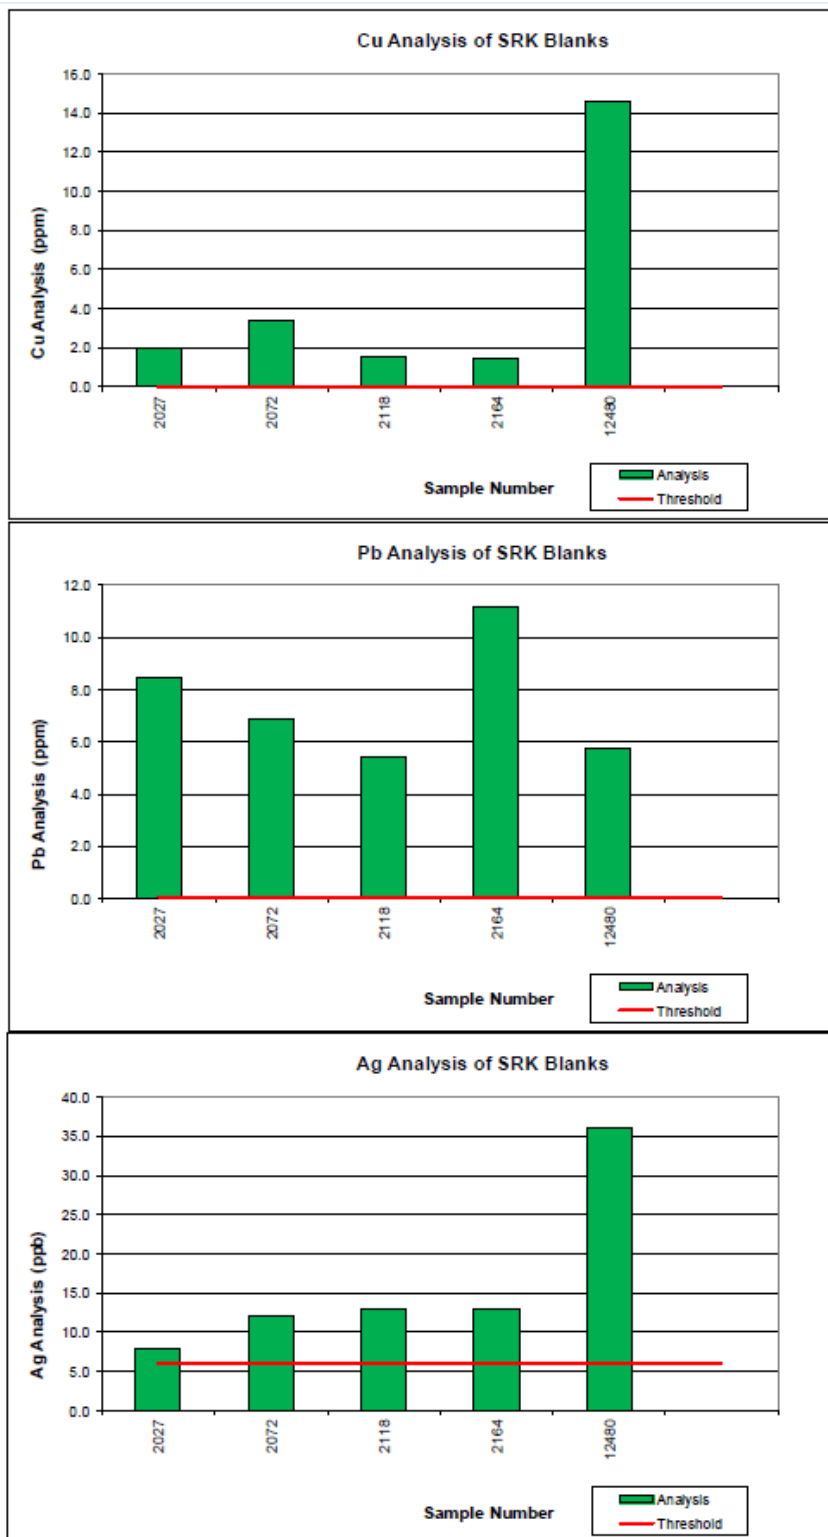A total of five blanks were used during the 2013 drilling campaign. The blank material (CND-BL-10) was certified for Gold, Platinum and Palladium. The figure below presents blank QAQC graphs for Copper, Lead and Silver.

Blank QAQC Results.

Source: P&E Mining, 2014

Blank QAQC Results**April 2017**

CRMs


A total of eight CRMs were used during the 2013 drilling campaign, of which four were CDN-ME-19 and the other four were CDN-ME-1201. The table below presents a summary of the CRMs QAQC results.

Summary of the CRMs QAQC

Standard	Acceptance	Remarks
CDN-ME-19 Cu%	Pass	Two values within -two standard deviations
CDN-ME-19 Pb%	Pass	Slightly low but within one standard deviation
CDN-ME-1201 Pb%	Pass	One of two values at +three standard deviations
CDN-ME-1201 Ag g/t	Pass	Slightly high but within +one standard deviation

The figure below depicts analysis of CDN-ME-19 CRM for both copper and silver. All samples are within the acceptable limits and therefore the results are deemed to be reliable.

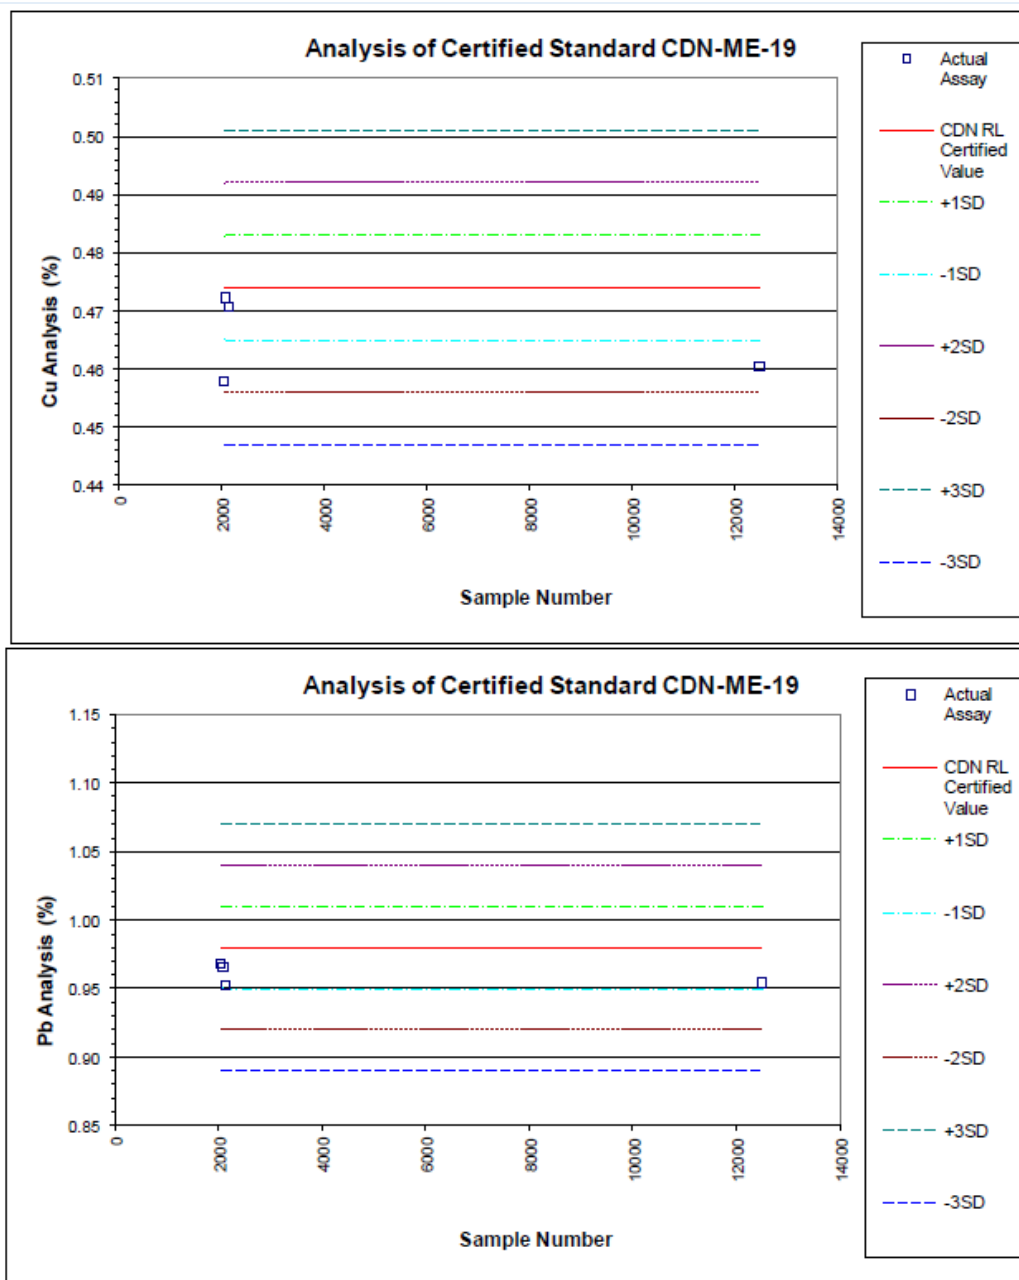Analysis of CDN-ME-19 CRM




Source: P&E Mining, 2014

Analysis of CDN-ME-19 CRM

April 2017

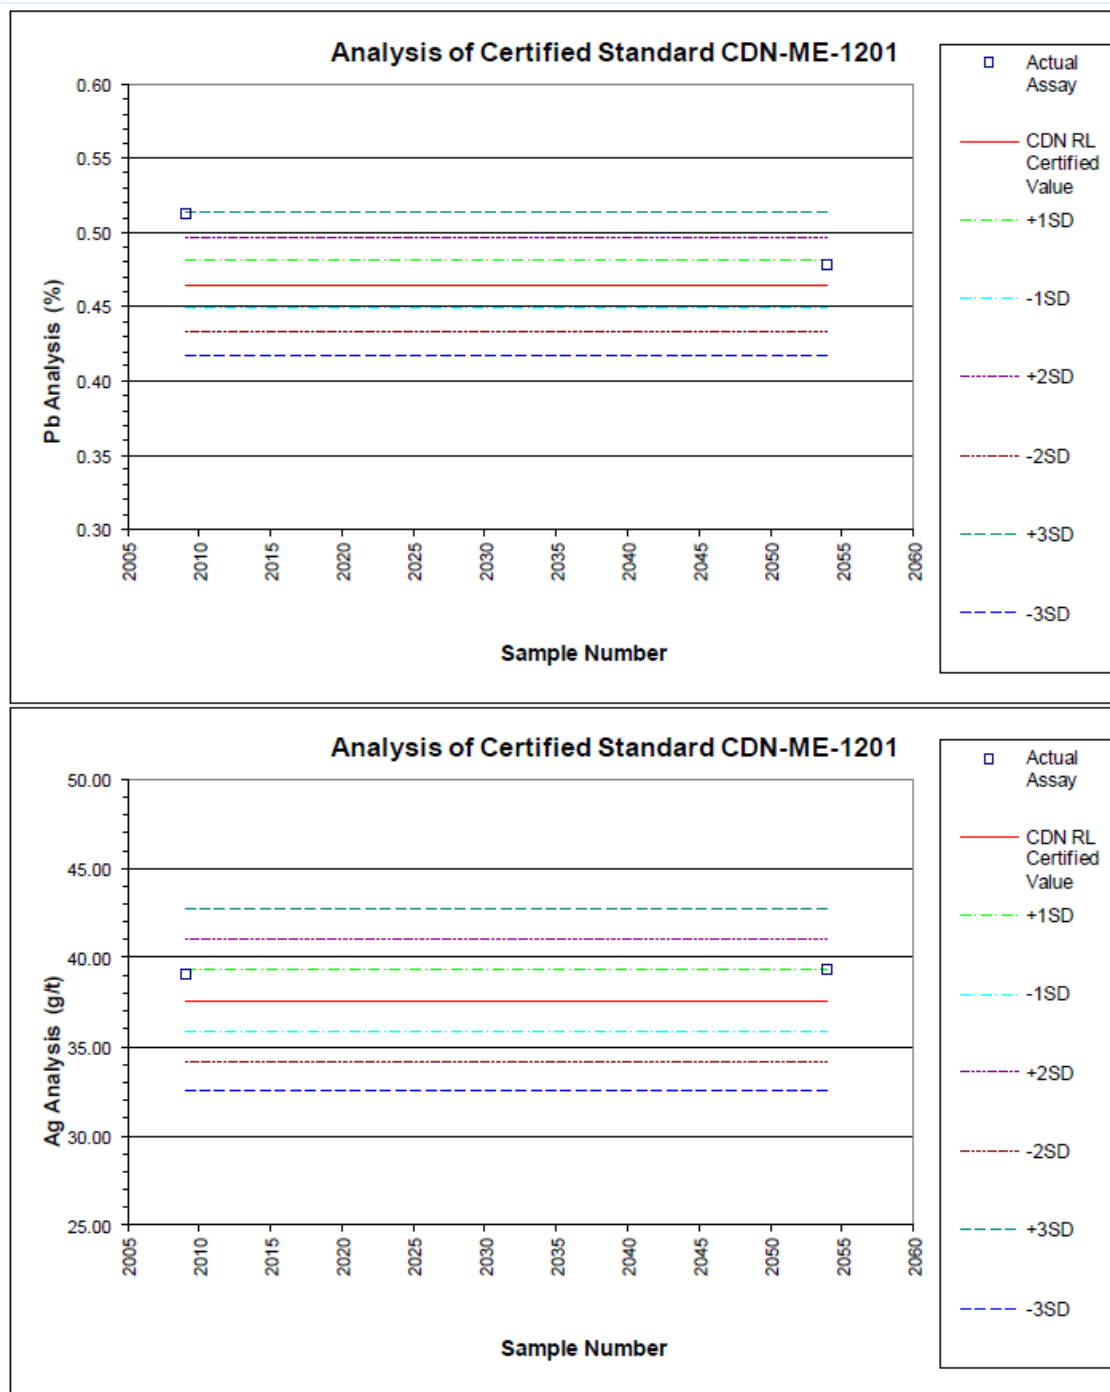The figure below presents analysis of CDN-ME-1201 CRM for both Lead and Silver. All samples are within the acceptable limits and therefore the results are deemed to be reliable.

Analysis of CDN-ME-1201.

Source: P&E Mining, 2014

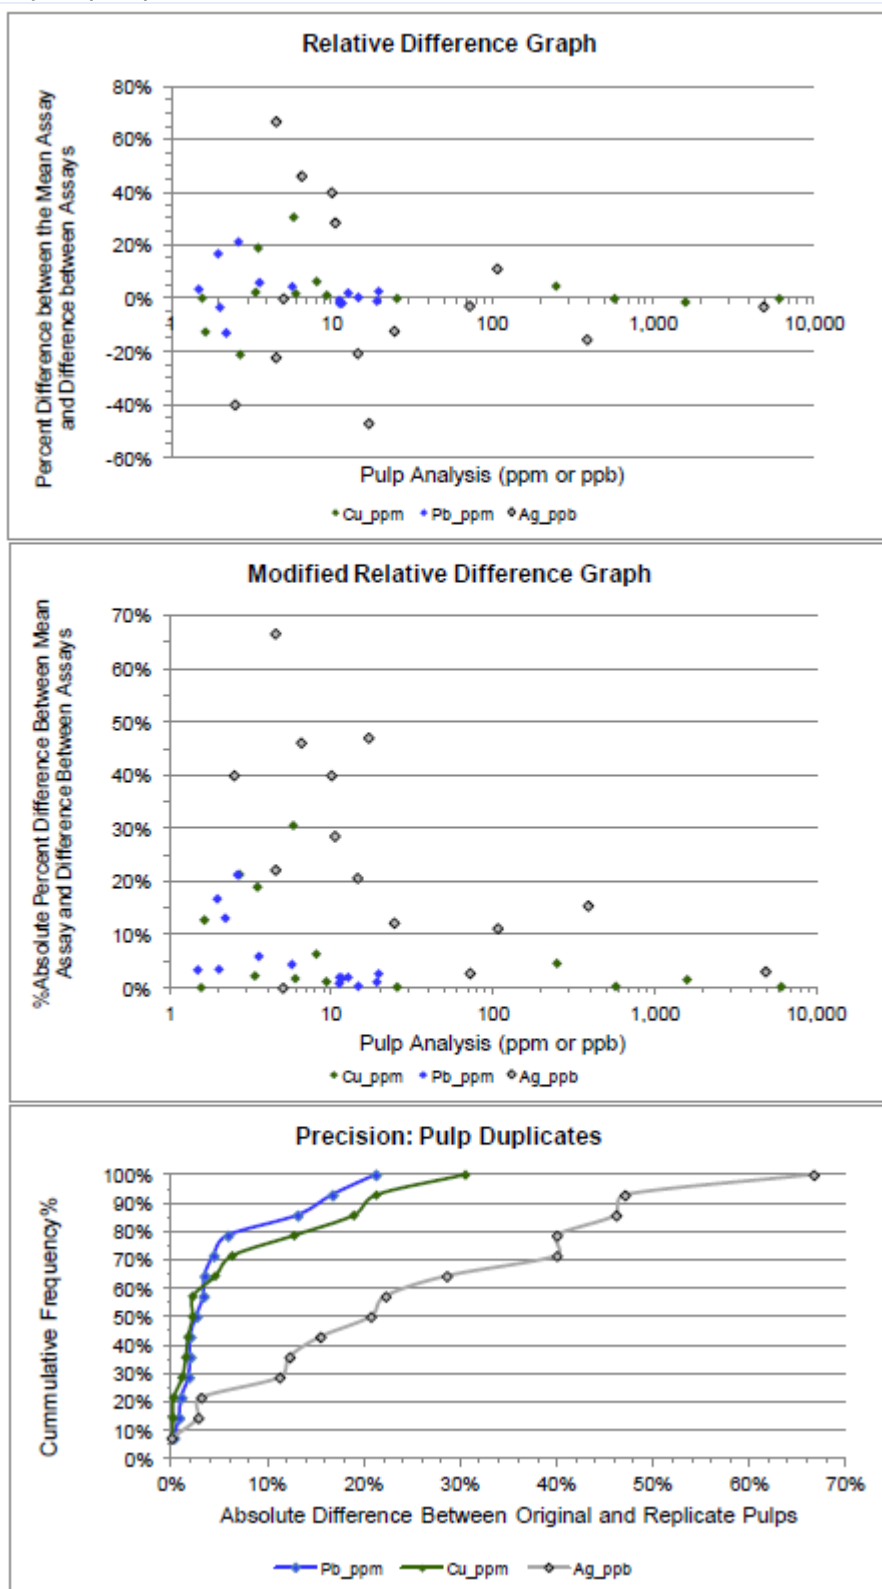
Analysis of CDN-ME-1201**April 2017****Pulp Duplicates**

As part of the internal laboratory QAQC, 14 pulp duplicates were analysed at Acme Analytical Laboratories. Precision was $\pm 10\%$ for copper and lead for values above 10 ppm. Lead showed a slight bias low for the duplicates. RSD of 4.3 % for copper and 2.4 % for lead are within accepted precision limits of 5% for pulps. Silver showed a bias for higher duplicate values (9 of 14) and a RSD of 8%, which exceeds the 5% limit for pulps and indicates lower precision.

All internal blanks returned less than three times the lower detection limit and indicate that analysis was contamination free. The performance of the internal reference standards shown in the figure below appears reasonable except for one silver analysis, however the performance limits for the laboratory standards was not available. All but one silver analysis are within 10% of the expected value. Three copper, one lead and two silver standards analysed higher than 5% from the expected value and are likely at the “warning” threshold for acceptance.

According to P&E Mining, the results of the QAQC program carried out in the 2012 re-sampling program indicate that the original assay data are not of current industry accepted quality and there appears to have been a high bias in the original Kombat Mine laboratory assaying. The bias may have arisen from contamination at the sample preparation stage but may also have arisen through historic core sampling practice.


The Relative Difference precision graphs for the laboratory pulp duplicates are presented in the graphs below.

Precision of Laboratory Pulp Duplicates.

Source: P&E Mining, 2014

Precision of Laboratory Pulp Duplicates**April 2017**

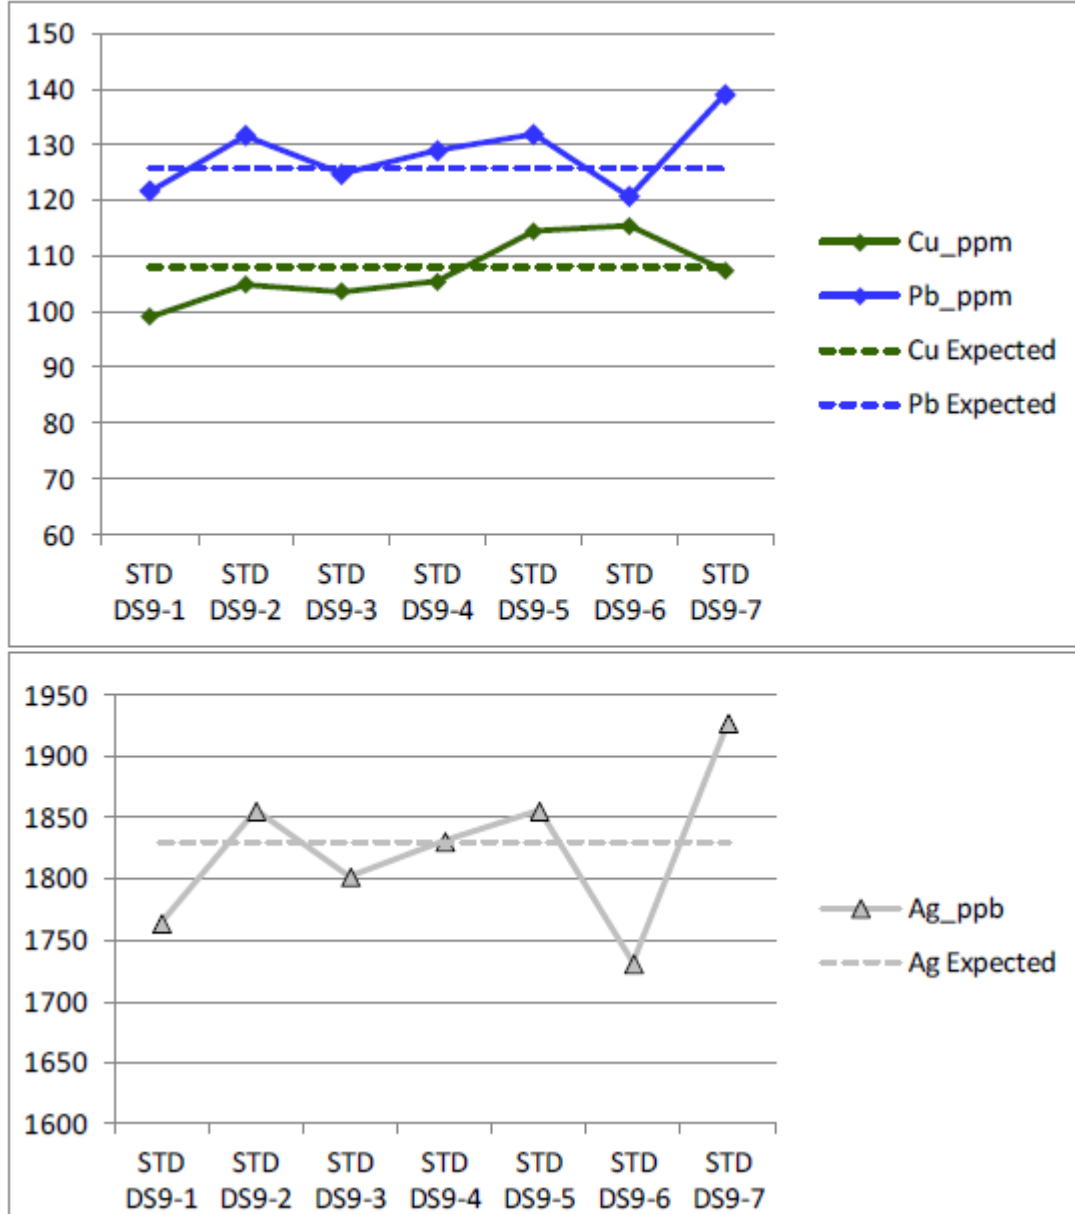The performance of the Acme Laboratory Internal CRMs is presented in the graphs below.

Performance of Acme Laboratory Internal CRMs

Source: P&E Mining, 2014



Precision of Laboratory Pulp Duplicates

April 2017